

The First Isolable Low-valent Ferrocene Enabling the Application of Unprecedented Ferrocene Anolyte

Authors: Hayoung Song^{1*}, Giyun Kwon², Cooper Citek³, Seungwon Jeon¹, Kisuk Kang,^{2,4,5‡} and Eunsung Lee^{1,6‡}

Affiliations:

¹ Department of Chemistry, Pohang University of Science and Technology. Pohang, 37673, Republic of Korea.

² Department of Materials Science and Engineering, Research Institute of Advanced Materials (RIAM), Seoul National University, 1 Gwanak Road, Seoul 151-742, Republic of Korea.

³ Division of Chemistry and Chemical Engineering, California Institute of Technology (Caltech), Pasadena, California 91125, United States.

⁴ Institute of Engineering Research, College of Engineering, Seoul National University, 1 Gwanak-ro, Gwanak-gu, Seoul 151-742, Republic of Korea.

⁵ Center for Nanoparticle Research, Institute of Basic Science, Seoul National University, 1 Gwanak-ro, Gwanak-gu, Seoul 151-742, Republic of Korea.

⁶ Division of Advanced Materials Science, Pohang University of Science and Technology. Pohang, 37673, Republic of Korea.

‡Correspondence to: eslee@postech.ac.kr (E.L.) and matlgen1@snu.ac.kr (K.K.).

*Current Address: Center for Self-Assembly and Complexity (CSC), Institute for Basic Science (IBS), Pohang, 37673, Republic of Korea.

Abstract: Here, we report the first isolable low-valent biscyclopentadienyl iron complexes stabilized by NHC-functionalized ligands (NHC-Cps), which were characterized by electron paramagnetic resonance (EPR) and ⁵⁷Fe Mössbauer spectroscopy. Additional theoretical studies on these formally low-valent ferrocene complexes clearly explain the origin of their thermodynamic stability and the orbital interactions between iron and NHC-Cp. Exploiting the facile Fe(II/I) redox chemistry, we successfully demonstrated that the NHC-Fc compounds can be applied as the first example of ferrocene anolyte for redox-flow batteries. These low-valent species will not only deepen our understanding of the intrinsic chemistry of low-valent ferrocene but have the potential to open the way for the rational design of low-valent metallocene derivatives for various applications.

Main Text:

Since its discovery by Pauson, Kealy,¹ and Miller,² the remarkable stability and reactivity of ferrocene have enabled its use in many applications, including electrochemistry,³ medicinal chemistry,⁴ bioorganometallic chemistry,⁵ host-guest chemistry,⁶ and transition metal catalysis.⁷ In particular, the pronounced reversible redox behavior of ferrocene solidifies its position in electrochemistry as a ubiquitous standard. Furthermore, the Fe(III)/Fe(IV) oxidation of ferrocenium has been achieved recently using a superacid medium.⁸ On the other hand, the synthesis of low-valent ferrocenes has not been successfully achieved and the only decomposition of the ferrocene unit in presence of strong reductants has been reported to date.⁹ Due to the high instability of low-valent ferrocenes, it was only possible to confirm a reversible

reduction of ferrocene using cyclic voltammetry at low temperatures.¹⁰ The instability of the low-valent ferrocene is due to the facile dissociation of the cyclopentadienyl anion ligand (Cp),⁹ as indicated by trapping experiments.¹¹ Despite numerous attempts to stabilize the low-valent ferrocene by the introduction of functional groups on the cyclopentadienyl rings, a persistent low-valent ferrocene stable at room temperature could not be obtained¹² (**Figure 1a**). Based on the fact that their high instability is caused by the dissociation of the cyclopentadienyl ligand, many attempts have been made to synthesize an isolobal structure of low-valent ferrocene stabilized by the introduction of other ligands.^{13,14} Astruc *et al.* reported the synthesis of an iron-based sandwich complex $[\text{Fe}(\text{Cp})(\eta^6\text{-C}_6\text{Me}_6)]$ ^{14a} its derivatives.^{14b} Tasumi *et al.* reported $[(\text{Cp}^*)\text{Fe}(\mu\text{-polyarene})\text{Fe}(\text{Cp}^*)]$ complexes obtained by the reduction of half-sandwich Fe(II)Cp* compounds using potassium polyarenides.^{14c} While previous studies on the reduction of heteroferrocenes to obtain low-valent heteroferrocenes had been unsuccessful,^{13a-c} Saito *et al.* reported the synthesis of stable anionic stannaferrocene from the reaction between $\text{Fe}(\text{acac})_3$ and dilithiostannol.^{14d} Recently, Mills and co-workers reported a fascinating work describing the characterization of ferrocenate under low temperature.¹⁵ Considering that the reduction of ferrocene occurs at high negative voltages (-3.3 V vs Fc/Fc^+)¹⁵, it can be applied to a wide range of electrochemistry, including the design of anolyte for high energy battery. However, there is still no example of the synthesis and characterization of a stable low-valent ferrocene including two intact cyclopentadienyl ligands so far.

On the other hand, recently, interest in *N*-heterocyclic carbenes (NHCs)¹⁶ has increased due to their novel chemical properties, such as the reactivity towards small molecules.¹⁷ Especially, their amazing properties to stabilize electron-rich main-group elements,¹⁸ radicals,¹⁹ and transition-metal centers²⁰ are enjoying the spotlight. However, the redox behavior of NHCs remains underexplored, presumably due to the thermodynamic instability of NHC radical ions generated by redox reactions. For example, the radical anion of triazol-5-ylidene was characterized by cyclic voltammetry and electron paramagnetic resonance (EPR) in 1997,²¹ but there has been no report of an NHC radical cation produced by one-electron oxidation.

Nevertheless, the reactivity of NHCs with various oxidants has been studied. In 2004, the reactivity of imidazol-2-ylidene with tetracyanoethylene (TCNE) and a ferrocenium salt was reported by Clyburne *et al.*²² They showed that TCNE reacted with the NHC to produce a cationic dimer, formation of which was considered as evidence of an NHC radical cation intermediacy. However, direct observation of the NHC radical cation intermediate was not possible. Subsequently, a potential proton-catalyzed dimerization pathway was suggested as an alternative mechanism for the cationic dimer formation.²³ This revised mechanism has been further strengthened by the inconsistency between the ionization energy of NHC (7.68 eV)²⁴ and the electron affinity of TCNE (3.16 eV)²⁵, as pointed out by the Arduengo group in 2015.²⁶ Furthermore, Arduengo²⁶ and our group²⁷ have also reported various adducts obtained from the reaction between NHCs and TCNE.

Interestingly, Clyburne and coworkers showed that ferrocenium salts react with NHCs to produce imidazolium salts, not dicationic dimers.²² They have postulated that the unstable NHC radical cation intermediate likely abstracts a hydrogen atom from the THF solvent. As Arduengo argued,²⁶ however, it is necessary to consider whether the charge transfer between an NHC and ferrocenium is thermodynamically feasible. In the light of their respective ionization potentials (NHC: 7.68 eV ,²⁴ ferrocene: 6.81 eV)²⁸, an alternative mechanism is needed to explain how the imidazolium salt forms. In addition, various phosphines, which are less nucleophilic than NHCs, were found to react with ferrocenium salts to produce ferrocene-phosphine adducts.²⁹ Inspired by this work, we speculated that ferrocene-NHC adducts could be formed by the direct reaction of NHCs with the C–H bond of ferrocenium salts. Assuming

we could access these ferrocene-NHC adducts, subsequent reduction yielding low-valent ferrocene complexes stabilized by the well-known π -accepting properties and significant steric hindrance of the NHC-derived fragment was considered feasible. Here, for the first time, we report the successful synthesis of *N*-heterocyclic carbene-functionalized cyclopentadiene iron complexes and elucidation of the first unambiguous one-electron reduction of ferrocene.

We first sought to investigate the imidazolium salts produced in the reaction of NHCs with ferrocenium salts, as reported by Clyburne.¹⁶ After the addition of 1,3-bis(2,6-diisopropylphenyl)imidazol-2-ylidene (IPr) to ferrocenium hexafluorophosphate (FcPF₆) in THF at room temperature, the corresponding imidazolium salt and ferrocene were obtained.²² However, we were able to identify an additional component of the reaction mixture that has not been characterized previously. This product was identified as the NHC-functionalized ferrocenium (IPr-Fc adduct, **1a**) and could be cleanly isolated in 56% yield. In the same manner, cyclic (alkyl)(amino)carbene (cAAC)-functionalized ferrocenium (cAAC-Fc adduct, **1b**) was also successfully obtained in 46% isolated yield (**Figure 1b**).

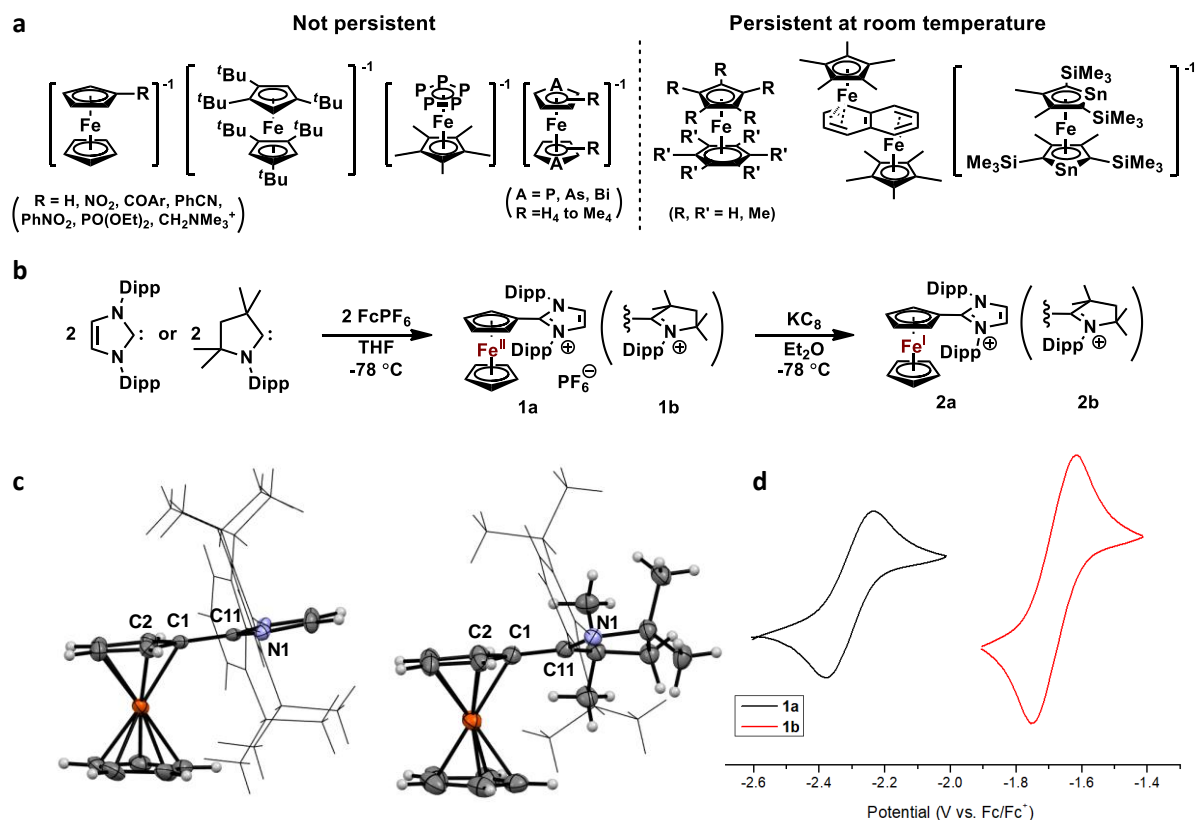


Figure 1. Synthesis of NHC-functionalized ferrocenes and their low-valent derivatives (a) Previous attempts to obtain persistent low-valent ferrocenes and their persistent isolobal structures. (b) Synthesis of **1a** and **1b** by the oxidative nucleophilic substitution of ferrocenium with NHCs and their further reduction to obtain **2a** and **2b**, with formal oxidation states indicated. (Fc = ferrocenium, Mes = 2,4,6-trimethylphenyl, Dipp = 2,6-diisopropylphenyl). (c) X-ray crystallographic analysis of **1a** and **1b**. (d) Cyclic voltammograms of **1a** and **1b** in 0.1 M of [Bu₄N]PF₆/MeCN (vs. Fc/Fc⁺, scan rate = 0.1 V s⁻¹).

Compared with the previous studies reported by Kunz³⁰ and Yuan.³¹ NHC-functionalized ferrocene with high steric hindrance on imidazolium ring **1a** is first reported. Furthermore, this is also the first report of cAAC-Fc adduct **1b**, which exhibits different chemical properties to **1a** due to the greater π -accepting nature of cAAC compared to IPr. The stability of these NHC-

Fc adducts may further enable research on ferrocene-based carbocation species,³² limited by dimerization pathways and dissociation of fulvene ligand from iron.

X-ray diffraction studies of **1a** and **1b** confirmed the NHC-Fc adduct structures (**Figure 1c**). The C1–C11 bond lengths of **1a** (1.447(6) Å) and **1b** (1.446(2) Å) are similar to Yuan's system (1.437(9) Å^{31a}). **1a** exhibits planarity across the cyclopentadiene and imidazolium rings (C2–C1–C11–N1 = 0.81 °), in contrast to the distorted structures of **1b** and Yuan's system (17.22 ° and 38.83 °^{31b}) due to the 1,3-allylic strain between the NHC and Cp rings.

To understand the formation of the NHC-Fc adducts, we investigated three possible initial reaction pathways by density functional theory (DFT) calculations:^{29, 33} (1) Oxidation of NHC by ferrocenium, (2) deprotonation of ferrocenium by NHC, and (3) nucleophilic addition of NHC to ferrocenium (**Figure S2** and **S3**). The computational studies indicate that the nucleophilic addition of NHC to ferrocenium is the most favorable reaction pathway, consistent with the previously reported reaction between ferrocenium and phosphines.²⁹ Due to the strong nucleophilicity of NHC, the activation barrier toward the nucleophilic addition of an NHC may be as much as 16 kcal mol⁻¹ lower than the reaction with a phosphine.²⁹

The UV-Vis spectra of **1a** and **1b** are shown in **Figure S10**. In the visible region, **1a** and **1b** show strong transitions at 471 nm ($\epsilon=2200$ cm⁻¹ M⁻¹) and 551 nm ($\epsilon=5500$ cm⁻¹ M⁻¹), respectively. Time-dependent DFT calculations of **1a** and **1b** at B3PW91/Def2-SVP level of theory predict a metal-to-ligand charge transfer (MLCT) in relatively good agreement with the experimental spectra (**Figure S8** and **S9**). Interestingly, the differences in the transition energies were largely dependent on the LUMO orbitals, which are strongly influenced by the vacant p-orbital at the NHCs. Thus, the absorption band of **1b** is red-shifted compared to that of **1a**, due to the stronger π -accepting nature of cAAC than IPr.

1a and **1b** exhibit irreversible oxidation near 0.60 V vs. Fc/Fc⁺ (**Figure S13**). However, Fe(II)/Fe(I) reduction at $E_{1/2} = -2.31$ V (**1a**) and $E_{1/2} = -1.69$ V (**1b**) (vs. Fc/Fc⁺) is reversible under inert conditions (**Figure 1d**). On the other hand, a reversible reduction of ferrocene is only observed at low temperature (-50 °C).¹⁰ The unusual reduction reversibility of these NHC-Fc species might be attributed to the radical stabilization effect of the NHC moiety^{19a, 19b} with the protection by sterically hindered substituents. To the best of our knowledge, intact low-valent ferrocenes have never been reported due to their low chemical stability.⁹ Thus, we attempted to prepare the reduced NHC-Fc radicals **2a** and **2b** to confirm the stabilization effect of the NHC-Cp ligands on low-valent transition metal centers. Hence, reduction of **1a** and **1b** by KC₈ in toluene at -78 °C generates deep green and deep purple solutions of **2a** and **2b**, respectively (**Figure 1b**). The UV-Vis spectra of **2a** and **2b** are shown in **Figure S11**. The near-infrared (NIR) transition of **2a** at 1036 nm is consistent with TD-DFT predictions (**Figure S7**). Interestingly, **2a** and **2b** immediately decomposed by attempted removal of the solvent under vacuum. Thus, **2a** and **2b** were isolated by the simple vaporization of solvent under ambient conditions in high yield (**2a**: 44% yield, **2b**: 99% yield). The **2a** and **2b** are stable for several weeks at -20 °C as solid and solution phase under an inert atmosphere.

2a and **2b** show relatively high thermodynamic stability in toluene solution at room temperature, as monitored by UV-Vis-NIR spectroscopy (**Figure S12**). The remarkable stability of **2a** and **2b** contrasts with previous studies on the reduction of ferrocene and their derivatives. The previously reported ferrocene radical anion showed a short lifetime of minutes at low temperatures (-50 °C)^{11b} and the reduced radical structures of several ferrocene derivatives could only exist with a short lifetime from seconds to minutes at room temperature.^{12b} On the other hand, **2a** and **2b** showed improved stability with a long lifetime in hours to days at room temperature (**Figure S12**).

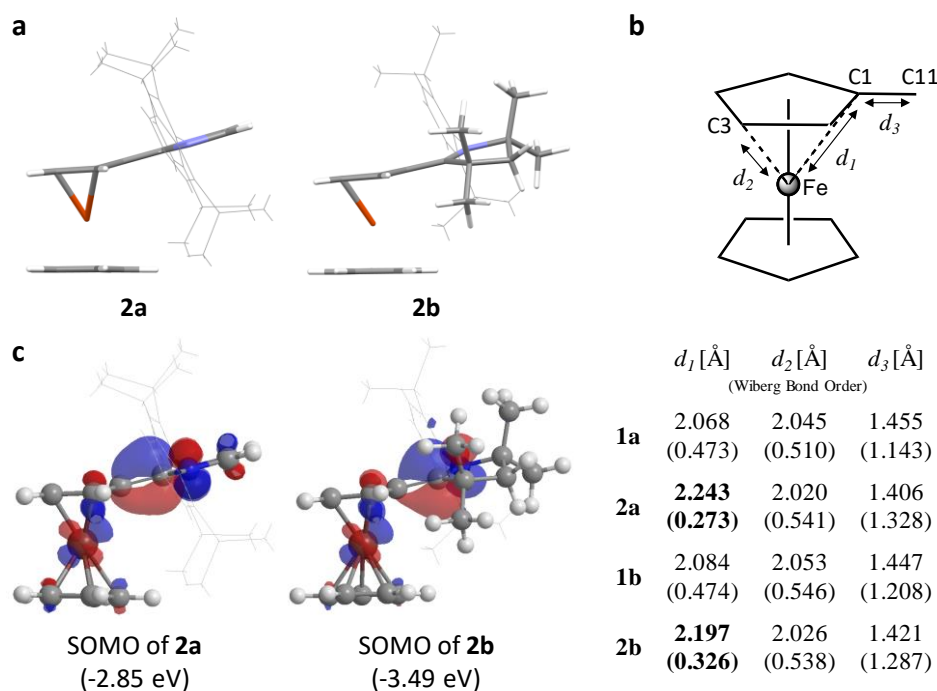


Figure 2. Structural characterization of low-valent ferrocenes with DFT-calculations (a) Optimized structures of **2a** and **2b** obtained using Gaussian 09W at B3PW91/Def2-SVP level. (b) SOMO of **2a** and **2b** (isovalue = 0.05 (electrons/bohr³)^{1/2}). (c) Selected bond lengths and Wiberg bond orders of **1a**, **2a**, **1b**, and **2b**.

The structures of **2a** and **2b** are evaluated by DFT optimization (**Figure 2a**). Interestingly, **2a** and **2b** show a slight distortion of the NHC-substituted Cp ring (**Figure 2b**). The results might be explained by inspection of the half-filled SOMO orbitals of **2a** and **2b** showing anti-bonding character between Fe and C1 (**Figure 2c**). The bond length between Fe–C1 in **2b** is shorter than that in **2a**, presumably because the SOMO population in the π -orbital (between C1–C11) is more localized on C11 in **2b** than it is in **2a**. We believe that the SOMO localization on the NHC moiety accounts for the bonding in **2a** and **2b** and explains the thermodynamic stability of the reduced species. Despite the increase in the length of Fe1–C1 and the decrease in the length of C1–C11 bond, the bond between Fe1 and C1 is still present and the C1–C11 bond remains in a single bond range. Thus, the NHC-Cp ligands of **2a** and **2b** still resemble the previously reported zwitterionic NHC-Cp structures^{30a} but differ significantly from the structures of iron η^4 -fulvene complexes³⁴.

For a clear classification as fulvene, we also considered the bond-length alternation (BLA) parameter of several fulvene derivatives including **1a**, **1b**, **2a**, and **2b** (**Figure S1**). In the case of intact fulvenes **A** and **B**, their BLA parameters are 11.9, which was close to polyethylene (~12). On the other hand, the BLA parameters of zwitterionic cyclopentadienide are low (**C**–4.0 and **D**–2.1). Interestingly, the fulvene complex (**E–H**) showed a lower value (6.7–3.7) than intact fulvene (**A**, **B**), but still showed a higher value, which could be classified as a fulvene, than zwitterionic cyclopentadienide **D**. On the other hand, **1a**, **1b**, **2a**, and **2b** showed low values of BLA parameters (0.9 – 2.7), which show a similar value with ferrocenyl carbocation (**I**, **J**). Thus, The ligands of **2a** and **2b**, as well as **1a** and **1b**, can be classified as cyclopentadienide.

Furthermore, the thermodynamic stability of **2a** and **2b** may in part be attributable to the spin delocalization from iron to the NHCs as calculated by DFT at the B3PW91/Def2-SVP level of

theory. The Mulliken atomic spin densities of **2a** and **2b** localize on the iron atom at 50% and 28% and in the empty p-orbital of the NHCs at 29% and 58%, respectively (**Figure S5**).

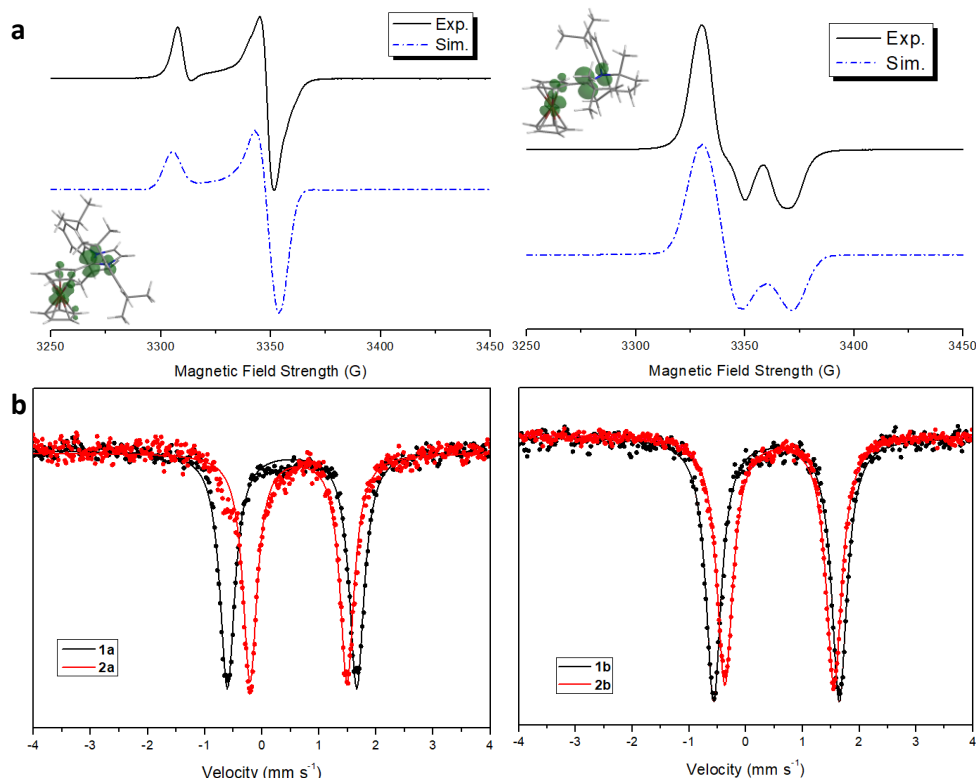


Figure 3. Spectroscopic characterization of low-valent ferrocene (a) X-band EPR spectrum of **2a** and **2b** in toluene at 160 K and the visualization of Mulliken spin densities of **2a** and **2b** (Gaussian 09W, B3PW91/Def2-SVP, isovalue = 0.05 (electrons/bohr³)^{1/2}). (b) Frozen solution Mössbauer spectra of **1a**, **1b**, **2a**, and **2b** collected at 80 K in the presence of a 50 mT parallel magnetic field.

The X-band EPR spectroscopy data also confirm the low spin, iron-based ground states ($S = 1/2$) of **2a** ($g = [2.040, 2.014, 2.010]$) and **2b** ($g = [2.027, 2.019, 2.000]$) (**Figure 3a**). The g -values of **2a** and **2b** are similar to the g -value of the transient anionic ferrocene characterized previously by a continuous *in-situ* EPR electrochemical reactor.^{11b} Additionally, the EPR spectra of **2a** and **2b** distinctly differ from the data obtained for “ferrocene-substituted radical anions,” which exhibit narrow signals with well-resolved ¹H couplings and symmetry for the center of the spectra.^{12b} The slightly rhombic spectra of **2a** and **2b** with comparatively wider, anisotropic signals are consistent with iron d-orbital character of the $S = 1/2$ ground state. The aforementioned ferrocene-substituted radical anions are best described as ligand-based, organic radicals, in contrast to the partially iron-centered, metalloradicals **2a** and **2b**.

We also performed ⁵⁷Fe Mössbauer spectroscopy of each compound in benzene or toluene solutions (**Figure 3b**). The ⁵⁷Fe Mössbauer spectra of **1a** and **1b** at 80 K feature symmetric quadrupole doublets at $\delta = 0.53$ mm s⁻¹ (**1a**) and 0.54 mm s⁻¹ (**1b**) (compared to ferrocene at approximately 0.53 mm s⁻¹) and quadrupole splitting $\Delta E_Q = 2.27$ mm s⁻¹ (**1a**) and 2.22 mm s⁻¹ (**1b**) (cf. 2.40 mm s⁻¹ for ferrocene).³⁵ However, the spectra of their reduced forms **2a** and **2b** are in both cases positively shifted to $\delta = 0.64$ mm s⁻¹ (**2a**) and 0.59 mm s⁻¹ (**2b**) and narrowed to $\Delta E_Q = 1.70$ mm s⁻¹ (**2a**) and 1.92 mm s⁻¹ (**2b**). The Mössbauer parameters for all four compounds are well-reproduced by a calibrated DFT method (see Supplementary Materials), and single-point calculations recapitulate the shared electron density between iron and the NHC.

To the best of our knowledge, there is no reported measurement of the Mössbauer parameters for a reduced, formally Fe(I) biscyclopentadienyl anion. Instead, the Mössbauer parameters of **2a** and **2b** can be indirectly validated by comparison with the similar quadrupole doublets of isolobal bis-Fe(I) sandwich complexes reported by Astruc *et al.* ($\delta = 0.56\text{--}0.66\text{ mm s}^{-1}$ and $\Delta E_Q = 1.31\text{--}1.66\text{ mm s}^{-1}$ between 10 and 260 K)^{14b} and Tasumi *et al.* ($\delta = 0.59\text{ mm s}^{-1}$ and $\Delta E_Q = 1.55\text{--}1.59\text{ mm s}^{-1}$ at 90 K).^{14c} On the other hand, Fe(I)-CpFe(C₆H₆) exhibits a quadrupole doublet near $\delta = 0.92\text{--}0.87\text{ mm s}^{-1}$ ($\Delta E_Q = 1.20\text{--}0.95\text{ mm s}^{-1}$ between 4.2 and 260 K), potentially excluding decomposition of the reduced products **2a** and **2b** to similar solvent adducts.^{14a} An increase in the measured isomer shift would be expected with a slight elongation of the Fe–C bonds in the complexes upon reduction; the narrowing of the quadrupole splitting is consistent with increased electron density in axial d_{xz}/d_{yz} -based SOMO orbitals orthogonal to the equatorial $d_{xy}/d_{x^2-y^2}$ HOMO orbitals of Fe(II) in **1a** and **1b**.³⁶ This investigation of the electronic environment of low-valent ferrocenes **2a** and **2b** supports the iron-based spin and lower valence state of **2a** and **2b** with respect to **1a** and **1b**.

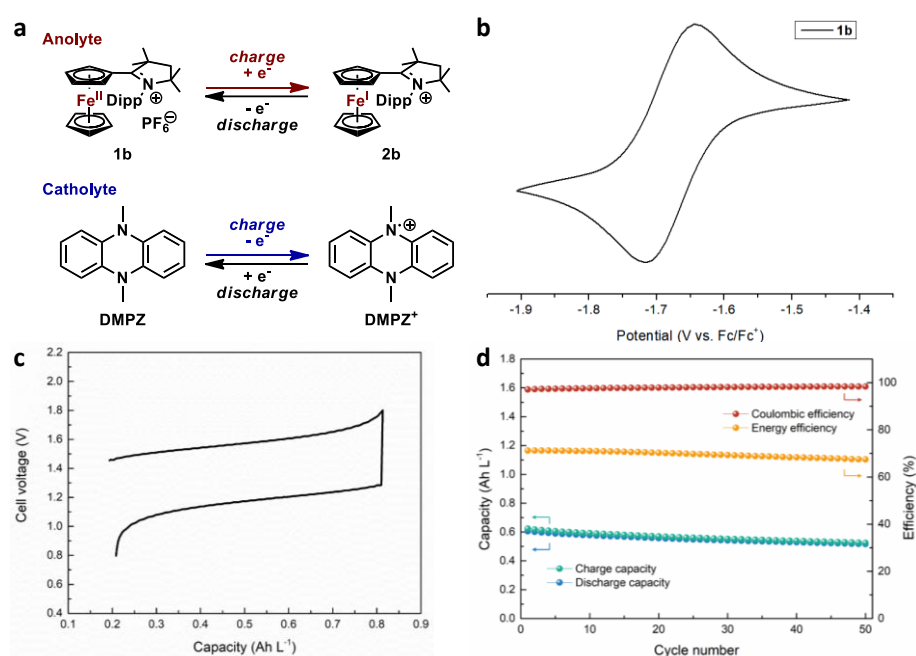


Figure 4. Application of low-valent ferrocenes in redox-flow battery (a) Redox mechanism of **1b** and DMPZ in a flow cell. (b) Cyclic voltammogram of **1b** in 0.5 M LiTFSI/MeCN (vs. Fc/Fc⁺, scan rate = 0.1 V s⁻¹). (c) Cell voltage vs. cell capacity. (d) Cycling efficiencies and capacities with 50 cycles.

Most applications of ferrocene derivatives have been limited to their oxidation chemistry due to their redox instability at negative potentials.³⁷ However, we found that **1b**, which exhibits a reversible Fe(II)/Fe(I) redox cycle, could be studied in a redox-flow battery (RFB) system as the first example of ferrocene anolyte.³⁸ Considering its remarkable stability, moderate reduction potential (-1.69 V vs Fc/Fc⁺ in 0.1 M [Bu₄N]PF₆/MeCN), and high solubility (0.561 M) in MeCN, we believed that **1b** could serve as a good anolyte candidate in a high-performance RFB. To construct an all-organic RFB,³⁹ commercially available 5,10-dimethyldihydrophenazine (DMPZ) was employed as a counter catholyte material (**Figure 4a**); DMPZ undergoes a reversible redox reaction at -0.26 V vs. Fc/Fc⁺.⁴⁰ As shown in **Figure 4b**, **1b** in MeCN with 0.5 M LiTFSI supporting electrolyte shows a reversible single-electron redox event at -1.68 V vs. Fc/Fc⁺, yielding a theoretical cell voltage of 1.42 V in a flow battery when coupled with DMPZ.

The electrochemical performance of the flow cell employing the DMPZ/**1b** system was also investigated using a customized flow cell (see Supplementary Materials). **Figure 4c** shows a representative charge-discharge curve at a current density of 20 mA cm⁻². An average cell voltage of 1.40 V was achieved, consistent with the cyclic voltammetry data. It should be noted that the initial capacity of 0.62 Ah L⁻¹ is reasonably close to the theoretical capacity of 0.80 Ah L⁻¹, indicating material utilization of ~78%. The cycling efficiency and capacity retention data for the RFB indicate that the flow cell maintains a high coulombic efficiency (CE) of ~99%, a voltage efficiency of ~71%, and acceptable energy efficiency (EE) of ~70% over 50 cycles (**Figure 4d**). Additionally, stable cycling is maintained in the flow cell without noticeable capacity degradation over 50 cycles, which is mainly attributed to the high stability of **2b** in the solution phase. These results illustrate that electrochemistry based on low-valent Fe(I)/Fe(II) ferrocene redox couples is feasible in practical battery operation and is enabled by the stereoelectronic stabilization of low-valent ferrocene by NHC moieties.

Ferrocene, one of the most representative compounds in the discipline of organometallic chemistry, attracted much attention because of its extremely high thermal, chemical, and Fe(II/III) redox stability. However, a well-characterized reduced ferrocene has not been achieved to date due to the fast dissociation of the cyclopentadienyl anion ligands from Fe(I). Thus, an Fe(I) biscyclopentadiene complex remained elusive for a long time. Here, we have shown that low-valent ferrocene derivatives **2a** and **2b** can be prepared by the one-electron reduction of **1a** and **1b** at ambient conditions, as confirmed by several complementary spectroscopic and theoretical methods. Additionally, a potential application in a redox-flow battery was successfully demonstrated using **1b** as the first example of ferrocene anolyte, in part due to the high degree of stabilization of low-valent state by the cAAC moiety. These NHC-Fc complexes may deepen our understanding of the electrochemical behavior of ferrocene compounds and open the way to the rational design of low-valent ferrocene derivatives.

Acknowledgments: The X-ray crystallography analysis with synchrotron radiation was performed at the Pohang Accelerator Laboratory (PLS-II BL2D SMC beamline). This work was supported by a National Research Foundation of Korea (NRF) grant funded by the Korean government [Ministry of Science, ICT and Future Planning (MSIP)] (No. NRF-2016H1A2A1907122 – Global Ph.D. Fellowship Program, NRF-2018R1A4A1024713, and NRF-2019M1A2A2067940). We thank Prof. Jonas C. Peters for use of the Mössbauer spectroscopy and Dr. Ewa Pietrasiak for helpful discussions. **Author contributions:** E.L. and H.S. conceived and designed the project. H.S. performed the synthesis and full characterizations of each compound, performed the computational studies and wrote the manuscript. K.K. oversaw the redox-flow battery investigation, and G.K. performed the experiments. C.C. performed ⁵⁷Fe Mössbauer spectroscopy measurements and DFT Mössbauer predictions. S.J. assisted in the synthesis of **1a** and **2a**. E.L. managed and guided the project and revised the manuscript. All authors discussed the results and commented on the manuscript.; **Competing interests:** Authors declare no competing interests. **Data and materials availability:** The crystallographic data for **1a** and **1b** are deposited in the Cambridge Crystallographic Data Centre (CCDC) with deposition numbers CCDC 1940623 and 1940622.

Supplementary Materials:

Materials and Methods

Figures S1-S21

Tables S1-S3

References and Notes:

- (1) Kealy, T. J.; Pauson, P. L., A New Type of Organo-Iron Compound. *Nature* **1951**, *168*, 1039.
- (2) Miller, S. A.; Tebboth, J. A.; Tremaine, J. F., 114. Dicyclopentadienyliron. *J. Chem. Soc.* **1952**, 632.
- (3) Gagne, R. R.; Koval, C. A.; Lisensky, G. C., Ferrocene as an Internal Standard for Electrochemical Measurements. *Inorg. Chem.* **1980**, *19*, 2854.
- (4) Patra, M.; Gasser, G., The Medicinal Chemistry of Ferrocene and Its Derivatives. *Nat. Rev. Chem.* **2017**, *1*, 0066.
- (5) van Staveren, D. R.; Metzler-Nolte, N., Bioorganometallic Chemistry of Ferrocene. *Chem. Rev.* **2004**, *104*, 5931.
- (6) Ko, Y. H.; Hwang, I.; Lee, D.-W.; Kim, K., Ultrastable Host–Guest Complexes and Their Applications. *Isr. J. Chem.* **2011**, *51*, 506.
- (7) Gómez Arrayás, R.; Adrio, J.; Carretero, J. C., Recent Applications of Chiral Ferrocene Ligands in Asymmetric Catalysis. *Angew. Chem. Int. Ed.* **2006**, *45*, 7674.
- (8) Malischewski, M.; Adelhardt, M.; Sutter, J.; Meyer, K.; Seppelt, K., Isolation and Structural and Electronic Characterization of Salts of the Decamethylferrocene Dication. *Science* **2016**, *353*, 678.
- (9) Trifan, D. S.; Nicholas, L., Reductive Cleavage of Ferrocene. *J. Am. Chem. Soc.* **1957**, *79*, 2746.
- (10) Ito, N.; Saji, T.; Aoyagui, S., Electrochemical Formation of Stable Ferrocene Anion and the Formal Rate Constant of the Ferrocene^{0/-} Electrode. *J. Organomet. Chem.* **1983**, *247*, 301.
- (11) (a) Brown, A. D.; Reich, H., Reductive Cleavage of Ferrocene Derivatives. *J. Org. Chem.* **1970**, *35*, 1191; (b) Khrizanforov, M.; Strekalova, S.; Kholin, K.; Khrizanforova, V.; Grinenko, V.; Gryaznova, T.; Budnikova, Y., One-Stage Synthesis of FcP(O)(OC₂H₅)₂ from Ferrocene and α -Hydroxyethylphosphonate. *RSC Adv.* **2016**, *6*, 42701.
- (12) (a) Slocum, D. W.; Jones, W. E.; Crimmins, T. F.; Hauser, C. R., Reduction of Ferrocene Methiodides. Synthesis of the Dimethylferrocenes. *J. Org. Chem.* **1969**, *34*, 1973; (b) Elschenbroich, C.; Cais, M., Organometallic Studies XXIX. Electron Spin Resonance of Ferrocene-Substituted Radical Anions. *J. Organomet. Chem.* **1969**, *18*, 135.
- (13) (a) Lemoine, P.; Gross, M.; Braunstein, P.; Mathey, F.; Deschamps, B.; Nelson, J. H., Electrochemistry of Phosphaferrocenes. 1. Comparison of the Redox Properties of Ferrocene, Diphosphaferrocene, 3,4-Dimethyl-1-Phosphaferrocene and 3,3',4,4'-Tetramethyl-1,1'-Diphosphaferrocene. *Organometallics* **1984**, *3*, 1303; (b) Ashe, A. J.; Al-Ahmad, S.; Pilotek, S.; Puranik, D. B.; Elschenbroich, C.; Behrendt, A., Comparison of the Properties of Polymethyl-1,1'-Diheteroferrocenes of the Group 15 Elements. *Organometallics* **1995**, *14*, 2689; (c) Winter, R. F.; Geiger, W. E., Electron-Transfer Properties of Cp*FeP₅: Evidence for Dimerization Reactions Following Both Oxidation and Reduction. *Organometallics* **1999**, *18*, 1827; (d) Greer, S. M.; Üngör, Ö.; Beattie, R. J.; Kiplinger, J. L.; Scott, B. L.; Stein, B. W.; Goodwin, C. A. P., Low-Spin 1,1'-Diphosphametalloccenates of Chromium and Iron. *Chem. Commun.* **2021**, DOI: 10.1039/D0CC06518H.
- (14) (a) Hamon, J. R.; Astruc, D.; Michaud, P., Syntheses, Characterizations, and Stereoelectronic Stabilization of Organometallic Electron Reservoirs: The 19-Electron d⁷ Redox Catalysts η^5 -C₅R₅Fe- η^6 -C₆R'₆. *J. Am. Chem. Soc.* **1981**, *103*, 758; (b) Rabaa, H.; Lacoste, M.; Delville-Desboise, M.-H.; Ruiz, J.; Gloaguen, B.; Ardoin, N.; Astruc, D.; Beuze,

- A. L.; Saillard, J.-Y., Electronic Interplay between Two Iron Centers across Polyaromatic Ligands: Syntheses, Redox Chemistry, and Electronic Structures of the Electron-Reservoir 36- to 38-Electron Complexes $[(\text{FeCp}^*)_2(\mu_2\text{-}\eta^{12}\text{-Polyaromatic})]^{q+}$ ($q = 0\text{-}2$) Including Mixed Valences and Biradicals. *Organometallics* **1995**, *14*, 5078; (c) Hatanaka, T.; Ohki, Y.; Kamachi, T.; Nakayama, T.; Yoshizawa, K.; Katada, M.; Tatsumi, K., Naphthalene and Anthracene Complexes Sandwiched by Two $\{(\text{Cp}^*)\text{Fe}^{\text{I}}\}$ Fragments: Strong Electronic Coupling between the Fe^{I} Centers. *Chem. Asian. J.* **2012**, *7*, 1231; (d) Saito, M.; Matsunaga, N.; Hamada, J.; Furukawa, S.; Tada, T.; Herber, R. H., Anionic Stannaferrocene and Its Unique Electronic State. *Chem. Lett.* **2019**, *48*, 163.
- (15) Goodwin, C. A. P.; Giansiracusa, M. J.; Greer, S. M.; Nicholas, H. M.; Evans, P.; Vonci, M.; Hill, S.; Chilton, N. F.; Mills, D. P., Isolation and Electronic Structures of Derivatized Manganocene, Ferrocene and Cobaltocene Anions. *Nat. Chem.* **2020**, DOI: 10.1038/s41557-020-00595-w.
- (16) Hopkinson, M. N.; Richter, C.; Schedler, M.; Glorius, F., An Overview of N-Heterocyclic Carbenes. *Nature* **2014**, *510*, 485.
- (17) (a) Martin, D.; Soleilhavoup, M.; Bertrand, G., Stable Singlet Carbenes as Mimics for Transition Metal Centers. *Chem. Sci.* **2011**, *2*, 389; (b) Song, H.; Kim, Y.; Park, J.; Kim, K.; Lee, E., Activation of Small Molecules at N-Heterocyclic Carbene Centers. *Synlett* **2016**, *27*, 477.
- (18) Nesterov, V.; Reiter, D.; Bag, P.; Frisch, P.; Holzner, R.; Porzelt, A.; Inoue, S., NHCs in Main Group Chemistry. *Chem. Rev.* **2018**, *118*, 9678.
- (19) (a) Martin, C. D.; Soleilhavoup, M.; Bertrand, G., Carbene-Stabilized Main Group Radicals and Radical Ions. *Chem. Sci.* **2013**, *4*, 3020; (b) Kim, Y.; Lee, E., Stable Organic Radicals Derived from N-Heterocyclic Carbenes. *Chem. Eur. J.* **2018**, *24*, 19110; (c) Kundu, S.; Sinhababu, S.; Chandrasekhar, V.; Roesky, H. W., Stable Cyclic (Alkyl)(Amino)Carbene (cAAC) Radicals with Main Group Substituents. *Chem. Sci.* **2019**, *10*, 4727.
- (20) Roy, S.; Mondal, K. C.; Roesky, H. W., Cyclic Alkyl(Amino) Carbene Stabilized Complexes with Low Coordinate Metals of Enduring Nature. *Acc. Chem. Res.* **2016**, *49*, 357.
- (21) Enders, D.; Breuer, K.; Raabe, G.; Simonet, J.; Ghanimi, A.; Stegmann, H. B.; Teles, J. H., A Stable Carbene as π -Acceptor Electrochemical Reduction to the Radical Anion. *Tetrahedron Lett.* **1997**, *38*, 2833.
- (22) Ramnial, T.; McKenzie, I.; Gorodetsky, B.; Tsang, E. M. W.; Clyburne, J. A. C., Reactions of N-Heterocyclic Carbenes (NHCs) with One-Electron Oxidants: Possible Formation of a Carbene Cation Radical. *Chem. Commun.* **2004**, 1054.
- (23) Canal, J. P.; Ramnial, T.; Dickie, D. A.; Clyburne, J. A. C., From the Reactivity of N-Heterocyclic Carbenes to New Chemistry in Ionic Liquids. *Chem. Commun.* **2006**, 1809.
- (24) Arduengo, A. J.; Bock, H.; Chen, H.; Denk, M.; Dixon, D. A.; Green, J. C.; Herrmann, W. A.; Jones, N. L.; Wagner, M.; West, R., Photoelectron Spectroscopy of a Carbene/Silylene/Germylene Series. *J. Am. Chem. Soc.* **1994**, *116*, 6641.
- (25) Khuseynov, D.; Fontana, M. T.; Sanov, A., Photoelectron Spectroscopy and Photochemistry of Tetracyanoethylene Radical Anion in the Gas Phase. *Chem. Phys. Lett.* **2012**, *550*, 15.
- (26) Arduengo III, A. J.; Calabrese, J. C.; Marshall, W. J.; Runyon, J. W.; Schiel, C.; Schinnen, C.; Tamm, M.; Uchiyama, Y., Imidazol-2-Ylidene Reactivity Towards Cyanocarbons. *Z. Anorg. Allg. Chem.* **2015**, *641*, 2190.
- (27) Song, H.; Kim, Y.; Park, J.; Ko, Y. H.; Kim, K.; Lee, E., An N-Heterocyclic-Carbene–Tetracyanoethylene Zwitterion: Experimental and Theoretical Study on Its Formation and Reactivity. *Eur. J. Org. Chem.* **2017**, 1231.
- (28) Meot-Ner, M., Ion Chemistry of Ferrocene. Thermochemistry of Ionization and

Protonation and Solvent Clustering. Slow and Entropy-Driven Proton-Transfer Kinetics. *J. Am. Chem. Soc.* **1989**, *111*, 2830.

(29) Chamkin, A. A.; Krivikh, V. V.; Nikitin, O. M.; Kreindlin, A. Z.; Shteltser, N. A.; Dolgushin, F. M.; Artyushin, O. I.; Ikonnikov, N. S.; Borisov, Y. A.; Belousov, Y. A., et al., Direct Phosphination of Ferrocenium Ion with Tertiary Phosphines by the Mechanism of Oxidative Nucleophilic Substitution. *Eur. J. Inorg. Chem.* **2018**, 4494.

(30) (a) Kunz, D.; Johnsen, E. Ø.; Monsler, B.; Rominger, F., Highly Ylidic Imidazoline-Based Fulvenes as Suitable Precursors for the Synthesis of Imidazolium-Substituted Metallocenes. *Chem. Eur. J.* **2008**, *14*, 10909; (b) Schmid, D.; Seyboldt, A.; Kunz, D., A Direct Synthesis of a Strongly Zwitterionic 6,6'-Diaminofulvalene. *Z. Naturforsch. B Chem. Sci.* **2014**, *69*, 580.

(31) (a) Wang, J.; Feng, L.; Ma, F.; Lin, F.; Xie, L.; Yuan, Y., Synthesis, Crystal Structure and Properties of Iodide and Hexafluorophosphate Salts of 2-Ferrocenyl (or Binuclear Ferrocenyl)-1,3-Dialkylbenzimidazolium. *Chin. J. Org. Chem.* **2012**, *32*, 1479; (b) Lai, Z.-M.; Ye, H.-M.; Wan, Q.; Xie, L.-L.; Bai, S.; Yuan, Y.-F., Synthesis, Crystal Structure and Properties of Benzimidazole-Bridged Dinuclear Ferrocenyl Derivatives. *J. Mol. Struct.* **2014**, *1059*, 33.

(32) Gleiter, R.; Bleiholder, C.; Rominger, F., A-Metallocenylmethyl cations and Isoelectronic Fulvene Complexes of d⁶ to d⁹ Metals. Structural Considerations. *Organometallics* **2007**, *26*, 4850.

(33) Babin, V. N.; Belousov, Y. A.; Belousova, T. A.; Borisov, Y. A.; Gumenyuk, V. V.; Nekrasov, Y. S., Reactions of Ferricinium Salts with Lewis Bases. *Russ. Chem. Bull.* **2011**, *60*, 2081.

(34) Edelmann, F.; Lubke, B.; Behrens, U., Übergangsmetall-Fulven-Komplexe, XVIII. Übergangsmetall(0)-Nickel(0)-Komplexe. Strukturvergleich Von (1,5-Cyclooctadien)(6,6-Diphenylfulven)Nickel Und Tricarbonyl-(6,6-Diphenylfulven)Eisen. *Chem. Ber.* **1982**, *115*, 1325.

(35) Good, M. L.; Buttone and, J.; Foyt, D., Mössbauer Spectroscopy of Metal Sandwich Compounds. *Ann. N. Y. Acad. Sci.* **1974**, *239*, 193.

(36) Gülich, P.; Bill, E.; Trautwein, A., *Mössbauer Spectroscopy and Transition Metal Chemistry: Fundamentals and Application*. Springer: Berlin, Heidelberg, 2011.

(37) Astruc, D., Why Is Ferrocene So Exceptional? *Eur. J. Inorg. Chem.* **2017**, 2017, 6.

(38) Soloveichik, G. L., Flow Batteries: Current Status and Trends. *Chem. Rev.* **2015**, *115*, 11533.

(39) Leung, P.; Shah, A. A.; Sanz, L.; Flox, C.; Morante, J. R.; Xu, Q.; Mohamed, M. R.; Ponce de León, C.; Walsh, F. C., Recent Developments in Organic Redox Flow Batteries: A Critical Review. *J. Power Sources* **2017**, *360*, 243.

(40) (a) Kwon, G.; Lee, S.; Hwang, J.; Shim, H.-S.; Lee, B.; Lee, M. H.; Ko, Y.; Jung, S.-K.; Ku, K.; Hong, J., et al., Multi-Redox Molecule for High-Energy Redox Flow Batteries. *Joule* **2018**, *2*, 1771; (b) Kwon, G.; Lee, K.; Lee, M. H.; Lee, B.; Lee, S.; Jung, S.-K.; Ku, K.; Kim, J.; Park, S. Y.; Kwon, J. E., et al., Bio-Inspired Molecular Redesign of a Multi-Redox Catholyte for High-Energy Non-Aqueous Organic Redox Flow Batteries. *Chem* **2019**, *5*, 2642; (c) Lee, M.; Hong, J.; Lee, B.; Ku, K.; Lee, S.; Park, C. B.; Kang, K., Multi-Electron Redox Phenazine for Ready-to-Charge Organic Batteries. *Green Chem.* **2017**, *19*, 2980.