

Discovery of a Two-Dimensional Type I Superionic Conductor

Alexander J. E. Rettie^{1,2,*}, Jingxuan Ding,³ Michael J. Johnson,² Christos D. Malliakas,⁴ Naresh C. Osti,⁵ Duck Young Chung¹, Raymond Osborn,¹ Olivier Delaire,³ Stephan Rosenkranz,^{1,*} Mercouri G. Kanatzidis^{1,4,*}

1. Materials Science Division, Argonne National Laboratory, Lemont, IL, 60439, USA

2. Electrochemical Innovation Lab, Department of Chemical Engineering, University College London, Bloomsbury, London, WC1E 6BT, UK

3. Departments of Mechanical Engineering, Materials Science and Physics, Duke University, Durham, NC, 27708, USA

4. Department of Chemistry, Northwestern University, Evanston, IL, 60208, USA

5. Neutron Scattering Division, Oak Ridge National Laboratory, Oak Ridge, TN, 37831, USA

Superionic conductor, two-dimensional, quasi-elastic neutron scattering, molecular dynamics

ABSTRACT: Type I superionic conductors (e.g., AgI, Ag₂Se, etc.) are defined by an abrupt transition to the superionic state and have so far been found exclusively in 3D crystal structures. Here, we reveal a new 2D type I superionic conductor, α -KAg₃Se₂ by total scattering techniques and complementary simulations. Quasi-elastic neutron scattering (QENS) from the high temperature superionic phase match a simple Fickian diffusion mechanism with a diffusion coefficient of $\sim 10^{-5}$ cm² s⁻¹ between 710 and 740 K. *Ab initio* molecular dynamics simulations confirm that the mobile Ag⁺ ions are confined to 4 Å thick layers, in addition to reproducing the experimental diffusion coefficient from QENS and the local structure obtained from X-ray powder pair-distribution-function analysis. Finally, chemical substitutions suggest that the nature of alkali metal ions comprising the charge-balancing layers can facilitate or inhibit the phase transition temperature.

INTRODUCTION

Superionic conductors (SICs) are solids which host liquid-like ionic conductivity, i.e., a diffusion coefficient, D of order $\sim 10^{-5}$ cm² s⁻¹, comparable to that of water at room temperature.¹ In addition to attracting long-standing scientific interest,²⁻³ this rapid ionic diffusion naturally lends itself to a wide application in energy storage.⁴⁻⁵ Recently, SICs have found utility in thermoelectric energy conversion, as atomic disorder and anharmonicity are linked to low lattice thermal conductivity⁶⁻⁷ and hence, high thermoelectric efficiency.⁸

Three classes have been used to categorize SICs based on the nature of the superionic transition.^{1,9} Type I SICs exhibit an abrupt transition to the superionic state (e.g., AgI, Ag₂Se, etc.),¹⁰ which becomes less well-defined for type II (continuous transition, e.g., PbF₂, AgCrSe₂)¹¹⁻¹², and non-existent in the case of type III SICs (e.g., the β -aluminas).¹³ In the superionic state, a non-conducting sublattice remains. This rigid network dictates the available conduction pathways and can be linked in one, two or three dimensions. Two-dimensional SICs, where rapid ionic diffusion is confined between immobile layers are well represented in types II and III, such as AgCrSe₂¹⁴ and Ag: β -Al₂O₃¹⁵ respectively. In both cases the underlying layered structures are unchanged at the onset of fast ionic conduction. Conversely, type I SICs known to date have exclusively 3D crystal structures (cubic or hexagonal, cf Table 3.2, ref 1),¹ with the archetypical AgI undergoing a first-order superionic phase transition to a body-centered cubic (bcc) arrangement of I ions (α -AgI) at

420 K.¹⁶ Similarly, orthorhombic α -Ag₂Se transforms to the bcc superionic phase, α -Ag₂Se at 406 K.¹⁷

Previously, we identified a first order, order-disorder phase transition in 2D KAg₃Se₂ – a dimensionally-reduced derivative of 3D Ag₂Se – at ~ 700 K using in-situ X-ray diffraction.¹⁸ However, the elevated temperature of the transition prevented measurement of the ionic conductivity because of reactions between KAg₃Se₂ and the electrode materials. Here, we use quasi-elastic neutron scattering (QENS) and complementary *ab initio* molecular dynamics (AIMD) simulations to reveal that the high temperature phase, α -KAg₃Se₂, is a superionic Ag⁺ ion conductor, with the quasi-molten Ag sublattice restricted to 4 Å thick layers. To the best of our knowledge, this represents the first type I superionic conductor with a 2D structure. Progressive reduction of long-range order through the melting point was probed by X-ray pair-distribution-function analysis, and the superionic local structure is also in good agreement with the AIMD simulations.

Chemical substitution has been an important tool in the design and modification of SICs; the most famous example being RbAg₄I₅, where substitution of Rb for Ag in AgI resulted in the highest room temperature solid-state ionic conductivity to date.¹⁹ To investigate these effects we synthesized a series of cation-substituted A Ag₃Se₂ (A = Li-Cs) compounds. Thermal analyses indicate that the superionic transition temperature can be tuned by the composition of alkali metal ions within the immobile layers.

EXPERIMENTAL SECTION

Reagents. The following reagents were used as received: sodium metal (99.9%, Sigma-Aldrich), potassium metal (99%, Sigma-Aldrich), rubidium metal (99%, Johnson Matthey), caesium metal (99.8%, Sigma-Aldrich), silver shot (99.99%, Alfa Aesar) and selenium shot (99.999%, Plasmaterials Inc.).

Synthesis. All chemical manipulations were conducted inside an Ar-filled glovebox (M-Braun) with oxygen and moisture levels < 0.1 ppm. Flame-sealing was performed by evacuating ampules to $< 10^{-3}$ mbar. Phase-pure KAg_3Se_2 powder was synthesized directly from the elements, with K and Se physically separated by Ag shot to avoid a strongly exothermic reaction. Elemental ratios K:Ag:Se of 1.05:3:2 were used, with a 5% molar excess K to account for surface oxidation of the metal. In a typical experiment, K metal chunks (1.101 g, 28 mmol) were compacted in the bottom of an 18 mm O.D. (outer diameter) \times 16 mm I.D. (inner diameter) fused-silica tube. Ag shot (8.682 g, 80 mmol) was then loaded followed by Se shot (4.237 g, 54 mmol) on top. To minimize the free volume inside the ampule, a 15 mm O.D. \times 13 mm I.D. fused-silica tube was used as a snug-fitting plug above the elements. This assembly was then flame-sealed and placed upright in a box furnace. The mixture was heated to 400 °C in 12 h and held for 12 h after which the furnace was turned off.

A_2Se_3 ($\text{A} = \text{Rb}, \text{Cs}$) precursor powders were synthesized using a tube-in-tube method. Briefly, a stoichiometric amount of Se was suspended in an alumina crucible above Rb or Cs metal and flame-sealed in an 18 mm O.D. \times 16 mm I.D. fused-silica tube while the bottom of the tube was submerged in liquid nitrogen. This assembly was placed upright in a muffle furnace and heated to 500 °C in 20 h and held at that temperature for 12 h before natural cooling to room temperature. A black A_2Se_3 ingot could be removed from the bottom of the tube in both cases. Li_2Se and Na_2Se were produced by combining the elements in a 2:1 molar ratio in liquid ammonia using established procedures.²⁰

To synthesize the RbAg_3Se_2 and CsAg_3Se_2 ternary compounds, A_2Se_3 ($\text{A} = \text{Rb}, \text{Cs}$), Ag and Se powders were homogenized in a mortar and pestle in a 1:6:1 molar ratio, loaded into a graphite crucible and capped with a graphite plug before being flame-sealed in a 15 mm O.D. \times 13 mm I.D. fused-silica tube. These mixtures were heated to 400 °C in 3 h and held for 12 h before the furnace was turned off. Similar procedures were used for targeting LiAg_3Se_2 and $\text{Na}_x\text{K}_{1-x}\text{Ag}_3\text{Se}_2$ ($x = 0.05, 1$) using stoichiometric molar ratios of Li_2Se , Na_2Se , Ag, Se and KAg_3Se_2 . In all cases a black, homogeneous powder compact was produced. Powder X-ray diffractograms for all products can be located in the Supporting Information (SI, Figures S1-4).

Quasi-Elastic Neutron Scattering. Quasi-elastic neutron scattering (QENS) data were collected at the backscattering silicon spectrometer (BASIS)²¹ at the Spallation Neutron Source, Oak Ridge National Laboratory (ORNL) using a Closed Cycle Re-

frigerator sample environment (maximum operating temperature: 740 K). Because of the high absorption cross-section of Ag, ~ 10 g of KAg_3Se_2 was loaded into four 7 mm O.D. \times 6 mm I.D. fused-silica tubes and flame-sealed. These were placed side-by-side in the Al sample can to approximate a flat plate scattering geometry (see Figure S5 in the SI). Furnaces capable of higher temperature operation had much larger background scattering from Al and so were not suitable. First, short elastic scans from 300 to 740 K were measured. Spectra were then collected on cooling between 740 and 710 K in 10 K increments, followed by a long QENS measurements at 300 K, which was used as the instrument resolution function. Finally, four nominally identical, empty, evacuated tubes were used for the background measurement at 740 K. $S(Q, \omega)$ data were reduced using Mantid software²² in the range -100 to 100 μeV and binned in 0.04 μeV steps over a Q range of 0.3-1.3 \AA^{-1} binned in 0.1 \AA^{-1} steps. Fitting of the QENS data (see section S1 in SI) was performed using the Data Analysis and Visualization Environment (DAVE) package.²² The bandwidth of incoming neutron was centered at 6.4 \AA . Coherent scattering from Bragg peaks was present between $Q^2 = 0.5\text{-}0.64 \text{\AA}^{-2}$ and $Q^2 > 1.9 \text{\AA}^{-2}$, thus these Q -ranges were excluded from the analysis (Figure S6A in the SI).²³ However, we note that the inclusion of these data did not markedly affect the fitting results.

Ab initio Molecular Dynamics Calculations. *Ab initio* molecular dynamics (AIMD) simulations were performed using the Vienna Ab initio Simulation Package (VASP),²⁴⁻²⁶ using as exchange-correlation functional the generalized gradient approximation (GGA) in the Perdew-Burke-Ernzerhof (PBE) form.²⁷⁻²⁸ Convergence tests were conducted with low temperature β - KAg_3Se_2 , where a plane-wave cut-off energy of 350 eV and an electronic k -point mesh of $3 \times 12 \times 6$ were used. The electronic self-consistent loop converged to 10^{-8} eV and the forces were smaller than 10^{-4} eV/ \AA on all atoms. AIMD simulations were performed on a $4 \times 4 \times 1$ supercell of the superionic α - KAg_3Se_2 (288 atoms) using the experimental lattice constants, $a = 4.56 \text{\AA}$, and $c = 25.41 \text{\AA}$, with the Brillouin zone center, Γ , as the only k -point. Three parallel trajectories starting with random initial structures were calculated at 700, 800, and 900 K, and averaged for mean square displacement (MSD) and PDF calculations. For each initial structure, the stoichiometry (75% Ag site occupancy) was maintained by randomly removing 25% of Ag atoms in each layer. Each trajectory was at least 22 ps long with 2 fs steps, and the first 5 ps were treated as equilibration time.

Synchrotron X-ray Scattering. In-situ X-ray total scattering data were collected at Sector 17-BM-B at the Advanced Photon Source from 300 to 950 K using a PerkinElmer amorphous silicon flat panel detector. KAg_3Se_2 powder was sieved to $< 45 \mu\text{m}$ and loaded into a 0.3 mm diameter fused-silica capillary and flame-sealed. The sample was spun during collection and the wavelength used was 0.24141 \AA . Integration and background subtraction was performed using GSAS-II software (version 3667),²⁹ transformation from $S(Q)$ to $G(r)$ using PDFgetX3³⁰ (with $Q_{\text{max}} = 18 \text{\AA}^{-1}$) and fitting using pdfgui software.³¹

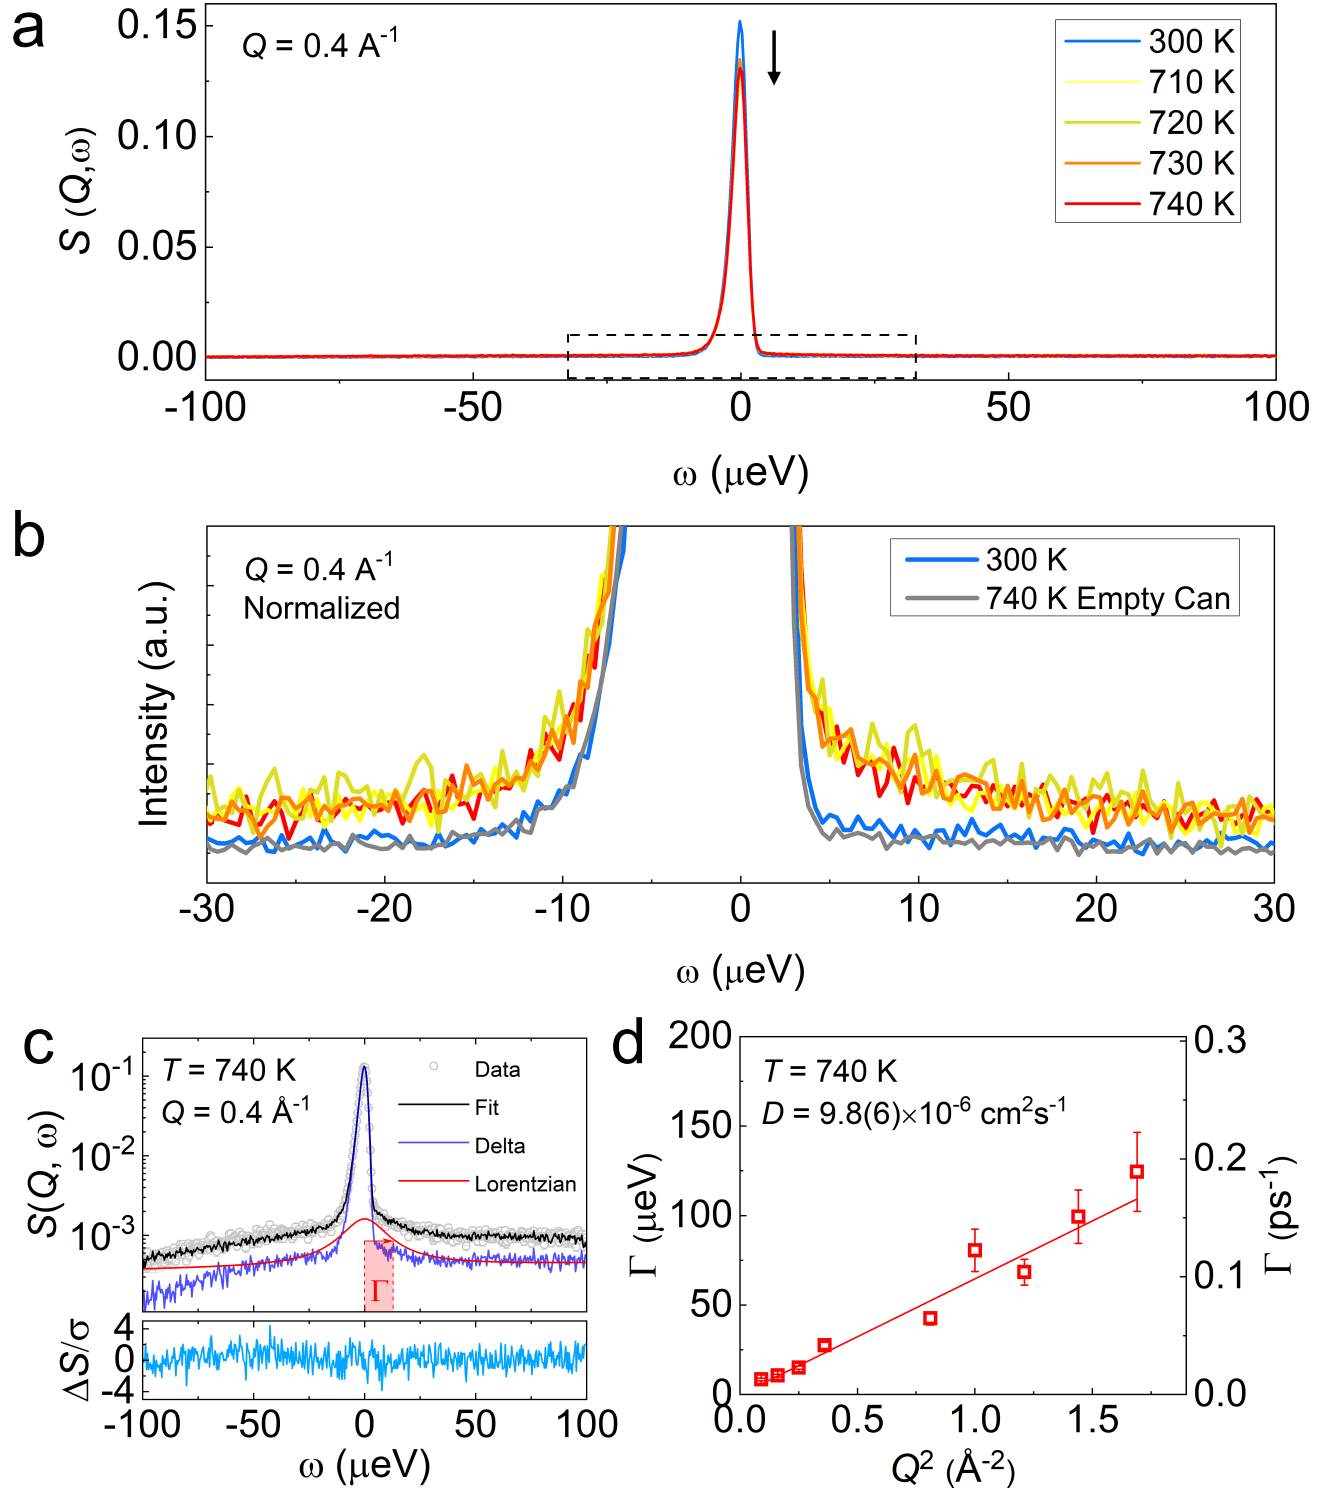


Figure 1. **a)** Representative QENS spectra at $Q = 0.4 \text{ \AA}^{-1}$ as a function of temperature for KAg_3Se_2 . The arrow shows a sharp decrease in elastic intensity for the high temperature α -phase. **b)** Normalized $S(Q, \omega)$ from the boxed region in **B)**, illustrating quasi-elastic broadening in α - KAg_3Se_2 . The legend is the same as **A)**. **c)** Fitting of $S(Q, \omega)$ at 740 K and $Q = 0.4 \text{ \AA}^{-1}$ using linear background (BG), delta and Lorentzian functions. Note that the BG function has been added to the Lorentzian component for clarity. **d)** Half-width half-maximum of the Lorentzian component, Γ vs. Q^2 . A linear fit yielded the diffusion coefficient, D . Q -regions that include strong Bragg contributions have been omitted.

Powder X-ray Diffraction. Phase purity was determined by powder X-ray diffraction (PXRD). Data were collected using a Rigaku Miniflex diffractometer with a Ni-filtered Cu K α source operating at 15 mA and 40 kV. Continuous scanning was utilized with a step size of 0.015°. Materials were finely ground and uniformly coated on a flat plate sample holder and protected from ambient conditions using Kapton film and vacuum grease.

Differential Thermal Analysis. Differential thermal analyses (DTA) were carried out using a Shimadzu DTA-50 thermal analyzer. The powder samples (~30 mg total mass) were evacuated and sealed in carbon-coated, fused-silica ampules. A fused-silica ampule containing alumina powder was used as a reference. All samples were heated to the desired temperature at 5 K min⁻¹, followed by cooling at the same rate to 343 K. Transition temperatures were determined from the onset of endothermic features.

RESULTS AND DISCUSSION

Quasi-Elastic Neutron Scattering (QENS). QENS probes small energy transfers around a central elastic scattering peak. Dynamic processes, such as diffusion, manifest as peak broadening that grows at the expense of elastic intensity.²³ The Q -dependence of this broadening yields information on these processes, with a linear dependence on Q^2 being indicative of translational diffusion following Fick's second law.³²

Elastic scans from 300 to 740 K showed a sharp decrease in elastic intensity at ~680 K (Figure S6B in the SI), concurrent with the β - α phase transition previously reported,¹⁸ and the onset of quasi-elastic scattering (Figure 1A). The spectra collected of the can containing only empty fused-silica tubes overlapped with the elastic peak observed at room temperature (Figure 1B) – therefore the quasi-elastic component was from the sample only. These data were fit using delta, linear background and Lorentzian functions (Figure 1C and Section S1 in the SI), where the delta function represented purely elastic scattering and a single Lorentzian function captured the QE scattering component. The half-width half-maximum of this peak, Γ was plotted a function of Q^2 to yield information on diffusing species in the sample.

These QE scattering data were well-described by a linear fit through the origin, indicating translational Fickian diffusion in the superionic phase (see Figure 1D and Figure S7 in the SI). Similar QENS results were observed in α -Ag₂Se where simple Fickian diffusion was also assigned.³³ In more complex jump-diffusion models, *e.g.*, the Chudley-Elliott model,³⁴ oscillatory behavior of Γ occurs with increasing Q^2 , associated with discrete jumps on a crystalline sublattice. Although the limited Q -range here means we cannot comment on the applicability of more complex models, this should not significantly affect the magnitude of the diffusion coefficient.³⁵ The diffusion coefficient, D determined from this analysis was approximately 10⁻⁵

cm² s⁻¹ from 710 to 740 K, corresponding to superionic diffusion in α -KAg₃Se₂.

Interpretation of QENS data is straightforward in the case of incoherent scattering, which pertains to single particle dynamics and hence, directly to diffusion.³² Ag primarily scatters neutrons coherently, with the coherent scattering cross-section being roughly an order of magnitude larger than that of the incoherent contribution (4.41 and 0.58 barns respectively).³⁶ To account for coherency effects, the structure factor, $S(Q)$ should be considered when modelling $\Gamma(Q)$.³⁷ However, in QENS studies of superionic α -Ag₂Se, coherency effects were found to be negligible for $Q^2 < 2 \text{ \AA}^{-2}$ (the maximum Q^2 value in our experiments), and the extracted diffusion coefficient from DQ^2 analysis matched values from ionic conductivity measurements and AIMD simulations.³³ Similarly, incoherent QENS analysis of the Cu⁺-ion SICs (Cu also mainly scatters neutrons coherently), α -Cu₂Se⁶ and α -CuCrSe₂³⁸ also yielded diffusion coefficient values in good agreement with conductivity measurements and molecular dynamics simulations – again suggesting minimal coherency effects. Therefore, our approach is reasonable based on previous results and the agreement between our incoherent DQ^2 analysis and complementary AIMD simulations.

Ab initio Molecular Dynamics (AIMD) Simulations. Molecular dynamics simulations were performed to gain insights into the superionic behavior of KAg₃Se₂. Initial simulations of the low temperature β -KAg₃Se₂ showed no diffusion, but larger displacements for Ag atoms, consistent with the single-crystal structure solution (Figure S8 in the SI).³⁹ As shown in Figure 2A, simulations of the superionic α -phase (space group $R\bar{3}m$) showed superionic Ag⁺ diffusion on the order of 10⁻⁵ cm² s⁻¹ at 800 K, in excellent agreement with the QENS analysis. In contrast, K and Se did not show characteristics of diffusion and so comprise the rigid sublattice in α -KAg₃Se₂. Mobile Ag⁺ ions are therefore sandwiched between [KSe₂]³⁻ slabs of edge-sharing KSe₆ octahedra (see Video S1 in the SI). This quasi-2D confinement is unique in the category of Type I SICs. Significant similarities exist between α -KAg₃Se₂ and other 2D Ag⁺-ion SICs; especially with AgCrSe₂ (type II) which shares the $R\bar{3}m$ space group and Se anion network, but also with Ag: β -Al₂O (type III) which exhibits a hexagonal ($P6_3/mmc$ space group) crystal structure (Figure 2B).

Additional AIMD simulations were performed at 700 and 900 K to obtain data points for activation energy analysis (Figure S9 in the SI). Simple fitting of D as a function of temperature was performed using an Arrhenius relationship,

$$D(T) = D_0 \exp(-E_a/k_B T), \quad (1)$$

where, D_0 is a model-dependent pre-exponential factor, E_a is the activation energy for diffusion, k_B is the Boltzmann constant

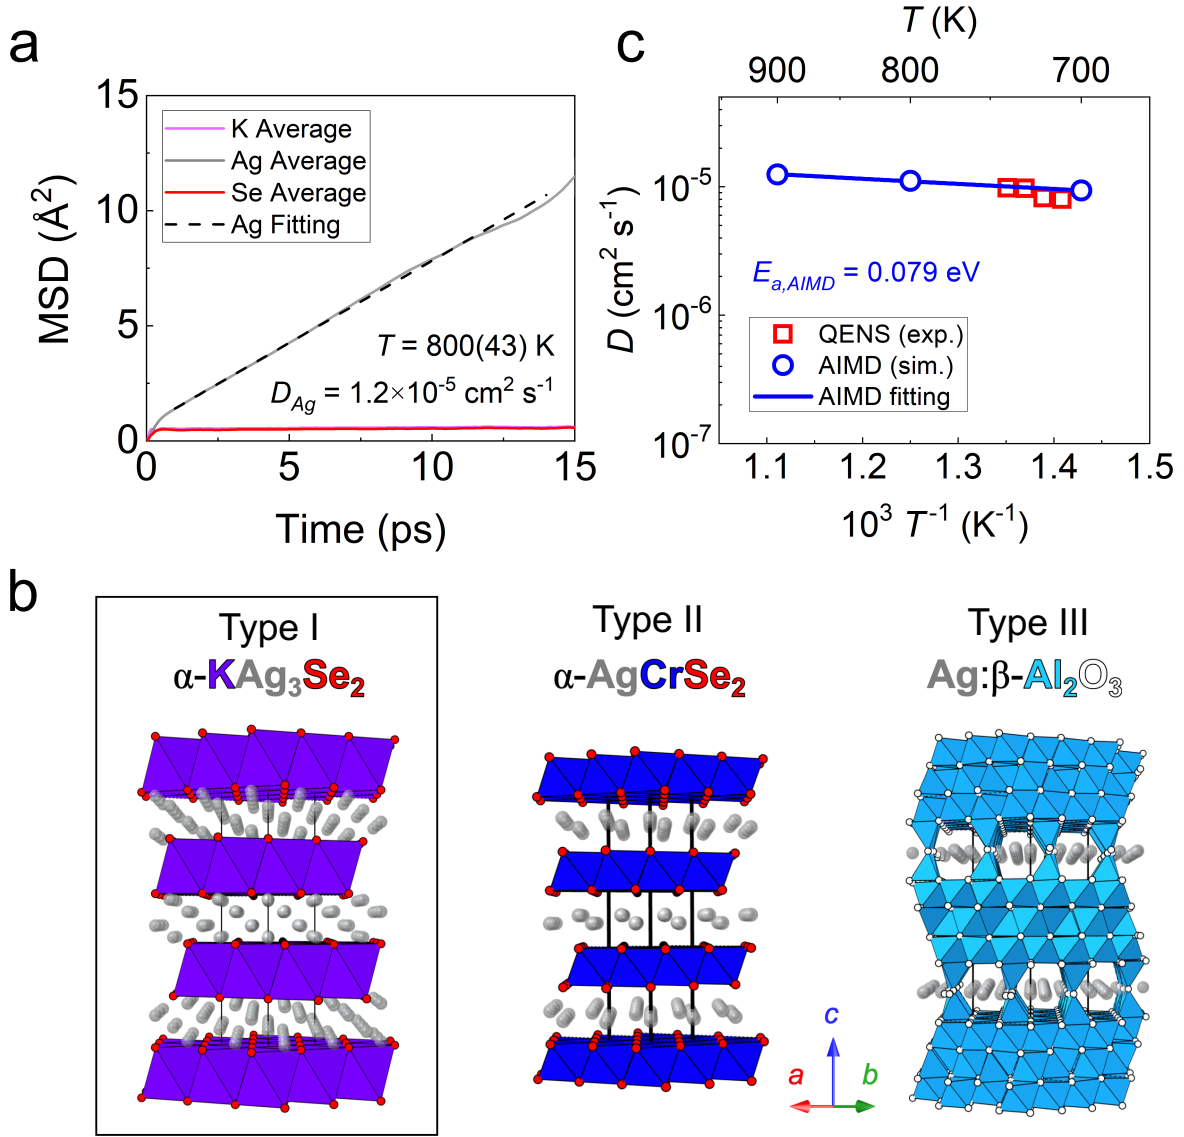


Figure 2. **a)** AIMD simulated mean square displacement (MSD) of atomic species in $\alpha\text{-KAg}_3\text{Se}_2$ at 800 K. The linear fit yields the diffusion coefficient of Ag ions. **b)** Crystal structures of 2D Ag^+ ion SICs organized by type. The immobile rigid lattice is represented by solid polyhedra and the mobile Ag^+ ions as translucent spheres. The unit cells are drawn with solid black lines. **c)** Extracted diffusion coefficients from QENS (open blue squares) and those derived from AIMD simulations (open red circles) vs. reciprocal temperature. Error bars have been omitted for clarity but were used in the determination of the AIMD activation energy (linear fit represented by a solid red line).

and T is temperature. Application of Equation 1 yielded an $E_{a,AIMD} = 0.079(4) \text{ eV}$ and $D_{0,AIMD} = 3.47(1) \times 10^{-5} \text{ cm}^2 \text{ s}^{-1}$. The small E_a value, on the order of $k_B T$, was consistent with facile ionic diffusion and that measured for 3D type I SICs such as AgI ,⁴⁰ Ag_2S ⁴¹ and Ag_2Se .⁴²⁻⁴³ The experimental QENS data are consistent with the trend over the wider T range from simulations (Figure 2C).

Pair-Distribution-Function Analysis. Detailed analyses of the local structures of the β , α and liquid phases of KAg_3Se_2 were achieved using X-ray pair-distribution-function (PDF) analysis. In the superionic α -phase, atomic correlations were broader and

weaker in magnitude than in the ordered β -phase (Figure 3A). Liquid KAg_3Se_2 closely resembled nearest-neighbor Ag-Se, Se-Se and Ag-Ag correlations in liquid Ag_2Se .⁴⁴

The local structures of both β - and $\alpha\text{-KAg}_3\text{Se}_2$ were well described using the previously reported average structures and refining anisotropic atomic displacement parameters (ADPs). Weighted residuals (R_w) of $\sim 10\%$ and $\sim 20\%$ were achieved in the ordered β -phase and disordered α -phase respectively (Figure S10 in the SI). Full fitting details can be located in Section S2 in the SI. PDF analysis has been shown to produce reliable

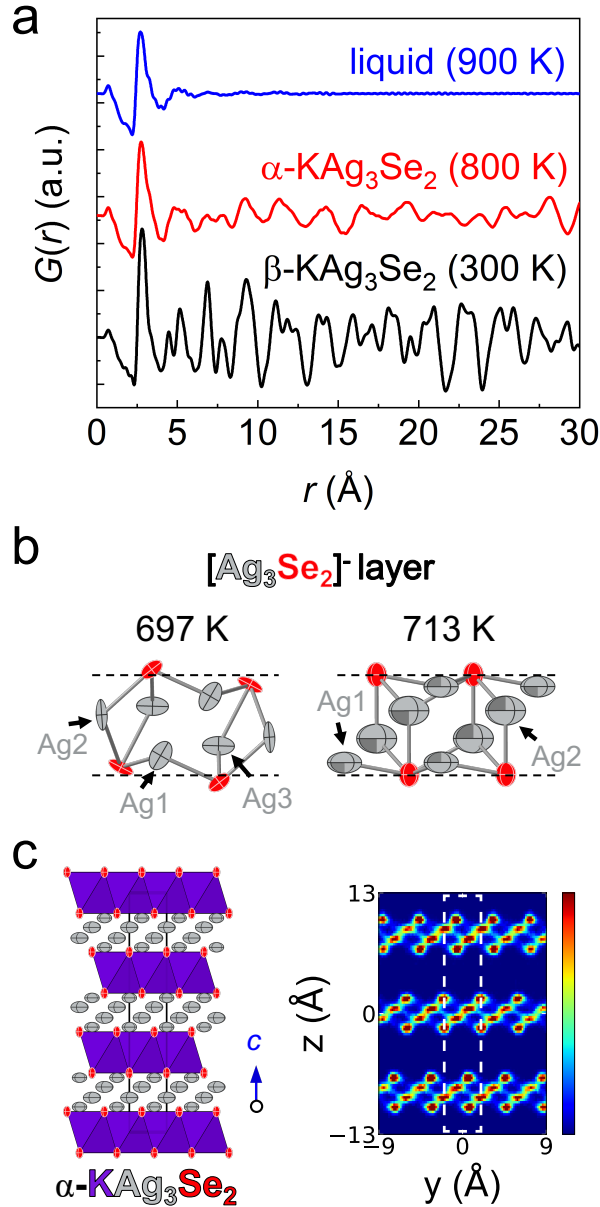


Figure 3. **a)** In-situ X-ray PDF of KAg₃Se₂ powder. **b)** Refined local structures of the Ag-Se layers just below (697 K) and just above (713 K) the superionic transition, in the β - and α -phases respectively. Note that the Ag atoms at 713 K (α -phase) have 75% occupancy. **c)** Crystal structure of α -KAg₃Se₂ from PDF analysis (left) compared with simulated Ag probability densities, both at 800 K (right). The unit cell is shown by solid black and dashed white lines respectively. Thermal ellipsoids are shown at 50%.

ADPs, comparable to those from single-crystal refinement.⁴⁵ Indeed, for the low temperature phase, the anisotropic ADPs were in good agreement with those from single-crystal data (Figure S11 in the SI). Three unique Ag atoms describe the corrugated [Ag₃Se₂]⁻ layers, with Ag1 and Ag3 forming tunnels along the

b -axis, which are bridged by Ag2 (Figure 3B). The type I superionic phase transition was observed around 700 K, fully occurring in a ~ 15 K window. As shown in Figure 3B, the Ag ADPs became very large (all with U_{eq} of ~ 0.1) and anisotropic as the transition was approached, consistent with the vibrations of these atoms destabilizing the ordered phase and driving the transition to the superionic state.

In superionic α -KAg₃Se₂, the silver layers are comprised of two unique sites with 75% occupancy: Ag1 in a bent trigonal planar and Ag2 in a distorted tetrahedral coordination (Figure 3B). Both Ag sites are characterized by large displacement parameters which can indicate static or dynamic disorder. The Ag probability densities derived from AIMD simulations qualitatively match the ADPs from PDF analysis, suggesting that the Ag ions are dynamically disordered – a common feature of SICs.⁹ Our simulations indicated no strong preference between Ag1 or Ag2 sites on the timescales probed here and that all Ag⁺ ions were mobile, thus an in-plane ionic conductivity, $\sigma_l = neDZ/k_B T$, of ~ 0.5 S cm⁻¹ could be estimated at 800 K. In contrast, probability distributions for K and Se showed localized and isotropic distributions, reflecting harmonic potentials (Figure S12 in the SI).

Cation Substitution. As shown in the preceding section, strongly anisotropic Ag thermal motion appears to drive the superionic transition with seemingly little contribution from the charge-balancing K-Se layers. Substitutions of K⁺ with Na⁺, Rb⁺ and Cs⁺ in the ordered β -phase of KAg₃Se₂ were accomplished by solid-state methods and solid-transition temperatures, T_t , were monitored using DTA (Figures 4 and S13 in the SI). Attempts at full replacement of K⁺ with Li⁺ or Na⁺ ions resulted in no ternary formation or a new, unknown ternary phase respectively (see Figure S2 in the SI). Na-doping resulted in a lower T_t for Na_{0.05}K_{0.95}Ag₃Se₂ by ~ 30 K, while neither RbAg₃Se₂ nor CsAg₃Se₂ exhibited features consistent with a solid phase transition before melting.

The lack of sharp transitions in the latter compounds was somewhat unexpected. Both RbAg₃Se₂ and CsAg₃Se₂ are isostructural with β -KAg₃Se₂, with virtually no change in Ag-Se interatomic distances (< 0.01 Å).³⁹ Similarly minor structural effects are expected in Na_{0.05}K_{0.95}Ag₃Se₂ due to the low level of doping. Therefore, we attribute these trends to the character of the immobile, charge-balancing layers as opposed to “chemical pressure”. Taken altogether, we speculate that the larger alkali metal ions are unable to adopt the perfect octahedral geometry with Se observed in α -KAg₃Se₂ (Figures 2B and 3C), inhibiting the superionic transition and vice versa. However, further characterization (e.g., in-situ X-ray ray scattering, differential scanning calorimetry, QENS) of additional members of the solid solutions $A_xK_{1-x}Ag_3Se_2$, where A = alkali metals will be required to definitively establish this trend and will be the focus of future work.

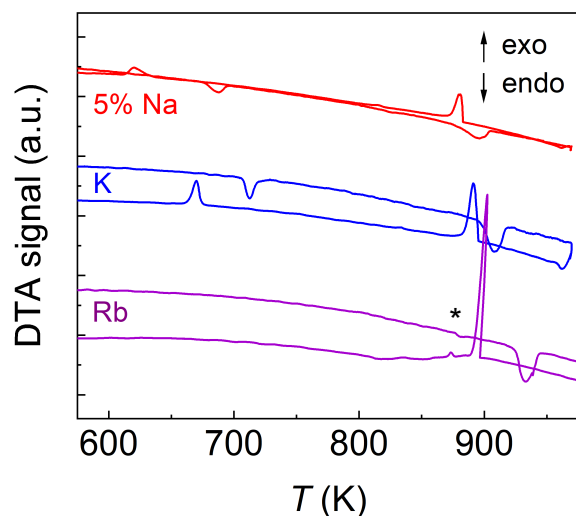


Figure 4. DTA curves for $\text{Na}_{0.05}\text{K}_{0.95}\text{Ag}_3\text{Se}_2$, KAg_3Se_2 and RbAg_3Se_2 , illustrating the effect of cation substitution on endo/exothermic features prior to melting/crystallization at *ca.* 900 K. DTA data for CsAg_3Se_2 have been omitted for clarity and can be located in Figure S13 in the SI. The DTA signal is not quantitative, *i.e.*, the signal depends on sample and reference masses as well as sample composition. Small unknown impurity peaks and an anomalous change in baseline for the RbAg_3Se_2 trace are indicated with a “*” symbol.

CONCLUSIONS

α - KAg_3Se_2 is a new type I superionic conductor and the first with a 2D crystal structure. Quasi-elastic neutron scattering (QENS) between 710 and 740 K yields a diffusion coefficient of $\sim 10^{-5} \text{ cm}^2 \text{ s}^{-1}$, comparable to that of liquid water at room temperature. Our *ab initio* molecular dynamics (AIMD) simulations show that K and Se atoms form the immobile sublattice and the superionic Ag^+ ions reside in 4 Å thick infinite slabs. The AIMD simulations reproduce the diffusion coefficient from QENS and the local structure measured by powder X-ray pair-distribution-function analysis. Initial exploration of isostructural analogues suggests that, rather than any chemical pressure effects on the Ag-Se network, the malleability of the charge-

balancing ions facilitates or inhibits the superionic phase transition temperature. The availability of this compound opens a new stage for experimentation aimed at studying in detail ionic motion confined in two dimensions. Our work extends the known classes of superionic conductors and should facilitate the design of new materials with tailored ionic conductivities and phase transitions.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website.

Powder XRD of $A\text{Ag}_3\text{Se}_2$ ($A = \text{Li-Cs}$) compounds, experimental details of QENS measurements, additional AIMD simulations, PDF analysis and DTA data.

AUTHOR INFORMATION

Corresponding Authors

- * a.rettie@ucl.ac.uk
- * srosenkranz@anl.gov
- * m-kanatzidis@northwestern.edu

ACKNOWLEDGMENTS

AR acknowledges Wenqian Xu for assistance in acquisition and analysis of X-ray total scattering data. This work was performed primarily at the Materials Science Division at Argonne National Laboratory supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division. We gratefully acknowledge the computing resources provided on Bebop, the high-performance computing clusters operated by the Laboratory Computing Resource Center at Argonne National Laboratory. First-principles modeling at Duke University (JD, OD) was supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division, under Award No. DE-SC0019299. Work at ORNL's Spallation Neutron Source is supported by the U.S. Department of Energy, Office of Basic Energy Sciences. The Oak Ridge National Laboratory is managed by UT-Battelle, LLC, for U.S. DOE under Contract No. DEAC05-00OR22725.

REFERENCES

- Boyce, J. B.; Huberman, B. A., Superionic conductors: Transitions, structures, dynamics. *Phys. Rep.* **1979**, *51* (4), 189-265.
- Faraday, M., *Phil. Trans. R. Soc* **1838**, *90*.
- Hull, S., Superionics: crystal structures and conduction processes. *Rep. Prog. Phys* **2004**, *67* (7), 1233-1314.
- Goodenough, J. B., Review Lecture-Fast ionic conduction in solid. *Proceedings of the Royal Society of London. A. Mathematical and Physical Sciences* **1984**, *393* (1805), 215-234.
- Solid State Electrochemistry*. Cambridge University Press: 1997; Vol. 5.
- Vonshen, D.; Walker, H.; Refson, K.; Goff, J., Hopping Time Scales and the Phonon-Liquid Electron-Crystal Picture in Thermoelectric Copper Selenide. *Phys. Rev. Lett.* **2017**, *118* (14), 145901.
- Ding, J.; Niedziela, J. L.; Bansal, D.; Wang, J.; He, X.; May, A. F.; Ehlers, G.; Abernathy, D. L.; Said, A.; Alatas, A., Anharmonic lattice dynamics and superionic transition in AgCrSe_2 . *Proceedings of the National Academy of Sciences* **2020**, *117* (8), 3930-3937.
- Bailey, T. P.; Uher, C., Potential for Superionic Conductors in Thermoelectric Applications. *Curr. Opin. Green Sustainable Chem* **2017**, *4*, 58-63.
- Keen, D. A., Disordering phenomena in superionic conductors. *J. Phys.: Condens. Matter* **2002**, *14* (32), R819.
- Funke, K., AgI-type solid electrolytes. *Prog. Solid State Chem.* **1976**, *11*, 345-402.
- Derrington, C.; O'Keeffe, M., Anion conductivity and disorder in lead fluoride. *Nature Physical Science* **1973**, *246* (151), 44-46.
- Boukamp, B.; Wieggers, G., Ionic and electronic processes in AgCrSe_2 . *Solid State Ionics* **1983**, *9*, 1193-1196.

13. Yao, Y.-F. Y.; Kummer, J., Ion exchange properties of and rates of ionic diffusion in beta-alumina. *J. Inorg. Nucl. Chem.* **1967**, *29* (9), 2453IN12467-24662475.
14. Engelsman, F.; Wiegers, G.; Jellinek, F.; Van Laar, B., Crystal structures and magnetic structures of some metal (I) chromium (III) sulfides and selenides. *J. Solid State Chem.* **1973**, *6* (4), 574-582.
15. Newsam, J.; Cheetham, A., Stoichiometric silver beta alumina studied at 25, 300 and 500 degrees C by powder neutron diffraction. *J. Phys.: Condens. Matter* **1990**, *2* (10), 2335.
16. Tubandt, C.; Lorenz, E., Molekularzustand und elektrisches Leitvermögen kristallisierter Salze. *Z. Phys. Chem.* **1914**, *87* (1), 513-542.
17. Miyatani, S.-y., Ionic conductivity in silver chalcogenides. *J. Phys. Soc. Jpn.* **1981**, *50* (10), 3415-3418.
18. Rettie, A. J.; Malliakas, C. D.; Botana, A. S.; Hodges, J. M.; Han, F.; Huang, R.; Chung, D. Y.; Kanatzidis, M. G., Ag₂Se to KAg₃Se₂: Suppressing Order–Disorder Transitions via Reduced Dimensionality. *Journal of the American Chemical Society* **2018**, *140* (29), 9193-9202.
19. Raleigh, D. O., Ionic Conductivity of Single-Crystal and Polycrystalline RbAg₄S₅. *J. Appl. Phys.* **1970**, *41* (4), 1876-1877.
20. Sharp, K. W.; Koehler, W. H., Synthesis and characterization of sodium polyselenides in liquid ammonia solution. *Inorg. Chem.* **1977**, *16* (9), 2258-2265.
21. Mamontov, E.; Herwig, K. W., A time-of-flight backscattering spectrometer at the Spallation Neutron Source, BASIS. *Rev. Sci. Instrum.* **2011**, *82* (8), 085109.
22. Arnold, O.; Bilheux, J.-C.; Borreguero, J. M.; Buts, A.; Campbell, S. I.; Chapon, L.; Doucet, M.; Draper, N.; Leal, R. F.; Gigg, M. A., Mantid—Data analysis and visualization package for neutron scattering and μ SR experiments. *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **2014**, *764*, 156-166.
23. Mamontov, E., Fast oxygen diffusion in bismuth oxide probed by quasielastic neutron scattering. *Solid State Ionics* **2016**, *296*, 158-162.
24. Kresse, G.; Furthmüller, J., Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54* (16), 11169.
25. Kresse, G.; Furthmüller, J., Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Computational materials science* **1996**, *6* (1), 15-50.
26. Kresse, G.; Hafner, J., Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **1993**, *47* (1), 558.
27. Perdew, J. P.; Burke, K.; Ernzerhof, M., Generalized gradient approximation made simple. *Phys. Rev. Lett.* **1996**, *77* (18), 3865-3868.
28. Perdew, J. P.; Zunger, A., Self-interaction correction to density-functional approximations for many-electron systems. *Phys. Rev. B* **1981**, *23* (10), 5048.
29. Toby, B. H.; Von Dreele, R. B., GSAS-II: the genesis of a modern open-source all purpose crystallography software package. *J. Appl. Crystallogr.* **2013**, *46* (2), 544-549.
30. Juhás, P.; Davis, T.; Farrow, C. L.; Billinge, S. J. L., PDFgetX3: a rapid and highly automatable program for processing powder diffraction data into total scattering pair distribution functions. *J. Appl. Crystallogr.* **2013**, *46* (2), 560-566.
31. Farrow, C.; Juhas, P.; Liu, J.; Bryndin, D.; Božin, E.; Bloch, J.; Proffen, T.; Billinge, S., PDFfit2 and PDFgui: computer programs for studying nanostructure in crystals. *J. Phys.: Condens. Matter* **2007**, *19* (33), 335219.
32. Bée, M., Localized and long-range diffusion in condensed matter: state of the art of QENS studies and future prospects. *Chemical Physics* **2003**, *292* (2-3), 121-141.
33. Hamilton, M.; Barnes, A.; Howells, W.; Fischer, H., Ag⁺ dynamics in the superionic and liquid phases of Ag₂Se and Ag₂Te by coherent quasi-elastic neutron scattering. *J. Phys. Condens. Matter* **2001**, *13* (11), 2425.
34. Chudley, C.; Elliott, R., Neutron scattering from a liquid on a jump diffusion model. *Proceedings of the Physical Society* **1961**, *77* (2), 353.
35. Embs, J. P.; Juranyi, F.; Hempelmann, R., Introduction to quasielastic neutron scattering. *Z. Phys. Chem.* **2010**, *224* (1-2), 5-32.
36. Hempelmann, R., *Quasielastic neutron scattering and solid state diffusion / Rolf Hempelmann*. Oxford : Clarendon: Oxford, 2000.
37. Wind, J.; Mole, R. A.; Yu, D.; Ling, C. D., Liquid-like Ionic Diffusion in Solid Bismuth Oxide Revealed by Coherent Quasielastic Neutron Scattering. *Chem. Mater.* **2017**, *29* (17), 7408-7415.
38. Niedziela, J. L.; Bansal, D.; May, A. F.; Ding, J.; Lanigan-Atkins, T.; Ehlers, G.; Abernathy, D. L.; Said, A.; Delaire, O., Selective breakdown of phonon quasiparticles across superionic transition in CuCrSe₂. *Nature Physics* **2019**, *15* (1), 73-78.
39. Bensch, W.; Dürichen, P., Crystal structure of potassium diselenotriargentate, KAg₃Se₂. *Z. Kristallogr. - New Cryst. Struct.* **1997**, *212* (1), 97-98.
40. Kvist, A.; Josefson, A.-M., The electrical conductivity of solid and molten silver iodide. *Zeitschrift für Naturforschung A* **1968**, *23* (4), 625-626.
41. Allen, R. L.; Moore, W. J., Diffusion of Silver in Silver Sulfide. *The Journal of Physical Chemistry* **1959**, *63* (2), 223-226.
42. Okazaki, H., Deviation from the Einstein relation in average crystals self-diffusion of Ag⁺ ions in α -Ag₂S and α -Ag₂Se. *J. Phys. Soc. Jpn.* **1967**, *23* (2), 355-360.
43. Rom, I.; Sitte, W., Composition dependent ionic and electronic conductivities and chemical diffusion coefficient of silver selenide at 160 °C. *Solid State Ionics* **1997**, *101*, 381-386.
44. Barnes, A.; Lague, S.; Salmon, P.; Fischer, H., A determination of the structure of liquid Ag₂Se using neutron diffraction and isotopic substitution. *J. Phys.: Condens. Matter* **1997**, *9* (29), 6159.
45. Lee, S.; Xu, H., Using Complementary Methods of Synchrotron Radiation Powder Diffraction and Pair Distribution Function to Refine Crystal Structures with High Quality Parameters—A Review. *Minerals* **2020**, *10* (2), 124.