

A potential–dependent Thiele modulus to quantify the effectiveness of porous electrocatalysts

Charles Tai-Chieh Wan^{1,2}, Katharine V. Greco^{1,2}, Amira Alazmi^{2,3}, Robert M. Darling⁴,
Yet-Ming Chiang^{1,5}, and Fikile R. Brushett^{1,3,z}

¹ Joint Center for Energy Storage Research, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, Massachusetts 02139, United States

² Department of Chemical Engineering, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, Massachusetts 02139, United States

³ Department of Chemistry, University Colleges at Nairiyah, University of Hafr Albatin (UHB), Nairiyah 31981, Saudi Arabia

⁴ Raytheon Technologies Research Center, East Hartford, Connecticut 06108, United States

⁵ Department of Materials Science and Engineering, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, Massachusetts 02139, United States

^z Corresponding Author Email Address: brushett@mit.edu

1 Abstract

Electrochemical reactors often employ high surface area electrocatalysts to accelerate volumetric reaction rates and increase productivity. While electrocatalysts can alleviate kinetic overpotentials, diffusional resistances at the pore-scale often prevent full catalyst utilization. The effect of intraparticle diffusion on the overall reaction rate can be quantified through an effectiveness factor expression governed by the Thiele modulus parameter. This analytical approach is integral to the development of catalytic structures for thermochemical processes and can be extended to electrochemical processes provided the relationship between reaction kinetics and electrode overpotential is incorporated. Here, we derive a potential-dependent Thiele modulus to quantify the effectiveness factor for porous electrocatalytic structures. We apply this mathematical framework to spherical microparticles as a function of applied overpotential across catalyst properties and reactant characteristics. The relative effects of kinetics and mass transport are related to overall reaction rates, revealing markedly lower catalyst utilization at increasing overpotential. Subsequently, we generalize the analysis to alternative catalyst shapes and provide guidance on the design of porous catalytic materials for use in electrochemical reactors.

Keywords: porous electrocatalyst, surface area utilization, electrochemical engineering, Thiele modulus, effectiveness factor

2 Introduction

Porous architectures have been strategically employed in heterogeneous catalytic processes to enhance volumetric reaction rates by increasing active site density. However, there exists a trade-off with mass-transport through the porous catalyst, which impacts the effective use of these catalyst sites. Classical approaches in chemical reactor design and engineering introduce an effectiveness factor to assess the ratio between the observed reaction rate and the reaction rate if the entire catalyst surface area been exposed to bulk concentration conditions. Intuitively, particle geometry (i.e., size and shape), catalyst surface reactivity, and intraparticle diffusion all impact the effectiveness factor. A dimensionless parameter, commonly termed the Thiele modulus, conveniently describes the relative balance between kinetic and mass transport resistances in the catalyst particle, quantifying the relation between catalyst particle size and activity.¹⁻⁵ Specifically, the Thiele modulus is the ratio of the reaction rate to the diffusion rate. At large Thiele modulus values, overall reaction rate is limited by diffusional resistance and the reaction is confined to the outer catalyst layers, whereas at small Thiele modulus values, the overall reaction rate is limited by the catalyst volume (i.e., total amount of accessible pore surface area). Generally, increases in this dimensionless group indicate mass-transport-limited behavior and a more non-uniform concentration profile throughout the catalyst.

Historically, the Thiele modulus has been used to inform materials design for thermochemical processes, wherein relevant reactions are driven by temperature and pressure, supporting the development of effective porous media used in catalytic, separation, and adsorption technologies.^{6,7} This analytical approach can be extended to evaluate catalysts for electrochemical processes, but the potential-dependence of reaction rates requires a reformulation of the traditional effectiveness factor. Unlike temperature and pressure, which still impact reaction kinetics and

mass transport in electrochemical systems, potential primarily impacts the reaction rate as it perturbs the free energy of the electrode-electrolyte interface, where the heterogeneous reactions occur, but does not typically impact bulk electrolyte properties.⁸

Previous work has extended traditional reactor engineering approaches to the development of effectiveness factors for electrochemical systems including room temperature fuel cells,^{9–13} solid oxide fuel cells,^{14,15} and thermo-electrochemical cells.¹⁶ In these efforts, the effectiveness factor was derived for configurations where the majority of the reactions occurred on dispersed catalyst sites impregnated in larger supporting particles,¹⁰ across entire catalytic layers,^{9,13–16} or for particulate bed electrodes.^{17,18} However, micrometric electrocatalysts of uniform composition are also employed to increase available surface area. For example, recent efforts to improve the performance of redox flow batteries have included the deposition of high surface carbonaceous microparticles onto the surface of carbon-fiber bed electrodes.^{19–23} While some of the reported surface areas exceeding $500 \text{ m}^2 \text{ g}^{-1}$ are 2–3 orders of magnitude larger than the low surface area fibrous scaffolds they are deposited on ($\sim 0.1 - 10 \text{ m}^2 \text{ g}^{-1}$),²⁴ cell-level performance improvements are comparatively marginal. While a number of factors can impact flow cell performance,^{25,26} this discrepancy suggests incomplete catalyst utilization, or, specifically, that the benefits derived from increasing surface area in this fashion have an upper bound. More broadly, understanding the interplay between active surface area and diffusion is universally applicable and has utility in electrochemical engineering. The diverse portfolio of electrode configurations (e.g., volumetric matrixes,^{8,27,28} packed beds,^{17,18} slurry electrodes^{29,30}) tailored to various objectives (e.g., removal of trace contaminants,^{31,32} electro-assisted selective adsorbent design,³³ energy storage,^{28,34} flow capacitors^{35–37}) motivate the general mathematical framework presented in this study.

Here, we derive a potential-dependent Thiele modulus to quantify the effectiveness factor and utilization of porous electrocatalysts as functions of particle and reactant properties. We develop formulations to assess effectiveness factors as a function of applied potential using both Tafel and Butler–Volmer kinetics, and assuming one-dimensional reaction-diffusion through a porous sphere. We then outline design principles for electrocatalyst sizing based on desired utilization. Subsequently, we explore and quantify internal transport limitations arising from diffusional processes within the catalyst and external transport limitations arising from mass transfer from the bulk electrolyte to the outer surface of the catalyst. Finally, we extend the model to other common catalyst geometries using a shape factor analysis. While the reactant and catalyst conditions used in this work are based on an aqueous electrolyte at room temperature, we anticipate that the mathematical framework is generalizable and applicable to porous electrocatalysts across a range of conditions.

3 Model Development

3.1 *Assumptions and formulation*

The model described herein considers the effectiveness factor in porous, spherical electrocatalysts (depicted in **Figure 1**). In this treatment, we contemplate a single-electron oxidation half-cell reaction (i.e., free electrons are treated as reactants or products) under isothermal conditions using full Butler–Volmer kinetics and the Tafel approximation. We assume dilute solution theory holds for describing ion transport properties.²⁷ By convention, oxidative currents are positive, while reductive currents are negative. Three distinct concentration regions are considered, specifically the bulk region (C_{bulk}), the external boundary layer from the bulk to the surface of the catalyst (C_{external}), and the internal porous electrocatalyst (C_{internal}). The electrolyte solution is treated as a typical aqueous electrolyte consisting of a dissolved electroactive species with excess supporting salt. Several assumptions are made about the catalyst particle and its interaction with the surrounding electrolyte. Specifically, we assume that i) the electrolyte wets the entirety of the particle; ii) the physical properties of the particle (e.g., porosity and tortuosity) are spatially invariant and can be approximated by a single value; and iii) the species diffusion coefficient and rate constant remain at the same values throughout the particle.^{2,3,5} As such, we inherently assume that continuum behavior of the electrolyte holds throughout the catalyst and neglect non-idealities that may arise in confined spaces of nanometric dimensions,^{38–40} setting a lower bound on the particle and pore sizes that may be considered via this approach. We neglect ohmic losses across the particle as these contributions are expected to be minor in comparison to the charge transfer and mass transfer losses. More specifically, if the particle is electronically conductive, only the electrolyte conductivity is significant, and if the cross-sectional area traversed by the reactants and

supporting salt dissolved in the solvent is identical, the ohmic drop across the particle ($\Delta\eta$ (V)) can be estimated as **Equation (1)**:⁹

$$\Delta\eta \cong \frac{nFD_{eff}\Delta C}{\kappa_{eff}} \quad (1)$$

where n (-) is the number of electrons transferred, F (C mol⁻¹) is the Faraday constant, ΔC (mol cm⁻³) is the maximum possible concentration drop across the pellet, κ_{eff} (S cm⁻¹) is the effective conductivity of the solution, and D_{eff} (cm² s⁻¹) is the effective reactant diffusivity through the particle. The effective diffusivity in the catalyst pores is assumed to be $D_{eff} = (\varepsilon_{cat}/\tau_{cat})D_{bulk}$, where ε_{cat} and τ_{cat} are the porosity and tortuosity of the catalyst pellet, respectively, and D_{bulk} (cm² s⁻¹) is the molecular diffusivity of the reactant species in the bulk electrolyte absent the influence of the catalyst particle.² Based on this expression, the order of magnitude ohmic loss is $\ll 10^{-3}$ V for reasonable ranges of bulk active species electrolyte concentrations (ca. 5×10^{-4} mol cm⁻³, or equivalently, 0.5 mol L⁻¹), effective diffusion coefficients (ca. 10^{-6} cm² s⁻¹), and effective conductivities (ca. 0.2 S cm⁻¹) observed in typical aqueous electrolytes.

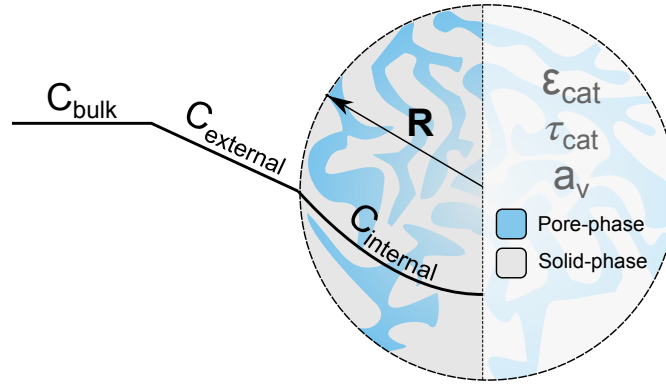


Figure 1 – Modeling domain. A two-dimensional representation of the reactant concentration in a spherical porous electrocatalyst. The concentration profile through the modeling domain can be divided into three distinct regions, namely the bulk (C_{bulk}), the external boundary layer (C_{external}), and the internal structure (C_{internal}). Important physical properties of the electrocatalyst, including bulk porosity (ϵ_{cat}), bulk tortuosity (τ_{cat}), and volumetric surface area (a_v), are listed on the schematic. The pore-phase and the solid-phase of the catalyst are represented by blue and gray, respectively.

3.2 Tafel Kinetics

First, consider a species A irreversibly oxidizing to species B in a single-electron half-cell reaction ($n = 1$) as shown in **Equation (2)**:



The expression for the reaction rate assuming Tafel kinetics relating current to the applied overpotential for the oxidation reaction can be written as **Equation (3)**:

$$\bar{r} = \frac{i}{nF} = k_f c_A \quad (3)$$

where \bar{r} ($\text{mol cm}^{-2} \text{s}^{-1}$) is the reaction rate, i (mA cm^{-2}) is the current density, k_f (cm s^{-1}) is the potential-dependent heterogeneous forward rate constant, and c_A (mol cm^{-3}) is the concentration of species A.

The electrochemical rate constant, k_f , can be written in terms of the standard heterogeneous rate constant, k^0 (cm s⁻¹) in **Equation (4)** as follows:⁴¹

$$k_f = k^0 \exp \left[\frac{\alpha_f n F \eta}{RT} \right] \quad (4)$$

where α_f (-) is the forward charge-transfer coefficient, R (J mol⁻¹ K⁻¹) is the universal gas constant, T (K) is the absolute temperature, and η (V) is the overpotential, defined here as $\eta = E - E_f^0$, where E (V) is the potential and E_f^0 (V) is the formal potential.

The derivation of the effectiveness factor for a porous sphere that is a function of the Thiele modulus reflects traditional chemical engineering treatments,^{2,3} and, for completeness, is provided in **Section 1 of the Supporting Information**. The non-dimensionalized differential equation with boundary conditions of 1) reactant concentration at the surface of the sphere equal to the bulk concentration, $c_{A,bulk}$ (mol cm⁻³), and 2) zero-flux at the center of the sphere can be written as **Equation (5)**:

$$\frac{d^2\psi}{d\omega^2} + \frac{2}{\omega} \frac{d\psi}{d\omega} - \phi^2 \psi = 0; \quad \psi(\omega=1) = 1; \quad \frac{d\psi}{d\omega}(\omega=0) = 0 \quad (5)$$

The dimensionless concentration and dimensionless position are defined as $\psi = c_A / c_{A,bulk}$ and $\omega = r / R_p$, respectively, where r (cm) is the coordinate radius, and R_p (cm) is the particle radius; the dimensionless number ϕ is the Thiele modulus, written for electrochemical rate constants with units of cm s⁻¹ as **Equation (6)**:

$$\phi = R_p \sqrt{\frac{a_v k_f}{D_{eff}}} \quad (6)$$

where $a_v(\text{cm}^{-1})$ is the surface area to volume ratio, or volumetric surface area, of the catalyst particle. We note that the inclusion of terms in the differential equation indicates that the scaling of the kinetics and diffusion are on the same order of magnitude. The first boundary condition also implies rapid mass transfer through the boundary layer compared to mass transfer inside the sphere; this assumption is lifted in **Section 4.2**, where external transport limitations are explicitly treated.

The solution to **Equation (5)** that gives the dimensionless concentration profile is **Equation (7)**:

$$\psi = \frac{c_A}{c_{A,bulk}} = \frac{\sinh(\phi\omega)}{\omega \sinh(\phi)} \quad (7)$$

The effectiveness factor, H, compares the observed reaction rate in the presence of diffusional transport limitations through the porous electrocatalyst (\bar{r}_{obs}) to the reaction rate in the presence of bulk electrolyte concentrations (\bar{r}_{max}). The relationship is given by **Equation (8)**:

$$H = \frac{\bar{r}_{obs}}{\bar{r}_{max}} = \frac{\int_0^{V_p} \bar{r}(c_A) dV}{V_p \bar{r}(c_{A,bulk})} \quad (8)$$

where V_p (cm^3) is the geometric volume of the particle. Substituting terms and rearranging leads to an expression of the effectiveness factor for any first-order reaction in a sphere, **Equation (9)**:

$$H = \frac{3}{\phi^2(\eta)} [\phi(\eta) \coth(\phi(\eta)) - 1] \quad (9)$$

Introducing the potential-dependent heterogeneous rate constant, k_f , into **Equation (6)** yields a modified Thiele modulus, **Equation (10)**:

$$\phi^2(\eta) = R_p^2 \frac{a_v k^0}{D_{eff}} \exp\left(\frac{\alpha_f n F \eta}{RT}\right) \quad (10)$$

where the equation can be separated into two dimensionless entities, an overpotential-independent parameter, γ^2 , and an overpotential-dependent parameter, E, shown in **Equation (11)**:

$$\phi^2(\eta) = \gamma^2 E(\eta); \quad \gamma^2 = R_p^2 \frac{a_v k^0}{D_{eff}}; \quad E(\eta) = \exp\left(\frac{\alpha_f n F \eta}{RT}\right) \quad (11)$$

γ^2 is the conventional Thiele modulus squared without potential dependence, relating reaction kinetics to diffusion through the characteristic length of the particle. Note the above derivation is analogous for a reduction half-cell reaction. The combination of **Equation (9)** and the dimensionless expression in **Equation (11)** result in a potential-dependent effectiveness factor for a porous sphere. Providing input values for the parameters in **Equation (11)** enables evaluation of catalyst utilization, as will be expanded upon in subsequent sections.

3.3 Butler–Volmer Kinetics

A similar derivation can be performed for a reversible single electron transfer ($n = 1$) described by Butler–Volmer kinetics, as shown in **Equation (12)**:



Assuming that the reactant concentration at the outer surface of the particle can be approximated by the reactant concentration in the bulk electrolyte (i.e., initially ignoring mass transport effects), the reaction-rate flux is described by Butler–Volmer kinetics with **Equation (13)**:

$$\bar{r} = \frac{i}{nF} = k_f c_A - k_r c_B \quad (13)$$

where k_f (cm s⁻¹) is the potential-dependent forward rate constant (here, anodic), and k_r (cm s⁻¹) is the potential-dependent reverse rate constant (here, cathodic). Analogous to k_f , the electrochemical rate constant k_r can be written in **Equation (14)** as:

$$k_r = k^0 \exp\left[\frac{-\alpha_r nF\eta}{RT}\right] \quad (14)$$

Substitution of **Equations (4)** and **(14)** into **Equation (13)** leads to **Equation (15)**:

$$\bar{r} = k^0 \exp\left[\frac{\alpha_f nF\eta}{RT}\right] c_A - k^0 \exp\left[\frac{-\alpha_r nF\eta}{RT}\right] c_B \quad (15)$$

With Butler–Volmer kinetics, the Thiele modulus now includes forward and backward reaction rates, and is defined as **Equation (16)**:

$$\phi^2(\eta) = R_p^2 \frac{a_v k^0}{D_{eff}} \left[\exp\left(\frac{\alpha_f nF\eta}{RT}\right) + \exp\left(\frac{-\alpha_r nF\eta}{RT}\right) \right] \quad (16)$$

Similarly, the Thiele modulus can be deconvoluted into two dimensionless entities, shown in **Equation (17)**:

$$\phi^2(\eta) = \gamma^2 E(\eta); \quad \gamma^2 = R_p^2 \frac{a_v k^0}{D_{eff}}; \quad E(\eta) = \left[\exp\left(\frac{\alpha_f nF\eta}{RT}\right) + \exp\left(\frac{-\alpha_r nF\eta}{RT}\right) \right] \quad (17)$$

The effectiveness factor for the Butler–Volmer reaction is identical to **Equation (9)** with the only difference being the use of **Equation (16)** as the Thiele modulus; the full derivation for the Butler–Volmer effectiveness factor and recovery of **Equation (16)** can be found in the **Appendix**.

Computational analyses were executed in MATLAB® R2019a on a Dell Latitude 7280 laptop computer with an Intel® Core™ i7-6600U processor (2 Cores, 2.60 GHz) and random-access memory of 16 GB. All the calculations for multiples geometries (e.g., spherical, slab, annulus; *vide infra*) and generated plots were run on a single script that required ca. 1.5 – 2 min to execute.

3.4 Model Output

We next examine the model results for fixed parameters across varying applied oxidative overpotential. **Figure 2a** shows the dimensionless concentration as a function of dimensionless length at different overpotentials for the full Butler–Volmer (dashed lines) kinetics and the Tafel approximation (solid lines) for a fixed $\gamma^2 = 1$. The transfer coefficient is assumed to be 0.5 for both the forward and reverse reactions, with a single-electron transfer. The modified, potential-dependent Thiele modulus for various values of γ^2 is shown as a function of overpotential in **Figure 2b**, used to calculate the effectiveness factor in **Figure 2c**. As expected, an apparent deviation at low overpotential between the kinetic treatments disappears at greater applied potentials as the Tafel approximation becomes increasingly accurate. The deviation between the effectiveness factor using Tafel and Butler–Volmer kinetics is initially exacerbated at low overpotential as γ^2 increases; however, the difference between effectiveness factors becomes < 1% at ca. 100 mV overpotential, which is observable in **Figure 2c**. Because the model outputs for Tafel and Butler–Volmer kinetics are fairly similar, for simplicity, Tafel kinetics are assumed for the remainder of this study.

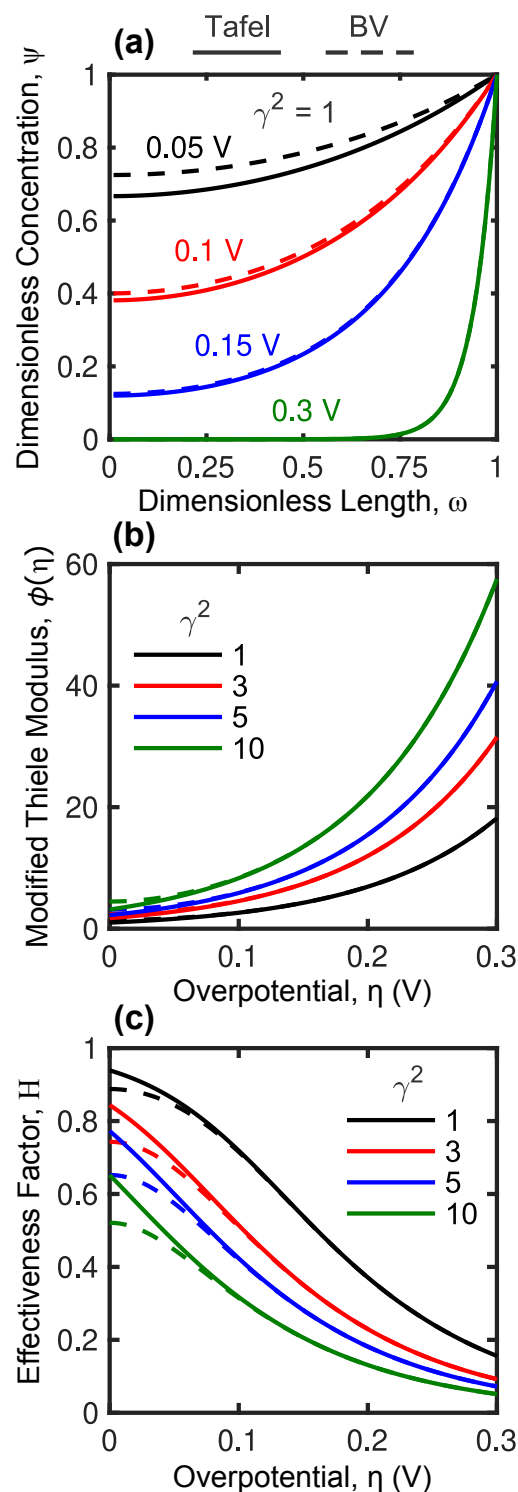


Figure 2 – Effectiveness factor through spherical porous electrocatalysts. (a) Dimensionless concentration as a function of dimensionless length for various oxidative overpotentials. (b) Modified Thiele modulus and (c) effectiveness factor as a function of overpotential for different γ^2 values (zero-potential Thiele modulus). Solid lines are for Tafel kinetics, while dashed lines indicate Butler–Volmer (BV) kinetics.

4 Results and Discussion

In the following section, we apply the framework developed in **Section 3** to size catalyst particles and generate polarization curves. We consider two regimes where transport effects take place⁵ (also depicted in **Figure 1**). *Internal transport limitations* arise when the reaction rate greatly exceeds the rate of reactant diffusion through the pore space of the catalyst particle. *External transport limitations* result as the reactant diffuses from the bulk to the catalyst surface through the boundary layer surrounding the particle. In **Section 4.1**, we consider solely internal transport limitations; in doing so, we implicitly assume rapid external mass transport (i.e., external transport limitations have a negligible effect). In **Section 4.2**, the assumption for rapid external mass transport is lifted, and both internal and external transport limitations are assessed.

4.1 Internal Transport Limitations

We now use the effectiveness factor derived in **Section 2** to estimate the interfacial current density, i , in the presence of internal transport limitations, shown in **Equation (18)**:

$$i = HnFk_f c_{A,bulk} \quad (18)$$

where H is the effectiveness factor. Substituting in for k_f and rearranging, we arrive at an expression for dimensionless internal current density, **Equation (19)**:

$$\frac{i}{nFk_f^0 c_{A,bulk}} = H \exp\left(\frac{\alpha_f nF\eta}{RT}\right) \quad (19)$$

The dimensionless current density increases exponentially with respect to overpotential. In the ideal scenario, H is 1. The presence of internal transport limitations, however, reduces the dimensionless current density, lowering catalyst utilization.

The relation between current density and effectiveness factor can be used to size catalysts to match a desired utilization efficiency, as shown in **Figure 3**. Lines in this figure represent the upper bound of particle radius for a given desired particle-specific current density for fixed effectiveness factors and volumetric surface areas. As particle radius increases, the efficiency (i.e., effectiveness factor) decreases; thus, the current density must be lowered to attain the desired efficiency. Similarly, as the volumetric surface area increases for fixed desired efficiency, the maximum allowable particle radius decreases accordingly. To generate **Figure 3**, fixed $D_{eff} = 10^{-6} \text{ cm}^2 \text{ s}^{-1}$ and $c_{A,bulk} = 5 \times 10^{-4} \text{ mol cm}^{-3}$ (also 0.5 mol L^{-1}) were selected as representative diffusivities and reactant concentrations.^{38,42,43} Ultimately, more precise values will depend on the specific electrolyte system (i.e., electrolyte composition, reactant concentration) and catalyst properties (i.e., tortuosity, porosity), which are combined into the effective diffusivity shown here.

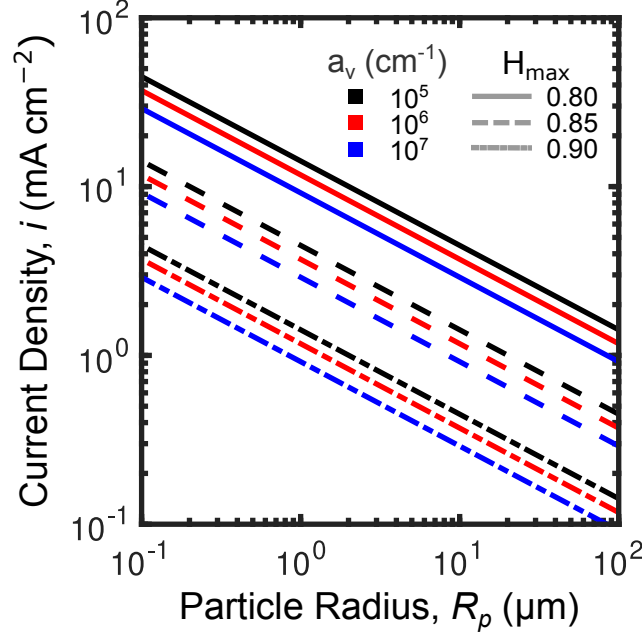


Figure 3 – Utilization and catalyst sizes. Particle-specific current density as a function of particle radius for the desired effectiveness factor (H_{\max}) and fixed volumetric surface areas (a_v). $D_{\text{eff}} = 10^{-6} \text{ cm}^2 \text{ s}^{-1}$ and $c_{A,\text{bulk}} = 5 \times 10^{-4} \text{ mol cm}^{-3}$ were held constant. The volumetric surface area is denoted by the line color, while the effectiveness factor is denoted by the line style. As particle volumetric surface area increases, the maximum allowable particle size at a given current density decreases. Similarly, increasing the utilization efficiency results in a lower maximum particle size.

The influence of the effectiveness factor on catalyst performance can also be visualized using polarization curves. **Figure 4a** shows the dimensionless internal current density as a function of overpotential according to **Equation (19)**, with the ideal case (no losses, $H = 1$) shown as the dotted black line, while the bold red, blue, and green curves represent the polarization curves for the three kinetic rate constants (k^0) of increasing orders of magnitude (10^{-5} , 10^{-4} , and $10^{-3} \text{ cm s}^{-1}$, respectively). Fixed values of $R_p = 3 \text{ } \mu\text{m}$, $D_{\text{eff}} = 10^{-6} \text{ cm}^2 \text{ s}^{-1}$, and $a_v = 10^5 \text{ cm}^{-1}$ were used based on experimentally-informed parameters.^{38,42,43} The volumetric surface area, a_v , is the product of the catalyst particle density and BET-derived surface area from nitrogen physisorption, based on approximate densities and surface area of porous carbon particles.^{44–46} The lightly shaded

lines in between the bold lines represent intermediate kinetic rate constant values. Increments of $10^{-5} \text{ cm s}^{-1}$ were used to transition from the red to blue curves, while increments of $10^{-4} \text{ cm s}^{-1}$ were used to transition from the blue to green curves. We note that while the rate constant was varied in **Figure 4**, changing the particle size by the square root of the proportional change in the kinetic rate constant has an equivalent effect on the effectiveness factor. As the kinetic rate constant linearly increases, the dimensionless current density gradually consolidates. **Figure 4b** shows the corresponding effectiveness factors which evince severe limitations. The magnitude of the reduction in effectiveness is increasingly stark as the intrinsic kinetic rate constant increases, and intraparticle diffusion becomes limiting. The results indicate that even if the entire surface area of the catalyst particle were accessible for the electrochemical reaction, diminishing returns would be observed due to internal diffusional resistances.

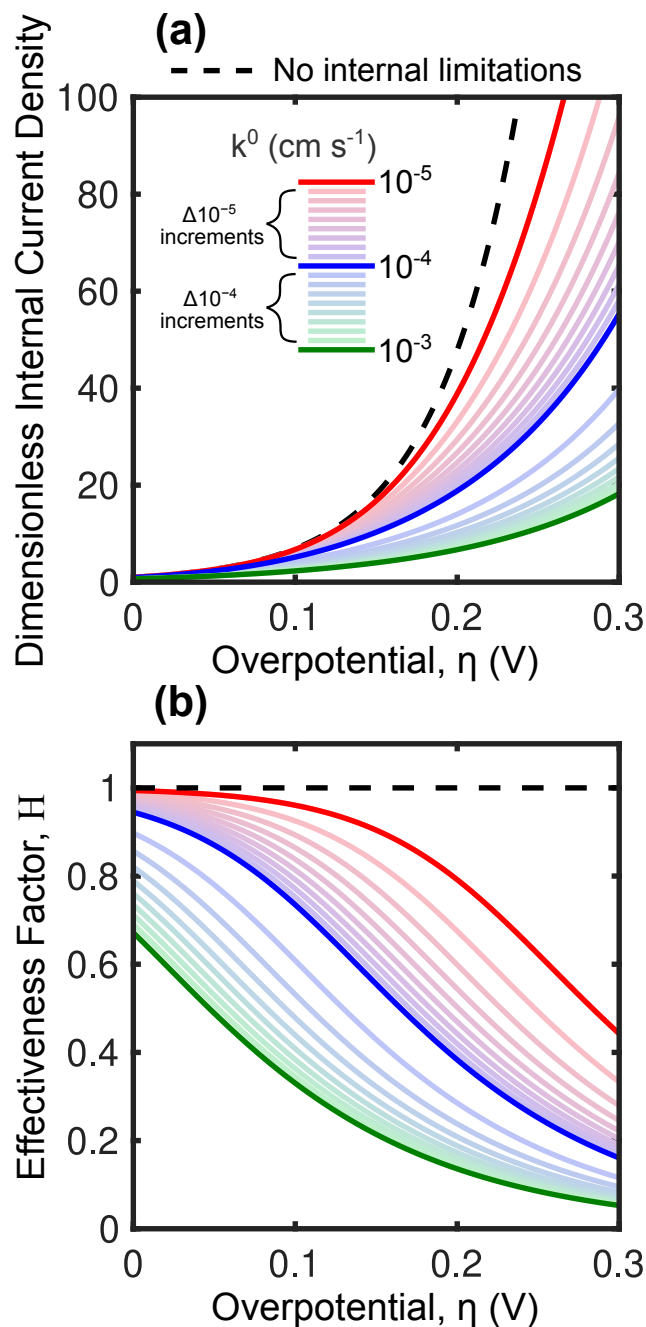


Figure 4 – Tafel plots for several kinetic rate constants at fixed diffusivity, volumetric surface area, and particle size. (a) Dimensionless internal current density as a function of overpotential. The black, dashed curve represents ideal polarization ($H = 1$), while the solid red, blue, and green represent the three different kinetic rate constants of 10^{-5} , 10^{-4} , and $10^{-3} \text{ cm s}^{-1}$, respectively. The lightly shaded lines are increments in the rate constant, either 10^{-5} or $10^{-4} \text{ cm s}^{-1}$ as indicated in the figure. (b) Effectiveness factor as a function of overpotential. The reaction rates follow the same coloring scheme as in (a).

4.2 External Transport Limitations

To account for the effect of external mass transport from the bulk concentration to the outer surface of the catalyst particle, the total reaction rate on the interior of the catalyst particle is set equal to the reactant flux to the external surface (i.e., no accumulation on the catalyst surface boundary due to fouling, surface species absorption, etc.). Here, we assume that the particle is surrounded by electrolyte of uniform concentration without hindrance or obstruction from other catalyst particles, substrates, or other system components.^{2,3,5} Assuming that contributions from reactions along the outer surface of the particle are negligible compared to contributions from reactions throughout the volumetric internal surface area of the particle,^{2,3,5} and including the impact of the effectiveness factor on the reaction rate throughout the particle, results in **Equation (20)** for the flux balance:

$$k_m a_c (c_{A,bulk} - c_{A,surf}) = H k_f a_v c_{A,surf} \quad (20)$$

where k_m (cm s⁻¹) is the external mass transfer coefficient accounting for effects of diffusion and convection, and a_c (cm⁻¹) is the catalyst shape factor, defined as the ratio of the particle external surface area to volume. Rearranging to solve for an expression for the surface concentration yields **Equation (21)**:

$$c_{A,surf} = \frac{k_m a_c}{k_m a_c + H k_f a_v} c_{A,bulk} \quad (21)$$

Thus, the expression for the current density is now given by **Equation (22)**:

$$i = H n F k_f c_{A,surf} = \frac{H k_f k_m a_c}{k_m a_c + H k_f a_v} n F c_{A,bulk} = \frac{H}{1 + H \frac{k_f a_v}{k_m a_c}} n F k_f c_{A,bulk} \quad (22)$$

Now, an expression for dimensionless current density including both internal and external transport with Ω as an overall effectiveness factor can be written as shown in **Equation (23)**:

$$\frac{i}{nFk^0c_{A,bulk}} = \Omega \exp\left(\frac{\alpha_f nF\eta}{RT}\right); \quad \Omega = \frac{H}{1 + H \frac{k_f a_v}{k_m a_c}} \quad (23)$$

The effect of bulk mass transport is seen in **Figure 5a**, where the mass transfer coefficient is varied for fixed conventional Thiele modulus (γ^2), and the current density at $\eta = 0.3$ V is shown on the ordinate. As the mass transport coefficient increases, losses due to reactant transport from the bulk to the catalyst surface decrease, and the dimensionless current density ultimately reaches a constant value which is dictated solely by internal diffusive losses through the catalyst particle. In other words, $\Omega \approx H$ in the limit of a high mass transfer coefficient. As γ^2 increases, the limiting dimensionless current density has a lower value, which reflects poor catalyst particle utilization, as shown on a log-log base-10 scale with γ^2 in **Figure 5b**.

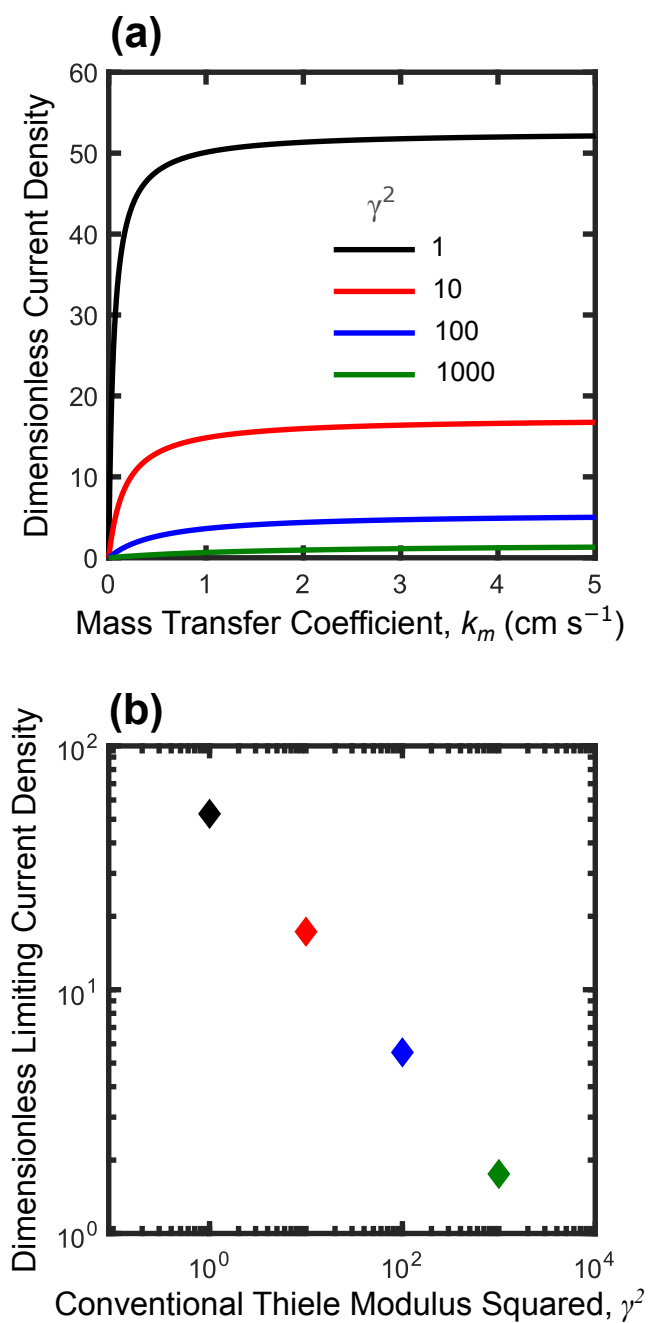


Figure 5 – Mass transfer dependence. (a) Dimensionless current density as a function of mass transfer coefficient for fixed γ^2 at $\eta = 0.3$ V. (b) Dimensionless limiting current density extracted from (a) as a function of γ^2 .

4.3 Extension of Model to General Geometries

In practice, catalysts assume broad and irregular shapes. To accommodate the range of particle morphologies, we describe a simple transformation that can be used to extend the aforementioned framework to alternative geometries by using the catalyst volume (V_p) to surface area (SA) ratio as a characteristic length scale ($L = V_p/SA$) in accordance with the seminal work of Aris.⁴⁷ Here, we use this facile strategy to analyze additional basic geometries (i.e., slab, cylinder, and annulus) as a demonstration for our model generalizability, although we posit that more advanced transformations with varying degrees of precision and complexity should also be compatible with the model formulation. Derivations for slab and cylinder catalysts are described in detail elsewhere;^{2–4,47} general equations for these geometries are presented in the **Section 2 of the Supporting Information**. A noteworthy geometry for fibrous catalysts is a porous reactive annulus that covers an impenetrable core. The porous reactive annulus can be realized via either additive or subtractive synthetic strategies. In additive processes, the porous layer is deposited or coated onto the fiber using particulate catalysts,⁴⁸ conformal films,⁴⁹ or porous mats;^{50–52} whereas in subtractive processes, the porous layer is formed by surface roughening or fiber etching by thermal,^{53,54} chemical,⁵⁵ or electrochemical⁵⁶ means.

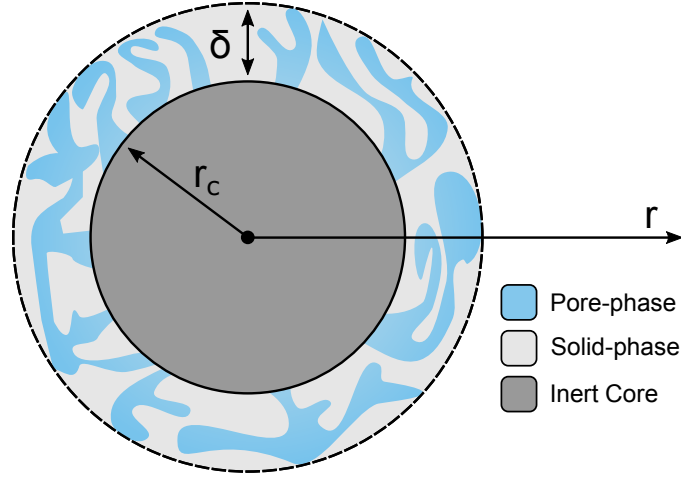


Figure 6 – Annulus geometry. Schema showing the annulus geometry and coordinates. r_c is the radius of the non-reacting core, while δ is the shell thickness. The dark gray signifies the non-porous inert core. In the reactive porous phase, the blue and light gray represent the pore-phase and solid-phase of the catalyst, respectively.

Although the annular film morphology and activity varies based on the synthesis route, the mathematical framework described here broadly encompasses this category of materials. If the porous layer surrounds an impenetrable and nonporous core as a concentric shell, the governing equation for the 1D radial diffusion and reaction problem to solve for the dimensionless concentration profile becomes **Equations (24) and (25)**.^{57,58}

$$\frac{\partial^2 \psi}{\partial \tilde{r}^2} + \frac{\xi}{\xi \tilde{r} + 1} \frac{\partial \psi}{\partial \tilde{r}} - \phi^2 \psi = 0; \quad \frac{\partial \psi}{\partial \tilde{r}}(\tilde{r} = 0) = 0; \quad \psi(\tilde{r} = 1) = 1 \quad (24)$$

$$\psi = \frac{c_A}{c_{A,bulk}}; \quad \tilde{r} = \frac{r - r_c}{\delta}; \quad \xi = \frac{\delta}{r_c}; \quad \phi^2 = \delta^2 \frac{a_v k_f}{D_{eff}} \quad (25)$$

where \tilde{r} (-) the dimensionless position, r_c (cm) the radius of the non-porous core, δ (cm) the thickness of the concentric shell, and ξ (-) the ratio of the shell thickness to core thickness. A schema of the annulus with labeled variables is shown in **Figure 6**. The full derivation and

numerical evaluation of **Equation (24)** are provided in **Section 2 of the Supporting Information**.

The Thiele modulus in this form factor has a diffusion pathway across δ . We can examine the limits of ξ to ascertain behavior of the annulus at relatively large or small shell thicknesses. As $\xi \rightarrow 0$ (i.e., $\delta \ll r_c$), the effectiveness factor approaches that of an infinite slab. As $\xi \rightarrow \infty$ (i.e., $\delta \gg r_c$), the effectiveness factor approaches that of a cylinder.

The numerical solution for an annulus with $\xi = 0.5$ as a function of overpotential is shown in **Figure 7**; effectiveness factors for an infinite slab, cylinder, and sphere corresponding to the same characteristic lengths are also shown for comparison. At low overpotentials – and consequently Thiele modulus — the effectiveness factor increases as the geometry transitions from the sphere to the slab. At high overpotentials — and consequently high Thiele modulus — the effectiveness factors collapse onto the same curve as diffusive limitations dominate and reactions are confined to the external layer, causing all geometries to behave effectively as slabs. **Figure 7** may also be used to approximate irregular catalysts geometries using the $L = V_p/SA$ parameter.

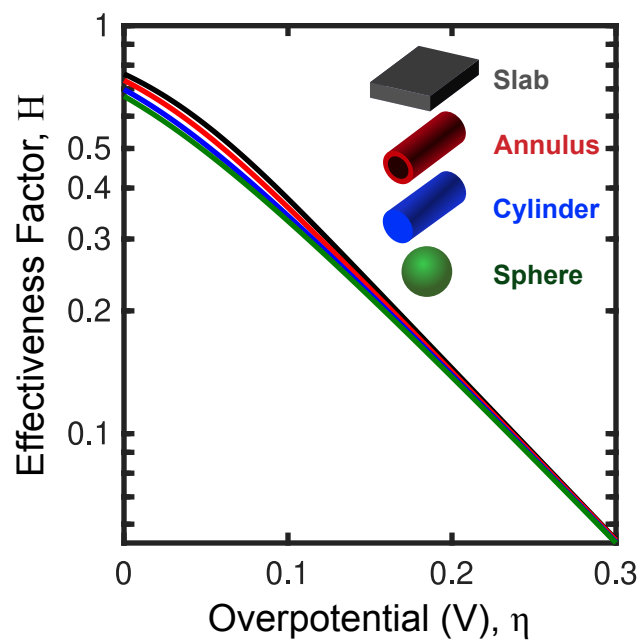


Figure 7 – Generalizability for various shape factors. Effectiveness factor as a function of overpotential calculated for a flat slab (grey), annulus (red), cylinder (blue), and sphere (green) based on their characteristic lengths. The curves collapse onto each other at larger overpotential as the reaction utilization shifts towards the outer edges of the catalyst independent of shape.

5 Conclusions

Here we present a general strategy for quantifying potential-dependent effectiveness factors in porous electrocatalysts. The methodology extends the traditional Thiele modulus approach to include first-order electrochemical reactions, enabling investigation of the effect that diffusional losses have on net reaction rate in porous microstructures. Using this framework, we assess transport limitations both internally through a spherical particle – from the surface to the center – and externally – from the bulk to the surface. We show how this approach may be used to target ideal catalyst sizes to achieve desired reaction efficiencies, assuming bulk-averaged morphological properties are known. Generally, the model suggests that low effectiveness factors manifest for larger driving forces, even at the relatively modest overpotentials examined (≤ 0.3 V). This work indicates that effective performance is not only dictated by the electrochemical reaction rate, but also by the comparative rate of mass transfer within the system; thus, the insights gained from the model findings highlight the existence of an upper-limit for effective surface area, and motivate the development of hierarchical structured electrocatalysts to mitigate diffusional pore-scale losses. To this end, a shape factor analysis is introduced to accommodate the breadth of catalyst geometries that may be used in electrochemical reactors. Future studies aiming to build on these findings should contemplate the role of electrolyte velocity and mass transfer coefficients on performance, the extension to other electrolyte systems, along with the accurate estimation of effective diffusion coefficient for liquid-phase reactions in highly tortuous microscale catalysts.

6 CRediT authorship contribution statement

Charles Tai-Chieh Wan: Conceptualization, Methodology, Software, Validation, Formal Analysis, Investigation, Data Curation, Writing – Original Draft, Writing – Review & Editing, Visualization. **Katharine V. Greco:** Conceptualization, Validation, Writing – Original Draft, Writing – Review & Editing. **Amira Alazmi:** Conceptualization. **Robert M. Darling:** Conceptualization, Methodology, Writing – Review & Editing. **Yet-Ming Chiang:** Resources. **Fikile R. Brushett:** Conceptualization, Writing – Original Draft, Writing – Review & Editing, Project administration.

7 Acknowledgements

Research by C.T.W., Y.M.C., R.M.D., and F.R.B. was supported by the Joint Center for Energy Storage Research (JCESR), an Energy Innovation Hub funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences. A.A. acknowledges support from the Ibn Khaldun Fellowship for Saudi Arabian Women at MIT. C.T.W. and K.V.G. acknowledge graduate fellowships through the National Science Foundation Graduate Research Fellowship Program under Grant No. 1122374. Any opinions, findings, and conclusions or recommendations expressed in this material are those of the authors and do not necessarily reflect the views of the National Science Foundation. The authors also thank Alexis Fenton, Bertrand Neyhouse, and Kevin Tenny of the Brushett Group for their insightful discussions.

8 Appendix

Full Butler–Volmer Kinetics Derivation

Here, we derive the Thiele modulus for a single-electron reaction described by Butler–Volmer kinetics. The reaction rate, \bar{r} , can be expressed as **Equation (A1)**:

$$\bar{r} = k_f c_A - k_r c_B \quad (\text{A1})$$

which can be set equal to **Equation (15)** in the main text.

Performing a mass balance, we let the total concentration be defined as C (mol cm⁻³) as shown in **Equation (A2)**:

$$C = c_{A,bulk} + c_{B,bulk} = c_A + c_B \quad (\text{A2})$$

Then, rearranging **Equation (A2)** and substituting into **Equation (A1)** results in **Equation (A3)**:

$$\bar{r} = k_f c_A - k_r (C - c_A) = k_f c_A + k_r c_A - k_r C = (k_f + k_r) c_A - k_r C \quad (\text{A3})$$

Defining a dimensionless parameter K as follows in **Equation (A4)**:

$$K = \frac{k_f}{k_r} = \frac{\exp\left[\frac{\alpha_f n F \eta}{RT}\right]}{\exp\left[\frac{-\alpha_r n F \eta}{RT}\right]} = \exp\left[\frac{(\alpha_f + \alpha_r) n F \eta}{RT}\right] \quad (\text{A4})$$

Equation (A1) can be rewritten in terms of k_f and concentration, giving **Equations (A5)** and **(A6)**:

$$\bar{r} = (k_f + k_r) c_A - k_r C = \left(k_f + \frac{k_f}{K}\right) c_A - \frac{k_f}{K} C \quad (\text{A5})$$

$$\bar{r} = k_f \left[1 + \frac{1}{K} \right] c_A - \frac{k_f}{K} C = k_f \left[1 + \frac{1}{K} \right] \left(c_A - \frac{C}{\left(1 + \frac{1}{K} \right) K} \right) = k_f \left(1 + \frac{1}{K} \right) \left(c_A - \frac{C}{K+1} \right) \quad (\text{A6})$$

Performing a material balance on the porous sphere (mathematical treatment shown in **Section 1 of the Supporting Information**), and assuming that the reactant and product have equal effective diffusivities through the particle, we arrive at the following differential equation for a spherical particle, shown in **Equation (A7)**:

$$D_{eff} \left[\frac{d^2 c_A}{dr^2} + \frac{2}{r} \frac{dc_A}{dr} \right] - a_v k_f \left(1 + \frac{1}{K} \right) \left(c_A - \frac{C}{K+1} \right) = 0 \quad (\text{A7})$$

A solution requires rescaling the concentration appropriately to include the total concentration of the species, $\psi = c_A - \frac{C}{K+1}$. Non-dimensionalizing the length scale by $\omega = r/R_p$ results in the potential dependent Thiele modulus, **Equation (A8)**:

$$\phi^2 = R_p^2 \frac{a_v k_f \left(1 + \frac{1}{K} \right)}{D_{eff}} = R_p^2 \frac{a_v k^0}{D_{eff}} \left[\exp \left(\frac{\alpha_f n F \eta}{RT} \right) + \exp \left(\frac{-\alpha_r n F \eta}{RT} \right) \right] \quad (\text{A8})$$

Which is equivalent to **Equation (16)** in the main text. Re-scaling of **Equation (A7)** and substitution of terms leads to **Equation (A9)**:

$$\frac{d^2 \psi}{d\omega^2} + \frac{2}{\omega} \frac{d\psi}{d\omega} - \phi^2 \psi = 0; \quad \psi(\omega=1) = c_{A,bulk} - \frac{C}{K+1}; \quad \frac{d\psi}{d\omega}(\omega=0) = 0 \quad (\text{A9})$$

which is the governing differential equation subject to the surface concentration and symmetric boundary conditions. The solution of **Equation (A9)** leads to a concentration profile for species A, **Equation (A10)**:

$$c_A(\omega) = \frac{C}{K+1} + \left(\frac{c_{A,bulk} - \frac{C}{K+1}}{\omega} \right) \frac{\sinh(\phi\omega)}{\sinh(\phi)} \quad (\text{A10})$$

The effectiveness factor for a sphere with Butler–Volmer kinetics can be derived by relating the actual rate of reaction at the external particle surface to the total reaction throughout the entire particle volume if the concentration were the same as the outer surface. This leads to **Equation (A11)**:

$$H = \frac{4\pi R_p^2 D_{eff} \frac{dc_A}{dr}}{r_{A,0} V_p} \quad (\text{A11})$$

Substituting for $V_p = \frac{4}{3}\pi R_p^3$, inserting the reaction rate, using the scaling for ψ and modifying by

ω results in **Equation (A12)**:

$$H = \frac{4\pi R_p D_{eff} \left(\frac{d\psi}{d\omega} \right)_{\omega=1}}{a_v k_f \left(1 + \frac{1}{K} \right) \left(c_{A,bulk} - \frac{C}{K+1} \right) \frac{4}{3} \pi R_p^3} \quad (\text{A12})$$

Evaluating the terms and plugging back in to the effectiveness factor yields **Equation (A13)**:

$$H = \frac{4\pi R_p D_{eff} \left(c_{A,bulk} - \frac{C}{K+1} \right) (\phi \coth(\phi) - 1)}{a_v k_f \left(1 + \frac{1}{K} \right) \left(c_{A,bulk} - \frac{C}{K+1} \right) \frac{4}{3} \pi R_p^3} = \frac{3D_{eff} (\phi \coth(\phi) - 1)}{a_v k_f \left(1 + \frac{1}{K} \right) R_p^2} \quad (\text{A13})$$

Recalling the definition of the Thiele modulus results in **Equation (A14)**:

$$H = \frac{3}{\phi^2} (\phi \coth(\phi) - 1) \quad (\text{A14})$$

Which is the same as the effectiveness factor for the first-order reaction shown in **Equation (9)** in the main text, with an additional term for the reverse reaction in the potential-dependent portion of the Thiele modulus expression.

9 Glossary

List of Symbols

Symbol	Description	Units
a_c	Exterior volumetric surface area, or shape factor	cm^{-1}
a_v	Volumetric surface area	cm^{-1}
C	Concentration	mol cm^{-3}
$c_{A,bulk}$	Bulk electrolyte concentration of species A	mol cm^{-3}
$c_{A,surf}$	Concentration at the surface of the catalyst	mol cm^{-3}
$c_{B,bulk}$	Bulk electrolyte concentration of species B	mol cm^{-3}
D_{bulk}	Molecular diffusivity of reactant species in the bulk electrolyte	$\text{cm}^2 \text{s}^{-1}$
D_{eff}	Effective reactant diffusivity	$\text{cm}^2 \text{s}^{-1}$
E_f^0	Formal potential	V
F	Faraday constant	C mol^{-1}
i	Current density	mA cm^{-2}
K	Dimensionless ratio of forward to reverse rate constant	--
k^0	Standard heterogeneous electrochemical rate constant	cm s^{-1}
k_f	Potential-dependent heterogeneous forward rate constant	cm s^{-1}
k_m	External mass transfer coefficient	cm s^{-1}
k_r	Potential-dependent heterogeneous reverse rate constant	cm s^{-1}
L	Characteristic length scale	cm
n	Number of electrons transferred	--
r	Coordinate radius	cm
R	Universal gas constant	$\text{J mol}^{-1} \text{K}^{-1}$
r_c	Radius of the non-porous core in annulus derivation	cm
R_p	Particle radius	cm
\bar{r}	Reaction rate flux	$\text{mol cm}^{-2} \text{s}^{-1}$
\bar{r}_{obs}	Observed reaction rate	$\text{mol cm}^{-2} \text{s}^{-1}$
\bar{r}_{max}	Maximum reaction rate	$\text{mol cm}^{-2} \text{s}^{-1}$
\tilde{r}	Dimensionless position in annulus analysis	--
SA	Generic catalyst surface area	cm^2
T	Absolute temperature	K
V_p	Generic catalyst volume	cm^3

Greek

Symbol	Description	Units
α_f	Forward charge-transfer coefficient	--
α_r	Reverse charge-transfer coefficient	--
γ^2	Electrochemically independent Thiele modulus squared	--

δ	Thickness of the concentric shell	cm
ε_{cat}	Porosity of catalyst pellet	--
E	Overpotential dependent parameter	--
η	Overpotential	V
H	Effectiveness factor, internal transport limitations only	--
κ_{eff}	Effective conductivity	S cm ⁻¹
ξ	Ratio of the shell to core thickness	--
τ_{cat}	Tortuosity of catalyst pellet	--
ϕ	Thiele modulus	--
ψ	Dimensionless concentration using bulk concentration as normalizing basis	--
ω	Dimensionless position using particle radius as the normalizing basis	--
Ω	Overall effectiveness factor	--

10 References

1. E. W. Thiele, *Industrial & Engineering Chemistry*, **31**, 916–920 (1939).
2. O. Levenspiel, *Chemical reaction engineering*, 3rd ed., p. 668, Wiley, New York, (1999).
3. H. S. Fogler, *Elements of Chemical Reaction Engineering*, p. 607–625, Prentice Hall, Englewood-Cliffs, (1986).
4. G. Froment, K. Bischoff, and J. De Wilde, *Chemical reactor analysis and design*, Wiley, New York, (1990).
5. M. E. Davis and R. J. Davis, *Fundamentals of Chemical Reaction Engineering*, p. 385, Courier Corporation, (2012).
6. J. Pérez-Ramírez, C. H. Christensen, K. Egeblad, C. H. Christensen, and J. C. Groen, *Chemical Society Reviews*, **37**, 2530–2542 (2008).
7. R. T. Driessen, S. R. A. Kersten, and D. W. F. Brilman, *Industrial & Engineering Chemistry Research*, **59**, 6874–6885 (2020).
8. D. Pletcher and F. C. Walsh, *Industrial Electrochemistry*, p. 669, Springer Science & Business Media, (2012).
9. P. Stonehart and P. N. Ross, *Electrochimica Acta*, **21**, 441–445 (1976).
10. R. M. Darling, *Journal of The Electrochemical Society*, **165**, F571–F580 (2018).
11. R. M. Darling and S. F. Burlatsky, *J. Electrochem. Soc.*, **167**, 104506 (2020).
12. R. M. Darling, *J. Electrochem. Soc.*, **167**, 084505 (2020).
13. T. Duan, J. W. Weidner, and R. E. White, *Journal of Power Sources*, **107**, 24–33 (2002).
14. D. Shin and J. H. Nam, *Electrochimica Acta*, **171**, 1–6 (2015).
15. S. M. Baek, D. Shin, S. Sohn, and J. H. Nam, *Fuel Cells*, **16**, 591–599 (2016).
16. J. H. Kim and T. J. Kang, *ACS Applied Materials & Interfaces*, **11**, 28894–28899 (2019).
17. K. Scott, *Electrochimica Acta*, **27**, 447–451 (1982).
18. K. Scott, *Electrochimica Acta*, **28**, 1191–1200 (1983).
19. D. Aaron, S. Yeom, K. D. Kihm, Y. Ashraf Gandomi, T. Ertugrul, and M. M. Mench, *Journal of Power Sources*, **366**, 241–248 (2017).
20. M. H. Moghim, R. Eqra, M. Babaiee, M. Zarei-Jelyani, and M. M. Loghavi, *Journal of Electroanalytical Chemistry*, **789**, 67–75 (2017).

21. M. Park, J. Ryu, Y. Kim, and J. Cho, *Energy & Environmental Science*, **7**, 3727–3735 (2014).
22. Y. Jiang, Y. Li, J. Zhu, Z. He, W. Meng, H. Zhou, L. Wang, and L. Dai, *J. Electrochem. Soc.*, **165**, A1813–A1821 (2018).
23. C. T.-C. Wan, D. López Barreiro, A. Forner-Cuenca, J.-W. Barotta, M. J. Hawker, G. Han, H.-C. Loh, A. Masic, D. L. Kaplan, Y.-M. Chiang, F. R. Brushett, F. J. Martin-Martinez, and M. J. Buehler, *ACS Sustainable Chem. Eng.*, **8**, 9472–9482 (2020).
24. A. Forner-Cuenca and F. R. Brushett, *Current Opinion in Electrochemistry*, **18**, 113–122 (2019).
25. A. Z. Weber, M. M. Mench, J. P. Meyers, P. N. Ross, J. T. Gostick, and Q. Liu, *J Appl Electrochem*, **41**, 1137 (2011).
26. Y. Yao, J. Lei, Y. Shi, F. Ai, and Y.-C. Lu, *Nature Energy*, 1–7 (2021).
27. J. Newman and K. E. Thomas-Alyea, *Electrochemical Systems*, p. 672, John Wiley & Sons, (2012).
28. K. Jae Kim, M.-S. Park, Y.-J. Kim, J. Ho Kim, S. Xue Dou, and M. Skyllas-Kazacos, *Journal of Materials Chemistry A*, **3**, 16913–16933 (2015).
29. M. Duduta, B. Ho, V. C. Wood, P. Limthongkul, V. E. Brunini, W. C. Carter, and Y.-M. Chiang, *Advanced Energy Materials*, **1**, 511–516 (2011).
30. Z. Li, K. C. Smith, Y. Dong, N. Baram, F. Y. Fan, J. Xie, P. Limthongkul, W. C. Carter, and Y.-M. Chiang, *Phys. Chem. Chem. Phys.*, **15**, 15833–15839 (2013).
31. X. Zhao, B. Jia, Q. Sun, G. Jiao, L. Liu, and D. She, *Royal Society Open Science*, **5**, 180472.
32. B. P. Chaplin, *Acc. Chem. Res.*, **52**, 596–604 (2019).
33. H. Dong, Z. Wu, M. J. Liu, and W. A. Tarpeh, *Chemical Engineering Journal*, **407**, 127821 (2021).
34. L. F. Arenas, C. Ponce de León, and F. C. Walsh, *Current Opinion in Electrochemistry*, **16**, 117–126 (2019).
35. V. Presser, C. R. Dennison, J. Campos, K. W. Knehr, E. C. Kumbur, and Y. Gogotsi, *Advanced Energy Materials*, **2**, 895–902 (2012).
36. M. Boota, K. B. Hatzell, E. C. Kumbur, and Y. Gogotsi, *ChemSusChem*, **8**, 835–843 (2015).
37. T. Tomai, H. Saito, and I. Honma, *J. Mater. Chem. A*, **5**, 2188–2194 (2017).
38. W. M. Deen, *Analysis of Transport Phenomena*, (1998).

39. B. Corry, S. Kuyucak, and S. H. Chung, *Chemical Physics Letters*, **320**, 35–41 (2000).
40. H. Daiguji, *Chem. Soc. Rev.*, **39**, 901–911 (2010).
41. R. G. Compton and C. E. Banks, *Understanding Voltammetry (Second Edition)*, p. 429, World Scientific, (2011).
42. J. D. Milshtein, K. M. Tenny, J. L. Barton, J. Drake, R. M. Darling, and F. R. Brushett, *J. Electrochem. Soc.*, **164**, E3265–E3275 (2017).
43. S. Zhong and M. Skyllas-Kazacos, *Journal of Power Sources*, **39**, 1–9 (1992).
44. A. Alazmi, O. E. Tall, M. N. Hedhili, and P. M. F. J. Costa, *Inorganica Chimica Acta*, **482**, 470–477 (2018).
45. <https://www.fuelcellstore.com/spec-sheets/vulcan-xc72-spec-sheet.pdf>.
46. <http://www.mtixtl.com/TIMCALGraphiteandCarbonSuperPConductiveCarbonBlack100g/bag-EQ-Li.aspx>.
47. R. Aris, *Chemical Engineering Science*, **6**, 262–268 (1957).
48. K. Amini, J. Gostick, and M. D. Pritzker, *Advanced Functional Materials*, **30**, 1910564 (2020).
49. M. H. Gharahcheshmeh, C. T.-C. Wan, Y. A. Gandomi, K. V. Greco, A. Forner-Cuenca, Y.-M. Chiang, F. R. Brushett, and K. K. Gleason, *Advanced Materials Interfaces*, **7**, 2000855 (2020).
50. D.-S. Yang, J. H. Han, J. W. Jeon, J. Y. Lee, D.-G. Kim, D. H. Seo, B. G. Kim, T.-H. Kim, and Y. T. Hong, *Materials Today Energy*, **11**, 159–165 (2019).
51. X. Zhang, Q. Wu, Y. Lv, Y. Li, and X. Zhou, *Journal of Materials Chemistry A*, **7**, 25132–25141 (2019).
52. J. Sun, H. R. Jiang, M. C. Wu, X. Z. Fan, C. Y. H. Chao, and T. S. Zhao, *Applied Energy*, **271**, 115235 (2020).
53. B. Sun and M. Skyllas-Kazacos, *Electrochimica Acta*, **37**, 1253–1260 (1992).
54. K. V. Greco, A. Forner-Cuenca, A. Mularczyk, J. Eller, and F. R. Brushett, *ACS Appl. Mater. Interfaces*, **10**, 44430–44442 (2018).
55. B. Sun and M. Skyllas-Kazacos, *Electrochimica Acta*, **37**, 2459–2465 (1992).
56. Y. Men and T. Sun, *Int. J. Electrochem. Sci.*, **7**, 7 (2012).
57. D. K. Stevens, P. M. Berthouex, and T. W. Chapman, *Journal of Environmental Engineering*, **113**, 1149–1155 (1987).

58. J. P. Lopes, S. S. S. Cardoso, and A. E. Rodrigues, *Chemical Engineering Science*, **71**, 46–55 (2012).