

Bagasse derived C@Fe₃C/Fe₃O₄ composite: An Approach towards low cost electrocatalyst for oxygen reduction reaction

Sai Rashmi Manippady,^a Ziyauddin Khan,^b Akshaya Kumar Samal,^a Manav Saxena*^a

^a Centre for Nano and Material Sciences, Jain University, Bengaluru, Karnataka-562112, India.

^b Laboratory of Organic Electronics, Department of Science and Technology, Linköping University, Norrköping, SE-60174 Sweden

Corresponding author email:

manavsaxena19@gmail.com; s.manav@jainuniversity.ac.in (MS)

Abstract

As the world is heading towards sustainable future, it is highly important to develop low-cost electrocatalysts for energy generation devices. Herein, we report synthesis of iron-carbon hybrid (C@Fe₃C/Fe₃O₄) nanocomposite for oxygen reduction reaction (ORR), synthesized using bagasse as a carbon source material and Fe(III) precursor at 900 °C. The synthesized C@Fe₃C/Fe₃O₄ composite exhibits a high surface area of ~930 m²/g. The electrode material has a 0.86 V overpotential vs RHE. Moreover, the electrocatalyst shows catalytic stability upto 44,000 s at the static potential of 0.25 V vs RHE at the rotation speed of 1600 rpm. Herein, the electron transfer number is calculated to be 3.76-3.94 which suggest that the electrocatalyst could catalyze ORR nearly through a 4 electron transfer process in alkaline solution.

1. Introduction

The world's energy need is fuelled by fossil fuels, yet consumption is skyrocketing owing to population growth. There has been growing upsurge towards upgradation of the renewable energy technologies in order to counter the future energy crisis caused due to exponentially increased populations. In this regards, regenerative fuel cells[1, 2] and rechargeable metal-air batteries[3, 4] are the most promising energy storage and conversion pathways that has potential to fulfil required energy demands. The oxygen reduction reactions (ORR) plays an important role towards the energy efficiency of the fuel cells.[5] However, kinetics and feasibility of electrochemical reactions during energy conversion in these devices has great impact to their performances. ORR is an important half-cell reaction in energy devices but on contrary have sluggish reaction kinetics due to strong O=O bond. Acceleration of this reaction becomes a question of optimizing reaction rates using different metals as electrocatalyst for driving the reaction in the forward direction. To accelerate the kinetics, different electrocatalyst such as noble metals and metal oxide etc. must be used to optimise reaction rates, as the reaction requires an additional electrocatalyst to drive it forward. Platinum (Pt), Palladium (Pd) and Iridium (Ir)-based materials were extensively explored as electrocatalysts due to its excellent catalytic performances since they are the most effective electrocatalysts for ORR. The platinum percentage of commercial Pt/C catalysts ranged from 10 to 60% by weight, with a Pt loading of 0.4 to 0.8 mg Pt/cm². However, the high cost of Pt and the limited durability of support materials impede its commercialization. Xiao et al. reported Pd based nanocatalyst with active sites which improves ORR performance by tuning strain and particle size.[6] However, Pd is very precious and is practically essential in catalytic converters in automobiles.[7] Beermann et al. reported good stability of shape-controlled Pt-Ni nanoparticles for ORR activity.[8] Although the catalyst meets good stability, it does not meet an approach to sustainability or practical feasibility due to its high cost. Zhang et al. reported single-atomic Ruthenium catalytic

sites on nitrogen-doped graphene for ORR activity. The catalyst showed onset potential of 0.89V vs RHE with remarkable durability.[9] However, Their widespread commercial scope is restricted by their high price, restricted storage in the earth, and poor stability. Clearly, inventing new high-activity nonprecious metal (NPM) ORR catalysts to replace Pt-based catalysts is critical.[10]

In the last decades, there have been several reports on non-precious electrocatalysts such as inorganic nanoparticles ($\text{Cu}_{1.4}\text{Mn}_{1.6}\text{O}_4$, $\text{TaC}_x\text{F}_y\text{O}_z/\text{gC}$, Ru),[11-13] transition metal-nitrogen-carbon catalysts (Mn, Fe, Co and Ni based, Fe/Co containing N-doped porous carbon; iron-nitrogen/carbon),[14-21] transition metal oxides ($\text{Fe@Fe}_2\text{O}_3$),[22, 23] non-metal (N, P, S, F etc) doped carbon materials,[24-30] CNT,[29, 31] metal organic framework (MOF) based porous carbon[17, 32-34] etc. based electroactive materials have gained significant attention in order to overcome the cost and sluggish reaction kinetics of ORR. The carbon-based catalysts have attracted a greater attention because of its decent catalytic activity, low capital consumption and longer durability.[35] Non-precious metal catalysts (NMPCs) are appropriate in view of their potential applications for fuel cells and metal-air batteries because they have: (i) sufficient active sites to improve ORR kinetics and achieve results comparable to noble-metal catalysts; (ii) near to 4 e- reduction pathway; (iii) long-term stability and higher tolerance to methanol/CO poisoning compared to noble-metal catalysts.[36] In particular, pyrolyzed carbon-based catalysts with heteroatoms/transition metals (e.g. Fe and/or Co) [37-39] are the most promising alternatives due to reach to more active sites, high activity and low-cost as ORR catalysts. Nevertheless, further improvement in view of synthetic feasibility, material cost and catalytic performances remains an exciting and interesting cause for developing new electro-active materials towards ORR.

Biomass-derived carbon is one of the previously stated support materials that has recently attracted a lot of attention. [28, 40-42] Lignin-rich biomass has been shown to be an

excellent precursor for high surface area carbon synthesis. The majority of agriculture-industry by-products are traditionally burnt, so there is a compelling need to explore more efficient ways to commodify numerous by-products. This could also aid in the replacement of precious catalyst carriers in energy conversion systems with greener and less expensive biomass-based materials with strong electrocatalytic activity.

To overcome all the challenges, herein, we report designing of a simple and sustainable carbon-transition metal oxide composite material using a waste agricultural, biomass material “bagasse (*Saccharum officinarum*)” via carbonization process in N₂ atmosphere without any KOH activation step. Bagasse is dry fibrous residue made up of 32-34% cellulose, 19-24% hemicellulose, 25-32% lignin, 6-12% extractives, and 2-6% ash that remains after sugarcane stalks are crushed to extract juice.[43, 44] The oxygen moieties present in the bagasse coordinates with Fe³⁺ ions and helps in homogenous distribution of iron oxides during the carbonization. Interestingly, composite material showed an impressive overpotential of 0.86 V vs RHE in 0.1 M KOH for ORR. The composite shows long term catalytic stability at the static potential of 0.25 V vs RHE at rotation speed of 1600 rpm. The electron transfer number is close to 4 which suggest that synthesized electrocatalyst might be prominent application with very less amount of hydrogen peroxide as side product. The present work provides useful insight to design carbon based electrocatalyst using low cost and sugar cane industry waste materials which can be further utilized for metal air battery and fuel cells.

2. Experimental section

2.1 Synthesis of the composite material

5g of powdered bagasse was soaked in 20 mL Fe(NO₃)₃·9H₂O solution with known concentration of Fe³⁺ for 24 h. Three samples were prepared by choosing 5%, 10 and 30% (wt%) of Fe-precursor (w.r.t. bagasse weight). The iron treated bagasse were dried in hot air

oven at 60 °C for 12h followed by carbonization at 900 °C (heating rate of 10 °C/min) in a quartz tube furnace under a continuous flow of N₂ at 1 atm pressure. After maintaining furnace at 900 °C for an hour, the furnace was allowed to cool to RT under continuous N₂ flow. The ‘control’ sample was also synthesized without Fe-precursor. The iron-treated samples were referred to **CF1**, **CF2** and **CF3**, which represents the 5, 10 and 30% (wt%, wrt bagasse weight) of iron precursor respectively. The mass percentages of iron in 5, 10 and 30% (wt%) samples with respect to total mass (iron salt + bagasse) are 0.66, 1.26, and 3.2%.

2.2 Material Characterization

The Brunauer-Emmett-Teller (BET) surface area analyzer was used to record nitrogen sorption isotherms at 77 K. (Bellsorp Max, Japan). Pore size distribution plots were taken from the desorption isotherms using the Barrett-Joyner-Halenda (BJH) model. The samples were degassed for 12 hours at 200 °C under vacuum before to measurement. Powder X-ray diffraction (PXRD) with Cu-K α radiation was recorded across a range of 5-80° with a scan speed of 3°/min (Rigaku X-ray diffraction ultima-IV, Japan). Thermo Scientific™ Talos™ F200S High-Resolution Transmission Electron Microscope was used to examine the surface morphology of the samples (HRTEM). The PHI 5000 Versa ProbeII, FEI Inc., was used to perform X-ray photoelectron spectroscopic (XPS) characterization. Raman spectra was recorded using Horiba Jobin Yvon Xplora Plus V1.2 Multiline with 532 nm excitation wavelength. Electrochemical characterization was performed using OrigaLys ElectroChem multichannel workstation equipped with Autolab RRDE setup.

2.3 Electrochemically catalyzed ORR:

The ORR experiment was performed in a three-electrode system using an aqueous solution of 0.1 M KOH. Glassy carbon (GC) electrode was used as working electrode. Whereas, platinum (Pt) and Hg/HgO electrode were served as counter and reference electrode, respectively.

Electrocatalytic ink was prepared by mixing of 1 mg active material with 1 mg volcan carbon in the solvent mixture of water (200 μ l) and isopropanol (200 μ l). Next, 6 μ l of Nafion was added which acts as a binder. The mixture was sonicated for 30 minutes in order to get fine dispersion before using for electrocatalytic studies. Now, 4 μ l of freshly prepared electrocatalytic ink was drop casted over the GC electrode (working electrode) and allowed to dry for 3h at ambient condition. This GC electrode coated with electrocatalyst was used for electrochemical studies. All the electrochemical experiments were performed at the scan rate of 5 mV/s. Cyclic voltammetry (CV) experiments were done at static conditions whereas, linear sweep voltammetry (LSV) was performed at different rotation speeds in continuous flow of O₂. All the electrochemical data were plotted with respect to the reversible hydrogen electrode (RHE).

Oxygen Reduction Reaction:

The reference electrode was calibrated with respect to the reversible hydrogen electrode (RHE). All potentials were rescaled to the pH-independent reversible hydrogen electrode (RHE). The long-term stability for ORR catalysis was evaluated by chronoamperometry, performed in 0.1 M KOH solution at a static potential of 0.25V. To avoid accumulation of gas bubbles on the electrode surface, the electrode was maintained at a rotation of 1600 rpm during the experiment. The number of electrons were calculated using K-L plot (see SI). Rotating ring disk electrode (RRDE) voltammetry was used to calculate the number of electrons and the amount of H₂O₂ formed during ORR based on the ratio of the disk and the ring current (see SI).

3. Results and discussion

Designing catalyst is one of the greatest challenge in any chemical reaction with understanding of different factors. We had designed the composite by using the coordinating ability of oxygen

groups (methoxy, carboxyl, phenolic) from sugar and lignin moieties present in bagasse (a typical bio waste from the sugar industry) with Fe^{3+} ions, to synthesize active material. The Fe^{3+} ions interacted with oxygen groups and present homogeneously in the bagasse. During the carbonization process, iron oxide particles are evenly dispersed throughout the carbon precursor. The synthesis process, Fe^{3+} binding with bagasse and electrocatalytic application toward ORR is schematically represented in Figure 1 and further discussed.

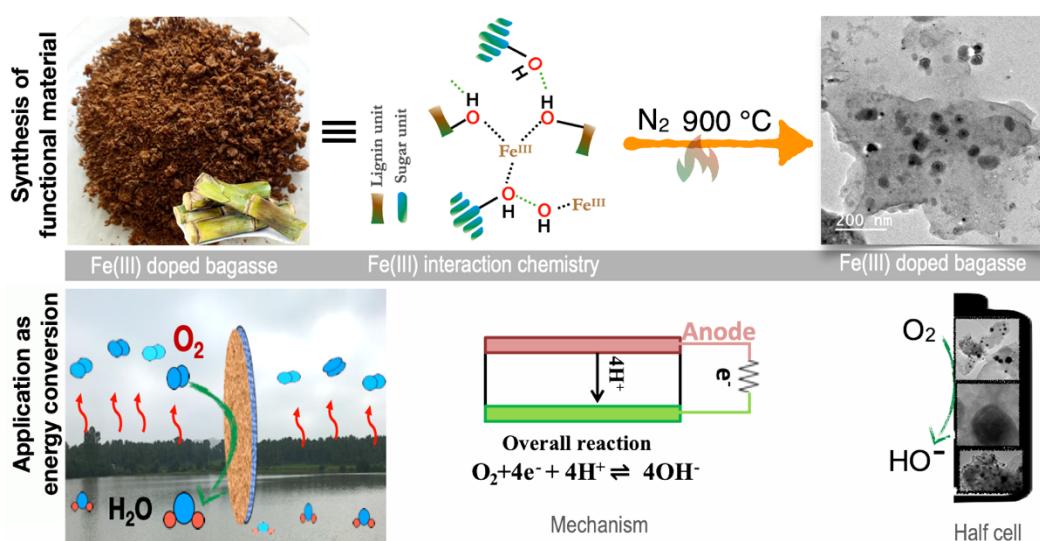


Figure1: Schematic representation for the synthesis of the functional composite material and ORR application.

The surface area and the pore size distribution of CF2 was characterize using N_2 adsorption-desorption at 77 K. The adsorption-desorption curves of CF-2 were ascribed to typical type IV profile (Figure 2a). The surface area of CF2 is $\sim 930 \text{ m}^2\text{g}^{-1}$ which is $\sim 25\%$ higher compared to that of CF0 ($\sim 740 \text{ m}^2\text{g}^{-1}$). The maximal absorption of N_2 gas (77 K) by CF2 was determined to be 344 cc/g at 1 atm pressure. The pore size distribution (PSD) for CF2 revealed pore diameters in the range of 0.4-1.7 nm (Figure 2b), indicating micropore nature. Table 1 lists the detailed textural characteristics of control, CF1, CF2, and CF3. The presence of

nanoparticles on the carbon surface may plug the pores, resulting in decreased in surface area as the iron content increases.

Table 1: Textural properties of Control, CF1, CF2 and CF3.

Textural properties	Control	CF1	CF2	CF3
Surface area ($\text{m}^2 \text{g}^{-1}$)	740	623	930	462
Total pore volume ($\text{cm}^3 \text{g}^{-1}$)	0.330	0.319	0.533	0.505
Micropore size (nm)	1.2-1.8	1.0-1.5	0.4-1.7	1.0-1.5

PXRD analysis was performed to know the crystallinity and crystallographic structure of the control and CF2. Sharp peaks in CF2 suggest the crystalline nature of the material (Figure 2c). For CF-2, the sharp peaks at $2\theta = 25.6^\circ$, 44.6° and 57.2° corresponds to the (002), (101) and (004) planes of graphite.[45] The lattice spacing corresponds to (002) plane is 3.5 \AA which is very close to the lattice spacing observed by HRTEM (3.7 \AA). The peaks at $2\theta = 37.6^\circ$ and 43.1° corresponds to the (112) and (121) plane of Fe_3C (ref. code 01-085-0871). The peaks at $2\theta = 30.2^\circ$, 35.6° , 45.7° , 53.6° , 62.7° corresponds to the (022), (131), (242) and (044) crystal planes of Fe_3O_4 (ref. code 96-900-5839). On the basis of PXRD analysis, the structural composition of CF2 could be written as $\text{C@Fe}_3\text{C/Fe}_3\text{O}_4$ composite. The presence of graphitic structure, Fe_3O_4 and Fe_3C as a hybrid structure is also supported through HRTEM analysis which is discussed later in the current section. PXRD of control shows broad peaks at $2\theta = 23.2^\circ$ and 43.6° refers to the (002) and (100) planes suggesting the amorphous nature of control (Figure S1a). The process of Fe_3C synthesis and graphitization in CF2 is fascinating. Bagasse treated with Fe^{3+} ions includes a considerable number of O atoms, which lead to the nucleation/formation of iron oxide particles when heated to a higher temperature. These iron oxide particles now act as a nucleation site and stimulate the development of a graphitized layer outward. Carbon has temperature dependent solubility in iron. Carbon diffusion into iron oxide

particles occurred simultaneously with the synthesis of iron oxides at higher temperatures. Upon cooling, carbon gets precipitated out as disordered graphitized structure and iron carbide. The schematic presentation of mechanism is shown in Figure 2d. Thus it follows ‘solution-dissolution’ mechanism.

Comparative Raman spectra of control and CF2 are shown in Figure 2e. The G band for control and CF2 are positioned at 1605 and 1593 cm^{-1} respectively. The D band of control and CF2 are positioned at 1350 and 1343 cm^{-1} . The FWHM of D-band of CF2 is 114 cm^{-1} as compared to 173 cm^{-1} of control. The formation of ordered structure causes the decrease in FWHM of the D-band, indicating the presence of graphitized structure. The presence of graphitized carbon structure, which is missing in control, is confirmed by a new band at 2685 cm^{-1} matching to the 2D band that appears in CF2. PXRD and HRTEM analysis show that CF2 graphitization is likewise consistent.

In order to understand the chemical composition of CF2 material, X-ray photoelectron spectroscopy (XPS) was performed. The high-resolution Fe 2p spectrum of CF2 shows two broad peaks at 710.6 and 725.5 eV which are separated by split spin-orbit components of 14.9 eV (Figure 2f). The peak at 710.6 eV corresponds to Fe 2p_{3/2} which is in accordance with the previous report. [46] The broad nature of peak at 710.6 eV might be due to the combine 2p_{3/2} peak of Fe₃O₄ and Fe₃C (708.3 eV) [47]. The nature and peak position of high resolution O1s spectrum shows the peak maxima at 529 eV (Figure 2g) which is well matched with the literature report of Fe₃O₄. [46] The iron-content in CF2 is 1.82 at% as quantified by XPS which is in well agreement with the EDS analysis. The quantification of C, N, O and Fe has been tabulated in Table S1.

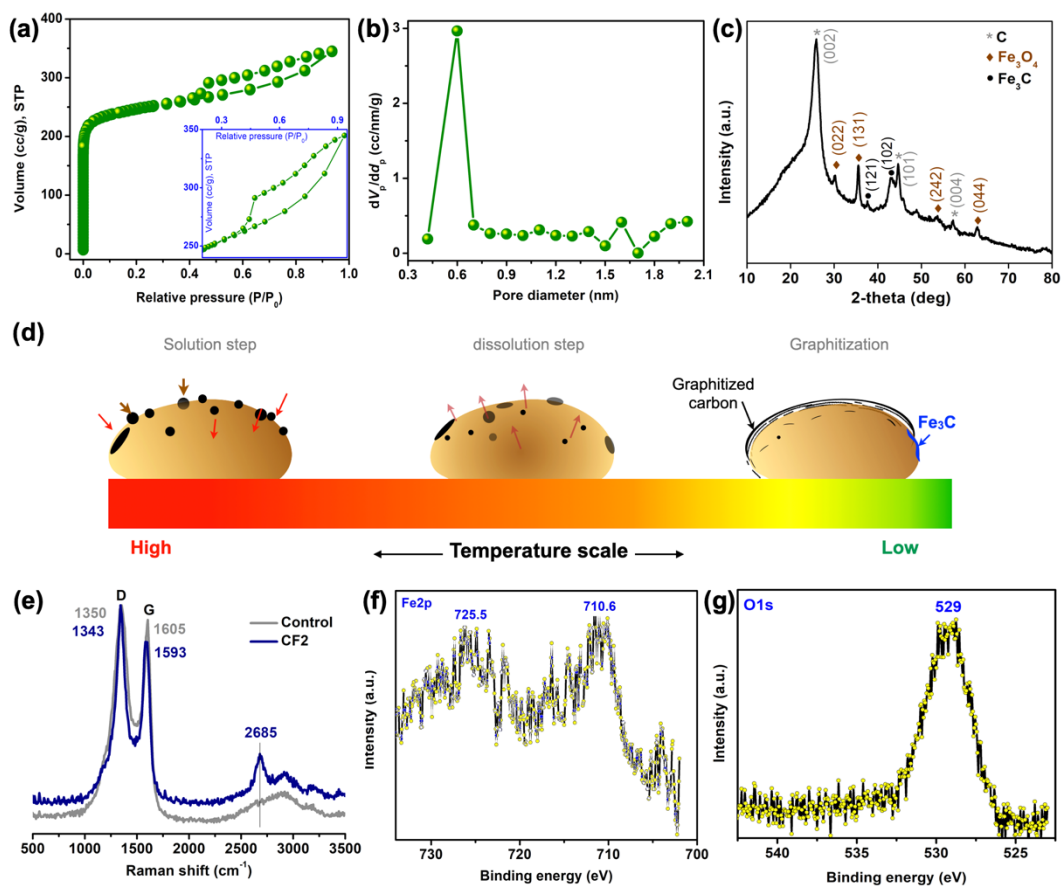


Figure 2: (a) N_2 adsorption-desorption (inset: magnified N_2 adsorption-desorption), (b) Pore size distribution, (c) PXRD of CF2, (d) Graphitization mechanism, (e) Raman spectra, XPS spectra (f) Fe 2p, (g) O 1s of CF2.

FESEM and HRTEM analysis were carried out to study the surface morphology of the composite. FESEM of control shows irregular morphology, whereas CF1, CF2, and CF3 confirm the presence of Fe_3O_4/Fe_3C particles embedded in the carbon structure. (Figure 3a-d). HRTEM analysis of control reveals the porous layered carbon structure (Figure 3e) which is amorphous in nature as suggested by the diffuse ring SAED pattern of the control material (Figure S1b). The amorphous nature and absence of graphitized carbon in control is supported by broad PXRD peaks (Figure S1a). Low and high magnification HRTEM of CF2 is shown in Figure 3g,h. Figure 3g suggests that Fe_3O_4 nanoparticles (high contrast) are embedded homogeneously in the thin layer carbon matrix. The dense contrast area in Figure 3g is Fe_3O_4 , whereas yellow

arrows indicate the graphitized carbon layers in the CF2. The yellow and red coloured dotted area in Figure 3g is magnified and shown as Figure 3h and 3i respectively. The two different type of lattice-spacing 2.39 Å and 3.7 Å could be seen at the middle and edges of CF2 (Figure 3h). The lattice spacing of 2.39 Å corresponds to the (121) plane of Fe₃C (ref code 96-901-6232). The graphitic layers could be easily seen at the top-right corner adjacent to Fe₃C (Figure 3h). The 3.7 Å lattice spacing of graphitic layers corresponds to the (002) plane which is further corroborated with PXRD (Figure 2c). The lattice spacing is slightly higher than standard interlayer graphite distance (3.4 Å) suggests that graphitic layers in CF2 are defected. The presence of Fe₃C and graphitic layer together confirms the “solution-dissolution” based growth mechanism as discussed and represented in Figure 2d. The blue color marked area of Figure 3i is shown as Figure 3j where lattice fringes could be clearly visible suggested high crystallinity of the particle. The lattice spacing of 2.9 Å corresponds to the (022) plane of Fe₃O₄ (ref. code 96-900-5839). The graphitization of CF2 as per discussed ‘solution-dissolution’ mechanism is also confirmed by presence of the graphitized layers in the other regions as show in Figure 3k. The SAED pattern of CF2 exhibits characteristic diffraction spots for different planes of Fe₃O₄, Fe₃C, and graphitized carbon, confirming that the CF2 structure may be represented as C@Fe₃C/Fe₃O₄ composite. (Figure 3l). Energy-dispersive X-ray spectroscopy (EDS) analysis was also performed to quantify the C, N, O and Fe content in control and CF2. (Table S1). The iron content in control and CF2 are 0% and 1.3% (at.%) which is in well agreement with XPS data.

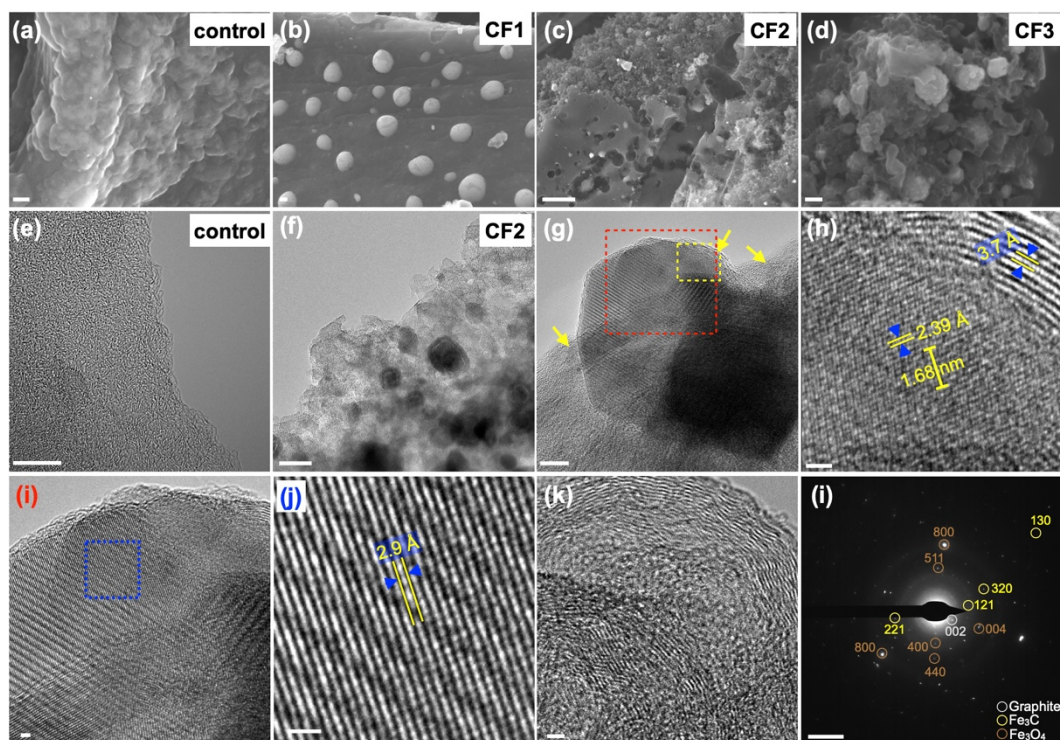


Figure 3: FESEM image of (a) control (b) CF1 (c) CF2 (d) CF3. HRTEM images of (e) control (f-k) CF2. (l) SAED pattern of CF2. Scale bar: (a-d) 100 nm, (e) 10 nm (f) 50 nm (g) 10 nm (h) 1 nm (i-k) 1 nm (l) 5 1/nm.

Electrochemical studies:

The electrochemical activities of the synthesized carbon composites (control, CF1, CF2 and CF3) are first evaluated by cyclic voltammetry (CV) in O₂ saturated solution (Figure S3). All the samples show reduction peak at 0.61 V suggesting that the all the synthesized materials are electrochemically active. The current density increases with increase in the iron loading. The CV of CF2 recorded in the oxygen saturated electrolyte shows an intense reduction peak at 0.61 V vs RHE (Figure 4a). Notably, this peak is absent in the nitrogen saturated solution which unambiguously showed the potential of CF2 towards catalyzing the oxygen reduction reaction. To confirm the activity of synthesized active materials toward ORR, linear scan voltammetry (LSV) was performed for all the synthesized material at 1600 rpm. Among all the samples, CF2 shows highest current density of -7.7 mA/cm² as compared with the control (-3.2

mA/cm²), CF1 (-5.5 mA/cm²) and CF3 (-4.5 mA/cm²) (Figure 4b). The highest current density of CF2 suggests its superior electrocatalytic performance towards ORR and thus CF2 sample is used for further detailed electrochemical analysis. Further, LSV of CF2 was performed at different rotation speed. The LSV shows that limiting current increases with increasing rotation rate (Figure 4c) and did not show any limiting current. This trend in LSV suggest that the ORR process is still under mixed kinetics and diffusion control despite the large overpotentials applied. This could be related to the intrinsic catalytic activity and porosity of prepared carbon composite. [48] The current density at the highest rotation speed of 3600 rpm was found to be -9.1 mA/cm². The high current density values might be due to the abundant O₂ dissolution and diffusion in the electrolyte by continuous flow of O₂. [49] Importantly, the onset potential to initiate the ORR for CF2 was found to 0.86V vs RHE which is comparable to the recent literature reports (Table 2). reference At the same time, overpotential for catalyzing ORR would be 140 mV for the CF2. Notably, overpotential required for ORR and obtained current density for CF2 is comparable and in fact better than some of the reported electrocatalyst materials. Add some more [50, 51] Further, Koutecky-Levich (K-L) plot was derived from LSV profile in order to understand the kinetics of the ORR process. Notably, linearity of Koutecky-Levich (K-L) plot between j^{-1} and $\omega^{-1/2}$ is indicative for the first order reaction kinetics (Figure 4d). Typically, the benchmark electrocatalyst for ORR such as Pt/C utilized direct 4e⁻ pathway [$O_2 + 2H_2O + 4e^- \leftrightarrow 4OH^-(aq)$] which does not proceed via formation of a peroxide intermediate. [48] Herein, the electron transfer number is close to 4 which suggest that our electrocatalyst can be a potential alternate to expensive Pt/C. This has further validated by the rotating ring and disc electrode (RRDE) experiment (Figure 4e). The number of electrons calculated between the potential range 0.3-0.5 V through RRDE experiment was found to be 3.76-3.94 which is in well agreement with K-L plot (Figure 4f). Both, K-L plot and RRDE plot has clearly indicated that the ORR process catalyzed by CF2 is a four-electron

process and therefore, water is expected to be the end product in the ORR process. As estimated, H_2O_2 formed during ORR was found to be 3.1-8.6% in the potential range 0.3-0.5 V (Figure 4f). Further, the catalytic stability test was performed upto 44,000 s at the static potential of 0.25 V vs RHE at the rotation speed of 1600 rpm (Figure S4). The relative current retention was observed 86.5% after 10,000 sec and 64.3% after 40,000 sec, which demonstrates excellent catalytic stability towards ORR process. The presence of graphitized carbon in CF2 is noteworthy that is expected to enhance the stability of the ORR catalysts. [52]

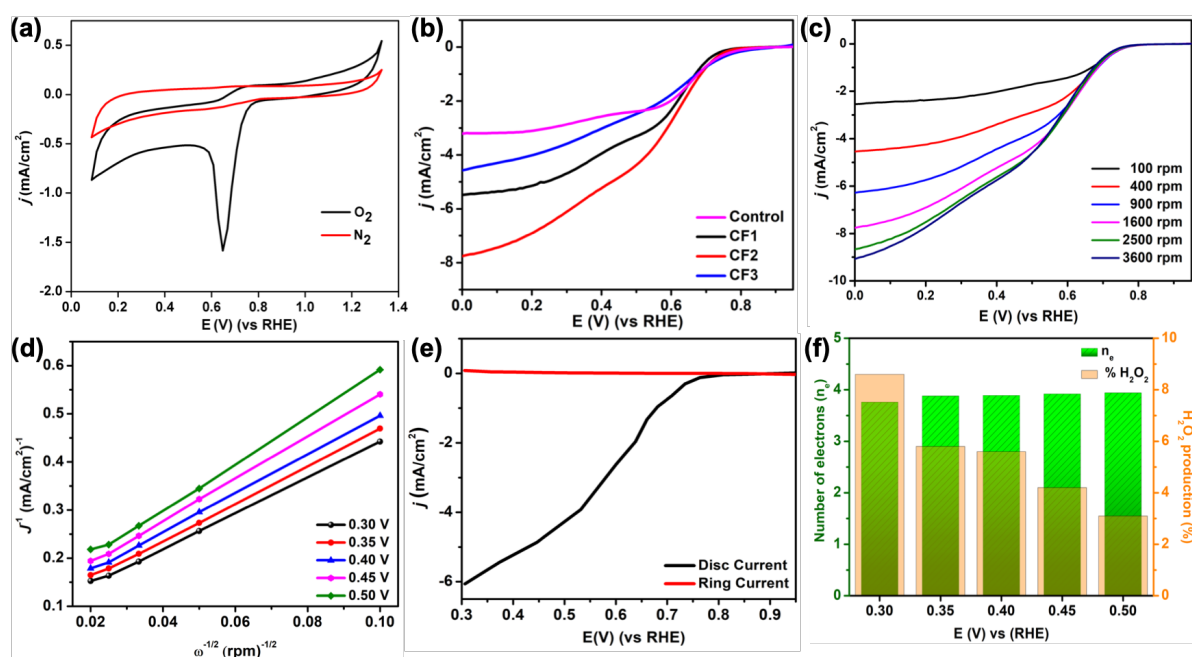


Figure 4: (a) CV of CF2 in N_2 and O_2 -saturated solution; scan rate: 5 mV/s, (b) LSV of different samples at 1600 rpm. Electrochemical studies of CF2 (c) LSV at different scan speed, (d) K-L plots, (e) RRDE measurement in O_2 -saturated solution (rotation speed: 1600 rpm), (f) Plot showing the number of electron transferred and average % of H_2O_2 production. All studies were performed at 0.1 M KOH solution.

Table 2: Comparative ORR performance for Iron based active material.

Active material	Onset potential	Limiting current density	n (e ⁻)	Electrolyte	Reference
	(V vs RHE)	(mA cm ⁻²)			
Fe/FeN@N-C-2-800	0.87	6.04	~4	0.1 M KOH	[53]
ZnCl ₂ -Fe/C/N@bio-C	0.89	6.20	4	0.1 M KOH	[10]
Fe-N _x -C-2	0.92	6.50	~4	0.1 M KOH	[54]
Fe/S-NC	1.00	4.30	3.92	0.1 M KOH	[55]
mFe ₃ O ₄ @C NPs	-0.05	5.22	~4	0.1 M KOH	[56]
Fe-N-C/Fe ₃ C/C-S-C nanohybrid	1.08	5.80	4.03	0.1 M KOH	[18]
Fe ₃ N/Fe-N-C	0.85	5.99	~4	0.1 M KOH	[57]
Fe/N-C	0.81	5.43	3.98	50 mM PBS	[58]
C@Fe ₃ C/Fe ₃ O ₄	0.86	9.1	3.7-3.9	0.1 M KOH	This work

4. Conclusion

The synergy between a strong catalytic chemistry of metal oxide composite materials and the sustainable carbon material gives a path towards low cost, earth abundant, renewable, and well-being electrocatalysts. The successfully synthesised carbon-metal composite (C@Fe₃C/Fe₃O₄) via carbonization method shows uniform distribution Fe₃C/Fe₃O₄ nanoparticles on the partially graphitized layered carbon surface. Due to the synergetic effect between heterosystem, the C@Fe₃C/Fe₃O₄ also shows an impressive catalytic performance toward the ORR and catalytic stability up to 55,000 sec. The 4e⁻ reaction (less H₂O₂ formation) suggests that our electrocatalyst may have an impact on efficient electrocatalyst designing for ORR in alkaline solution. The prepared catalyst derived from sugarcane industry waste can be an efficient catalyst utilized in metal-air batteries and fuel cells in future.

Acknowledgement

SRM expresses gratitude to Jain University for providing a Junior Research Fellowship. MS appreciates the financial support of the SERB in New Delhi, India, for supporting the research (EMR/2017/003368). The authors thank the FESEM and PXRD facilities provided by the NANOMISSION project (SR/NM/NS-20/2014). The authors gratefully appreciate the TEM Facility, which was supported by a TPF Nanomission, GoI project, and Raman characterization at the Centre for Nano and Soft Matter Sciences in Bengaluru, India, as well as XPS characterization at the Indian Institute of Technology Kanpur in Kanpur, India.

Reference

- [1] Pu Z, Zhang G, Hassanpour A, Zheng D, Wang S, Liao S, et al. Regenerative fuel cells: Recent progress, challenges, perspectives and their applications for space energy system. *Appl. Energy*. 2021;283:116376.
- [2] Lim A, Jeong H-Y, Lim Y, Kim JY, Park HY, Jang JH, et al. Amphiphilic Ti porous transport layer for highly effective PEM unitized regenerative fuel cells. *Sci. Adv.* 2021;7:eabf7866.
- [3] Khan Z, Vagin M, Crispin X. Can Hybrid Na–Air Batteries Outperform Nonaqueous Na–O₂ Batteries? *Adv. Sci.* 2020;7:1902866.
- [4] Khan Z, Senthilkumar B, Park SO, Park S, Yang J, Lee JH, et al. Carambola-shaped VO₂ nanostructures: a binder-free air electrode for an aqueous Na–air battery. *J. Mater. Chem. A*. 2017;5:2037-44.
- [5] Wang S, Zhang L, Xia Z, Roy A, Chang DW, Baek J-B, et al. BCN Graphene as Efficient Metal-Free Electrocatalyst for the Oxygen Reduction Reaction. *Angew. Chem. Int. Ed.* 2012;51:4209-12.
- [6] Xiao W, Liuthevicene Cordeiro MA, Gong M, Han L, Wang J, Bian C, et al. Optimizing the ORR activity of Pd based nanocatalysts by tuning their strain and particle size. *J. Mater. Chem. A*. 2017;5:9867-72.
- [7] Farrauto RJ, Deeba M, Alerasool S. Gasoline automobile catalysis and its historical journey to cleaner air. *Nature Catalysis*. 2019;2:603-13.

- [8] Beermann V, Gocyla M, Kühl S, Padgett E, Schmies H, Goerlin M, et al. Tuning the Electrocatalytic Oxygen Reduction Reaction Activity and Stability of Shape-Controlled Pt–Ni Nanoparticles by Thermal Annealing – Elucidating the Surface Atomic Structural and Compositional Changes. *J. Am. Chem. Soc.* 2017;139:16536-47.
- [9] Zhang C, Sha J, Fei H, Liu M, Yazdi S, Zhang J, et al. Single-Atomic Ruthenium Catalytic Sites on Nitrogen-Doped Graphene for Oxygen Reduction Reaction in Acidic Medium. *ACS Nano.* 2017;11:6930-41.
- [10] Li Y, Hu H, Song J, Wu Y, Lv X, Xiao Z, et al. An Excellent Fe, N Co-Doped Porous Biomass Carbon Oxygen Reduction Reaction Electrocatalyst: Effect of Zinc-Based Activators on Catalytic Activity. *Energy Technol.* 2020;8:2000625.
- [11] Yue X, He C, Zhong C, Chen Y, Jiang SP, Shen PK. Fluorine-Doped and Partially Oxidized Tantalum Carbides as Nonprecious Metal Electrocatalysts for Methanol Oxidation Reaction in Acidic Media. *Adv. Mater.* 2016;28:2163-9.
- [12] Zhen S, Sun W, Li P, Tang G, Rooney D, Sun K, et al. High performance cobalt-free $\text{Cu}_{1.4}\text{Mn}_{1.6}\text{O}_4$ spinel oxide as an intermediate temperature solid oxide fuel cell cathode. *J. Power Sources.* 2016;315:140-4.
- [13] Masud J, Nath M. Co_7Se_8 Nanostructures as Catalysts for Oxygen Reduction Reaction with High Methanol Tolerance. *ACS Energy Letters.* 2016;1:27-31.
- [14] Rojas-Carbonell S, Santoro C, Serov A, Atanassov P. Transition metal-nitrogen-carbon catalysts for oxygen reduction reaction in neutral electrolyte. *Electrochem. Commun.* 2017;75:38-42.
- [15] Zu Z-Y, Mi J-L, Wu B, Liu L. Fe/Co Containing N-Doped Hierarchical Porous Carbon Microcuboids and Microcylinders as Efficient Catalysts for Oxygen Reduction Reaction. *ChemCatChem.* 2020;12:5780-8.
- [16] Mao K, Yang L, Wang X, Wu Q, Hu Z. Identifying Iron–Nitrogen/Carbon Active Structures for Oxygen Reduction Reaction under the Effect of Electrode Potential. *J. Phys. Chem. Lett.* 2020;11:2896-901.

- [17] Jing Y, Cheng Y, Wang L, Liu Y, Yu B, Yang C. MOF-derived Co, Fe, and Ni co-doped N-enriched hollow carbon as efficient electrocatalyst for oxygen reduction reaction. *Chem. Eng. J.* 2020;397:125539.
- [18] Al-Shahat Eissa A, Kim NH, Lee JH. Rational design of a highly mesoporous Fe–N–C/Fe₃C/C–S–C nanohybrid with dense active sites for superb electrocatalysis of oxygen reduction. *J. Mater. Chem. A.* 2020;8:23436-54.
- [19] Jin X, Xie Y, Wang L, Huang J. Highly Efficient Oxygen Reduction Reaction Electrocatalysts FeCo–N–C Derived from Two Metallomacrocycles and N-doped Porous Carbon Materials. *ChemElectroChem.* 2020;7:865-72.
- [20] Cao L, Wang Z, Liu J, Wang B, Wang Z, Yang M, et al. A novel Mn/Co dual nanoparticle decorated hierarchical carbon structure derived from a biopolymer hydrogel as a highly efficient electro-catalyst for the oxygen reduction reaction. *Chem. Commun.* 2019;55:13900-3.
- [21] Shen M, Wei C, Ai K, Lu L. Transition metal–nitrogen–carbon nanostructured catalysts for the oxygen reduction reaction: From mechanistic insights to structural optimization. *Nano Research.* 2017;10:1449-70.
- [22] Wu M, Cui M, Wu L, Hwang S, Yang C, Xia Q, et al. Hierarchical Polyelemental Nanoparticles as Bifunctional Catalysts for Oxygen Evolution and Reduction Reactions. *Adv. Energy Mater.* 2020;10:2001119.
- [23] Mu Y, Ai Z, Zhang L. Phosphate Shifted Oxygen Reduction Pathway on Fe@Fe₂O₃ Core–Shell Nanowires for Enhanced Reactive Oxygen Species Generation and Aerobic 4-Chlorophenol Degradation. *Environ. Sci. Technol.* 2017;51:8101-9.
- [24] Liu Z, Zhao Z, Wang Y, Dou S, Yan D, Liu D, et al. In Situ Exfoliated, Edge-Rich, Oxygen-Functionalized Graphene from Carbon Fibers for Oxygen Electrocatalysis. *Adv. Mater.* 2017;29:1606207.
- [25] Zhang P, Wei J-S, Chen X-B, Xiong H-M. Heteroatom-doped carbon dots based catalysts for oxygen reduction reactions. *J. Colloid Interface Sci.* 2019;537:716-24.

- [26] Wang M, Li Y, Fang J, Villa CJ, Xu Y, Hao S, et al. Superior Oxygen Reduction Reaction on Phosphorus-Doped Carbon Dot/Graphene Aerogel for All-Solid-State Flexible Al–Air Batteries. *Adv. Energy Mater.* 2020;10:1902736.
- [27] Lai L, Potts JR, Zhan D, Wang L, Poh CK, Tang C, et al. Exploration of the active center structure of nitrogen-doped graphene-based catalysts for oxygen reduction reaction. *Energy Environ. Sci.* 2012;5:7936-42.
- [28] Zhang Z, Yang S, Li H, Zan Y, Li X, Zhu Y, et al. Sustainable Carbonaceous Materials Derived from Biomass as Metal-Free Electrocatalysts. *Adv. Mater.* 2019;31:1805718.
- [29] Niu W-J, Wang Y-P, He J-Z, Liu W-W, Liu M-C, Shan D, et al. Highly stable nitrogen-doped carbon nanotubes derived from carbon dots and metal-organic frameworks toward excellent efficient electrocatalyst for oxygen reduction reaction. *Nano Energy.* 2019;63:103788.
- [30] Lv Y, Yang L, Cao D. Nitrogen and Fluorine-Codoped Porous Carbons as Efficient Metal-Free Electrocatalysts for Oxygen Reduction Reaction in Fuel Cells. *ACS Appl. Mater. Interfaces.* 2017;9:32859-67.
- [31] Li J-C, Hou P-X, Liu C. Heteroatom-Doped Carbon Nanotube and Graphene-Based Electrocatalysts for Oxygen Reduction Reaction. *Small.* 2017;13:1702002.
- [32] Chai L, Zhang L, Wang X, Xu L, Han C, Li T-T, et al. Bottom-up synthesis of MOF-derived hollow N-doped carbon materials for enhanced ORR performance. *Carbon.* 2019;146:248-56.
- [33] Chen X, Wang N, Shen K, Xie Y, Tan Y, Li Y. MOF-Derived Isolated Fe Atoms Implanted in N-Doped 3D Hierarchical Carbon as an Efficient ORR Electrocatalyst in Both Alkaline and Acidic Media. *ACS Appl. Mater. Interfaces.* 2019;11:25976-85.
- [34] Ding D, Shen K, Chen X, Chen H, Chen J, Fan T, et al. Multi-Level Architecture Optimization of MOF-Templated Co-Based Nanoparticles Embedded in Hollow N-Doped Carbon Polyhedra for Efficient OER and ORR. *ACS Catal.* 2018;8:7879-88.
- [35] Meng FL, Wang ZL, Zhong HX, Wang J, Yan JM, Zhang XB. Reactive Multifunctional Template-Induced Preparation of Fe-N-Doped Mesoporous Carbon Microspheres Towards Highly Efficient Electrocatalysts for Oxygen Reduction. *Adv. Mater.* 2016;28:7948-55.

- [36] Gu W, Hu L, Li J, Wang E. Recent Advancements in Transition Metal-Nitrogen-Carbon Catalysts for Oxygen Reduction Reaction. *Electroanalysis*. 2018;30:1217-28.
- [37] Wang C, Yang F, Qiu T, Cao Y, Zhong H, Yu C, et al. Preparation of an efficient Fe/N/C electrocatalyst and its application for oxygen reduction reaction in alkaline media. *J. Electroanal. Chem.* 2018;810:62-8.
- [38] Cao C, Wei L, Zhai Q, Ci J, Li W, Wang G, et al. Gas-Flow Tailoring Fabrication of Graphene-like Co-Nx-C Nanosheet Supported Sub-10 nm PtCo Nanoalloys as Synergistic Catalyst for Air-Cathode Microbial Fuel Cells. *ACS Appl. Mater. Interfaces*. 2017;9:22465-75.
- [39] Wang Q, Zhou Z-Y, Lai Y-J, You Y, Liu J-G, Wu X-L, et al. Phenylenediamine-Based FeNx/C Catalyst with High Activity for Oxygen Reduction in Acid Medium and Its Active-Site Probing. *J. Am. Chem. Soc.* 2014;136:10882-5.
- [40] Kaare K, Yu E, Volperts A, Dobelev G, Zhurinsk A, Dyck A, et al. Highly Active Wood-Derived Nitrogen-Doped Carbon Catalyst for the Oxygen Reduction Reaction. *ACS Omega*. 2020;5:23578-87.
- [41] Tian X, Lu XF, Xia BY, Lou XW. Advanced Electrocatalysts for the Oxygen Reduction Reaction in Energy Conversion Technologies. *Joule*. 2020;4:45-68.
- [42] Pérez-Rodríguez S, Sebastián D, Alegre C, Tsoncheva T, Petrov N, Paneva D, et al. Biomass waste-derived nitrogen and iron co-doped nanoporous carbons as electrocatalysts for the oxygen reduction reaction. *Electrochim. Acta*. 2021;387:138490.
- [43] Manippady SR, Singh A, Rout CS, Samal AK, Saxena M. Partially Graphitized Iron-Carbon Hybrid Composite as an Electrochemical Supercapacitor Material. *ChemElectroChem*. 2020;7:1928-34.
- [44] Haghdan S, Renneckar S, Smith GD. 1 - Sources of Lignin. In: Faruk O, Sain M, editors. *Lignin in Polymer Composites*: William Andrew Publishing; 2016. p. 1-11.
- [45] Li ZQ, Lu CJ, Xia ZP, Zhou Y, Luo Z. X-ray diffraction patterns of graphite and turbostratic carbon. *Carbon*. 2007;45:1686-95.
- [46] Hawn DD, DeKoven BM. Deconvolution as a correction for photoelectron inelastic energy losses in the core level XPS spectra of iron oxides. *Surf. Interface Anal.* 1987;10:63-74.

- [47] Shabanova IN, Trapeznikov VA. A study of the electronic structure of Fe₃C, Fe₃Al and Fe₃Si by x-ray photoelectron spectroscopy. *J. Electron. Spectrosc. Relat. Phenom.* 1975;6:297-307.
- [48] Khan Z, Park SO, Yang J, Park S, Shanker R, Song H-K, et al. Binary N,S-doped carbon nanospheres from bio-inspired artificial melanosomes: A route to efficient air electrodes for seawater batteries. *J. Mater. Chem. A.* 2018;6:24459-67.
- [49] Zhong G, Xu S, Liu L, Zheng CZ, Dou J, Wang F, et al. Effect of Experimental Operations on the Limiting Current Density of Oxygen Reduction Reaction Evaluated by Rotating-Disk Electrode. *ChemElectroChem.* 2020;7:1107-14.
- [50] Shao M, Chang Q, Dodelet J-P, Chenitz R. Recent Advances in Electrocatalysts for Oxygen Reduction Reaction. *Chem. Rev.* 2016;116:3594-657.
- [51] Rana M, Mondal S, Sahoo L, Chatterjee K, Karthik PE, Gautam UK. Emerging Materials in Heterogeneous Electrocatalysis Involving Oxygen for Energy Harvesting. *ACS Appl. Mater. Interfaces.* 2018;10:33737-67.
- [52] Meng H, Liu Y, Liu H, Pei S, Yuan X, Li H, et al. ZIF67@MFC-Derived Co/N-C@CNFs Interconnected Frameworks with Graphitic Carbon-Encapsulated Co Nanoparticles as Highly Stable and Efficient Electrocatalysts for Oxygen Reduction Reactions. *ACS Appl. Mater. Interfaces.* 2020;12:41580-9.
- [53] Feng C, Guo Y, Qiao S, Xie Y, Zhang L, Zhang L, et al. 2-Methylimidazole as a nitrogen source assisted synthesis of a nano-rod-shaped Fe/FeN@N-C catalyst with plentiful FeN active sites and enhanced ORR activity. *Appl. Surf. Sci.* 2020;533:147481.
- [54] Gao L, Xiao M, Jin Z, Liu C, Ge J, Xing W. Hydrogen etching induced hierarchical meso/micropore structure with increased active density to boost ORR performance of Fe-N-C catalyst. *Journal of Energy Chemistry.* 2019;35:17-23.
- [55] Zhang P, Chen C, Zhang X, Jiang Z, Huang J, Chen J. Fe and S co-doped N-enriched hierarchical porous carbon polyhedron as efficient non-noble-metal electrocatalyst toward oxygen reduction reaction in both alkaline and acidic medium. *Electrochim. Acta.* 2019;298:570-9.
- [56] Zhao J, Li C, Liu R. Enhanced oxygen reduction of multi-Fe₃O₄@carbon core-shell electrocatalysts through a nanoparticle/polymer co-assembly strategy. *Nanoscale.* 2018;10:5882-7.

[57] Xue N, Liu J, Wang P, Wang C, Li S, Zhu H, et al. Scalable synthesis of Fe₃N nanoparticles within N-doped carbon frameworks as efficient electrocatalysts for oxygen reduction reaction. *J. Colloid Interface Sci.* 2020;580:460-9.

[58] Fan Z, Li J, Yang W, Fu Q, Sun K, Song Y-C, et al. Green and facile synthesis of iron oxide nanoparticle-embedded N-doped biocarbon as an efficient oxygen reduction electrocatalyst for microbial fuel cells. *Chem. Eng. J.* 2020;385:123393.