

Graphitic Cathodes for Aluminum Batteries with Aqueous Electrolytes

Jasmin Smajic^{*[a]}, Amira Alazmi^{[a],[b]}, Nimer Wehbe^[c] and Pedro M. F. J. Costa^{*[a]}

[a] Physical Science and Engineering Division, King Abdullah University of Science and Technology (KAUST), Thuwal 23955-6900, Saudi Arabia

[b] Department of Chemistry, University Colleges at Nairiyah, University of Hafr Al-Batin, Hafr Al-Batin 39524, Saudi Arabia

[c] Core Labs, King Abdullah University of Science and Technology (KAUST), Thuwal 23955-6900, Saudi Arabia

E-mail: jasmin.smajic@kaust.edu.sa; pedro.dacosta@kaust.edu.sa

ABSTRACT

Concerns over lithium-ion battery safety and environmental impact have led to increased exploration of alternative energy storage systems. Of these, aluminum is of particular interest, being environmentally friendly, safe and easy to handle. In this work, we explore graphitic cathodes with an aqueous electrolyte (aluminum trifluoromethanesulfonate) and study their electrochemical performance. Finally, a reduced graphene cathode with tailored porosity results in an eco-friendly and inherently safe rechargeable battery with promising electrochemical performance.

KEYWORDS: Carbon, Graphene, Aluminum, Aqueous electrolyte, Battery

INTRODUCTION

Lithium-ion batteries (LIBs) have developed into a reliable and high energy density solution for consumer electronics.^{1,2} However, with the advent of electric vehicles and stationary electrochemical storage, there are mounting concerns related to their operational safety, cost and sustainability.^{3,4} In fact, until recently, little consideration had been given to the environmental aspects of lithium extraction, which is known to cause freshwater shortages, chemical pollution and other adverse effects on ecosystems.⁵

To address the above issues, much attention is being directed to alternative energy storage chemistries such as those based on Na, K, Mg, Zn and Al metals.⁶⁻¹⁰ Of these, aluminum batteries are particularly interesting. Al is considered a "green metal" as it is environmentally friendly, safe and easy to handle. Besides, Al is the most abundant metal in the Earth's crust, with an industrially mature approach for mineral extraction, processing and recycling. In particular, its recycling is economically attractive because of the overall low energy consumption (an estimated 5% of the energy needed to mine and process the ores). Today, 90% of Al used in transportation and construction and around 75% of all that was mined is still in circulation.¹¹⁻¹⁴ Hence, aluminum is a prime resource to build a circular economy industry. Adding to this, and from an electrochemical perspective, Al can store three charge equivalents per mole, leading to theoretical gravimetric and volumetric capacities of 2980 mAh g⁻¹ and 8046 mAh cm⁻³, respectively. These values are some of the highest known for battery materials.^{15,16}

For decades, the promise of Al-batteries has been delayed by the lack of compatible electrolytes and cathodes. Aqueous electrolytes are the most desirable, due to safety and sustainability, but their adoption has largely failed as an oxide surface layer forms spontaneously on Al metal plates (anode) contacting water. In such circumstances, potentials that exceed the thermodynamic stability of water are required for the electrochemical cell to operate. Consequently, non-aqueous ionic liquids (IL) have been the electrolyte of choice.¹⁷⁻¹⁹ In the most popular option, employing a deep eutectic melt based on AlCl₃ and IL generates a solid electrolyte interface (SEI) that enables reversible stripping and plating of Al, mediated by the interconversion of AlCl₄⁻ and Al₂Cl₇.^{9,20-25} Regrettably, depending on their structural composition, these electrolytes can be toxic, or their biodegradability an issue. Additional challenges include their high cost, corrosivity and moisture sensitivity.²⁶⁻³¹

The interest in aqueous electrolytes for Al-batteries was revived recently when Zhao et al. proposed an elegant step to make them compatible with Al anodes.³² By first dipping the Al plate in an AlCl₃-IL mixture, a protective coating is obtained that acts as an "artificial SEI" and prevents direct contact between the Al metal and aqueous electrolyte. Most importantly, the amount of AlCl₃-IL needed is minimal. At present, there are few reports where the ex-situ "artificial SEI" is employed. In those, the choice of the cathode

active material is rather limited, mostly metal oxides.³²⁻³⁴ Despite showing promising capacity performance, the oxide-based cathodes suffer from inadequate stability and low capacity retention. Curiously, carbon cathodes, a popular choice in batteries, have not been explored for aqueous Al-batteries integrating the above-mentioned "artificial SEI".^{35,36}

Here, in a bid to fabricate a low-cost, stable and environmentally friendly Al-battery, we build on top of Zhao's conclusions and explore the stability of the "artificial SEI" approach in conjunction with a salt-water electrolyte and several graphitic carbon cathodes.²⁹ We find that the composition of the aluminum oxide surface layer (at the anode) is severely affected by the AlCl_3 -IL pretreatment and the electrolyte's salt concentration. In addition, we observe that the graphitic carbon powders can have very interesting cathodic performance, provided their structure and chemistry are carefully tailored for this function.

RESULTS & DISCUSSIONS

The electrochemical window of aqueous electrolytes is notoriously narrow due to the H_2 evolution that takes place at higher potentials. This electrolyte degradation ought to be avoided if the longevity of the cell is to be maintained and catastrophic pressure buildup is to be averted. Assuming this, our first step was to test the electrolyte's potential window of electrochemical stability. Popular amongst the group of "artificial SEI" Al anodes, the $\text{Al}(\text{OTF})_3$ salt was selected.³²⁻³⁴ Circulating between Al (as-received state) and glassy carbon electrodes, the electrochemical response of the electrolyte was studied as a function of $\text{Al}(\text{OTF})_3$ concentration (**Figure S1**). Increasing the concentration of the aluminum salt effectively expanded the stability window of the electrolyte and suppressed the electrolysis of water. While a 1M solution offered a window of <0.5 V, for a 2M, the electrolyte was stable in the 0.2 V - 2.2 V range. The 3M solution was stable for 2 V, whereas the more concentrated 5M expanded the upper interval limit past the 3 V mark. The observed trend is an expected consequence of the tight binding between Al^{3+} and its water solvation shell ($\Delta G_{\text{hydration}} = -4525 \text{ kJ mol}^{-1}$).³⁷ Increasing the concentration of the Al salt results in less free water molecules, thus stronger potentials are needed to induce the electrolyte decomposition. This makes the electrolyte more stable and, on a first view, the 5M solution our best option.³⁸

Apart from the stability window, the concentration of the electrolyte must be chosen in accordance to its compatibility with other cell components. For this reason, a different story emerges when looking into the effects of repeated plating and stripping of the Al anode. In **Figure 1a**, it is quite perceptible that the 5M electrolyte leads to an unreliable performance, with drifting potentials and an increase in polarization (from ~ 0.7 V at 20 h, to 1.0 V at 180 h), possibly due to increased viscosity and reduced ionic conductivity.³⁹ By contrast, the other electrolyte concentrations result in much more stable responses and smaller polarization

values (0.35 V for 3M; 0.3 V for 2M; 0.25 V for 1M). Nevertheless, both the 1M and the 3M show sharp overshoot tails after a 6 h rest, instead of the desirable flat potentials. Such deviations are a fingerprint of inhibited charging/discharging processes. The 2M concentration, on the other hand, provides an extremely stable environment.

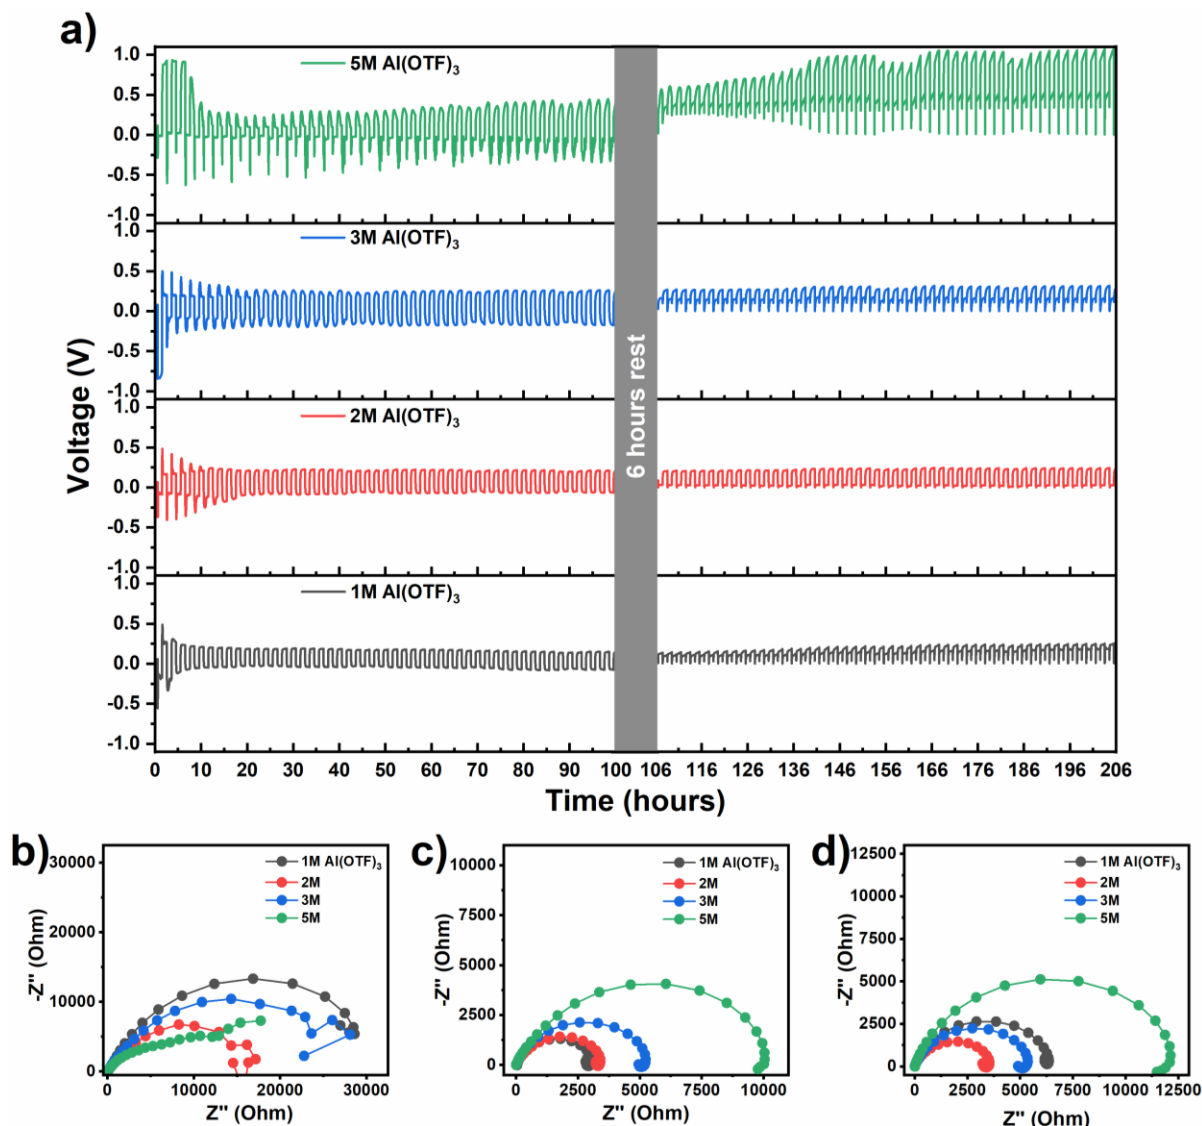


Figure 1. a) Long-term stability of the electrolyte under a cyclic load of 0.01 mA cm^{-2} , b) EIS of the electrolyte before cycling, c) EIS of the electrolyte after 100 h of charge-discharge cycles and d) EIS of the electrolyte after 200 h of charge-discharge cycles.

To understand the interfacial resistances contributing to the polarization and their dependence on the salt's concentration, we probed the system at different time-points of the plating-stripping cycling (0 h, 100 h and 200 h), using electrochemical impedance spectroscopy (EIS). Immediately after the assembly of the cells

(at 0 h), the EIS shows extremely high resistances. (**Figure 1b**). At this stage, the interface between the Al anode and the electrolyte is very immature and the inductive loops at low frequencies are indicative of its modification through ion adsorption processes.^{40,41} After 100 h of cycling (**Figure 1c**), lower resistances were seen. Both the 1M and 2M stand at around 3000 Ω , while the 3M and 5M show 5000 Ω and 10000 Ω , respectively. By leaving the cells to rest for 6 h and cycling them for an additional 100 h (**Figure 1d**), a resistance of around 6500 Ω is measured for the 1M electrolyte, while the 2M and 3M have resistances of 3000 Ω and 5000 Ω , respectively. The 5M resistance increases to 12000 Ω . From this, it is clear that the interface between the Al plate and the electrolyte is heavily dependent on the salt's concentration and immersion time. If the concentration is too high or too low, the interface appears unstable as observed for the 1M and 5M electrolytes. On the other hand, both 2M and 3M appear stable and have low polarization values. In fact, the 2M has the lowest charge-transfer resistance and it is stable for more than 200 h of cycling (**Figures 1a** and **1d**). Hereafter, in order to balance the interface stability, charge-transfer resistance and operational voltage window, a 2M electrolyte was used.

Even at the optimal salt's concentration, the charge-transfer resistance across the SEI on the Al plates remains too high for practical application. Hence, we looked into modifying the metal's surface by either polishing it with sandpaper (Emery, P1000), or exposing it to an $\text{AlCl}_3\text{-IL}$ electrolyte (to form an ex-situ "artificial SEI").³² The analysis with EIS (**Figure S2**) shows that just polishing the foil reduces the resistance by one order of magnitude to 600 Ω (cf. **Figure 1b** to **1c**). On the other hand, by just dipping the plate in the IL (as outlined by Zhao et al.), an even lower resistance of 250 Ω is obtained.²⁹ Clearly, mechanically removing the Al oxide film by polishing is not as good as the action of different organic and Cl-containing species in the $\text{AlCl}_3\text{-IL}$ mixture, at least to obtain a stable and sufficiently conductive SEI. Thus, and in agreement with previous studies, we used Al anodes with the artificial SEI for the rest of the experiments.

Next, XPS was used to examine the chemical composition of the electrochemically cycled Al anode (after 100 cycles) that had the "artificial SEI" coating. A depth profile assessment was rendered possible by etching the Al plates with a high-energy Ar beam. Besides the survey XPS spectra (**Figure S3**), a high-resolution analysis of the Al 2p, O 1s, C 1s and S 2p photoelectrons was performed before and after the etching procedure, with the plates in either charged or discharged states (**Figure 2**). All Al 2p spectra (**Figure 2a**) show two major features: 1) a smaller unsymmetrical signal, in the 72 eV - 70 eV range, that is attributed to spin-orbit splitting in metallic aluminum, and 2) a dominant symmetrical peak, in the 77 eV - 72 eV range. The latter can arise from both the Al-Cl component of the SEI and the Al-O/Al=O bonds from the native oxide and solvated Al^{3+} ions.^{42,43} This explains the different binding energies (BE) of the peaks, before and after etching. For instance, with increased depth, the dominant peak (77 eV - 72 eV range) shifts to lower BE due to a decrease in Al-Cl presence and a relative increase in contribution of Al-

O/Al=O components.⁴² Similarly, the BE of the metallic aluminum (72 eV - 70 eV) gets reduced post-etching, explained by the differences between surface and bulk Al atoms.⁴⁴ Curiously, the intensity of the metallic aluminum peaks, in charged state and before etching, resembles that in discharged state after etching. A possible explanation is the partial electrodeposition of Al on top of the ex-situ "artificial SEI" layer. This is opposite to the discharged state, wherein the metallic aluminum peak before etching has a significantly lower intensity than the post-etching one. We understand it as a consequence of the solvated Al ions migrating towards the anode during charging and diffusing in the opposite direction (i.e. away from the anode) during discharge. This is further confirmed by the higher BE of the charged state after etching.

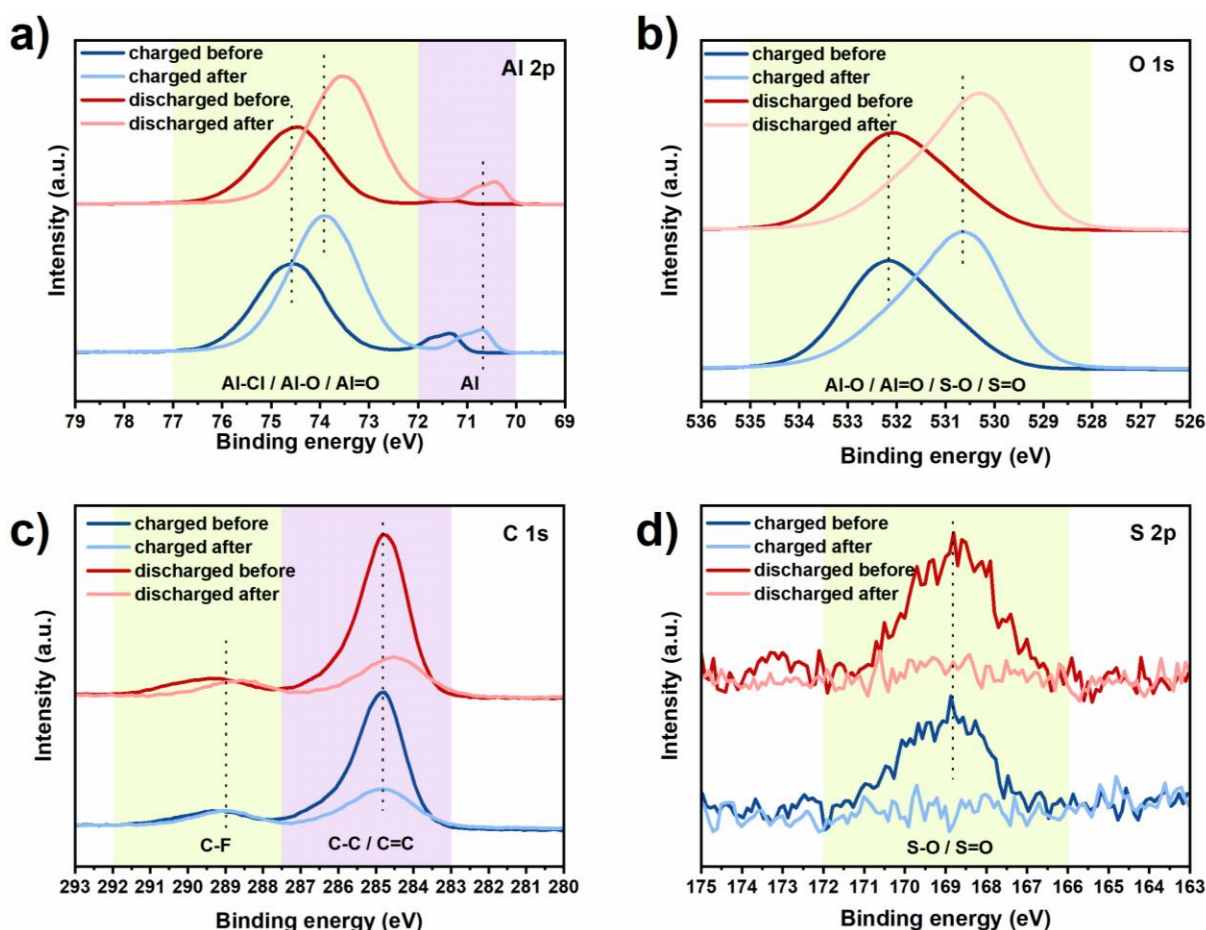


Figure 2. High-resolution XPS spectra of the Al anode, in charged and discharged states, before and after the etching step: a) Al 2p, b) O 1s, c) C 1s and d) S 2p. The dashed lines are guides for the eyes. The legends of chemical bonds refer to the regions (outlined in green and purple colored background) where they are commonly found.

The Al 2p analysis was complemented by the O 1s study (**Figure 2b**). Again, a BE shift was observed as a function of depth. The peaks are asymmetric and can originate from the electrolyte (S-O/S=O) present in

CF₃SO₃⁻), the Al³⁺ solvation shell (Al-O) and the native aluminum oxide (Al-O/Al=O). The etching step resulted in a ~2 eV shift to lower BE. This is explained by the elimination of the IL component and subsequent exposure of the aluminum oxide, in agreement with the Al 2p findings. After etching, the visibly higher BE of the charged state is explained by an increased presence of solvated Al ions. Not surprisingly, the C 1s and S 2p spectra are less informative (**Figures 2c** and **2d**, respectively). The C 1s spectrum consists of two main peaks. The smaller one, in the 291 eV – 288 eV range, is attributed to the C-F from the electrolyte and has constant intensity. The dominant peak, in the 287 eV – 283 eV range, originates from the organic component of the ionic liquid, [EMIm] (i.e. C-C/C=C), that integrates the AlCl₃-IL pretreatment.⁴⁵ This is also the region of adventitious C (284.8 eV). Upon etching, its intensity decreases significantly, as expected. Likewise, the S 2p peaks (from the SO₃⁻ of the Al(OTf) electrolyte) vanish after etching. Following the peak shift analysis, the elements identified with XPS were quantified, before and after etching (**Table 1**).

Table 1. Elemental analysis (at%) of the Al anode's surface, as calculated from XPS measurements.

	Al	O	C	S	F	Cl
Charged before	25.2	45.8	25.0	0.4	1.6	1.9
Charged after	34.3	52.8	11.4	n/a	0.8	0.6
Discharged before	21.7	45.5	29.7	0.4	1.3	0.3
Discharged after	33.7	52.4	11.4	n/a	0.6	n/a

On average, the Al and O presence increases by ~10 at%, while that of C decreases by ~15 at%. Albeit present in small quantities before etching, the concentration of F and Cl decays further, indicating limited but stable adsorption on the anode. On the other hand, the little S that was identified, decreases below the detection limit after etching. Taken together, the native aluminum oxide layer in the anode is clearly affected by the IL pretreatment. However, the IL coating is also modified by the electrolyte. An SEM analysis of the surface (**Figure S4**) identified pits, indicating that the aforementioned SEI does not inhibit the stripping of Al³⁺ ions.

After identifying the characteristics of the cycled Al anode, we questioned the available repertoire of cathodes for aqueous Al batteries. Confronted with the predominance of metal oxides, we looked for possible alternatives and tested two of the most common carbon electrode materials: graphite and expanded graphite (i.e. processed expanded graphite, see *Experimental Section*). As seen in **Figure 3a**, their cyclic voltammetry exhibit broad redox peaks that can be attributed to the intercalation of ions into the layered carbons.

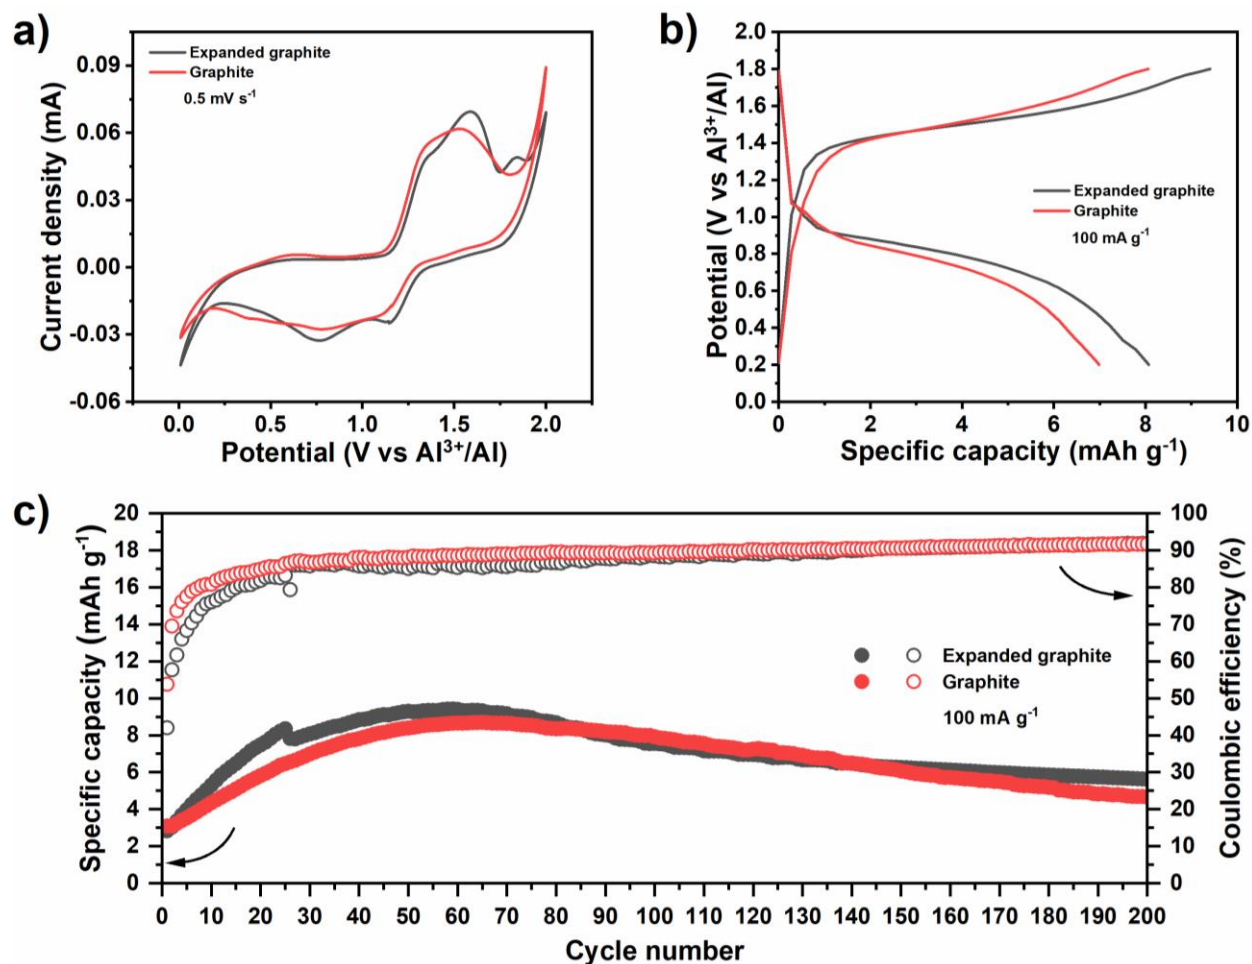


Figure 3. Electrochemical performance of the graphite and expanded graphite cathode: a) cyclic voltammetry, b) voltage profiles and c) cycling stability.

The voltage curves (**Figure 3b**) show plateaus centered at 0.9 V and 1.4 V, for discharge and charge, respectively. These agree well with the cyclic voltammetry. The capacity, however, peaks at around 10 mAh g^{-1} (**Figure 3c**), declining by $\sim 50\%$ after 200 cycles. Assuming that the Al^{3+} (a strong Lewis acid) remains solvated throughout, this behavior is a likely consequence of the large size of the intercalant (0.38 nm).⁴⁶ This hypothesis is also supported by a slightly higher capacity of expanded graphite, due to its expanded interlayer distance. Carbons are a versatile family of materials. Besides a number of allotropes, it is possible to tailor their structure and surface chemistry.^{47,48} In fact, depending on the process selected, powders derived from graphite can be modified to accommodate large ions. Previously, we demonstrated the importance of the drying method as we tuned the porosity of reduced graphene oxide (rGO) to optimize its performance for batteries and supercapacitors.^{20,49} Supercritical drying methods yield rGO powders with a moderate surface area and an average pore size of 20 nm that could accommodate the large size of solvated

Al^{3+} ions through mostly pseudocapacitive charge storage.^{20,49} In these circumstances, allying the chemical stability of graphitic carbon powders to the mesoporosity of the rGOs could be advantageous when exploring alternative cathode materials for aqueous Al-batteries (**Figure 4**).

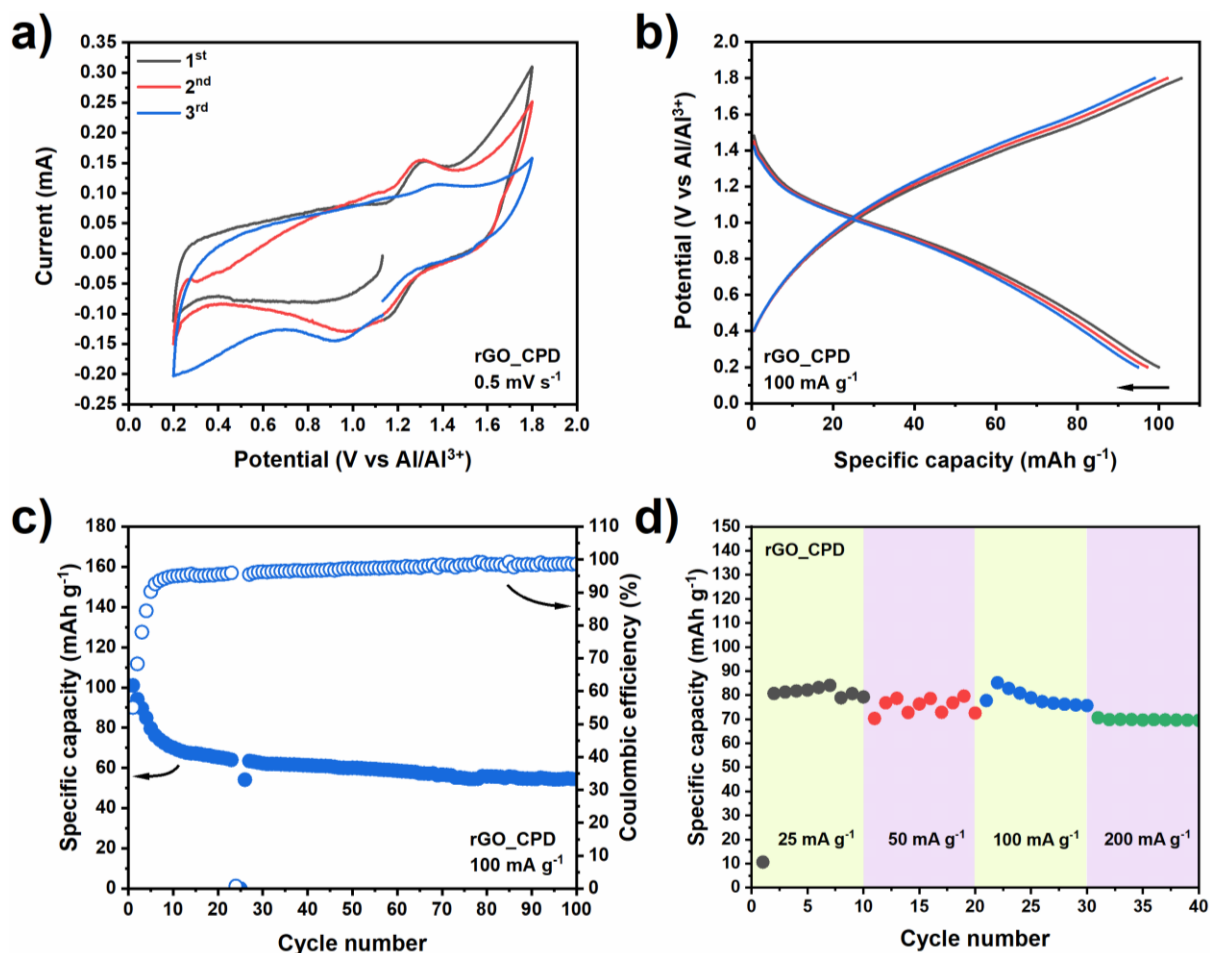


Figure 4. Electrochemical performance of the rGO_CPD: a) cyclic voltammetry, b) charge-discharge voltage profiles, c) cycling stability with Coulombic efficiency and d) rate capability.

As seen in **Figure 4**, the supercritically-dried rGO (rGO_CPD) exhibits vastly superior performance than both graphite and expanded graphite. Its cyclic voltammogram (**Figure 4a**) shows broad peaks at 1.0 V and 1.3 V for discharge and charge, respectively. These values are similar to those previously found for graphite and expanded graphite, however, their intensity is lower and the area enclosed by the cyclic voltammogram curves is higher, indicating an increased pseudocapacitive component of the charge-storage mechanism. The voltage curves (**Figure 4b**) show sloping profiles, instead of plateaus, in agreement with the pseudocapacitive character of the electrode and justifies the remarkable increase in capacity (by one order of magnitude), with the initial capacity at $\sim 100 \text{ mAh g}^{-1}$. Furthermore, the rGO_CPD's cycling stability and

the Coulombic efficiency are also superior (**Figure 4c**), with 77% of capacity retention between 10th and 100th cycle at a constant Coulombic efficiency of ~98 %. Finally, its rate capability (**Figure 4d**) yields similar capacities for different current densities, confirming the resilience of the rGO_CPD cathode. Such a response speaks to the stability and efficiency of this system. It also demonstrates that "opening up" the graphitic structure (by increasing the surface area and inducing mesoporosity), successfully overcomes the inherent limitations of the large ion size. Ultimately, the ~20 nm mesopores network of the rGO_CPD enables a better wetting of the cathode mass as well as facilitating the access of the Al ions to redox-active sites.⁵⁰

CONCLUSIONS

A modified Al anode, a reduced graphene oxide cathode and a 2M Al(OTF)₃ electrolyte can be used to form an eco-friendly and inherently safe rechargeable battery. We find that the SEI layer on the Al anode is dependent on both the pretreatment method and the electrolyte. Further to this, increasing the pseudocapacitive component of the carbon cathode is beneficial in improving the electrochemical performance of an aqueous Al-battery.

EXPERIMENTAL

Materials Synthesis

Graphite (Alfa Aesar; 99.99% purity; 44 μm average flake size) and expanded graphite were used as-received.⁵¹ To prepare the reduced graphene oxide (rGO), we followed a procedure described elsewhere.⁵⁰ Briefly, graphite powder (99%, crystalline, 325 mesh, Alfa Aesar) was oxidized and exfoliated using the improved Hummers' method. Following this, the graphene oxide (GO) powder was dried with supercritical CO₂ for 24 h, and hydrothermally reduced, at 180 °C for 24 h. Upon collection, the rGO product was dried under supercritical conditions (for 24 h).

The aqueous electrolyte was prepared by mixing the salt aluminum trifluoromethanesulfonate Al(OTF)₃ (Alfa Aesar) with appropriate volumes of deionized water to obtain various concentrations, 1M, 2M, 3M and 5M. To prepare the ionic liquid electrolyte, 1-ethyl-3-methyl imidazolium chloride [EMIm]Cl was first annealed in a tube furnace, in vacuo, at 70 °C and for 16 h, to remove residual water. This powder was then introduced into an Ar-filled glove box (MBraun LabStar, <0.5 ppm O₂, <0.5 ppm H₂O), always avoiding exposure to air. The anhydrous AlCl₃ powder was used as received from the vendor (Alfa Aesar). With these two components, the AlCl₃:[EMIm]Cl = 1.3 (mol mol⁻¹) electrolyte was prepared by slowly adding

the AlCl_3 to $[\text{EMIm}]\text{Cl}$, inside the glove box. Mixing of the two powders produced a clear light-yellow liquid through an exothermic reaction. Finally, the obtained electrolyte was stirred for 30 min and left to stand.

Materials Characterization

Optical microscopy was performed on a Zeiss STEMI 2000-C. The X-ray photoelectron spectroscopy (XPS) characterization was done on a Kratos Axis Ultra, equipped with a monochromatic Al $\text{K}\alpha$ X-ray source ($h\nu = 1486.6$ eV) and operated at a power of 150 W under ultrahigh-vacuum conditions (10^{-9} mbar). The etching process was performed using argon cluster beam Ar500+, operated at 5 keV. The raster size of the etched area was about 4 mm x 4 mm and the etching was done until S could not be detected ($\sim 30 - 50$ nm). The spectra were collected from the middle of the etched area, in order to avoid the edge effect.

Electrochemical Measurements

The electrochemical studies were made with two potentiostats, a Bio-Logic VMP3 and a BCS-800, in a 2023 coin cell configuration. Electrochemical impedance spectroscopy (EIS) was carried out from 10 mHz to 100 kHz with an amplitude of 10 mV. The cells were assembled using the carbon powders and an Al foil (99.999%, 0.25 mm, Sigma-Aldrich) as the active electrode materials (cathode and anode, respectively). The cathode was prepared by sandwiching the carbons (~ 1 mg cm^{-2}) between a glass fiber separator and a current collector. No binders were used. Carbon paper was the current collector of choice for the electrochemical performance assessment. In all experiments, 100 μl of aqueous electrolyte was used for each cell.

Data availability

The raw/processed data required to reproduce these findings cannot be shared at this time as the data also forms part of an ongoing study.

Acknowledgements

This work was funded by KAUST (BAS/1/1346-01-01). The authors thank the KAUST Core Labs for technical assistance.

Conflict of Interest

Parts of this work have been filed as a provisional patent application (USPTO 63/186,362, filed: May 10, 2021).

REFERENCES

- 1 Li, M., Lu, J., Chen, Z. & Amine, K. 30 years of lithium-ion batteries. *Advanced Materials* **30**, 1800561 (2018).
- 2 Smajic, J., Alazmi, A., Patole, S. P. & Costa, Pedro M. F. J. Single-walled carbon nanotubes as stabilizing agents in red phosphorus Li-ion battery anodes. *RSC Advances* **7**, 39997-40004 (2017).
- 3 Scrosati, B. & Garche, J. Lithium batteries: Status, prospects and future. *Journal of Power Sources* **195**, 2419-2430 (2010).
- 4 Choi, J. W. & Aurbach, D. Promise and reality of post-lithium-ion batteries with high energy densities. *Nature Reviews Materials* **1**, 1-16 (2016).
- 5 Wanger, T. C. The Lithium future—resources, recycling, and the environment. *Conservation Letters* **4**, 202-206 (2011).
- 6 Hwang, J. Y., Myung, S. T. & Sun, Y. K. Recent progress in rechargeable potassium batteries. *Advanced Functional Materials* **28**, 1802938 (2018).
- 7 Mao, M., Gao, T., Hou, S. & Wang, C. A critical review of cathodes for rechargeable Mg batteries. *Chemical Society Reviews* **47**, 8804-8841 (2018).
- 8 Li, H., Ma, L., Han, C., Wang, Z., Liu, Z., Tang, Z. & Zhi, C. Advanced rechargeable zinc-based batteries: Recent progress and future perspectives. *Nano Energy* **62**, 550-587 (2019).
- 9 Lin, M.-C., Gong, M., Lu, B., Wu, Y., Wang, D.-Y., Guan, M., Angell, M., Chen, C., Yang, J. & Hwang, B.-J. An ultrafast rechargeable aluminium-ion battery. *Nature* **520**, 324-328 (2015).
- 10 Vaalma, C., Buchholz, D., Weil, M. & Passerini, S. A cost and resource analysis of sodium-ion batteries. *Nature Reviews Materials* **3**, 1-11 (2018).
- 11 Rombach, G. Raw material supply by aluminium recycling—Efficiency evaluation and long-term availability. *Acta Materialia* **61**, 1012-1020 (2013).
- 12 Bertram, M., Hryniuk, M., Kirchner, G. & Pruvost, F. Aluminium recycling in Europe: the road to high quality products. (European Aluminum Association, 2006).
- 13 Bertram, M., Martchek, K. J. & Rombach, G. Material flow analysis in the aluminum industry. *Journal of Industrial Ecology* **13**, 650-654 (2009).
- 14 Bai, Y., Essehli, R., Jafta, C. J., Livingston, K. M. & Belharouak, I. Recovery of cathode materials and aluminum foil using a green solvent. *ACS Sustainable Chemistry & Engineering* **9**, 6048-6055 (2021).
- 15 Lide, D. R. *CRC Handbook of Chemistry and Physics*. Vol. 85 (CRC press, 2004).
- 16 Zhang, M., Xiang, L., Galluzzi, M., Jiang, C., Zhang, S., Li, J. & Tang, Y. Uniform distribution of alloying/dealloying stress for high structural stability of an Al anode in high-area-density lithium-ion batteries. *Advanced Materials* **31**, 1900826 (2019).
- 17 Zhou, J., Yu, X., Zhou, J. & Lu, B. Polyimide/metal-organic framework hybrid for high performance Al-Organic battery. *Energy Storage Materials* **31**, 58-63 (2020).
- 18 Lin, M. C., Gong, M., Lu, B., Wu, Y., Wang, D. Y., Guan, M., Angell, M., Chen, C., Yang, J., Hwang, B. J. & Dai, H. An ultrafast rechargeable aluminium-ion battery. *Nature* **520**, 325-328 (2015).
- 19 Faegh, E., Ng, B., Hayman, D. & Mustain, W. E. Practical assessment of the performance of aluminium battery technologies. *Nature Energy* **6**, 21-29 (2021).
- 20 Smajic, J., Alazmi, A., Batra, N., Palanisamy, T., Anjum, D. H. & Costa, P. M. Mesoporous reduced graphene oxide as a high capacity cathode for aluminum batteries. *Small* **14**, 1803584 (2018).
- 21 Smajic, J., Wee, S., Simoes, F. R. F., Hedhili, M. N., Wehbe, N., Abou-Hamad, E. & Costa, P. M. Capacity retention analysis in aluminum-sulfur batteries. *ACS Applied Energy Materials* **3**, 6805-6814 (2020).

- 22 Wu, Y., Gong, M., Lin, M.-C., Yuan, C., Angell, M., Huang, L., Wang, D.-Y., Zhang, X., Yang, J., Hwang, B.-J. & Dai, H. 3D graphitic foams derived from chloroaluminate anion intercalation for ultrafast aluminum-ion battery. *Advanced Materials* **28**, 9218-9222 (2016).
- 23 Wang, S., Yu, Z., Tu, J., Wang, J., Tian, D., Liu, Y. & Jiao, S. A novel aluminum-ion battery: Al/AlCl₃-[EMIm]Cl/Ni₃S₂@graphene. *Advanced Energy Materials* **6**, 1600137 (2016).
- 24 Hu, Y., Luo, B., Ye, D., Zhu, X., Lyu, M. & Wang, L. An innovative freeze-dried reduced graphene oxide supported SnS₂ cathode active material for aluminum-ion batteries. *Advanced Materials* **29**, 1606132 (2017).
- 25 Zhang, L., Chen, L., Luo, H., Zhou, X. & Liu, Z. Large-sized few-layer graphene enables an ultrafast and long-life aluminum-ion battery. *Advanced Energy Materials* **7**, 1700034 (2017).
- 26 Leitch, A. C., Abdelghany, T. M., Probert, P. M., Dunn, M. P., Meyer, S. K., Palmer, J. M., Cooke, M. P., Blake, L. I., Morse, K. & Rosenmai, A. K. The toxicity of the methylimidazolium ionic liquids, with a focus on M8OI and hepatic effects. *Food and Chemical Toxicology* **136**, 111069 (2020).
- 27 Bubalo, M. C., Radošević, K., Redovniković, I. R., Slivac, I. & Srček, V. G. Toxicity mechanisms of ionic liquids. *Archives of Industrial Hygiene and Toxicology* **68**, 171-179 (2017).
- 28 Smajic, J., Simoes, F. R. F. & Costa, P. M. F. J. How metallic impurities in carbon cathodes affect the electrochemistry of aluminum batteries. *ChemElectroChem* **7**, 4810-4814 (2020).
- 29 Smajic, J., Alazmi, A. & Costa, P. M. F. J. The Role of the binder/solvent pair on the electrochemical performance of aluminium batteries. *MRS Advances* **4**, 807-812 (2019).
- 30 Shi, J., Zhang, J. & Guo, J. Avoiding pitfalls in rechargeable aluminum batteries research. *ACS Energy Letters* **4**, 2124-2129 (2019).
- 31 Costa, S. P., Azevedo, A. M., Pinto, P. C. & Saraiva, M. L. M. Environmental impact of ionic liquids: recent advances in (eco) toxicology and (bio) degradability. *ChemSusChem* **10**, 2321-2347 (2017).
- 32 Zhao, Q., Zachman, M. J., Al Sadat, W. I., Zheng, J., Kourkoutis, L. F. & Archer, L. Solid electrolyte interphases for high-energy aqueous aluminum electrochemical cells. *Science Advances* **4**, eaau8131 (2018).
- 33 Zhao, Q., Liu, L., Yin, J., Zheng, J., Zhang, D., Chen, J. & Archer, L. Proton intercalation/de-intercalation dynamics in vanadium oxides for aqueous aluminum electrochemical cells. *Angewandte Chemie* **59**, 3048-3052 (2019).
- 34 Cai, Y., Kumar, S., Chua, R., Verma, V., Du, Y., Kou, Z., Ren, H., Arora, H. & Srinivasan, M. Bronze-type vanadium dioxide holey nanobelts as high performing cathode material for aqueous aluminium-ion battery. *Journal of Materials Chemistry A* **8**, 12716-12722 (2020).
- 35 Nandi, S. & Das, S. K. Realizing a low-cost and sustainable rechargeable aqueous aluminum-metal battery with exfoliated graphite cathode. *ACS Sustainable Chemistry & Engineering* (2019).
- 36 Zhang, Q., Cheng, X., Wang, C., Rao, A. M. & Lu, B. Sulfur-assisted large-scale synthesis of graphene microspheres for superior potassium-ion batteries. *Energy & Environmental Science* **14**, 965-974 (2021).
- 37 Marcus, Y. Thermodynamics of solvation of ions. Part 5.—Gibbs free energy of hydration at 298.15 K. *Journal of the Chemical Society, Faraday Transactions* **87**, 2995-2999 (1991).
- 38 Suo, L., Borodin, O., Gao, T., Olguin, M., Ho, J., Fan, X., Luo, C., Wang, C. & Xu, K. "Water-in-salt" electrolyte enables high-voltage aqueous lithium-ion chemistries. *Science* **350**, 938-943 (2015).
- 39 Kumar, S., Verma, V., Arora, H., Manalastas Jr, W. & Srinivasan, M. Rechargeable Al-metal aqueous battery using NaMnHCF as a cathode: investigating the role of coated-Al anode treatments for superior battery cycling performance. *ACS Applied Energy Materials* **3**, 8627-8635 (2020).

- 40 Xu, L.-n., Zhu, J.-y., Lu, M.-x., Zhang, L. & Chang, W. Electrochemical impedance spectroscopy study on the corrosion of the weld zone of 3Cr steel welded joints in CO₂ environments. *International Journal of Minerals, Metallurgy, and Materials* **22**, 500-508 (2015).
- 41 Boukamp, B. A. Interpretation of an 'inductive loop' in the impedance of an oxygen ion conducting electrolyte/metal electrode system. *Solid State Ionics* **143**, 47-55 (2001).
- 42 Sherwood, P. M. Introduction to studies of aluminum and its compounds by XPS. *Surface Science Spectra* **5**, 1-3 (1998).
- 43 Elmi, C., Guggenheim, S. & Gieré, R. Surface crystal chemistry of phyllosilicates using X-ray photoelectron spectroscopy: A review. *Clays and Clay Minerals* **64**, 537-551 (2016).
- 44 Bagus, P., Pacchioni, G. & Parmigiani, F. Surface core-level spectroscopy of Cu (100) and Al (100). *Physical Review B* **43**, 5172 (1991).
- 45 Palchan, I., Crespin, M., Estrade-Szwarczkopf, H. & Rousseau, B. Graphite fluorides: an XPS study of a new type of CF bonding. *Chemical Physics Letters* **157**, 321-327 (1989).
- 46 Marcus, Y. Ionic radii in aqueous solutions. *Chemical Reviews* **88**, 1475-1498 (1988).
- 47 Batra, N. M., Ashokkumar, A. E., Smajic, J., Enyashin, A. N., Deepak, F. L. & Costa, P. M. Morphological phase diagram of gadolinium iodide encapsulated in carbon nanotubes. *The Journal of Physical Chemistry C* **122**, 24967-24976 (2018).
- 48 Wang, Y., Zhang, M., Shen, X., Wang, H., Wang, H., Xia, K., Yin, Z. & Zhang, Y. Biomass-derived carbon materials: controllable preparation and versatile applications. *Small*, 2008079 (2021).
- 49 Alazmi, A., El Tall, O., Rasul, S., Hedhili, M. N., Patole, S. P. & Costa, P. M. A process to enhance the specific surface area and capacitance of hydrothermally reduced graphene oxide. *Nanoscale* **8**, 17782-17787 (2016).
- 50 Alazmi, A., Rasul, S., Patole, S. P. & Costa, P. M. Comparative study of synthesis and reduction methods for graphene oxide. *Polyhedron* **116**, 153-161 (2016).
- 51 Alzahrani, A. A. *Production of High-quality Few-layer Graphene Flakes by Intercalation and Exfoliation* (2017).