

Dual promotional effect of Cu_xO clusters grown with atomic layer deposition on TiO₂ for photocatalytic hydrogen production

Saeed Saedy^{*a}, Nico Hiemstra^a, Dominik Benz^a, Hao Van Bui^b, Michael Nolan^c, J. Ruud van Ommen^a

^aDepartment of Chemical Engineering, Delft University of Technology, Van der Maasweg 9, 2629 HZ, Delft, The Netherlands

^bFaculty of Materials Science and Engineering, Phenikaa University, Yen Nghia, Ha-Dong District, Hanoi 12116, Vietnam

^cTyndall National Institute, University College Cork, Lee Maltings, Dyke Parade, Cork, T12 R5CP, Ireland

*corresponding author: s.saedy@tudelft.nl

Abstract

The promotional effects on photocatalytic hydrogen production of Cu_xO clusters deposited using atomic layer deposition (ALD) on P25 TiO₂ are presented. The structural and surface chemistry study of Cu_xO/TiO₂ samples, along with first principles Density Functional Theory simulations, reveal the strong interaction of ALD deposited Cu_xO with TiO₂, leading to the stabilization of Cu_xO clusters on the surface; it also demonstrated substantial reduction of Ti⁴⁺ to Ti³⁺ on the surface of Cu_xO/TiO₂ samples after Cu_xO ALD. The Cu_xO/TiO₂ photocatalysts showed remarkable improvement in hydrogen productivity, with 11 times greater hydrogen production for the optimum sample compared to unmodified P25. With the combination of the hydrogen production data and characterization of Cu_xO/TiO₂ photocatalysts, we inferred that ALD deposited Cu_xO clusters have a dual promotional effect: increased charge carrier separation and improved light absorption, consistent with known copper promoted TiO₂ photocatalysts and generation of a substantial amount of surface Ti³⁺ which results in self-doping of TiO₂ and improves its photo-activity for hydrogen production. The obtained data were also employed to modify the previously proposed expanding photocatalytic area and overlap model to describe the effect of cocatalyst size and weight loading on photocatalyst activity. Comparing the trend of surface Ti³⁺ content increase and the photocatalytically promoted area, calculated with our model, suggests that the depletion zone formed around the heterojunction of Cu_xO-TiO₂ is the main active area for hydrogen production, and the hydrogen productivity of the photocatalyst depends on the surface coverage by this active area. However, the overlap of these areas initiates the deactivation of the photocatalyst.

Keywords: photocatalyst, solar hydrogen, cuprous oxide, titanium dioxide, atomic layer deposition

Introduction

Climate change and its devastating environmental effects constitute the major long-term threats that our planet is facing. On the other hand, the depletion of fossil fuel reserves is a big challenge to the energy security of our society. It is anticipated that the annual energy consumption will be doubled by 2050 compared to 2015 [1]. Relying on fossil fuels may partly solve this issue from an energy supply perspective; however, it will further escalate the environmental crisis via enormous CO₂ release and that of other harmful emissions such as NO_x and SO_x [2]. The use of hydrogen as a carbon-free energy carrier is a promising solution, offering a sustainable energy system [3]. Hydrogen is potentially the most sustainable and cleanest transportation fuel [4, 5] and is already used in fuel cells. It produces no pollutants nor greenhouse gases while having a high energy capacity [5]. The primary advantage of hydrogen is that it can be transported and stored with minor losses using the current chemical fuel infrastructure with some modifications [6], making a smooth transition from fossil fuels possible. Nowadays, the majority of hydrogen, c.a. 95%, is produced from fossil fuels via processes like methane

reforming, coal gasification, etc. [7] and is known as grey hydrogen. These processes are not environmentally friendly, use fossil fuels and contribute to significant CO₂ emissions, so that the hydrogen obtained in this way is unsustainable.

The solar energy arriving at the earth's surface every hour is enough for one year of global consumption [2]. The photocatalytic (solar) production of hydrogen is regarded as a cost-efficient and sustainable approach for hydrogen production that enables harvesting of sunlight and long-term storage of the most abundant and renewable energy source available [2, 3, 8]. Since the first publication from Fujishima and Honda [9] on photolytic water splitting using titanium dioxide (TiO₂), there has been significant research on solar hydrogen production, and it is well-reviewed [2, 3, 5-7, 10]. Among the different photocatalytically active materials, TiO₂ shows superiority for solar hydrogen production due to its unique properties, including high chemical stability, non-toxic nature, environmental compatibility, availability, and low cost [3, 5, 10]. However, TiO₂ suffers from a wide bandgap, which is larger than 3 eV for its different crystal structures, making absorption and utilization of UV light dominant rather than absorption of visible light [2, 11]. It also suffers from significant electron-hole recombination, reducing its photocatalytic efficiency [3].

There are several approaches to improve the photocatalytic efficiency of TiO₂, which mainly focus on bandgap narrowing to activate it for visible light and enhance the electro-hole separation [3, 5]. Doping non-metal dopants like nitrogen, sulfur, and phosphorous, and surface decoration/doping using metal/metal oxide nanoparticles (NPs) such as copper, iron, silver, gold, and platinum are some of the more widely studied attempts to improve the photocatalytic activity of TiO₂ [2, 3, 5]. Additionally, self-doping of TiO₂ by Ti³⁺ also improves its photo-activity for hydrogen production [12-14]. Among these photocatalytic activity promoters, copper is a promising candidate for promoting solar hydrogen production due to its low cost, narrow bandgap, and comparable cocatalyst activity to expensive promoters such as gold and silver [3]. Copper oxide is a narrow bandgap p-type semiconductor that, in combination with the n-type TiO₂, improves its visible light absorption and produces a p-n junction, enhancing the overall photocatalytic activity toward hydrogen production [3, 15-22].

The promotional effects in the cocatalyst-promoted TiO₂ systems are well studied, and numerous attempts have been made to describe the effect of cocatalyst loading on the photocatalytic activity of TiO₂, suggesting the existence of an optimum point for cocatalyst loading [23-28]. A fundamental understanding of the correlation between the cocatalyst particle size/loading and the photocatalytic activity of the photocatalyst will pave the way for the design, development, and large-scale production of a high-performance photocatalyst. Recently, Mills et al. [29] developed a model which they term "expanding photocatalytic area and overlap (EPAO)" based on the previously developed metal support interface (MSI) model by Bowker et al. [30] to describe the relationship between the hydrogen production rate and the cocatalyst loading during photocatalytic methanol reforming. The EPAO model is built upon six assumptions [29] and is validated for Pd/TiO₂ and Pt/TiO₂ systems, suggesting that hydrogen production rate is proportional to the total photocatalytically active area surrounding the cocatalyst particle; it also suggests that the overlap of these active areas at high coverage results in a drop in hydrogen production. The EPAO model makes the quantification of the relation between the cocatalyst loading and the photocatalyst activity possible. In this paper, we seek to further improve the EPAO model using copper oxide modified TiO₂ where copper oxide is deposited by atomic layer deposition.

Developing an insightful understanding that can lead us to a precise model to describe the correlation between the cocatalyst particle size/loading and the photocatalytic activity requires a set of catalysts with a well-defined structure. Such catalysts are usually developed for surface science studies on single crystal flat substrates; however, translating those systems into real catalytic systems is quite challenging. On the other hand, a catalyst prepared using the conventional liquid phase methods such as impregnation and precipitation lacks such a well-defined structure [31, 32]. Atomic layer deposition

(ALD) is a leading method for synthesizing well-defined advanced functional nanomaterials and can be employed to surmount this issue. As an excellent technique for supported NPs synthesis, ALD makes the precise deposition of well-controlled particles in terms of size and composition possible; it also allows controlling the amount of material deposited on the substrate at the atomic level [31, 33-35]. The possibility of depositing uniform NPs on the support with controlled size, shape, and morphology using ALD provides an excellent opportunity to obtain high-activity photocatalysts with a well-controlled structure.

In this work, we aim to elucidate the correlation between the cocatalyst particle size/loading of Cu_xO on TiO_2 and the photocatalytic activity during solar hydrogen production. We employed ALD to deposit Cu_xO NPs on AEROXIDE® P25 TiO_2 NPs with precise control over loading and Cu_xO particle size. The obtained samples were used as photocatalysts for the solar production of hydrogen from methanol reforming, showing superior hydrogen productivity compared to pristine TiO_2 . The XPS analysis revealed Ti^{4+} reduction to Ti^{3+} after copper ALD, with an initial linear trend with copper loading, and plateauing of Ti^{3+} content at about 2.3 wt.% of copper. This is the copper content at which hydrogen productivity is maximum. The modified EPAO model was validated using these results with a good fit. The model indicates the development of a photocatalytically promoted area (PPA) around Cu_xO clusters, revealing a dual promotional effect of ALD grown Cu_xO clusters: increased charge carrier separation and improved light absorption, known for copper promoted TiO_2 photocatalysts, and generation of a substantial amount of surface Ti^{3+} , leading to self-doping of TiO_2 . Complementary first-principles density functional theory (DFT) simulations are also utilized to understand the interaction of Cu_xO clusters with the TiO_2 support and assess the origin of titanium and copper oxidation states. The DFT results align with our experimental observations, indicating the stabilization of Cu_xO clusters on TiO_2 , and a partial reduction of Ti^{4+} to Ti^{3+} due to the interaction of Cu_xO clusters with TiO_2 .

Experimental

Materials

Evonik P25 powder (Evonik Industries - Hanau, Germany), containing TiO_2 NPs with an average diameter of ~ 21 nm and a specific surface area of ~ 50 $\text{m}^2\cdot\text{g}^{-1}$, was employed as substrate for copper deposition. Copper (I) hexafluoropentanedionate-vinyltrimethylsilane (Cu(I)(hfac)(TMVS)) complex was purchased from Advanced Tech. & Ind. Co., Ltd, and used as the CuO_x precursor.

Atomic layer deposition of copper (I/II) oxide

The $\text{CuO}_x/\text{TiO}_2$ samples were synthesized following the procedure described in our previous work [36]. In summary, a vibration-assisted fluidized bed reactor [34, 37] operating at atmospheric pressure was employed to deposit Cu_xO ultrafine clusters on P25 NPs. Cu(I)(hfac)(TMVS) evaporated at 60 $^\circ\text{C}$ was delivered to the ALD reactor, heated up to 250 $^\circ\text{C}$ using an IR lamp, while water evaporated at room temperature was used as the second reactant. Nitrogen (99.999 vol.%) was used as the carrier gas to deliver ALD reactants and purge the reactor. Typically, 1.5 g of TiO_2 powder was fluidized using 0.5 $\text{L}\cdot\text{min}^{-1}$ nitrogen stream (superficial gas velocity of ~ 1.7 $\text{cm}\cdot\text{s}^{-1}$); and a combination of different pulse times of Cu(I)(hfac)(TMVS) and water, and different ALD cycle numbers were employed to obtain Cu_xO particles on TiO_2 with a well-controlled control particle size. **Table 1** summarizes the details of the synthesis condition used to prepare the different samples in this study.

Table 1. The ALD synthesis parameters, used for Cu_xO ALD on P25 TiO_2 nanopowder.

Sample	Cu(I)(hfac)(TMVS) pulse (min)	Purge 1 (min)	Water pulse (min)	Purge 2 (min)	Number of cycles
1	2.5	5	10	5	10
2	5	5	5	5	10
3	5	5	10	5	10

4	10	5	2.5	5	10
5	10	5	10	5	10
6	5	5	5	5	20
7	30	5	10	5	10

Characterization

The copper loading on ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples was analyzed using inductively coupled plasma – optical emission spectrometry (ICP-OES) method employing a PerkinElmer Optima 5300 DV ICP-OES instrument. Typically, about 25 mg of sample was digested in 4.5 ml 30% HCl+1.5 ml 65% HNO_3 + 0.2 ml 40% HF while microwave irradiation. The digestion time in the microwave was 60 min at maximum power. The digested samples were diluted to 50 ml with Milli-Q water prior to measurement.

The transmission electron microscopy (TEM) images of the ALD deposited Cu_xO clusters on P25 TiO_2 were acquired using a JEOL JEM1400 microscope operating at a voltage of 120 kV working in bright-field mode. The $\text{Cu}_x\text{O}/\text{TiO}_2$ particles were dispersed in ethanol via sonication in an ultra-sound bath and transferred onto Quantifoil copper TEM grids (coated with perforated carbon). The particle size of individual particles was measured using ImageJ software. The average particle size and particle size distribution (PSD) curves were obtained using the size of more than 350 individual particles measured using ImageJ.

The surface chemistry of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples was studied using a Thermo Scientific™ K-Alpha™ X-ray photoelectron spectrometer. The monochromated X-ray with a spot of 400 μm was generated using aluminum $\text{K}\alpha$ radiation (photon energy of 1486.7 eV), and the differential charging was compensated using a flood gun. A step size of 0.1 eV was used for acquiring the high-resolution scans. The CasaXPS software was employed to analyze the obtained XPS spectra, and the positions of peaks were calibrated using the aliphatic carbon 1s peak (284.8 eV).

Photocatalytic hydrogen evolution reaction

The photocatalytic hydrogen evolution reaction (HER) activity of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples was evaluated using a photocatalytic setup described in detail elsewhere [8]. The $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalyst samples were suspended ($0.2 \text{ g}\cdot\text{L}^{-1}$) in a 10% v/v methanol in water solution. A custom-made Pyrex reactor with quartz window with a total volume of 42.1 mL, including 17.1 mL headspace and equipped with a water jacket, was employed for photocatalytic HER evaluation under UV-Visible light generated using a 500 W Xe/Hg lamp (66983, Newport) without an optical filter. The produced hydrogen was quantified using a CP 9001 gas chromatograph (GC, Chrompack). Typically, the suspension of photocatalyst in methanol-water solution was placed in the photoreactor, and the headspace of the photoreactor was purged with $10 \text{ mL}\cdot\text{min}^{-1}$ Argon flow for 30 min under dark condition; after deoxygenating the headspace of the photoreactor, the Argon flow was reduced to $1 \text{ mL}\cdot\text{min}^{-1}$ to carry the headspace gas to GC sampling loop. The photoreactor was kept under dark condition for 1 hour while the headspace gas was analyzed using GC, then the photoreactor was illuminated for 20 hours while the HER products were analyzed using GC with 30 min injection intervals. The temperature of the photoreactor was kept at 27 °C, and the photocatalyst was kept suspended in the solution via magnetic stirring.

DFT simulations

We performed periodic plane wave density functional theory calculations of the (101) surface of anatase TiO_2 that is modified with Cu and CuO as a model for the Cu/ CuO_x -modified anatase system using the VASP5.3 code [38, 39]. A kinetic energy cut-off of 400 eV is used. The core-valence interaction is described with projector augmented wave (PAW) potentials [40, 41], with 4 valence electrons for Ti, 6 for O, and 17 for Cu. The Perdew-Burke-Ernzerhof approximation to the exchange-correlation functional was used [42]. The anatase (101) substrate was modeled as a 4 O-Ti-O trilayer slab, with a

(4×4) surface supercell expansion ($a = 21.776 \text{ \AA}$, $b = 15.104 \text{ \AA}$) and a vacuum gap of 16 \AA . This is the lowest energy surface of anatase TiO_2 . Due to the size of the surface supercell expansion, Γ -point sampling was used, and the convergence criteria for the energy and forces were 10^{-4} eV and 0.02 eV/\AA . All calculations were spin-polarized, and there were no symmetry constraints applied. Hubbard U corrections were implemented, with $U(\text{Ti}) = 4.5 \text{ eV}$, to consistently describe the partially filled 3d state in reduced Ti^{3+} [43, 44]. Cation oxidation states were determined from Bader charge analysis and spin magnetizations. To model the different surface modifications, we build the following models: Cu_{20} cluster on anatase (101), $\text{Cu}_{10}\text{O}_{10}$ on anatase (101), 2 Cu_{10} nanoclusters on anatase (101), and reduced CuO nanoclusters (by removing oxygen from CuO). The energy gain, E^{ads} , when the Cu or CuO nanocluster is adsorbed on the anatase (101) surface, is computed from

$$E^{\text{ads}} = E(\text{CuO}_x@\text{TiO}_2) - [E(\text{CuO}_x) + E(\text{TiO}_2)] \quad (1)$$

Where $E(\text{CuO}_x)$ is the energy of the free copper ($x = 0$) or CuO nanocluster, $E(\text{TiO}_2)$ is the energy of the bare anatase (101) slab and $E(\text{CuO}_x\text{-TiO}_2)$ is the energy of the Cu/ CuO_x nanocluster interfaced with the anatase (101) slab.

The formation energy for oxygen vacancies in CuO_x is

$$E^{\text{ads}} = [E(\text{CuO}_{x-\delta}@\text{TiO}_2) + \frac{1}{2} E(\text{O}_2)] - E(\text{CuO}_x\text{-TiO}_2) \quad (2)$$

Where $E(\text{CuO}_{x-\delta}@\text{TiO}_2)$ is the energy of the CuO nanocluster with an oxygen vacancy interfaced with anatase (101), $E(\text{CuO}_x\text{-TiO}_2)$ is the energy of the CuO_x nanocluster interfaced with the anatase (101) slab, and $E(\text{O}_2)$ is the energy of the free O_2 molecule. The use of O_2 as a reference is common in oxide vacancy formation energy calculations and the δ in Eqn. (2) signifies CuO_x with removed oxygen.

Results and discussions

We employed ALD synthesis to attain good control over the cocatalyst particle size and dispersion in a wide range of copper loading and obtain a set of well-defined photocatalysts to investigate the correlation between the cocatalyst particle size/loading and the photocatalytic activity. The ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts were characterized using ICP-OES, TEM, and XPS methods and were employed for solar hydrogen production as photocatalysts during methanol reforming. DFT simulations also were carried out to develop a better understanding of the interaction of Cu_xO clusters with TiO_2 . The obtained results demonstrated the dual promotional effect of ALD deposited Cu_xO clusters and helped us modify the EPAO model and quantitatively approximate the surface coverage of photocatalytically promoted area by Cu_xO clusters and correlate it to Ti^{3+} content on the surface of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples.

Physiochemical properties of $\text{CuO}_x/\text{TiO}_2$ photocatalysts

The ALD deposition of p-type Cu_2O film using Cu(I)(hfac)(TMVS) and water at atmospheric pressure is previously reported by Muñoz-Rojas et al. [45]; additionally, we recently reported the self-limiting behavior and ALD deposition of ultra-fine Cu_2O clusters on P25 TiO_2 NPs using a fluidized bed reactor operating at atmospheric pressure [36]. Using the same procedure and applying different precursor/co-reactant pulse times (**Table 1**), we aimed to control the size of Cu_xO clusters. The ICP-OES analysis indicated copper weight loading in the range of about 1 – 5 %; the exact values are given in **Table 2**. The TEM images revealed highly dispersed ultra-fine Cu_xO clusters deposited on P25 nanopowder with well-controlled size (**Figure 1**). The PSD analysis demonstrates narrow size distribution for samples with copper content below 3.8 wt. % (**Figure S3**); while the PSD of the samples with 4.40 and 4.85 wt. % copper becomes wider and right-skewed. Interestingly, the samples with copper content up to 3.8 wt. % have almost the same average Cu_xO size, i.e., $\sim 1.7 \text{ nm}$ (**Table 2** and **Figure 2**). The almost constant Cu_xO particle size trend, shown in **Figure 2**, for the samples with copper content below 3.80 wt. %, which obviously can be seen in TEM images (**Figure 1** and **Figure S3**), suggests that the Cu_xO

nucleation is dominant until this loading. Therefore, in copper content below 3.80 wt. %, further copper added to the surface results in new grown Cu_xO clusters. At copper content higher than ~ 3.80 wt. %, the increase of the number of small Cu_xO clusters, and consequently the decrease of distance between them, changes the dominant mechanism from nucleation to particle diffusion and coalescence, resulting in particle size growth and the decrease of the number of particles, since some small particles merge and form larger ones [46, 47]. The decrease of the population of Cu_xO clusters and their growth can be seen in **Figure 1** for samples with the copper content of 4.40 and 4.85 wt. %. The right-skewed PSD graph of these samples (**Figure S3**) also indicates that the dominant growth mechanism for these samples is particle diffusion and coalescence [46, 47].

Table 2. The copper content of the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples, obtained by ICP-OES analysis and the average copper particle size obtained by TEM imaging.

Sample	Copper loading (wt. %)	Average copper particle size (nm)
1	1.19	1.6 ± 0.5
2	1.68	1.5 ± 0.4
3	2.28	1.7 ± 0.4
4	3.08	1.8 ± 0.4
5	3.79	1.7 ± 0.5
6	4.40	2.6 ± 0.7
7	4.85	2.7 ± 1.0

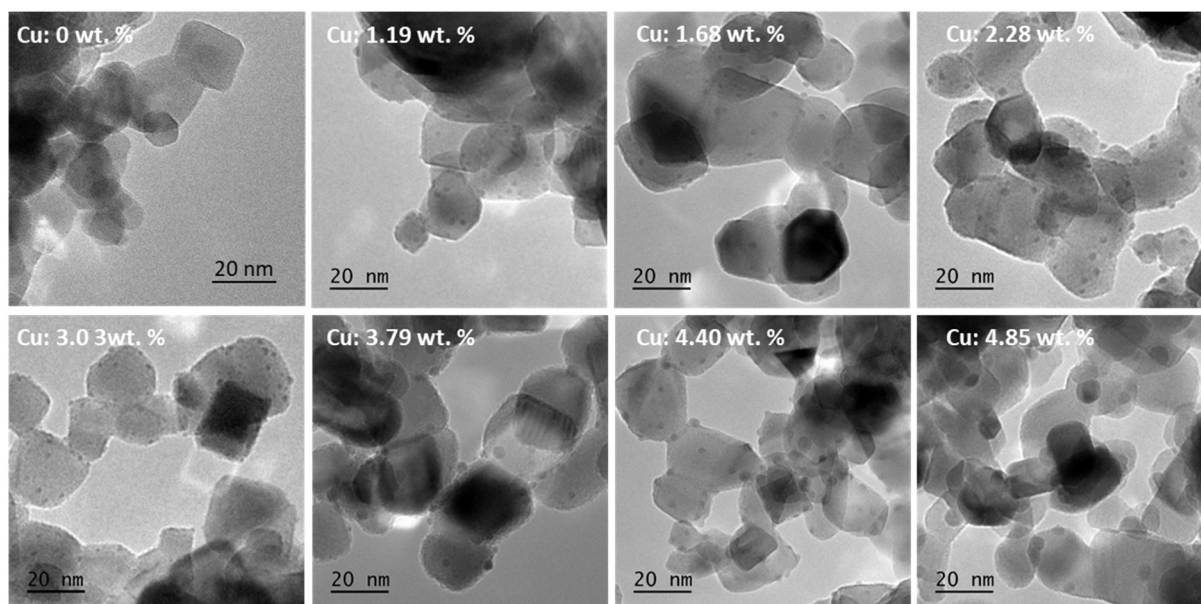


Figure 1. The TEM images of pristine P25 TiO_2 nanopowder the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples with different copper content.

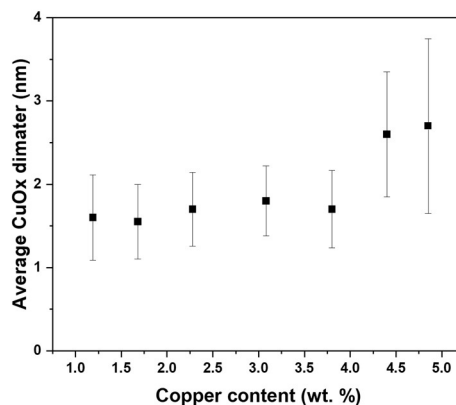


Figure 2. The average Cu_xO particle size as a function of copper loading.

The surface chemistry of the samples and the changes of P25 support upon Cu_xO ALD were studied using XPS analysis. Since the average Cu_xO particle size observed using TEM images for all studied samples is below 4 nm (**Figure 2**), the XPS spectra acquired for copper can be assumed as the representative of entire Cu_xO clusters, and it could be employed for describing the bulk of Cu_xO clusters. **Figure 3** shows the high-resolution copper 2p spectra obtained for ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples. The different copper species reveal 2p spectra with ~ 19.75 eV spin-orbit splitting, which the $2p_{3/2}$ peak is commonly used for quantification. The metallic copper (Cu^0) and Cu^{1+} in Cu_2O reveal a nearby $2p_{3/2}$ peak at binding energies of 932.6 eV and 932.4 eV for Cu^0 and Cu^{1+} , respectively, which makes the distinction of these two species difficult using XPS. The use of LMM Auger peak is a more efficient solution for identification/quantification of Cu^0 and Cu^{1+} ; however, due to overlap of this spectral region with titanium 1s binding energy, we cannot employ LMM Auger spectra for this purpose [48]. Considering the average size of the ALD synthesized Cu_xO clusters (~ 2 nm or smaller) and the oxidative condition of the synthesis process, it is reasonable to assume that the deposited copper is oxidized to some degree and the ALD prepared samples are Cu^0 free. On the other hand, Cu^{2+} of CuO with a distinct $2p_{3/2}$ peak at 933.6 eV is easily distinguishable. The Cu^{2+} species also reveal a shake-up satellite peak in the binding energy range of 940 – 945 eV for $2p_{3/2}$ [49]. The range that satellite peaks may appear for different copper species is marked in **Figure 3**. The copper 2p XPS spectra of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples in **Figure 3** indicate that the majority of copper in the sample with low copper content is Cu^{1+} , and the Cu^{2+} content becomes clearly detectable in the case of the sample with the copper content of 2.28 wt. % or higher, depicting distinguishable satellite peaks and the main $2p_{3/2}$ peak around 933.6 eV.

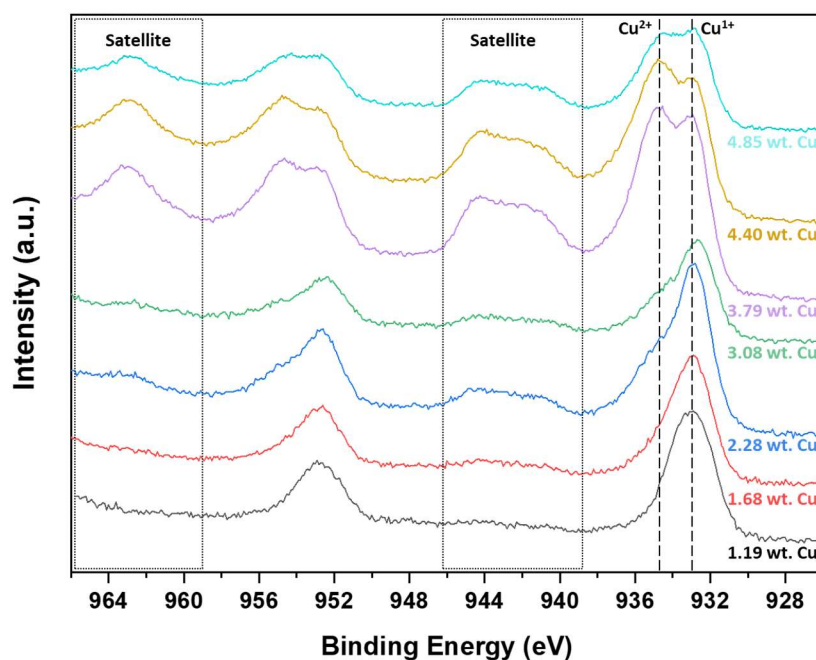


Figure 3. The copper 2p spectra of the fresh ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples.

The contribution of Cu^{1+} and Cu^{2+} to the $\text{Cu } 2p_{3/2}$ spectra was calculated using the method that Biesinger has proposed [49]. The $\text{Cu } 2p_{3/2}$ peak and the corresponding satellite peak were carefully deconvoluted (**Figure S4**); each sample's Cu^{1+} and Cu^{2+} content was calculated by considering the ratio of the area of the main peak of CuO (Cu^{2+}) to the shake-up peak area equal to 1.89. The calculated oxidation states enabled us to calculate the average oxidation of copper in the $\text{Cu}_x\text{O}/\text{TiO}_2$ samples and consequently approximate the Cu_xO loading of each sample using equation **S4**; for the details of calculations, please refer to the electronic supporting information. **Table 3** summarizes the results of these calculations. These results suggest that the Cu^{1+} is the most likely oxidation state for ultra-fine Cu_xO clusters, and the increase of Cu_xO particle size increases the Cu^{2+} content. Fang et al. [50] reported that the strong interaction of CuO_x and TiO_2 stabilizes the Cu_2O species on TiO_2 . Accordingly, we can infer that the smaller Cu_xO clusters have a stronger interaction with TiO_2 , resulting in higher Cu^{1+} content in low copper loading. The higher copper loading results in larger Cu_xO clusters with increased Cu^{2+} content, suggesting less interaction with the support.

Table 3. The different copper oxidation states, average copper oxidation state, and approximate Cu_xO loading, calculated using XPS analysis.

Sample	Copper loading (wt. %)	Cu^{1+} content (%)	Cu^{2+} content (%)	Average copper oxidation state	Calculated CuO_x loading (wt. %)
1	1.19	89.6	13.4	1.13	1.36
2	1.68	74.9	25.1	1.25	1.94
3	2.28	55.0	45.0	1.45	2.7
4	3.08	54.7	45.3	1.45	3.64
5	3.79	8.6	91.4	1.91	4.72
6	4.40	12.0	88.0	1.88	5.44
7	4.85	23.1	76.9	1.77	5.93

The quantification of the high-resolution titanium 2p spectra of pristine P25 TiO_2 nanopowder and the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples depicted intriguing trends in the oxidation state of titanium species (**Figure 4**). The different titanium species were identified based on the recent work of Biesinger et al. [49], and the percentage of each oxidation state was calculated by normalizing the $2p_{3/2}$ peak area

of each species to the peak area of the entire $2p_{3/2}$ (**Figure S5**). As is shown in **Figure 4**, the pristine P25 TiO_2 powder mainly contains Ti^{4+} (ca. 90 %); however, the Ti^{4+} content decreases drastically upon ALD of Cu_xO onto TiO_2 , and consequently, the Ti^{3+} increases. Whilst the Ti^{2+} content seems to be independent of copper loading and remains constant. The decrease of Ti^{4+} and increase of Ti^{3+} plateaus at copper content higher than 2.28 wt.%.

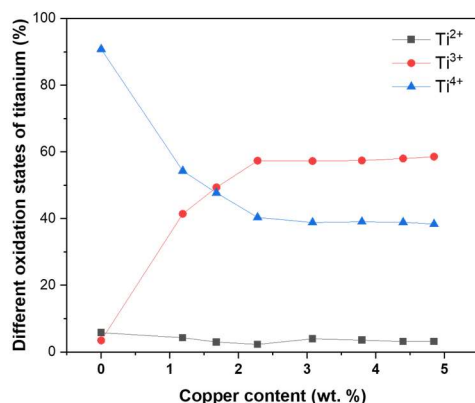


Figure 4. The different titanium oxidation states as a function of copper weight loading in fresh $\text{Cu}_x\text{O}/\text{TiO}_2$ samples.

The drastic change of Ti^{4+} and Ti^{3+} content after ALD of Cu_xO clusters indicates the surface modification of P25 during ALD of Cu_xO and a strong interaction between the titanium oxide and copper oxide phases in these samples. This interaction facilitates charge transfer between Cu_xO and TiO_2 [15, 20, 50, 51], leading to Cu^{2+} incorporation into TiO_2 structure and Ti^{4+} reduction to Ti^{3+} ; it also stabilizes the Cu_2O species on TiO_2 [50-52]. Recently, Huang and co-workers inferred for an incipient wetness impregnation synthesized $\text{CuO}_x\text{-TiO}_2$ system that this strong interaction increases the dispersion of Cu_2O , consequently the intensity of $\text{Cu}_2\text{O-TiO}_2$ heterojunction, which is active in photocatalytic hydrogen production [15]. It is also reported that the formation of Ti^{3+} efficiently hampers the recombination of photogenerated electrons/holes [53]. Considering the nature of the ALD synthesis, which proceeds via chemisorption of precursors onto the substrate, a stronger interaction between the ALD deposited copper add atoms and TiO_2 substrate is expected than the conventionally impregnated CuO_x NPs; the chemisorption of ALD precursor on the surface and its dissociation can modify the P25 surface. The surface study of the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples (**Figure 4** and **Figure S5**) demonstrates such surface modification and strong interaction, suggesting that the outmost layer of TiO_2 particles is dominated with Ti^{3+} species due to the strong interaction of highly dispersed ALD deposited Cu_xO clusters and TiO_2 .

First Principles Density Functional Theory Simulations of $\text{Cu}/\text{Cu}_x\text{O-TiO}_2$

In addition to XPS analysis, we performed DFT simulations to understand better the interactions and oxidation states of the $\text{Cu}_x\text{O}/\text{TiO}_2$ system. A Cu_{20} cluster deposited on the anatase (101) surface was the first studied case. **Figure 5** (a) and (b) show the atomic structure of this system. We can see the formation of new Cu-O bonds between Cu and surface oxygen, with Cu-O distances of 1.82, 1.97, and 2.10 Å. The energy gain when the Cu nanocluster adsorbs on the anatase (101) surface is -5.13 eV, indicating a very strong interaction at the TiO_2 support. Examining oxidation states, two surface Ti cations are reduced to Ti^{3+} , with computed Bader charges of 1.72 electrons (compared to 1.32 electrons for Ti^{4+} cations). As a result, two Cu atoms are oxidized to Cu^+ , with computed Bader charges of 16.6 and 16.7 electrons, compared to 17 for metallic copper.

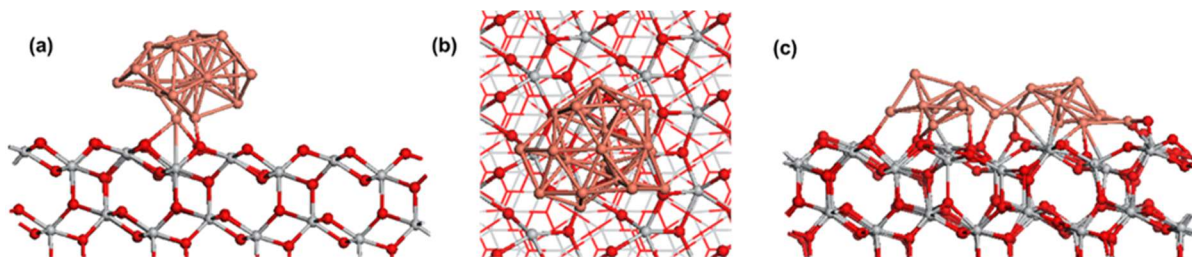


Figure 5. (a), (b): side and top views of the atomic structure of Cu₂₀ nanocluster adsorbed at anatase (101), (c): relaxed atomic structure of two initially separated Cu₁₀ nanoclusters on anatase (101). Colour coding: Grey spheres represent Ti, red spheres represent O and pink spheres represent Cu.

Given the preference for copper clusters to aggregate into larger species with increased coverage, we compared the Cu₂₀ nanocluster with two initially separated Cu₁₀ nanoclusters on the same anatase (101) surface, and the final structure is shown in **Figure 5-c**. After relaxation, we see that the two clusters have aggregated, with the clear formation of Cu-Cu bonds between the two clusters, even for a 0K relaxation. Examining the oxidation states of the metal cations, we see 11 reduced Ti³⁺ cations, with computed Bader charges between 1.56 and 2.0 electrons. Copper atoms that directly bind to the anatase surface are oxidized to Cu²⁺ and Cu⁺, with computed Bader charges between 16.2 and 16.4 electrons for Cu²⁺ and 16.5 electrons for Cu⁺.

For pure copper metal, we would therefore expect that aggregation into larger clusters will be promoted, reducing dispersion while Cu²⁺, Cu⁺, and Cu⁰ oxidation states will be present. This is not consistent with the finding of Cu¹⁺ and Cu²⁺ oxidation states dominating after ALD, and we, therefore, examine oxidized Cu nanoclusters interfaced with anatase (101).

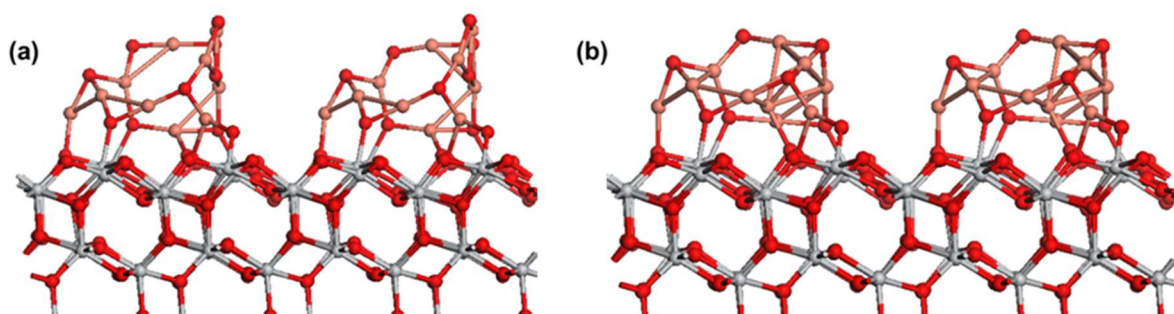


Figure 6. Atomic structure of two Cu_xO nanoclusters adsorbed on anatase (101). (a): Cu₁₀O₉ (b): Cu₁₀O₇ stoichiometries. Colour coding: Grey spheres represent Ti, red spheres represent O and pink spheres represent Cu.

Figure 6 shows the atomic structure of two CuO-derived nanoclusters supported on anatase (101). Similar to Cu-anatase (101), we explored the fate of two separated CuO nanoclusters, and after relaxation, we find that they do not aggregate, which is in contrast to pure copper nanoclusters, however, in agreement with our observation for stable Cu_xO particle size for a wide range of copper content (**Figure 2**).

In exploring the chemical state of adsorbed CuO, we investigated the removal of oxygen (one from each cluster), and we found that the loss of the first oxygen vacancy (**Figure 6-a**) is favorable with a negative energy change of -0.2 eV. Although the energy cost to form the next oxygen vacancy is positive, it is only +0.06 eV, which suggests this will form. The third O vacancy, **Figure 6-b** has an energy cost of +1.24 eV per O vacancy, so this is the reduced from the CuO_x-modified TiO₂, with stoichiometry Cu₁₀O₇.

Examining the oxidation states, we see the formation of partially reduced Ti^{3+} cations, with computed Bader charges of 1.40 electrons. In the CuO_x , both Cu^{1+} and Cu^{2+} are present, with Bader charges of 10.2 – 10.3 for Cu^{2+} and 10.5 for Cu^{1+} . These results agree with our experimental observations from XPS analysis, confirming the TiO_2 surface modification upon Cu_xO ALD and the strong interaction of Cu_xO clusters with TiO_2 , leading to Ti^{4+} reduction to Ti^{3+} .

Solar hydrogen production

The solar hydrogen productivity of ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples were evaluated and compared with pristine P25 TiO_2 nanopowder (**Figure 7** and **Figure S6**). As **Figure 7** shows, the Cu_xO ALD significantly increases the hydrogen activity of photocatalysts by one order of magnitude compared to pristine P25 TiO_2 , with about 11 times more hydrogen production for the sample with 2.28 wt. % copper. Such remarkable activity improvement can be attributed to the co-existence of Cu^{1+} and Ti^{3+} species in $\text{Cu}_x\text{O}/\text{TiO}_2$ samples, demonstrated using XPS analysis. The band edge potentials of Cu^{1+} and Cu^{2+} are sufficiently reductive to drive the HER reaction [2]; additionally, both Cu^{1+} and Cu^{2+} are narrow bandgap p-type semiconductors with a bandgap of 1.7 eV and 2.1 eV, respectively [54]. Copper (I/II) oxide deposition on TiO_2 can narrow the bandgap of the $\text{Cu}_x\text{O}-\text{TiO}_2$ system and increase the sunlight utilization, resulting in enhanced photocatalytic activity. Valero et al. suggested that the highly dispersed Cu^{2+} species are directly related to high hydrogen productivity [22]. Furthermore, it is demonstrated that the $\text{CuO}_x-\text{TiO}_2$ undergoes an in-situ reduction/restructuring under solar radiation, resulting in $\text{Cu}_2\text{O}-\text{TiO}_2$ formation, revealing the Cu_2O is the active copper species in $\text{CuO}_x-\text{TiO}_2$ photocatalysts [3, 16, 17, 21, 22, 55]. The Cu^{2+} species usually reduce to Cu^{1+} or Cu^0 under light radiation, acting as the effective cocatalysts for the water reduction reaction.

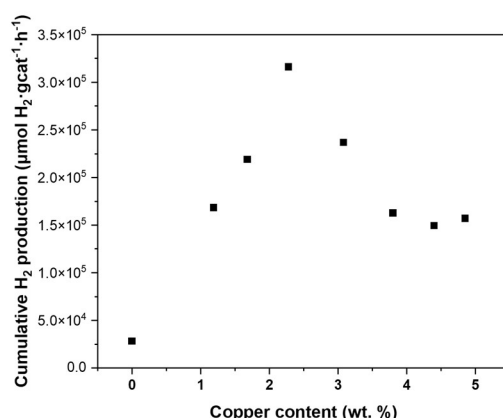


Figure 7. The cumulative hydrogen production after 20 hours of reaction as a function of copper loading in $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts.

The interfacial interaction between the Cu_xO (p-type semiconductor) with TiO_2 (n-type semiconductor) forms a heterojunction (Schottky junction) which results in charge transfer and separation between Cu_xO and TiO_2 [15, 19, 20, 50, 51, 56]. Such strong interaction and charge transfer can reduce Ti^{4+} to Ti^{3+} , which is demonstrated using XPS analysis (**Figure 4**) and DFT simulations. It is suggested that the formation of surface Ti^{3+} species has a great contribution to the photocatalytic activity of $\text{Cu}_2\text{O}-\text{TiO}_2$ photocatalyst [53]; Ji et al. [57] suggested that the surface Ti^{3+} species significantly promote the H-free radical production, which is responsible for enhancing hydrogen production. It is also demonstrated that Ti^{3+} extends the photocatalytic activity of TiO_2 from UV to visible light, increasing its hydrogen generation rate [12-14]. This suggests that the drastic increase of Ti^{3+} content on the $\text{Cu}_x\text{O}/\text{TiO}_2$ samples surface is the second promotional effect of ALD of Cu_xO clusters on hydrogen production in addition to the known effect of CuO_x clusters: the increased visible light absorption, and charge carrier separation [3]. Accordingly, we infer that the ALD grown Cu_xO clusters on TiO_2 have a

dual promotional effect on photocatalytic hydrogen production. The copper content that the highest hydrogen productivity is observed (**Figure 7**) coincides with the copper content at which the Ti^{3+} content plateaus (**Figure 4**). This unveils a better picture of the relation between the surface Ti^{3+} content and the hydrogen productivity of $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts.

Modified expanding photocatalytic area and overlap model

The characterization of the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts unveils the dual promotional effect of ALD deposited Cu_xO clusters; furthermore, it reveals the characteristics which are previously identified as the properties of a photocatalyst that is appropriately promoted with copper. These characteristics include highly dispersed Cu_xO particles with a significant amount of Cu^{1+} content and a considerable amount of Ti^{3+} content due to the strong interaction of ALD grown Cu_xO clusters and TiO_2 . Such properties resulted in a highly active photocatalyst for HER reaction, with a minimum of 5 times more hydrogen production than pristine P25 TiO_2 for $\text{Cu}_x\text{O}/\text{TiO}_2$ samples (**Figure 7** and **Figure S6**). Beyond the significantly increased solar hydrogen production of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples, an intriguing trend in hydrogen productivity of ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts is observable. **Figure 7** indicates a linear increase of hydrogen productivity by increasing copper weight percent until a pinnacle at a copper content of 2.28 wt. %, then it declines and plateaus afterward. On the other hand, the surface Ti^{3+} content of these samples increases with almost a linear trend and plateaus at the copper content of 2.28 wt. % (**Figure 4**). Furthermore, the PSD of Cu_xO clusters becomes wider by the increase of copper content (**Figure S3**), and their particle size starts growing at copper content higher than 4.40 wt. % (**Figure 2**). This suggests a direct relation between the photocatalytic activity of $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalyst and its Ti^{3+} content, copper oxide loading, and copper oxide particle size. We modified the EPAO developed by Mills et al. [26] to quantify this relation.

The EPAO model [29] is a kinetic model based on the previous metal support interface (MSI) model of Bowker et al. [30]. The EPAO model describes the relationship between the cocatalyst weight loading and hydrogen production rate during photocatalytic methanol reforming using six main assumptions. These assumptions are described in detail in the original work [29]. The model assumes that the metal particles deposited on TiO_2 support (for a Pt/TiO_2 system) form an electric field with the surrounding TiO_2 , resulting in a photocatalytically active circular area around the particle whose radius is a simple linear function of the radius of the metal particle. They also assumed that the number of metal particles is constant, and their size grows by increasing metal loading. Based on the insight obtained into our ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts, we modified the original EPAO model via more realistic assumptions and adapted it with our observations; however, the main assumptions of this model are maintained. These new assumptions of the modified EPAO (M-EPAO) model are based on the characteristics of the ALD synthesized $\text{Cu}_x\text{O}/\text{TiO}_2$ samples, making it a more realistic model; the four new assumptions are as below:

- i. The number of cocatalyst islands depends on the cocatalyst loading and the dominant stage of the nucleation and growth processes. During the nucleation stage, the number of islands increases, while when the growth becomes dominant, the number of the particles may remain constant or decrease, depending on the governing mechanism.
- ii. The average size of cocatalyst islands remains constant during the nucleation stage, and it increases during the growth stage.
- iii. The increase of hydrogen production rate ($r(\text{H}_2)$) stems from the rise of the number of cocatalyst islands in the cocatalyst loading range in which the nucleation is dominant, leading to an increase of photocatalytically promoted area.
- iv. The heterojunction of cocatalyst/support (p-n junction in our case) and their strong interaction leads to the formation of a depletion zone (area) around the cocatalyst particles. As long as these areas do not overlap much, their extension increases the hydrogen production rate ($r(\text{H}_2)$).

Like the original EPAO model, the M-EPAO model assumes that each cocatalyst particle creates a photocatalytically promoted area (PPA) around it (a depletion zone), which its radius is a linear function of the radius of the cocatalyst particle. As **Figure 8** illustrates, the M-EPAO model consists of three stages. In the first stages, due to the low population of the cocatalyst particles on the surface, the distance between the particles is long, and the PPA does not overlap. At this stage, the increase of copper oxide loading and consequently growth of new cocatalyst clusters on the surface increases the PPA, resulting in increased hydrogen production. The photocatalyst activity will increase by the increase of cocatalyst content until the point that the PPA of individual clusters starts overlapping due to the increasing number of particles (near the maximum activity copper content). This stage describes the ascending part of **Figure 7**.

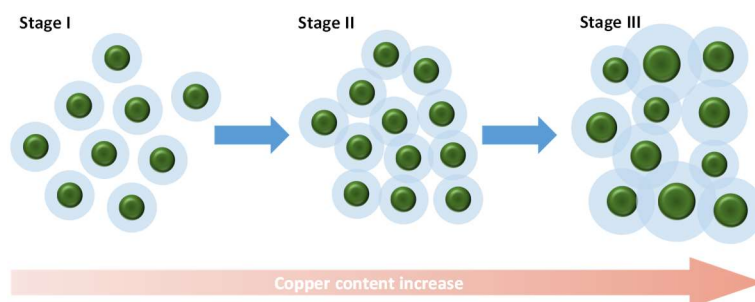


Figure 8. The schematic representation of three stages in the M-EPAO model.

The overpopulation of cocatalyst clusters and overlap of PPA marks the decay of activity of the photocatalyst as a function of the cocatalyst loading. The photocatalytic activity decay resulting from PPA overlap can be attributed to local depletion of the reaction intermediates on the catalyst surface, which has a strong negative effect on the reaction rate in the case of densely spaced surface islands [58]. The overlap of PPA also results in interference of the electrical field around the cocatalyst particles and reduces the electron-hole separation efficacy [29, 56]. The negative effect of PPA overlap outweighs the promotional effects of the cocatalyst, and further copper added to the photocatalyst does not contribute to activity enhancement but leads to hydrogen production rate decay. This situation is described in stage II of the M-EPAO model, representing the descending section of **Figure 7**. The last stage of the M-EPAO model deals with the cocatalyst loading, which above it the particle growth dominates. At this stage, due to the coalescence of some of the particles, the number of cocatalyst particles decreases; nevertheless, as a result of the growth of cocatalyst particles and reduction in their number, the amount of available PPA and the overlapped area do not change significantly, and the photocatalytic activity of samples does not change considerably. The last stage of the M-EPAO model describes the range of cocatalyst loading in which the hydrogen productivity remains constant (copper wt. % higher than 3.80 in **Figure 7**).

Since the M-EPAO model needs the Cu_xO particle size to calculate the PPA, we used the Cu_xO content approximated using XPS analysis (**Table 3**) in our calculation. The Cu_xO particle size as a function of Cu_xO content was approximated using a linear function (**Figure S7-a**), including two stages of nucleation (constant size) and particle diffusion and coalescence (growth). This function is used in the M-EPAO model to estimate the Cu_xO particle size in different Cu_xO content. Also, the number of Cu_xO clusters was calculated using equation **S9**, and a curve was fitted to this data (**Figure S7-b**). This figure shows how the population of Cu_xO particles on the surface is changing.

We considered two surface packing of cubic and hexagonal for Cu_xO cluster arrangement on the $\text{Cu}_x\text{O}/\text{TiO}_2$ particles. By implementing the particle growth function in the M-EPAO model and optimizing its variables (a and b' in equation **S7**) in Matlab via minimizing the sum of square errors using the Globalsearch function, the M-EPAO model fit to the experimental data was obtained and is plotted in **Figure 9** (for the details of calculations, please refer to the electronic supporting information). A quick visual comparison indicates that the M-EPAO model is able to predict the hydrogen production

rate pretty well, especially for the cubic packing of Cu_xO clusters. The average absolute relative deviations (AARD) calculated for cubic and hexagonal packing are 4.8 % and 10.1 %, respectively, demonstrating that the M-EPAO model fits better with the experimental data using cubic packing of Cu_xO clusters.

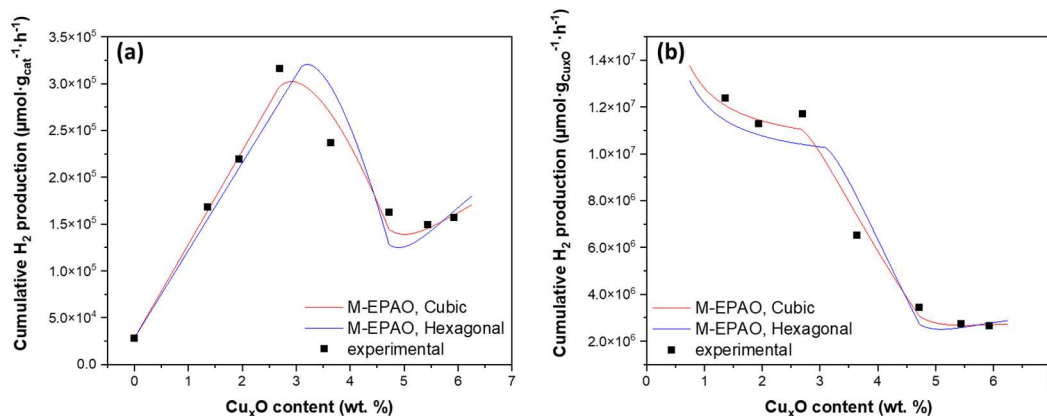


Figure 9. The cumulative hydrogen production after 20 hours of reaction normalized by the mass of (a) photocatalyst and (b) Cu_xO as a function of Cu_xO loading. The solid lines are generated using the M-EPAO model for cubic (black) and hexagonal (blue) packing of Cu_xO clusters.

The M-EPAO model enables us to calculate the photocatalytically promoted area (A_T in equation S5) of the photocatalyst created due to the strong interaction of Cu_xO cocatalyst clusters and TiO_2 support. **Figure 10** illustrates the surface coverage of $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalyst with PPA as a function of Cu_xO content calculated with M-EPAO model for cubic and hexagonal Cu_xO cluster packings and compares them with the surface Ti^{3+} content on the photocatalyst measured using XPS analysis. **Figure 10** reveals the similarity between the PPA development on $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalyst (calculated value) and the trend of surface Ti^{3+} increase (experimental data); this demonstrates that the assumptions of the M-EPAO model are valid, and it can consistently describe the cocatalyst decorated photocatalyst systems. It also agrees with the previous observations, suggesting the significant contribution of Ti^{3+} to photocatalytic activity of $\text{Cu}_x\text{O}/\text{TiO}_2$ catalysts [53, 57]. The Ti^{3+} species are produced due to the transfer of photo-excited electrons of Cu_xO clusters to TiO_2 [59], and the increase of Ti^{3+} content in $\text{Cu}_x\text{O}/\text{TiO}_2$ samples indicates the expansion of the depletion zone on the photocatalyst. It can be inferred that the depletion zone around the cocatalyst particles is the photocatalytically active area, and its growth increases the photocatalyst activity. It is worth noting that the maximum surface Ti^{3+} content that we observe using XPS is $\sim 60\%$, while the M-EPAO model predicts that at the Cu_xO content above 3.5 wt. % the photocatalyst surface is almost covered with the PPA. This discrepancy is likely to arise from two points: 1) the speciation of TiO_2 in the depletion zone is unknown for us, and we cannot consider it entirely consists of Ti^{3+} . Nevertheless, since Ti^{3+} is the main product of the strong interaction of Cu_xO clusters and TiO_2 , we correlate the size of depletion zone to the amount of Ti^{3+} . 2) considering ca. 1 keV kinetic energy of Ti 2p photoelectrons (when using aluminum $K\alpha$ radiation for XPS analysis), about one-third of the detected Ti 2p photoelectrons are coming from the depth of 4 nm or more. This suggests that a considerable part of the detected Ti^{4+} signal might originate from the interior of TiO_2 NPs, which is not affected by the Cu_xO clusters; however, we cannot exclude the contribution of this portion of Ti^{4+} to the overall Ti 2p XPS signal, while they are not present in the model.

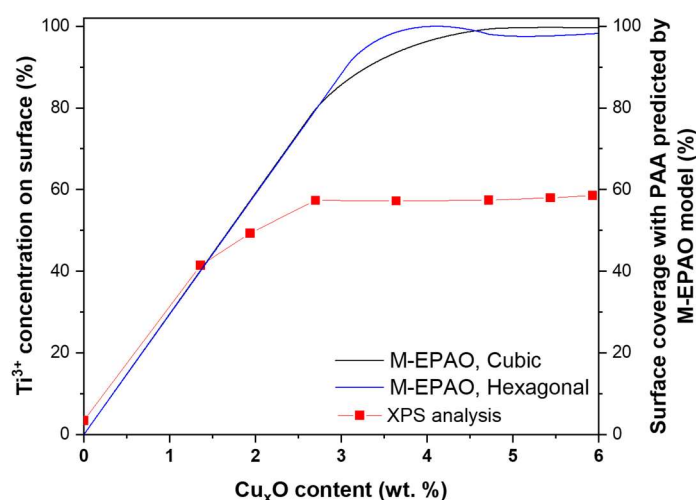


Figure 10. The Ti^{3+} content on the photocatalyst surface obtained with XPS analysis, and surface PPA coverage of photocatalyst as a function of Cu_xO content calculated with the M-EPAO model for cubic and hexagonal packing of Cu_xO cluster.

Recently, Mills et al. [29, 60] successfully visualized the concept of photocatalytically active area around a platinum dot deposited on TiO_2 via soot oxidation experiment. Our XPS analysis, in agreement with their observation, shows how the surface coverage of photocatalyst with Ti^{3+} , or in other words the expansion of depletion zone, increases the photocatalytic activity of cocatalyst decorated photocatalysts. Our results suggest that the depletion zone formed around the cocatalyst particles, due to charge separation at the heterojunction, is the main active zone for hydrogen production during photocatalytic methanol reforming. The M-EPAO model can be employed to describe the photocatalyst promoted by surface decoration using metal or metal oxide clusters, and it can predict the optimum cocatalyst loading to maximize the photocatalytic activity via maximizing the photocatalytically active area.

Conclusions

A set of $\text{Cu}_x\text{O}/\text{TiO}_2$ photocatalysts with high control over the Cu_xO cluster size was prepared using ALD. TEM imaging and particle size distribution analysis showed a narrow PSD with an average Cu_xO particle size of ~ 1.7 nm for the samples with a copper content below 3.8 wt. %. The XPS analysis of these samples revealed Cu^{1+} as the dominant copper species for low copper content, while Cu^{2+} increases with higher copper content. The XPS analysis also revealed the drastic effect of Cu_xO ALD on the oxidation state of titanium, depicting a significant reduction of Ti^{4+} reduction to Ti^{3+} . The DFT simulations also showed the strong interaction of Cu_xO and TiO_2 , leading to Ti^{4+} reduction to Ti^{3+} and Cu_xO cluster stabilization. The results of photocatalytic hydrogen production and characterization of $\text{Cu}_x\text{O}/\text{TiO}_2$ samples unveil the dual promotional effect of ALD grown Cu_xO clusters, i.e., generation of a substantial amount of surface Ti^{3+} , and improved charge carrier separation and increased visible light absorption. The copper content at which the hydrogen productivity is maximum coincides with the copper content at which the Ti^{3+} content plateaus. This illustrates the effect of the Ti^{3+} content on the hydrogen productivity of copper-promoted TiO_2 photocatalysts and enables us to correlate the solar hydrogen production rate to the cocatalyst surface density, weight loading, and size. We modified the EPAO model to describe the behavior of $\text{Cu}_x\text{O}/\text{TiO}_2$ system based on Cu_xO content and average particle size. The similar trend of the increase of the surface Ti^{3+} content and the photocatalytically promoted area, calculated with the M-EPAO model, suggests that the depletion zone formed around the Cu_xO clusters is the main active area for hydrogen production, and its expansion increases the hydrogen

production rate. However, the overlap of the depletion zones results in activity loss of photocatalyst; hence, the increase of cocatalyst content will enhance the hydrogen rate until the point that the depletion zones of the individual cocatalyst clusters start to overlap.

Acknowledgment

The authors thank Mr. Bart van der Linden for his technical support during the photocatalytic hydrogen production experiments and Ms. Baukje Terpstra's support for ICP-EOS analysis. This research was supported by an award made through the ERA.Net for Materials Research and Innovation (M-ERA.Net), Horizon 2020 grant agreement number 685451. Funding was provided by the following funding organizations: Science Foundation Ireland, Ireland, Grant Number SFI/16/M-ERA/3418, Spanish Ministry MINECO/FEDER Grants Number PCIN-2017-056 and PCIN-2017-131, The Netherlands Organisation for Scientific Research, Grant Number 732.017.101, and the European Union. MN acknowledges support from Science Foundation Ireland through the US-Ireland R&D Parntershop program, Grant number SFI/US/14/E2915. We acknowledge access to SFI funded computing resources at Tyndall Institute and the SFI/HEA funded Irish Centre for High End Computing. We are grateful for support from the COST Action CA18234 "Computational materials sciences for efficient water splitting with nanocrystals from abundant elements".

Data Availability

All data for the DFT calculations will be freely available at the following repository upon acceptance of the paper: <https://github.com/MMD-group/VASP>

References

- [1] N.S. Lewis, D.G. Nocera, Powering the planet: Chemical challenges in solar energy utilization, *Proceedings of the National Academy of Sciences*, 103 (2006) 15729-15735.
- [2] P.D. Nguyen, T.M. Duong, P.D. Tran, Current progress and challenges in engineering viable artificial leaf for solar water splitting, *Journal of Science: Advanced Materials and Devices*, 2 (2017) 399-417.
- [3] M. Muscetta, R. Andreozzi, L. Clarizia, I. Di Somma, R. Marotta, Hydrogen production through photoreforming processes over Cu₂O/TiO₂ composite materials: A mini-review, *International Journal of Hydrogen Energy*, 45 (2020) 28531-28552.
- [4] S. Singh, S. Jain, V. Ps, A.K. Tiwari, M.R. Nouni, J.K. Pandey, S. Goel, Hydrogen: A sustainable fuel for future of the transport sector, *Renewable and Sustainable Energy Reviews*, 51 (2015) 623-633.
- [5] R. Singh, S. Dutta, A review on H₂ production through photocatalytic reactions using TiO₂/TiO₂-assisted catalysts, *Fuel*, 220 (2018) 607-620.
- [6] C. Acar, I. Dincer, G.F. Naterer, Review of photocatalytic water-splitting methods for sustainable hydrogen production, *International Journal of Energy Research*, 40 (2016) 1449-1473.
- [7] M. Ni, M.K.H. Leung, D.Y.C. Leung, K. Sumathy, A review and recent developments in photocatalytic water-splitting using TiO₂ for hydrogen production, *Renewable and Sustainable Energy Reviews*, 11 (2007) 401-425.

- [8] M.Z. Hussain, B. van der Linden, Z. Yang, Q. Jia, H. Chang, R.A. Fischer, F. Kapteijn, Y. Zhu, Y. Xia, Bimetal–organic framework derived multi-heterostructured TiO₂/Cu_xO/C nanocomposites with superior photocatalytic H₂ generation performance, *Journal of Materials Chemistry A*, 9 (2021) 4103-4116.
- [9] A. Fujishima, K. Honda, Electrochemical Photolysis of Water at a Semiconductor Electrode, *Nature*, 238 (1972) 37-38.
- [10] V. Kumaravel, S. Mathew, J. Bartlett, S.C. Pillai, Photocatalytic hydrogen production using metal doped TiO₂: A review of recent advances, *Applied Catalysis B: Environmental*, 244 (2019) 1021-1064.
- [11] M. Reza Gholipour, C.-T. Dinh, F. Béland, T.-O. Do, Nanocomposite heterojunctions as sunlight-driven photocatalysts for hydrogen production from water splitting, *Nanoscale*, 7 (2015) 8187-8208.
- [12] S. Mohajernia, P. Andryskova, G. Zoppellaro, S. Hejazi, S. Kment, R. Zboril, J. Schmidt, P. Schmuki, Influence of Ti³⁺ defect-type on heterogeneous photocatalytic H₂ evolution activity of TiO₂, *Journal of Materials Chemistry A*, 8 (2020) 1432-1442.
- [13] F. Zuo, L. Wang, T. Wu, Z. Zhang, D. Borchardt, P. Feng, Self-Doped Ti³⁺ Enhanced Photocatalyst for Hydrogen Production under Visible Light, *Journal of the American Chemical Society*, 132 (2010) 11856-11857.
- [14] D. Zywitzki, H. Jing, H. Tüysüz, C.K. Chan, High surface area, amorphous titania with reactive Ti³⁺ through a photo-assisted synthesis method for photocatalytic H₂ generation, *Journal of Materials Chemistry A*, 5 (2017) 10957-10967.
- [15] Y. Liu, Z. Ye, D. Li, M. Wang, Y. Zhang, W. Huang, Tuning CuO_x-TiO₂ interaction and photocatalytic hydrogen production of CuO_x/TiO₂ photocatalysts via TiO₂ morphology engineering, *Applied Surface Science*, 473 (2019) 500-510.
- [16] Z. Wang, Y. Liu, D.J. Martin, W. Wang, J. Tang, W. Huang, CuO_x-TiO₂ junction: what is the active component for photocatalytic H₂ production?, *Physical Chemistry Chemical Physics*, 15 (2013) 14956-14960.
- [17] Q. Hu, J. Huang, G. Li, J. Chen, Z. Zhang, Z. Deng, Y. Jiang, W. Guo, Y. Cao, Effective water splitting using CuO_x/TiO₂ composite films: Role of Cu species and content in hydrogen generation, *Applied Surface Science*, 369 (2016) 201-206.
- [18] D. Praveen Kumar, N. Lakshmana Reddy, B. Srinivas, V. Durgakumari, V. Roddatis, O. Bondarchuk, M. Karthik, Y. Ikuma, M.V. Shankar, Stable and active Cu_xO/TiO₂ nanostructured catalyst for proficient hydrogen production under solar light irradiation, *Solar Energy Materials and Solar Cells*, 146 (2016) 63-71.
- [19] D. Praveen Kumar, M.V. Shankar, M. Mamatha Kumari, G. Sadanandam, B. Srinivas, V. Durgakumari, Nano-size effects on CuO/TiO₂ catalysts for highly efficient H₂ production under solar light irradiation, *Chemical Communications*, 49 (2013) 9443-9445.
- [20] Y. Liu, Z. Wang, W. Huang, Influences of TiO₂ phase structures on the structures and photocatalytic hydrogen production of CuO_x/TiO₂ photocatalysts, *Applied Surface Science*, 389 (2016) 760-767.
- [21] M. Jung, J.N. Hart, J. Scott, Y.H. Ng, Y. Jiang, R. Amal, Exploring Cu oxidation state on TiO₂ and its transformation during photocatalytic hydrogen evolution, *Applied Catalysis A: General*, 521 (2016) 190-201.
- [22] J.M. Valero, S. Obregón, G. Colón, Active Site Considerations on the Photocatalytic H₂ Evolution Performance of Cu-Doped TiO₂ Obtained by Different Doping Methods, *ACS Catalysis*, 4 (2014) 3320-3329.
- [23] P. Khemthong, P. Photai, N. Grisdanurak, Structural properties of CuO/TiO₂ nanorod in relation to their catalytic activity for simultaneous hydrogen production under solar light, *International Journal of Hydrogen Energy*, 38 (2013) 15992-16001.

- [24] W.-T. Chen, V. Jovic, D. Sun-Waterhouse, H. Idriss, G.I.N. Waterhouse, The role of CuO in promoting photocatalytic hydrogen production over TiO₂, *International Journal of Hydrogen Energy*, 38 (2013) 15036-15048.
- [25] M. Jung, J. Scott, Y.H. Ng, Y. Jiang, R. Amal, CuOx dispersion and reducibility on TiO₂ and its impact on photocatalytic hydrogen evolution, *International Journal of Hydrogen Energy*, 39 (2014) 12499-12506.
- [26] A. Maria Dalcin Fornari, M.B. de Araujo, C. Bergamin Duarte, G. Machado, S.R. Teixeira, D.E. Weibel, Photocatalytic reforming of aqueous formaldehyde with hydrogen generation over TiO₂ nanotubes loaded with Pt or Au nanoparticles, *International Journal of Hydrogen Energy*, 41 (2016) 11599-11607.
- [27] E.P. Melián, C.R. López, A.O. Méndez, O.G. Díaz, M.N. Suárez, J.M. Doña Rodríguez, J.A. Navío, D. Fernández Hevia, Hydrogen production using Pt-loaded TiO₂ photocatalysts, *International Journal of Hydrogen Energy*, 38 (2013) 11737-11748.
- [28] L. Li, L. Xu, W. Shi, J. Guan, Facile preparation and size-dependent photocatalytic activity of Cu₂O nanocrystals modified titania for hydrogen evolution, *International Journal of Hydrogen Energy*, 38 (2013) 816-822.
- [29] A. Mills, M. Bingham, C. O'Rourke, M. Bowker, Modelled kinetics of the rate of hydrogen evolution as a function of metal catalyst loading in the photocatalysed reforming of methanol by Pt (or Pd)/TiO₂, *Journal of Photochemistry and Photobiology A: Chemistry*, 373 (2019) 122-130.
- [30] M. Bowker, D. James, P. Stone, R. Bennett, N. Perkins, L. Millard, J. Greaves, A. Dickinson, Catalysis at the metal-support interface: exemplified by the photocatalytic reforming of methanol on Pd/TiO₂, *Journal of Catalysis*, 217 (2003) 427-433.
- [31] B.J. O'Neill, D.H.K. Jackson, J. Lee, C. Canlas, P.C. Stair, C.L. Marshall, J.W. Elam, T.F. Kuech, J.A. Dumesic, G.W. Huber, Catalyst Design with Atomic Layer Deposition, *ACS Catalysis*, 5 (2015) 1804-1825.
- [32] S. Saedy, D. Palagin, O. Safonova, J.A. van Bokhoven, A.A. Khodadadi, Y. Mortazavi, Understanding the mechanism of synthesis of Pt₃Co intermetallic nanoparticles via preferential chemical vapor deposition, *Journal of Materials Chemistry A*, 5 (2017) 24396-24406.
- [33] H. Van Bui, F. Grillo, J.R. van Ommen, Atomic and molecular layer deposition: off the beaten track, *Chemical Communications*, 53 (2017) 45-71.
- [34] J.R. van Ommen, A. Goulas, Atomic layer deposition on particulate materials, *Materials Today Chemistry*, 14 (2019) 100183.
- [35] F.S.M. Hashemi, F. Grillo, V.R. Ravikumar, D. Benz, A. Shekhar, M.B.E. Griffiths, S.T. Barry, J.R. van Ommen, Thermal atomic layer deposition of gold nanoparticles: controlled growth and size selection for photocatalysis, *Nanoscale*, 12 (2020) 9005-9013.
- [36] D. Benz, Y.N.T. Nguyen, T.-L.T. Le, T.-H.T. Le, V.-T. Le, J.R. van Ommen, H. Van Bui, Controlled growth of ultrasmall Cu₂O clusters on TiO₂ nanoparticles by atmospheric-pressure atomic layer deposition for enhanced photocatalytic activity, *Nanotechnology*, 32 (2021) 425601.
- [37] R. Beetstra, U. Lafont, J. Nijenhuis, E.M. Kelder, J.R. van Ommen, Atmospheric Pressure Process for Coating Particles Using Atomic Layer Deposition, *Chemical Vapor Deposition*, 15 (2009) 227-233.
- [38] G. Kresse, J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Physical Review B*, 54 (1996) 11169-11186.
- [39] G. Kresse, J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Computational Materials Science*, 6 (1996) 15-50.
- [40] G. Kresse, D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Physical Review B*, 59 (1999) 1758-1775.

- [41] P.E. Blöchl, Projector augmented-wave method, *Physical Review B*, 50 (1994) 17953-17979.
- [42] J.P. Perdew, K. Burke, M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Physical Review Letters*, 77 (1996) 3865-3868.
- [43] J.-J. Tao, H.-P. Ma, K.-P. Yuan, Y. Gu, J.-W. Lian, X.-X. Li, W. Huang, M. Nolan, H.-L. Lu, D.-W. Zhang, Modification of 1D TiO₂ nanowires with GaOxNy by atomic layer deposition for TiO₂@GaOxNy core-shell nanowires with enhanced photoelectrochemical performance, *Nanoscale*, 12 (2020) 7159-7173.
- [44] C. Liu, S.L. Nauert, M.A. Alsina, D. Wang, A. Grant, K. He, E. Weitz, M. Nolan, K.A. Gray, J.M. Notestein, Role of surface reconstruction on Cu/TiO₂ nanotubes for CO₂ conversion, *Applied Catalysis B: Environmental*, 255 (2019) 117754.
- [45] D. Muñoz-Rojas, M. Jordan, C. Yeoh, A.T. Marin, A. Kursumovic, L.A. Dunlop, D.C. Iza, A. Chen, H. Wang, J.L.M. Driscoll, Growth of ~5 cm²V⁻¹s⁻¹ mobility, p-type Copper(I) oxide (Cu₂O) films by fast atmospheric atomic layer deposition (AALD) at 225°C and below, *AIP Advances*, 2 (2012) 042179.
- [46] F. Grillo, H. Van Bui, J.A. Moulijn, M.T. Kreutzer, J.R. van Ommen, Understanding and Controlling the Aggregative Growth of Platinum Nanoparticles in Atomic Layer Deposition: An Avenue to Size Selection, *The Journal of Physical Chemistry Letters*, 8 (2017) 975-983.
- [47] N.E. Richey, C.d. Paula, S.F. Bent, Understanding chemical and physical mechanisms in atomic layer deposition, *The Journal of Chemical Physics*, 152 (2020) 040902.
- [48] P.A. DeSario, J.J. Pietron, T.H. Brintlinger, M. McEntee, J.F. Parker, O. Baturina, R.M. Stroud, D.R. Rolison, Oxidation-stable plasmonic copper nanoparticles in photocatalytic TiO₂ nanoarchitectures, *Nanoscale*, 9 (2017) 11720-11729.
- [49] M.C. Biesinger, Advanced analysis of copper X-ray photoelectron spectra, *Surface and Interface Analysis*, 49 (2017) 1325-1334.
- [50] F. Fang, Y. Liu, X. Sun, C. Fu, Y. Prakash Bhoi, W. Xiong, W. Huang, TiO₂ Facet-dependent reconstruction and photocatalysis of CuOx/TiO₂ photocatalysts in CO₂ photoreduction, *Applied Surface Science*, 564 (2021) 150407.
- [51] Y. Liu, B. Zhang, L. Luo, X. Chen, Z. Wang, E. Wu, D. Su, W. Huang, TiO₂/Cu₂O Core/Ultrathin Shell Nanorods as Efficient and Stable Photocatalysts for Water Reduction, *Angewandte Chemie International Edition*, 54 (2015) 15260-15265.
- [52] M.Y. Kang, H.J. Yun, S. Yu, W. Kim, N.D. Kim, J. Yi, Effect of TiO₂ crystalline phase on CO oxidation over CuO catalysts supported on TiO₂, *Journal of Molecular Catalysis A: Chemical*, 368-369 (2013) 72-77.
- [53] L. Xiong, F. Yang, L. Yan, N. Yan, X. Yang, M. Qiu, Y. Yu, Bifunctional photocatalysis of TiO₂/Cu₂O composite under visible light: Ti³⁺ in organic pollutant degradation and water splitting, *Journal of Physics and Chemistry of Solids*, 72 (2011) 1104-1109.
- [54] R. Marschall, Semiconductor Composites: Strategies for Enhancing Charge Carrier Separation to Improve Photocatalytic Activity, *Advanced Functional Materials*, 24 (2014) 2421-2440.
- [55] S. Obregón, M.J. Muñoz-Batista, M. Fernández-García, A. Kubacka, G. Colón, Cu-TiO₂ systems for the photocatalytic H₂ production: Influence of structural and surface support features, *Applied Catalysis B: Environmental*, 179 (2015) 468-478.
- [56] A.T. Garcia-Esparza, K. Takanabe, A simplified theoretical guideline for overall water splitting using photocatalyst particles, *Journal of Materials Chemistry A*, 4 (2016) 2894-2908.
- [57] Y. Ji, W. Guo, H. Chen, L. Zhang, S. Chen, M. Hua, Y. Long, Z. Chen, Surface Ti³⁺/Ti⁴⁺ Redox Shuttle Enhancing Photocatalytic H₂ Production in Ultrathin TiO₂ Nanosheets/CdSe Quantum Dots, *The Journal of Physical Chemistry C*, 119 (2015) 27053-27059.

- [58] A. Holm, E.D. Goodman, J.H. Stenlid, A. Aitbekova, R. Zelaya, B.T. Diroll, A.C. Johnston-Peck, K.-C. Kao, C.W. Frank, L.G.M. Pettersson, M. Cargnello, Nanoscale Spatial Distribution of Supported Nanoparticles Controls Activity and Stability in Powder Catalysts for CO Oxidation and Photocatalytic H₂ Evolution, *Journal of the American Chemical Society*, 142 (2020) 14481-14494.
- [59] L. Luo, T. Zhang, X. Zhang, R. Yun, Y. Lin, B. Zhang, X. Xiang, Enhanced Hydrogen Production from Ethanol Photoreforming by Site-Specific Deposition of Au on Cu₂O/TiO₂ p-n Junction, *Catalysts*, 10 (2020).
- [60] A. Mills, M. Bingham, C. O'Rourke, Ring Photocatalysis: Bands of Activation Surrounding Macro-Sized (≥ 1 mm Radius) Pt Islands Deposited on TiO₂ Films, *The Journal of Physical Chemistry C*, 124 (2020) 13550-13559.