

Carbon Dioxide Capture Chemistry of Amino Acid Functionalized Metal-Organic Frameworks in Humid Flue Gas

Hao Lyu,[†] Oscar Iu-Fan Chen,[†] Nikita Hanikel,[†] Mohammad I. Hossain,[†] Robinson W. Flaig,[†] Xiaokun Pei,[†] Ameer Amin,[†] Mark D. Doherty,[‡] Rebekah K. Impastato,[‡] T. Grant Glover,[‡] David R. Moore,[‡] Omar M. Yaghi^{*,†}

[†] Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, California 94720, United States

[‡] Department of Chemical & Biomolecular Engineering, University of South Alabama, Mobile, Alabama 36688, United States

[‡] GE Global Research, 1 Research Circle, Niskayuna, New York 12309, United States

ABSTRACT: Metal-organic framework-808 has been functionalized with 11 amino acids (AA) to produce a series of MOF-808-AA structures. The adsorption of CO₂ under flue gas conditions revealed that glycine- and DL-lysine-functionalized MOF-808 (MOF-808-Gly and -DL-Lys) have the highest uptake capacities. Enhanced CO₂ capture performance in the presence of water was observed and studied using single-component sorption isotherms, CO₂/H₂O binary isotherm, and dynamic breakthrough measurements. The key to the favorable performance was uncovered by deciphering the mechanism of CO₂ capture in the pores and attributed to the formation of bicarbonate as evidenced by ¹³C and ¹⁵N solid-state nuclear magnetic resonance spectroscopy studies. Based on these results, we examined the performance of MOF-808-Gly in simulated coal flue gas conditions and found that it is possible to capture and release CO₂ by vacuum swing adsorption. MOF-808-Gly was cycled at least 80 times with full retention of performance. This study significantly advances our understanding of CO₂ chemistry in MOFs by revealing how strongly bound amine moieties to the MOF backbone create the chemistry and environment within the pores, leading to the binding and release of CO₂ under mild conditions without application of heat.

INTRODUCTION

The carbon dioxide capture problem is of paramount societal importance.^{1,2} Although aqueous amine solutions are currently being used to capture CO₂, they require significant energy input because of the high heat capacity of water and suffer from loss of amines.^{3–6} Porous solid-state materials are being studied for their potential in offering a platform for mounting amines and foregoing the heat requirement of aqueous solutions.^{7–9} In this regard, materials such as carbon,^{7,10} zeolites,¹¹ silica,^{12–15} resins,^{16,17} covalent organic frameworks,¹⁸ and metal-organic frameworks (MOFs),^{19–23} are being investigated [as summarized in Table 1, see Table S1 in the Supporting Information (SI) for more detailed comparison].^{7,10,19,24–28} At present, they all fall short of meeting the stringent performance requirements: high uptake capacity, high selectivity, low regeneration energy, fast kinetics, and long cycling lifetime.^{29,30} We believe that in order to solve the CO₂ problem, significant efforts are required in understanding the CO₂ chemistry in the pores of such materials and in using this knowledge to build viable structures.

Along these lines, we focus on MOFs and report a series of eleven amino acid functionalized MOF-808 structures (MOF-808-AA), in which the amino acid moieties are strongly bound to the backbone. We find that this construct creates an environment inside the pores where CO₂ uptake under humid conditions leads to the formation of bicarbonates, and therefore requiring no application of heat to regenerate the material. In this way, application of rough vacuum is

sufficient to remove the CO₂ and obviate the need for heating customarily used in aqueous amines and even some solid sorbents.

We and others have appended amines as coordinatively or covalently bound functionalities into MOFs.^{20,21,31–36} Specifically, MOF-74 has been used in obtaining high capacity for CO₂ uptake. In Mg-MOF-74 [termed Mg₂(dobdc), dobdc = 2,5-dioxidophenylene-1,4-dicarboxylate], the amines are bound directly to the Mg²⁺ to make a weak bonding interaction. Although this interaction allows for high CO₂ uptake mechanism, it is the Achilles' heel of the material as it results in (1) ease of hydrolysis of the MOF backbone, and (2) competition of water to CO₂ for Mg²⁺ sites, and therefore the loss of amines.^{35,37} Furthermore, the Mg-MOF-74 system and their derivatives require heating to 140–240 °C for regeneration.^{21,32–35} Here, we use a robust MOF-808 [Zr₆O₄(OH)₄(BTC)₂(HCOO)₆, BTC = 1,3,5-benzenetricarboxylate] system³⁸ and bind the amino acids through their carboxylates to Zr(IV) centers to create Zr(IV)-carboxylate interactions, which are 2–3 times stronger than the Mg(II)-amine interactions.^{39–41} The fact that the amino residue of the amino acid is dangling into the pores creates a basic environment for CO₂ binding in the presence of water. This structural design prevents water or CO₂ from interfering with the bond between Zr(IV) and the carboxylate of the amino acids.

In this study, we used MOF-808 as the basis for generating the amino acid functionalized forms. We measured and confirmed their enhanced CO₂ capture performance in the presence of water through sorption studies. These involved single-component

Table 1. Overview of CO₂ Capture Properties for State-of-the-Art Sorbents

Sorbent Classes		CO ₂ Uptake [†] Dry/Humid	Binding Mechanism	Regeneration Conditions	Operational Challenges [‡]
Physisorbents					
Carbon		L/L (↓)	Physisorption	25–100 °C/Vacuum	Low cyclability
Zeolites		M to H/None (↓)	Polar interaction	120–250 °C/Vacuum	Sensitivity to humidity, high regeneration T
MOFs		H/L (↓)	Open metal sites	100–200 °C	Hydrolysis, low uptake in humidity, high regeneration T
		H/H (↓)	Polar interaction	150–350 °C/Vacuum	Hydrolysis, high regeneration T
Chemisorbents					
Hydroxides		H	Carbonate	400–1000 °C	Solid management, high regeneration T
Carbonates		M	Bicarbonate	150–350 °C	Pore blockage, high regeneration T
Amine Liquids	Monoethanolamine	H/H (↑)	Carbamate-bicarbonate	90–100 °C	Amine loss, corrosion, amine oxidation
	Amino acid salts	M/M (↑)	Carbamate-bicarbonate	90–100 °C	Amine loss, amine oxidation
	Aminosilicones	M to H/M to H (↑)	Carbamate-bicarbonate	80–150 °C	Amine loss, amine oxidation, urea formation
Grafted Amines	Resins	M to H/M to H (↑)	Carbamate-bicarbonate	120 °C	High regeneration T
	Silica	M to H/M to H (↑)	Carbamate-bicarbonate	110 °C	Capacity loss (urea formation)
	MOFs, appended	H/H (↑ or ↓)	Metal Carbamate	100–180 °C	Hydrolysis, high regeneration T, amine loss
	MOFs, functionalized	M/M (↑)	Carbamate-bicarbonate	70–140 °C/Vacuum	Hydrolysis, high regeneration T

[†] Qualitative ranges of general uptake values indicated as high (H), medium (M), or low (L) with an arrow to signify whether the uptake increases (↑) or decreases (↓) with humidity using flue gas-relevant conditions. See Table S1 and corresponding references for further details.

[‡] T, temperature.

sorption isotherms, CO₂/H₂O binary sorption isotherms, and dynamic breakthrough experiments. We further explored the mechanistic aspects of CO₂ binding in the presence of water and confirmed the formation of bicarbonate using evidence from solid-state nuclear magnetic resonance (NMR) spectroscopy. The bicarbonate formation is further corroborated by the ease with which CO₂ can be removed by vacuum, and this led us to apply the CO₂ capture and release process in vacuum swing adsorption (VSA).^{42,43} A member of the MOF-808-AA series was subjected to a simulated coal flue gas and found to take up CO₂ and release it without heating. These studies, for the first time, combine humidity-enhanced CO₂ uptake and low-energy vacuum swing adsorption processes for post-combustion CO₂ capture.

RESULTS AND DISCUSSION

Synthesis of MOF-808-AA. MOF-808-AA (Figure 1a) was obtained through the post-synthetic incorporation of amino acids into MOF-808, for which the formate ligands have been removed to give what is referred to as MOF-808-FR. Typically, microcrystalline MOF-808 was first synthesized, and the formate (HCOO[−]) ligands were removed by treatment with hydrochloric acid (HCl) according to reported procedures.^{38,44} The product was then immersed in a saturated aqueous or dimethyl sulfoxide (DMSO) solution of an amino acid at a given temperature for 3 days (Figure 1b, Table 2, SI Section S3), during which exchange of fresh solutions was performed 3 times per day. The solid was then washed with deionized water 3 times per day for 3 days, followed by treatment with pH 10 buffer solutions of the amino acid or a 10% 1,8-diazabicyclo(5.4.0)undec-7-ene (DBU) solution in tetrahydrofuran for 1 day, and further washed with acetone for an additional day before activation under dynamic vacuum at 140 °C. In this work, 11 amino acids (Figure 1c) were loaded into

MOF-808-FR to yield a series of MOF-808-AAs with a general empirical formula of [Zr₆O₄(OH)₄(BTC)₂(AA)_N(OH)_{6-N}(H₂O)_{6-N}, AA = amino acid anion], where loading number *N* denotes the molar equivalence of amino acids per Zr₆O₄(OH)₄ cluster (or secondary building unit, SBU).

For easy reference, the names and abbreviations of the amino acids, and relevant information of the resulting MOF-808-AAs are summarized in Table 2. The composition of the amino acid-loaded MOFs was determined through liquid-state ¹H NMR measurements of the MOFs fully hydrolyzed into their components with hydrofluoric acid (HF) and deuterium chloride (DCl) in a solvent mixture of DMSO-*d*₆ and deuterium oxide (D₂O) (referred to as “digest NMR”, Section S3). To determine the loading of amino acids, the integrations of amino acid signals were compared to that of the BTC linker, thereby giving the ratio between amino acids and the linker. Fourier-transform infrared spectroscopy (FT-IR, SI Section S6), powder X-ray diffraction (PXRD, SI Section S5), scanning electron microscopy (SEM, SI Section S7), as well as N₂ and CO₂ sorption studies were carried out to further characterize the samples.

Structure of MOF-808-AA. The structure of MOF-808 is composed of the SBUs Zr₆O₄(OH)₄(−COO)₆(HCOO)₆,³⁸ which are connected to each other through 1,3,5-benzenetricarboxylate linkers, yielding a porous, extended, three-dimensional framework (Figure 1a). Each of the SBUs is comprised of six ZrO₈ tetragonal antiprisms linked by sharing tetragonal caps through μ₃-O atoms. On the periphery of the SBU are a total of 12 exchangeable coordination sites bridging between adjacent Zr atoms. In the precursor framework, MOF-808, these sites are occupied by formate (HCOO[−]) ligands in bidentate or monodentate binding mode, while in MOF-808-FR, the sites are most likely occupied by H₂O and OH[−] for

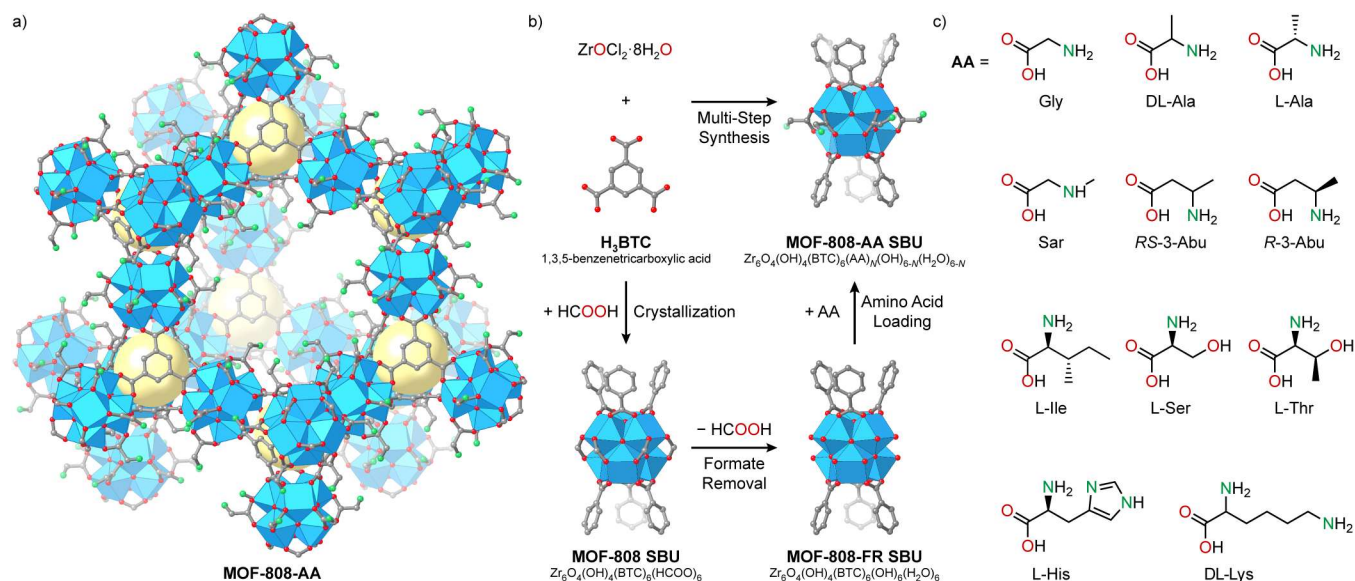


Figure 1. (a) The structure of MOF-808-AA and (b) general synthetic scheme for MOF-808-AA from crystallization of MOF-808 to post-synthetic formate removal and amino acid loading, represented with zoom-in views of the Zr SBUs to highlight the changes of coordination in each step. Structural schemes of the coordinatively loaded amino acids are provided in (c) corresponding to abbreviations in Table 2, respectively. Atomic models of MOF-808-Gly and its SBU with a loading number $N = 6$ are used to represent the general structure of MOF-808-AA. Zr atoms are represented as light blue polyhedra, while other atoms are represented as spheres (Color code: C, gray; O, red; N, green). H atoms are omitted, and the yellow spheres highlight the small tetrahedral pores for clarity.

Table 2. Summary of Loading and Reaction Conditions of Selected Amino Acids, and CO₂ Uptake Capacities of MOF-808-AAs

Amino Acid	Abbreviation	pK _a ^{45,46}	Loading (N)	Temperature (°C)	Solvent	Amine Loading (mmol g ⁻¹)	Uptake (mmol g ⁻¹ , 25 °C) [†]	
							4 kPa	15 kPa
Glycine	Gly	9.60	5.89	85	H ₂ O	3.84	0.247	0.540
							0.525 [‡]	0.693 [‡]
Sarcosine	Sar	10.35	1.71	85	H ₂ O	1.23	0.239	0.561
L-Alanine	L-Ala	9.69	3.55	100	H ₂ O	2.38	0.250	0.520
DL-Alanine	DL-Ala	9.69	2.98	100	H ₂ O	2.04	0.213	0.482
(R)-3-Aminobutanoic acid	R-3-Abu	10.53	2.12	85	H ₂ O [§]	1.47	0.132	0.317
(RS)-3-Aminobutanoic acid	RS-3-Abu	10.53	2.10	85	H ₂ O [§]	1.45	0.189	0.383
L-Isoleucine	L-Ile	9.60	1.44	85	H ₂ O	1.00	0.203	0.434
L-Serine	L-Ser	9.15	3.61	85	H ₂ O	2.32	0.248	0.603
L-Threonine	L-Thr	9.10	4.48	100	H ₂ O	2.67	0.119	0.320
L-Histidine	L-His	9.17	4.03	85	H ₂ O	2.26	0.108	0.331
DL-Lysine	DL-Lys	8.95, 10.53	1.87	120	DMSO	2.48	0.705	1.040

[†] CO₂ uptake extracted from single-component isotherm at 25 °C, unless specified otherwise.

[‡] CO₂ uptake in the presence of water extracted from CO₂/H₂O binary adsorption isotherm at RH ~10% (3.6 mmol g⁻¹ loading of water).

[§] 1 mol L⁻¹ aqueous solutions instead of saturated solutions.

charge balance (SI Section S3). The loading of amino acids involves binding of their carboxylate (–COO⁻) groups to these sites to form the desired derivatives used in this work (Figure 1a). The extended linking of Zr SBUs and BTC linkers form two kind of interconnected pores: small, tetrahedral pores of 1.2 Å in aperture diameter that are inaccessible to guest molecules; and large, adamantane-shaped pores of 18 Å in diameter that are highly interconnected through apertures of 14 Å in diameter.⁴⁴ The installation of amino acid ligands allows the amino groups (–NH₂ or –NH–) on the alkyl chains to point to the inside of the pores, which serve as the primary sites to

interact with, and thus capture CO₂ entering the pores from the exterior.

To validate this, single-crystal samples of a representative variant, MOF-808-Gly [Zr₆O₄(OH)₄(BTC)₂(Gly)_N(OH)_{6-N}(H₂O)_{6-N}, Gly = NH₂CH₂COO⁻], were prepared using a similar procedure as for the microcrystalline samples, with the acetone washing steps specifically avoided to eliminate possible assignment difficulties during the structural refinement. 20–40 μm-sized single crystals of MOF-808 were prepared according to the reported procedure,³⁸ which were further treated with 1 mol L⁻¹ HCl solution to remove formate ligands. Glycine was incorporated with retention of morphology and

crystallinity of the crystals, which were found suitable for single-crystal X-ray diffraction (SXRD) studies. Fully activated crystals were used for collection of SXRD data with synchrotron radiation at Beamline 12.2.1 of the Advanced Light Source (ALS) at Lawrence Berkeley National Laboratory at 100 K using a nitrogen cold stream. The structure of MOF-808-Gly was solved in the cubic space group $Fd\bar{3}m$, with the unit cell parameter of $a = 35.1413(12)$ Å (SI Section S4). The extended backbone of the MOF was well-resolved to show the same structure as in MOF-808, and relatively small thermal displacement parameters, indicating the retention of crystallinity during the post-synthetic modification (Figure S14).

An average of 2.9 glycinate ligands, as determined by the occupancies of the α -C and N atoms in the SXRD result, were found bound to each Zr SBU in a bidentate bridging fashion between two Zr atoms. The amino N atom was found in significant disorder, which was largely attributed to the free rotation of the C–C bond in the glycinate ligand, indicating no significant interaction with other parts of the MOF (Figure 2 and Figure S15). The lower loading ($N = 2.9$) of glycinate in the single-crystalline samples compared to microcrystalline samples ($N = 5.89$) was likely attributed to the limited diffusion of guest glycine molecules through the crystal during the incorporation reaction. However, since no significant intermolecular interactions have been found among glycinate ligands as observed in the single-crystal structure, we believe it represents the binding and conformation in the bulk, microcrystalline samples.

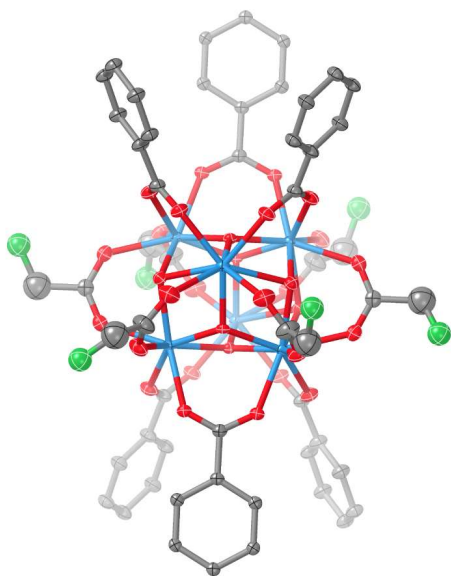


Figure 2. Single-crystal structure of a segment of MOF-808-Gly focused on one Zr₆ SBU, highlighting the bridging binding mode of glycinate to adjacent Zr atoms. Thermal ellipsoids of atoms are shown at 50% probability level. Color code: C, gray; O, red; N, green; Zr, blue. For clarity, H atoms, disordered μ_3 -O atoms, and OH[−]/H₂O groups are omitted. One randomly selected conformation among the refined rotationally disordered positions of each –NH₂ group is shown to help clarify the spatial arrangement of the amino acid residues in MOF-808-Gly.

For the bulk sample, the retention of crystallinity was first established through PXRD measurements (SI Section S5). The composition was then characterized with FT-IR measurements (SI Section

S6). Compared to MOF-808, nearly all formate ligands were absent in MOF-808-FR, as was evidenced by the absence of absorbance bands at 1582 cm^{−1} and 1337 cm^{−1} which have been assigned as –COO stretches of the formate ligands.⁴⁷ Furthermore, it was determined that >98.5% of the formate ligands were removed based on digest NMR results on MOF-808-FR.^{48,49} The incorporation of glycine molecules into MOF-808-FR was first probed by the appearance of FT-IR absorbance bands at ~2960 cm^{−1} assigned as the C–H stretch of glycinate ligands present in the product MOF-808-Gly.⁵⁰ Representative scanning electron micrographs of MOF-808 and MOF-808-Gly showed that the octahedral microcrystals of the MOF remained unaltered before and after the reactions (Figures S20 and S21). Energy dispersive X-ray spectroscopy (EDX) on a set of randomly sampled microcrystals indicated that no remaining chlorine (Cl) was found after the last step of the coordinative functionalization (Figure S22).

N₂ Sorption Isotherm Studies. N₂ sorption isotherms were measured for MOF-808, MOF-808-FR, and MOF-808-AAs at 77 K (Figure 3a, SI Section S8.1) to confirm their permanent porosity. Comparison among MOF-808, MOF-808-FR, and the representative MOF-808-Gly (Figure 3a) showed that the formate removal step increased the porosity, as indicated by the change of the Brunauer-Emmett-Teller (BET) surface area from 1680 m² g^{−1} to 1971 m² g^{−1} (Figures S23 and S24). By contrast, the amino acid loading reaction generally reduced the porosity. This was exemplified by MOF-808-Gly, whose BET surface area was reduced to 1427 m² g^{−1} (Figure S25).

It is likely that besides contributing to the total mass of the MOF, the residues of the amino acids occupy space in the pores, thus considerably reducing the surface area. Evidence from the pore size distribution data (Figures S26–S32) derived from N₂ sorption isotherms further indicate that the pore structures were retained in the intermediate and the final products. As expected, the amine ligands were introduced without altering the periodic porous MOF structures. N₂ isotherms and BET surface areas of other MOF-808-AAs are given in Figures S33–S41.

Single-Component CO₂ Sorption Isotherms. Single-component CO₂ adsorption and desorption isotherms were measured at 25 °C (~298 K) for all obtained MOF-808-AA variants and their precursor frameworks (Figures 3b and c, SI Section S8.2.1). Comparison of the isotherms of MOF-808 and MOF-808-FR, MOF-808-Gly show that the latter has increased uptake at carbon capture-relevant pressures (4 kPa and 15 kPa, Table 2). In addition, a significant hysteresis is observed between the adsorption branch and desorption branch, characteristic of CO₂ chemisorption, which is not fully reversible at 25 °C. This phenomenon was generally observed for other MOF-808-AA variants, while absent for MOF-808 or MOF-808-FR. This eliminates the possibility of having any unoccupied sites (open metal sites) in the MOF backbone contributing to the observed strong adsorption.

Comparison of CO₂ isotherms at 25 °C among the MOF-808-AAs (Figure 3c, Figures S43–S53, Table 2) yielded a range of CO₂ uptake performances, varying between 0.092 mmol g^{−1} and 0.705 mmol g^{−1} at 4 kPa (4% CO₂ in 1 atm gas mixture, relevant to natural gas combined cycle flue gas capture), and between 0.277 mmol g^{−1} and 1.040 mmol g^{−1} at 15 kPa (15% CO₂ in 1 atm gas mixture, relevant to coal flue gas capture).

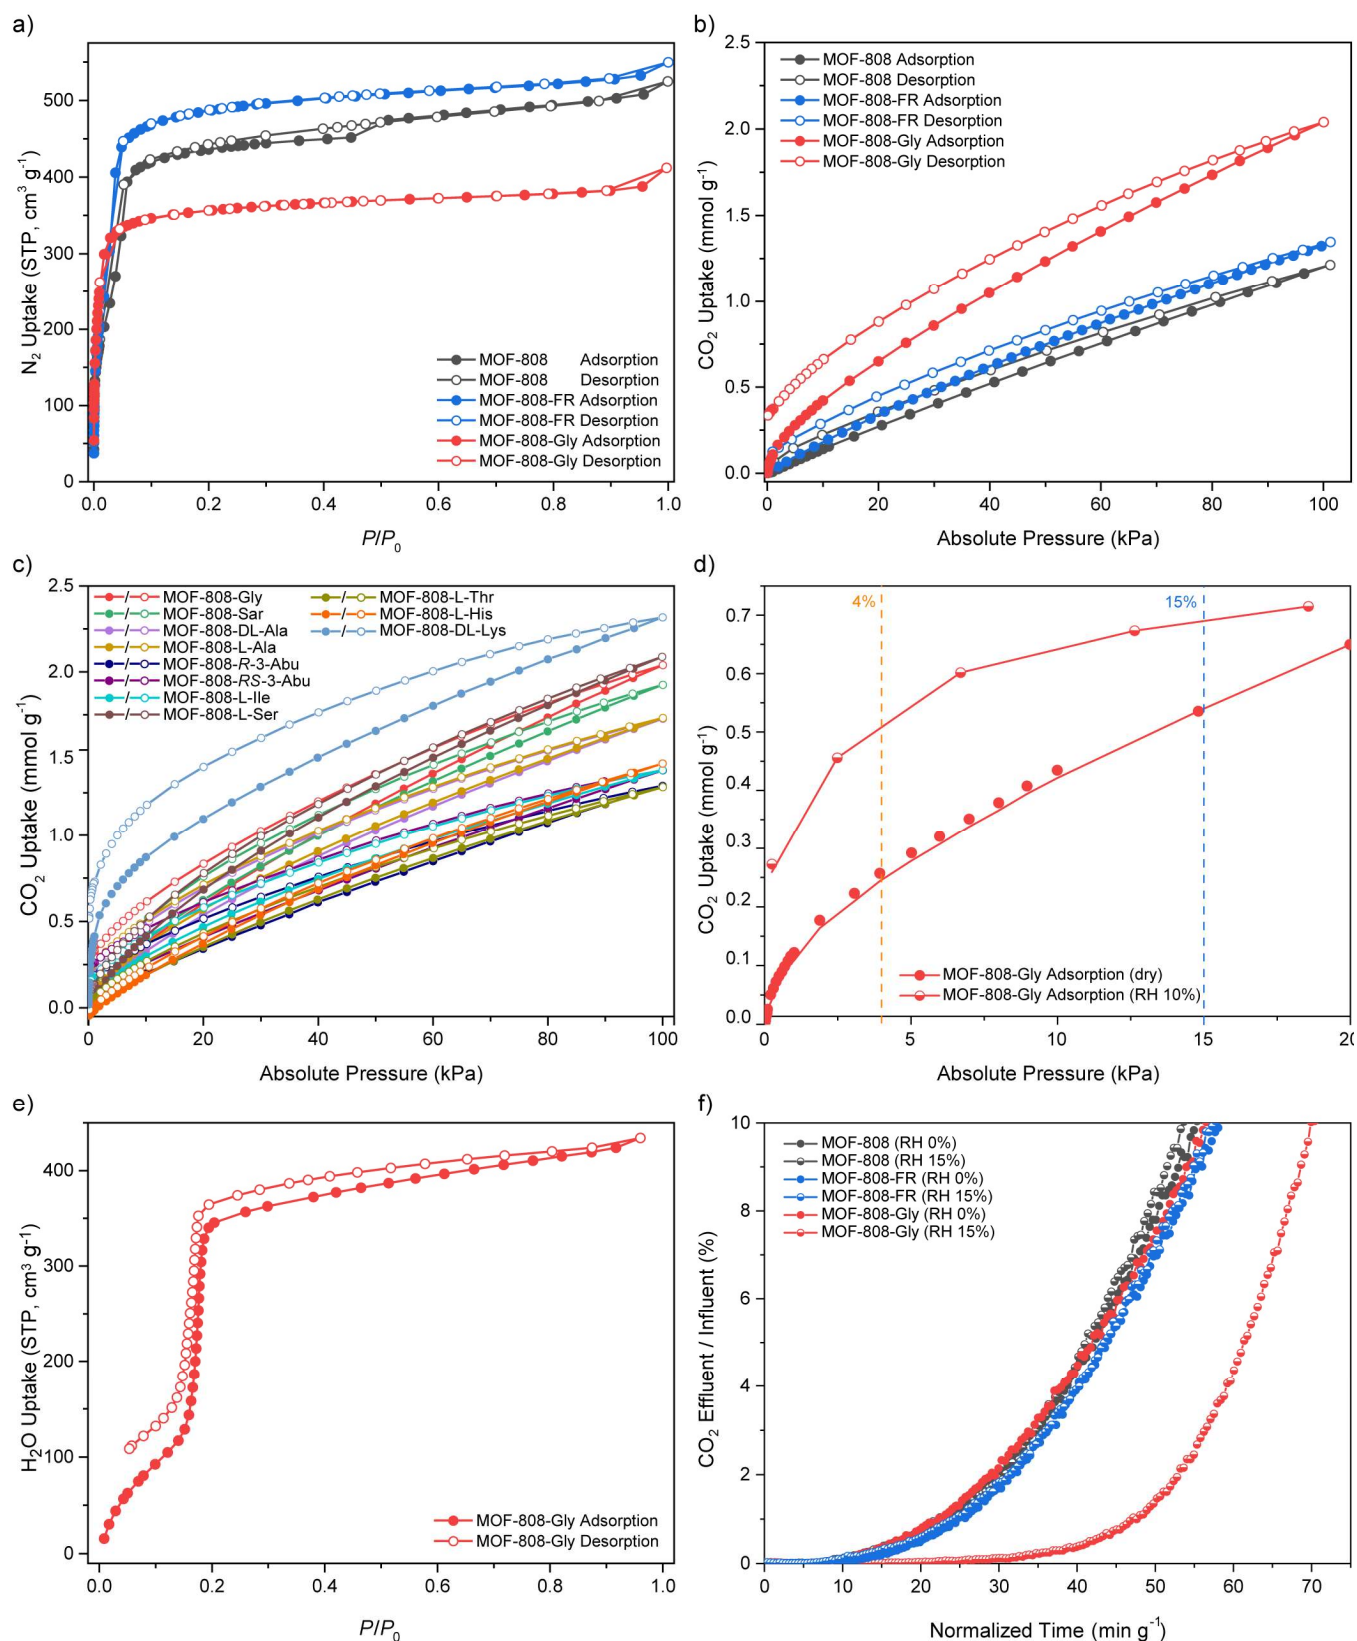


Figure 3. Comparison of (a) N₂ sorption isotherms measured at 77 K and (b) CO₂ sorption isotherms measured at 25 °C for MOF-808, MOF-808-FR, and representative MOF-808-Gly to show the pore geometry and CO₂ uptake change before and after post-synthetic modification reactions; (c) overlay of single-component CO₂ isotherms of the MOF-808-AA variants, (d) overlay of CO₂/H₂O binary adsorption isotherm with dry CO₂ isotherm at 25 °C, (e) water sorption isotherm of MOF-808-Gly measured at 25 °C; (f) dynamic CO₂ breakthrough curve comparison among MOF-808, MOF-808-FR, and MOF-808-Gly in dry and humid (RH 15%) conditions at 25 °C.

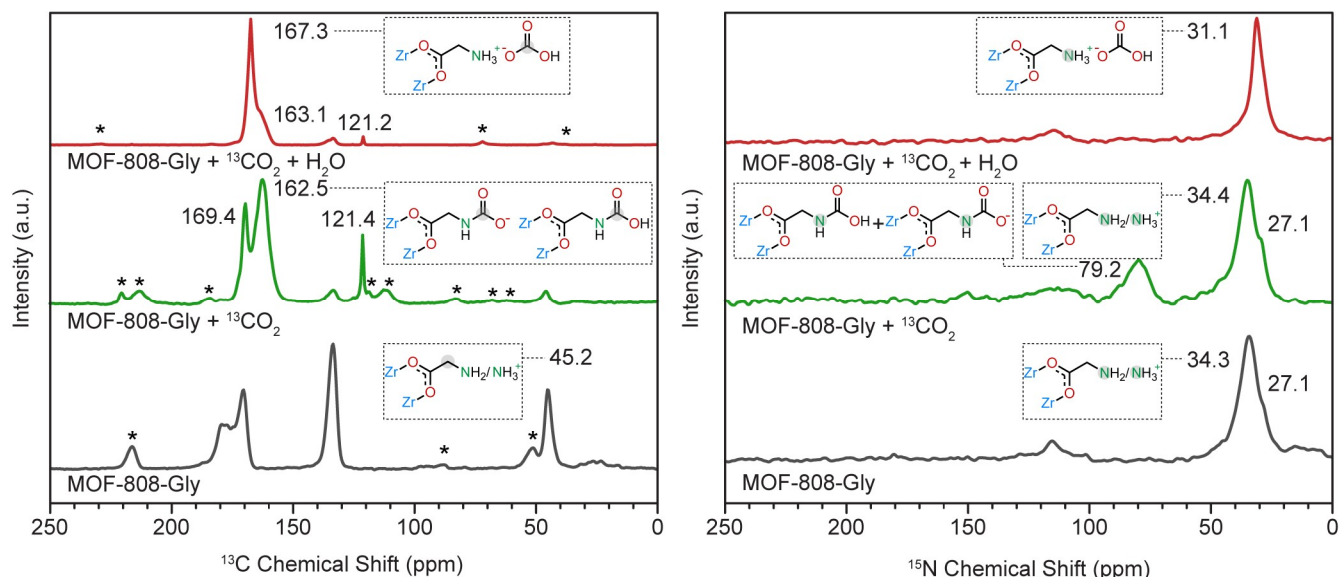


Figure 4. Stacked plots of solid-state ^{13}C (left) and ^{15}N (right) CP-MAS ssNMR spectra of ^{15}N -labeled MOF-808-Gly before and after adsorption of $^{13}\text{CO}_2$ with or without the presence of water. In dark gray (bottom) are the spectra for MOF-808-Gly fully activated under dynamic vacuum. In green (middle) are the spectra for MOF-808-Gly after exposure to 98.7 kPa $^{13}\text{CO}_2$ for 24 h. In red (top) are the spectra for MOF-808-Gly after exposure to a N_2 atmosphere with 95% relative humidity at 25 $^\circ\text{C}$ for 24 h, followed by 90.0 kPa $^{13}\text{CO}_2$ for 24 h. Signals of interest are marked with their ^{13}C or ^{15}N chemical shifts and the assignments of major species identified are shown in dashed boxes. Spinning sidebands are marked with “*”.

We found that multiple factors influence the CO_2 uptake: total amine loading, pK_a of the amine species, steric hindrance at the local environment in the pore, as well as proximity of adjacent functional groups. Most significantly, a larger gravimetric amine loading and a higher pK_a of the loaded amine species are correlated to a higher CO_2 uptake. The incorporation of DL-lysine into MOF-808-FR, despite a relatively low amino acid loading number N of 1.87, yielded a gravimetric amine loading of 2.48 mmol g^{-1} , third highest among the series due to the two-fold amine stoichiometry per amino acid loading. The pK_a of the $\epsilon\text{-NH}_2$ is 10.53, highest among the amino species, ensured a high affinity even at a low CO_2 pressure. These factors combined resulted in the highest CO_2 uptake observed for MOF-808-DL-Lys among all the MOF-808-AA sorbents at both CO_2 levels of interest.

To quantitatively evaluate the sorbents’ affinity for CO_2 , the isosteric heat of adsorption (Q_st) was determined by measuring CO_2 sorption isotherms at 15 $^\circ\text{C}$ (~ 288 K), 25 $^\circ\text{C}$, and 35 $^\circ\text{C}$ (~ 308 K) for selected MOF samples (SI Section S8.2.2). The Q_st value of MOF-808-DL-Lys at zero loading was estimated as ~ 80 kJ mol^{-1} (Figures S56 and S57). This is significantly higher when compared to ~ 46 kJ mol^{-1} of MOF-808-Gly (Figures S54 and S55), of which the $\alpha\text{-NH}_2$ were from glycine, having a comparatively lower pK_a value of 9.60. This observation further supports the proposed relationship between higher pK_a of the amine species and stronger CO_2 binding in relatively low CO_2 pressure among the MOF-808-AA series.

Binary $\text{CO}_2/\text{H}_2\text{O}$ Adsorption Isotherms and Dynamic Breakthrough Experiments. As moisture is unavoidable toward achieving low-cost, practical flue gas capture, studying the influence of water on the sorbent’s CO_2 uptake is important. To probe this, we measured the binary $\text{CO}_2/\text{H}_2\text{O}$ adsorption isotherm of the representative MOF-808-Gly. The experiment was carried out in a custom-built volumetric system (SI Section S8.3.1).⁵¹ The sample was

first fully regenerated *in situ* under vacuum at 150 $^\circ\text{C}$. Water was injected to achieve a headspace relative humidity of $\sim 10\%$ (3.6 mmol g^{-1} , Figure 3d and e), and then CO_2 was loaded on the water-loaded sorbent. The loadings of both CO_2 and H_2O were monitored with a gas chromatograph (GC) and the loadings of each species were determined *via* a mass balance. The Toth model⁵² was applied to fit the binary isotherm to extract the uptake at the given CO_2 pressures (Table 2, SI Section S8.3.2).

The resulting isotherm revealed a significant increase of CO_2 uptake of MOF-808-Gly in the presence of water compared to dry conditions. Specifically, overlay of the binary $\text{CO}_2/\text{H}_2\text{O}$ and single-component CO_2 sorption isotherms of MOF-808-Gly indicated a more than two-fold increase in CO_2 uptake at 4 kPa, which continued to be above the dry isotherm until ~ 20 kPa (Figure 3d).

The increased uptake in the presence of water was further studied in a dynamic manner with a breakthrough system (SI Section S9): MOF samples were loaded in a packed bed and a stream of CO_2 -containing gas mixture was passed through the sorbent and analyzed by GC. Normalized breakthrough curves of MOF-808, MOF-808-FR, and MOF-808-Gly are overlaid to compare the behavior of the sorbents with or without humidity (RH 15%, 25 $^\circ\text{C}$, Figure 3f). Both MOF-808 and MOF-808-FR exhibited no significant change or a slightly earlier breakthrough time upon humidification of the stream. In contrast, MOF-808-Gly exhibited a significant delay of the breakthrough, corresponding to an increased uptake in the presence of humidity. This is in line with the increased uptake observed in the binary adsorption isotherm study.

These observations combined support the sorbent’s characteristics of humidity-enhanced CO_2 uptake performance in such scenarios. This is being attributed to the sorption mechanism of MOF-808-AAs, achieved by the introduction of amino acids as presented in the next section.

Mechanistic Studies of CO₂ Chemisorption Using Solid-State NMR. To understand the mechanism of the CO₂ adsorption chemistry of MOF-808-AAs in the presence of water, solid-state cross-polarization magic-angle spinning (CP-MAS) ¹³C and ¹⁵N NMR experiments were conducted on the representative variant MOF-808-Gly to probe the change of chemical species before and after loading of ¹³CO₂, with and without the presence of water (Figure 4, SI Section S10). ¹⁵N-labeled glycine was used for the preparation of ¹⁵N-labeled MOF-808-Gly following the same synthetic and activation procedure. ¹³C and ¹⁵N CP-MAS solid-state NMR (ssNMR) experiments were performed on the resulting sample to establish the composition of the pristine MOF sorbent (Figure 4, bottom). Signals at $\delta^{13}\text{C} = 170.3$ and 133.6 ppm were attributed to the carboxylate and aromatic carbons of the BTC linker, respectively. Glycine ligand signals were found with chemical shifts of $\delta^{13}\text{C} = 179.5$ and 45.2 ppm, attributed to the carboxylate and α -carbons, respectively. ¹⁵N labeling of the α -amino N of the glycinate ligand allowed tracking any changes in its chemical environment, which is key to understanding the chemical nature of the sorption phenomenon. The signals at $\delta^{15}\text{N} = 34.3$ and 27.1 ppm are assigned to the amino groups in the protonated and deprotonated states.

The ¹⁵N-labeled MOF-808-Gly sample was kept in the same rotor and dosed with 98.7 kPa ¹³CO₂ at 25 °C, followed by repeating the CP-MAS ssNMR measurement. In the resulting spectra, signals appearing at $\delta^{13}\text{C} = 169.4$ and 162.5 ppm indicates the formation of carbamic acid (–NHCOOH) and carbamate (–NHCOO[–]) species, along with free CO₂ at $\delta^{13}\text{C} = 121.4$ ppm. This is further confirmed by the emerging signal at $\delta^{15}\text{N} = 79.2$ ppm in the ¹⁵N ssNMR spectrum, while the presence of signals at $\delta^{15}\text{N} = 34.4$ and 27.1 ppm indicate the presence of ammonium species as the counterions of the carbamate as well as unreacted α -amines.

For comparison, a fully activated, ¹⁵N-labeled MOF-808-Gly sample was humidified through exposure to 95% relative humidity in a N₂ atmosphere at 1 atm at 25 °C for 24 h. This was followed by exposure to 90.0 kPa ¹³CO₂ for 24 h prior to CP-MAS ssNMR measurements under the same conditions as the dry sample. The resulting ¹³C NMR spectrum showed that the predominant species exhibited a new signal at $\delta^{13}\text{C} = 167.3$ ppm, which was assigned to ammonium bicarbonate (–NH₃⁺ OCO₂H) species. This was accompanied by a shoulder peak observed at $\delta^{13}\text{C} = 163.1$ ppm, likely indicating small amounts of carbamates and carbamic acids. However, their ¹⁵N ssNMR signals expected around $\delta^{15}\text{N} = 79.2$ ppm were not observed, possibly due to their low population. A single peak was found at $\delta^{15}\text{N} = 31.1$ ppm predominant in the spectrum, which can be attributed to protonated α -ammonium in the glycinate ligands. We thus conclude that the predominant chemisorption product is ammonium bicarbonate.


To further probe the speciation of the sorption process, activation treatment at ambient and elevated temperature was applied to the samples dosed with ¹³CO₂ under dry and humid conditions. ¹⁵N-labeled MOF-808-Gly dosed with ¹³CO₂ in a dry condition was kept in the same rotor and evacuated under dynamic vacuum at room temperature (~25 °C) for 48 h, followed by measurements of CP-MAS ssNMR under the same conditions (Figure S62). Absence of signals around $\delta^{13}\text{C} = 121.4$ ppm, where free or physisorptive ¹³CO₂ was expected, indicated the removal of ¹³CO₂ in the rotor headspace being physisorbed in the MOF. Additionally, we observed relative

attenuation of the signals at $\delta^{13}\text{C} = 169.4$ and 162.5 ppm which we attributed to carbamic acid or carbamate species. Similarly, the signal at $\delta^{15}\text{N} = 79.2$ ppm in the ¹⁵N NMR spectrum was still present, indicating the retention of carbamic acid and carbamate species. This observation was in accordance with the non-zero uptake at very low pressures in the desorption branch of the single-component CO₂ isotherm of MOF-808-Gly, and similar phenomena in other MOF-808-AA variants. In a further step, the same sample (¹⁵N-labeled MOF-808-Gly, ¹³CO₂ dosed, activated at room temperature) was reactivated under dynamic vacuum while heated to 120 °C for 24 h (Figure S62). The resulting ¹³C and ¹⁵N NMR spectra largely resembled the ones measured on pristine ¹⁵N-labeled MOF-808-Gly prior to exposure to CO₂, confirming the requirement of heating to fully regenerate MOF-808-Gly from carbamate or carbamic acid sorption products.

By contrast, vacuum regeneration of ¹⁵N-labeled MOF-808-Gly that was loaded with ¹³CO₂ under a humid condition exhibited considerable bicarbonate removal at ambient temperature (Figure S63), as evidenced by significant attenuation of signals in ssNMR spectra from around $\delta^{13}\text{C} = 167.3$ ppm (bicarbonate) to a set of peaks at $\delta^{13}\text{C} = 168.0$, 165.6 , and 162.0 ppm. In addition, emerging signals at $\delta^{15}\text{N} = 82.8$ ppm further supported that part of the bicarbonate species transformed into carbamate and carbamic acid species during the vacuum regeneration process.

Based on these observations, we propose the overall mechanistic process of CO₂ chemisorption in MOF-808-AAs as summarized in Scheme 1: (1) in dry conditions, CO₂ reacts with amino groups to form carbamates or carbamic acids (1–2 amines to 1 CO₂) which necessarily require heat for regeneration; (2) in humid conditions, CO₂ reacts with amino groups to form carbamates or carbamic acids (1–2 amines to 1 CO₂) with a higher affinity at low CO₂ pressures;²⁰ (3) in humid conditions, where abundant CO₂ is present, CO₂ reacts with amino groups to form mostly bicarbonates (net ~1 amine to 1 CO₂) with a likely equilibrium with carbamic acids and carbamates,^{32,53} which can be reversed through vacuum regeneration

Scheme 1. Proposed Chemisorption Mechanism of CO₂ Uptake in MOF-808-AAs with (Humid) and without (Dry) the Presence of Water

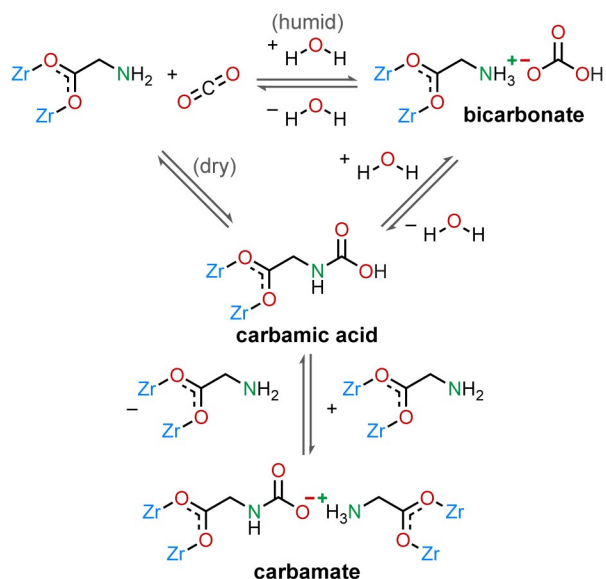

at ambient temperature. We thus hypothesized that the increased stoichiometry of the bicarbonate species formation in abundant CO₂ and humid conditions partly accounts for the enhanced capture performance of MOF-808-AA sorbents. More importantly, we envisioned that their facile vacuum regenerability should enable capturing CO₂ through vacuum swing adsorption under ambient conditions.

Vacuum Swing Adsorption Capture of CO₂ from Simulated Coal Flue Gas. In light of the discoveries above, we were encouraged to probe the practicality of applying MOF-808-AA sorbents in VSA cyclic capture scenarios. Particularly, we expected to utilize the formation of bicarbonate in humid coal flue gas conditions to allow for efficient CO₂ capture while regenerating using vacuum, a low-energy driving force, at ambient temperature. To examine this, the dynamic capture of CO₂ was implemented in an orthogonal packed-bed vacuum swing adsorption setup (detailed in SI Section S11). Cylindrical pellets (6 mm diameter × 5 mm height) were produced through pelletization of pure microcrystalline MOF-808-Gly with a packing density of 0.45 g cm⁻³. Such pellets, weighing 9 g in total, were activated and loaded into a cylindrical sorption bed (35 mm diameter). A simulated coal flue gas composed of 15% CO₂ (RH 20%) balanced with N₂ was passed through at 1 atm, 20–23 °C, and a fixed flow rate of 30 mL min⁻¹.

The adsorption-regeneration process was measured in a cyclic manner. The CO₂ concentration was monitored at the effluent of the sorption bed, and a threshold of 2% was set to switch to vacuum regeneration, which was set for a fixed time. For a typical cycle, the adsorption step lasted 5.9 min, when 6.1 min of vacuum regeneration (~10 Torr) was applied to remove the adsorbed CO₂ and H₂O, which were collected at the exhaust. The cyclic dynamic capture capacity was measured by numerical integration of the effluent CO₂ pressure as 0.42 mmol g⁻¹ h⁻¹, and a continuous monitoring of 80 cycles showed no decay in uptake capacity indicated by the downstream CO₂ concentration profile (Figure S67) and calculated CO₂ uptake capacity per cycle (Figure S68).

CONCLUSIONS

We showed in this work that MOF-808, when functionalized with amino acids where their carboxylate is bound directly to the Zr(IV), produce pores capable of selectively binding CO₂ from flue gas. The amine residues of the amino acid units point to the interior of the pores of the MOF, making them of sufficient affinity for CO₂ to allow the formation of bicarbonate, along with carbamate and carbamic acid. This CO₂ chemistry also allows for the CO₂ to be desorbed without heating. Based on this work, it is clear that creating the right environment in the pores of MOFs for maximization of CO₂ in the form of bicarbonate would contribute greatly to making energy-efficient carbon dioxide adsorption-desorption cycle.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website.

Detailed experimental procedures and data for reported compounds, supplementary figures and tables for characterization, and description of instrumental setups (PDF)

Crystal structure of MOF-808-Gly (CIF)

AUTHOR INFORMATION

Corresponding Author

Omar M. Yaghi — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California, 94720, United States; orcid.org/0000-0002-5611-3325; Email: yaghi@berkeley.edu

Authors

Hao Lyu — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States; orcid.org/0000-0001-7393-2456

Oscar Iu-Fan Chen — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States; orcid.org/0000-0003-4361-0768

Nikita Hanikel — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States; orcid.org/0000-0002-3292-5070

Mohammad I. Hossain — Department of Chemical & Biomolecular Engineering, University of South Alabama, Mobile, Alabama 36688, United States; ORCID: orcid.org/0000-0003-0315-709X

Robinson W. Flaig — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States; orcid.org/0000-0003-3090-4724

Xiaokun Pei — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States; orcid.org/0000-0002-6074-1463

Ameer Amin — Department of Chemistry and Kavli Energy Nanoscience Institute, University of California, Berkeley, Berkeley, California 94720, United States

Mark D. Doherty — GE Global Research, 1 Research Circle, Niskayuna, New York 12309, United States; orcid.org/0000-0003-3090-4724

Rebekah K. Impastato — Department of Chemical & Biomolecular Engineering, University of South Alabama, Mobile, Alabama 36688, United States

T. Grant Glover — Department of Chemical & Biomolecular Engineering, University of South Alabama, Mobile, Alabama 36688, United States; orcid.org/0000-0002-3393-6038

David R. Moore — GE Global Research, 1 Research Circle, Niskayuna, New York 12309, United States

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Notes

Crystallographic data of MOF-808-Gly are also available from the Cambridge Crystallographic Data Centre under the reference number CCDC 2118566.

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark,

manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

ACKNOWLEDGMENT

The synthesis, structure, and CO₂ uptake isotherms of MOF-808-AA compounds are supported by the Department of Energy under Award Number DE-FE0031956. We thank Dr. Ayan Zhumeikenov and Dr. Zhe Ji for their help with materials synthesis, and Dr. Hasan Celik for his support with solid-state NMR measurements. We thank Dr. Eugene A. Kapustin and Mr. Wentao Xu for helpful discussion regarding sorbent synthesis, Dr. Vitali Lissianski and his colleagues at GE Research for insightful discussions concerning materials characterization, and King Abdulaziz City for Science and Technology (KACST) for collaborations. O. I.-F. C. acknowledges financial support from the Taiwan Ministry of Education. N. H. acknowledges the receipt of the Kavli ENSI Philomathia Graduate Student Fellowship and thanks the Studienstiftung des deutschen Volkes. T. G. G., M. I. H., and R. K. I. acknowledge financial support from the NASA Cooperative Agreement Notice NNNH16ZHA001C Experimental Program to Stimulate Competitive Research under contract NNX16AT47A and the Alabama Space Grant Consortium Fellowship Program. This research used resources of Beamline 12.2.1 of the Advanced Light Source, a U.S. DOE Office of Science User Facility under contract no. DE-AC02-05CH11231. The NMR facility in the College of Chemistry at UC Berkeley is supported in part by NIH S10OD024998.

REFERENCES

- Bui, M.; Adjiman, C. S.; Bardow, A.; Anthony, E. J.; Boston, A.; Brown, S.; Fennell, P. S.; Fuss, S.; Galindo, A.; Hackett, L. A.; Hallett, J. P.; Herzog, H. J.; Jackson, G.; Kemper, J.; Krevor, S.; Maitland, G. C.; Matuszewski, M.; Metcalfe, I. S.; Petit, C.; Puxty, G.; Reimer, J.; Reiner, D. M.; Rubin, E. S.; Scott, S. A.; Shah, N.; Smit, B.; Trusler, J. P. M.; Webley, P.; Wilcox, J.; Mac Dowell, N. Carbon Capture and Storage (CCS): The Way Forward. *Energy Environ. Sci.* **2018**, *11* (5), 1062–1176. <https://doi.org/10.1039/C7EE02342A>.
- DOE/NETL Capture Program R&D: Compendium of Carbon Capture Technology; U.S. Department of Energy; National Energy Technology Laboratory, 2020.
- Fisher, K. S.; Beitler, C.; Rueter, C.; Searcy, K.; Rochelle, G.; Jassim, M. Integrating MEA Regeneration with CO₂ Compression and Peaking to Reduce CO₂ Capture Costs; DOE/ER/84111; Trimeric Corporation, 2005. <https://doi.org/10.2172/842857>.
- Rochelle, G. T. Amine Scrubbing for CO₂ Capture. *Science* **2009**, *325* (5948), 1652–1654. <https://doi.org/10.1126/science.1176731>.
- Knudsen, J. N.; Jensen, J. N.; Vilhelmsen, P.-J.; Biede, O. Experience with CO₂ Capture from Coal Flue Gas in Pilot-Scale: Testing of Different Amine Solvents. *Energy Procedia* **2009**, *1* (1), 783–790. <https://doi.org/10.1016/j.egypro.2009.01.104>.
- Ramezani, R.; Mazinani, S.; Felice, R. D. State-of-the-Art of CO₂ Capture with Amino Acid Salt Solutions. *Rev. Chem. Eng.* **2020**. <https://doi.org/10.1515/revce-2020-0012>.
- Samanta, A.; Zhao, A.; Shimizu, G. K. H.; Sarkar, P.; Gupta, R. Post-Combustion CO₂ Capture Using Solid Sorbents: A Review. *Ind. Eng. Chem. Res.* **2012**, *51* (4), 1438–1463. <https://doi.org/10.1021/ie200686q>.
- Wang, Q.; Luo, J.; Zhong, Z.; Borgna, A. CO₂ Capture by Solid Adsorbents and Their Applications: Current Status and New Trends. *Energy Environ. Sci.* **2010**, *4* (1), 42–55. <https://doi.org/10.1039/C0EE00064G>.
- Wang, J.; Huang, L.; Yang, R.; Zhang, Z.; Wu, J.; Gao, Y.; Wang, Q.; O'Hare, D.; Zhong, Z. Recent Advances in Solid Sorbents for CO₂ Capture and New Development Trends. *Energy Environ. Sci.* **2014**, *7* (11), 3478–3518. <https://doi.org/10.1039/C4EE01647E>.
- Raganati, F.; Miccio, F.; Ammendola, P. Adsorption of Carbon Dioxide for Post-Combustion Capture: A Review. *Energy Fuels* **2021**, *35* (16), 12845–12868. <https://doi.org/10.1021/acs.energyfuels.1c01618>.
- Lozinska, M. M.; Mangano, E.; Mowat, J. P. S.; Shepherd, A. M.; Howe, R. F.; Thompson, S. P.; Parker, J. E.; Brandani, S.; Wright, P. A. Understanding Carbon Dioxide Adsorption on Univalent Cation Forms of the Flexible Zeolite Rho at Conditions Relevant to Carbon Capture from Flue Gases. *J. Am. Chem. Soc.* **2012**, *134* (42), 17628–17642. <https://doi.org/10.1021/ja3070864>.
- Xu, X.; Song, C.; Andresen, J. M.; Miller, B. G.; Scaroni, A. W. Novel Polyethylenimine-Modified Mesoporous Molecular Sieve of MCM-41 Type as High-Capacity Adsorbent for CO₂ Capture. *Energy Fuels* **2002**, *16* (6), 1463–1469. <https://doi.org/10.1021/ef020058u>.
- Wurzbacher, J. A.; Gebald, C.; Steinfeld, A. Separation of CO₂ from Air by Temperature-Vacuum Swing Adsorption Using Diamine-Functionalized Silica Gel. *Energy Environ. Sci.* **2011**, *4* (9), 3584. <https://doi.org/10.1039/c1ee01681d>.
- Choi, W.; Min, K.; Kim, C.; Ko, Y. S.; Jeon, J. W.; Seo, H.; Park, Y.-K.; Choi, M. Epoxide-Functionalization of Polyethyleneimine for Synthesis of Stable Carbon Dioxide Adsorbent in Temperature Swing Adsorption. *Nat. Commun.* **2016**, *7* (1), 12640. <https://doi.org/10.1038/ncomms12640>.
- Krishnamurthy, S.; Boon, J.; Grande, C.; Lind, A.; Blom, R.; de Boer, R.; Willemssen, H.; de Scheemaker, G. Screening Supported Amine Sorbents in the Context of Post-Combustion Carbon Capture by Vacuum Swing Adsorption. *Chem. Ing. Tech.* **2021**, *93* (6), 929–940. <https://doi.org/10.1002/cite.202000172>.
- Alesi, W. R.; Kitchin, J. R. Evaluation of a Primary Amine-Functionalized Ion-Exchange Resin for CO₂ Capture. *Ind. Eng. Chem. Res.* **2012**, *51* (19), 6907–6915. <https://doi.org/10.1021/ie300452c>.
- Veneman, R.; Frigka, N.; Zhao, W.; Li, Z.; Kersten, S.; Brilman, W. Adsorption of H₂O and CO₂ on Supported Amine Sorbents. *Int. J. Greenh. Gas Control* **2015**, *41*, 268–275. <https://doi.org/10.1016/j.jggcc.2015.07.014>.
- Zeng, Y.; Zou, R.; Zhao, Y. Covalent Organic Frameworks for CO₂ Capture. *Adv. Mater.* **2016**, *28* (15), 2855–2873. <https://doi.org/10.1002/adma.201505004>.
- Ding, M.; Flaig, R. W.; Jiang, H. L.; Yaghi, O. M. Carbon Capture and Conversion Using Metal-Organic Frameworks and MOF-Based Materials. *Chem. Soc. Rev.* **2019**, *48* (10), 2783–2828. <https://doi.org/10.1039/c8cs00829a>.
- Flaig, R. W.; Osborn Popp, T. M.; Fracaroli, A. M.; Kapustin, E. A.; Kalmutzki, M. J.; Altamimi, R. M.; Fathieh, F.; Reimer, J. A.; Yaghi, O. M. The Chemistry of CO₂ Capture in an Amine-Functionalized Metal-Organic Framework under Dry and Humid Conditions. *J. Am. Chem. Soc.* **2017**, *139* (35), 12125–12128. <https://doi.org/10.1021/jacs.7b06382>.
- Kim, E. J.; Siegelman, R. L.; Jiang, H. Z. H.; Forse, A. C.; Lee, J.-H.; Martell, J. D.; Milner, P. J.; Falkowski, J. M.; Neaton, J. B.; Reimer, J. A.; Weston, S. C.; Long, J. R. Cooperative Carbon Capture and Steam Regeneration with Tetraamine-Appended Metal-Organic Frameworks. *Science* **2020**, *369* (6502), 392–396. <https://doi.org/10.1126/science.abb3976>.
- Bhatt, P. M.; Belmabkhout, Y.; Cadiau, A.; Adil, K.; Shekhah, O.; Shkurenko, A.; Barbour, L. J.; Eddaoudi, M. A Fine-Tuned Fluorinated MOF Addresses the Needs for Trace CO₂ Removal and Air Capture Using Physisorption. *J. Am. Chem. Soc.* **2016**, *138* (29), 9301–9307. <https://doi.org/10.1021/jacs.6b05345>.
- Lin, J.-B.; Nguyen, T. T. T.; Vaidhyanathan, R.; Burner, J.; Taylor, J. M.; Durekova, H.; Akhtar, F.; Mah, R. K.; Ghaffari-Nik, O.; Marx, S.;

- Fylstra, N.; Iremonger, S. S.; Dawson, K. W.; Sarkar, P.; Hovington, P.; Rajendran, A.; Woo, T. K.; Shimizu, G. K. H. A Scalable Metal-Organic Framework as a Durable Physisorbent for Carbon Dioxide Capture. *Science* **2021**, 374 (6574), 1464–1469. <https://doi.org/10.1126/science.abi7281>.
- (24) Adil, K.; Bhatt, P. M.; Belmabkhout, Y.; Abtab, S. M. T.; Jiang, H.; Assen, A. H.; Mallick, A.; Cadiau, A.; Aqil, J.; Eddaoudi, M. Valuing Metal-Organic Frameworks for Postcombustion Carbon Capture: A Benchmark Study for Evaluating Physical Adsorbents. *Adv. Mater.* **2017**, 29 (39), 1702953. <https://doi.org/10.1002/adma.201702953>.
- (25) Min, K.; Choi, W.; Kim, C.; Choi, M. Oxidation-Stable Amine-Containing Adsorbents for Carbon Dioxide Capture. *Nat. Commun.* **2018**, 9 (1), 726. <https://doi.org/10.1038/s41467-018-03123-0>.
- (26) Lashaki, M. J.; Khiavi, S.; Sayari, A. Stability of Amine-Functionalized CO₂ Adsorbents: A Multifaceted Puzzle. *Chem. Soc. Rev.* **2019**, 48 (12), 3320–3405. <https://doi.org/10.1039/C8CS00877A>.
- (27) Perry, R. J.; Rainka, M. P.; Doherty, M. D.; Wood, B. R.; Namjoshi, O.; Hatchell, D.; Liu, H.; Rochelle, G. T. Thermal Degradation of Amino-silicone Carbamates. *Energy Fuels* **2016**, 30 (12), 10671–10678. <https://doi.org/10.1021/acs.energyfuels.6b02284>.
- (28) Siegelman, R. L.; Kim, E. J.; Long, J. R. Porous Materials for Carbon Dioxide Separations. *Nat. Mater.* **2021**, 20 (8), 1060–1072. <https://doi.org/10.1038/s41563-021-01054-8>.
- (29) Hepburn, C.; Adlen, E.; Beddington, J.; Carter, E. A.; Fuss, S.; Mac Dowell, N.; Minx, J. C.; Smith, P.; Williams, C. K. The Technological and Economic Prospects for CO₂ Utilization and Removal. *Nature* **2019**, 575 (7781), 87–97. <https://doi.org/10.1038/s41586-019-1681-6>.
- (30) Zimmermann, A. W.; Wunderlich, J.; Müller, L.; Buchner, G. A.; Marxen, A.; Michailos, S.; Armstrong, K.; Naims, H.; McCord, S.; Styling, P.; Sick, V.; Schomäcker, R. Techno-Economic Assessment Guidelines for CO₂ Utilization. *Front. Energy Res.* **2020**, 8, 5. <https://doi.org/10.3389/fenrg.2020.00005>.
- (31) Fracaroli, A. M.; Furukawa, H.; Suzuki, M.; Dodd, M.; Okajima, S.; Gándara, F.; Reimer, J. A.; Yaghi, O. M. Metal-Organic Frameworks with Precisely Designed Interior for Carbon Dioxide Capture in the Presence of Water. *J. Am. Chem. Soc.* **2014**, 136 (25), 8863–8866. <https://doi.org/10.1021/ja503296c>.
- (32) Cao, Y.; Song, F.; Zhao, Y.; Zhong, Q. Capture of Carbon Dioxide from Flue Gas on TEPA-Grafted Metal-Organic Framework Mg₂(dobdc). *J. Environ. Sci.* **2013**, 25 (10), 2081–2087. [https://doi.org/10.1016/S1001-0742\(12\)60267-8](https://doi.org/10.1016/S1001-0742(12)60267-8).
- (33) McDonald, T. M.; Lee, W. R.; Mason, J. A.; Wiers, B. M.; Hong, C. S.; Long, J. R. Capture of Carbon Dioxide from Air and Flue Gas in the Alkylamine-Appended Metal-Organic Framework mmen-Mg₂(dobpdc). *J. Am. Chem. Soc.* **2012**, 134 (16), 7056–7065. <https://doi.org/10.1021/ja300034j>.
- (34) McDonald, T. M.; Mason, J. A.; Kong, X.; Bloch, E. D.; Gygi, D.; Dani, A.; Crocellà, V.; Giordanino, F.; Odoh, S. O.; Drisdell, W. S.; Vlaisavljevich, B.; Dzubak, A. L.; Poloni, R.; Schnell, S. K.; Planas, N.; Lee, K.; Pascal, T.; Wan, L. F.; Prendergast, D.; Neaton, J. B.; Smit, B.; Kortright, J. B.; Gagliardi, L.; Bordiga, S.; Reimer, J. A.; Long, J. R. Co-operative Insertion of CO₂ in Diamine-Appended Metal-Organic Frameworks. *Nature* **2015**, 519 (7543), 303–308. <https://doi.org/10.1038/nature14327>.
- (35) Milner, P. J.; Martell, J. D.; Siegelman, R. L.; Gygi, D.; Weston, S. C.; Long, J. R. Overcoming Double-Step CO₂ Adsorption and Minimizing Water Co-Adsorption in Bulky Diamine-Appended Variants of Mg₂(dobpdc). *Chem. Sci.* **2017**, 9 (1), 160–174. <https://doi.org/10.1039/C7SC04266C>.
- (36) Siegelman, R. L.; Milner, P. J.; Forse, A. C.; Lee, J.-H.; Colwell, K. A.; Neaton, J. B.; Reimer, J. A.; Weston, S. C.; Long, J. R. Water Enables Efficient CO₂ Capture from Natural Gas Flue Emissions in an Oxidation-Resistant Diamine-Appended Metal-Organic Framework. *J. Am. Chem. Soc.* **2019**, 141 (33), 13171–13186. <https://doi.org/10.1021/jacs.9b05567>.
- (37) Queen, W. L.; Hudson, M. R.; Bloch, E. D.; Mason, J. A.; Gonzalez, M. I.; Lee, J. S.; Gygi, D.; Howe, J. D.; Lee, K.; Darwish, T. A.; James, M.; Peterson, V. K.; Teat, S. J.; Smit, B.; Neaton, J. B.; Long, J. R.; Brown, C. M. Comprehensive Study of Carbon Dioxide Adsorption in the Metal-Organic Frameworks M₂(dobdc) (M = Mg, Mn, Fe, Co, Ni, Cu, Zn). *Chem. Sci.* **2014**, 5 (12), 4569–4581. <https://doi.org/10.1039/C4SC02064B>.
- (38) Furukawa, H.; Gándara, F.; Zhang, Y.-B.; Jiang, J.; Queen, W. L.; Hudson, M. R.; Yaghi, O. M. Water Adsorption in Porous Metal-Organic Frameworks and Related Materials. *J. Am. Chem. Soc.* **2014**, 136 (11), 4369–4381. <https://doi.org/10.1021/ja500330a>.
- (39) Vlaisavljevich, B.; Odoh, S. O.; Schnell, S. K.; Dzubak, A. L.; Lee, K.; Planas, N.; Neaton, J. B.; Gagliardi, L.; Smit, B. CO₂ Induced Phase Transitions in Diamine-Appended Metal-Organic Frameworks. *Chem. Sci.* **2015**, 6 (9), 5177–5185. <https://doi.org/10.1039/C5SC01828E>.
- (40) Choi, S.; Watanabe, T.; Bae, T.-H.; Sholl, D. S.; Jones, C. W. Modification of the Mg/DOBDC MOF with Amines to Enhance CO₂ Adsorption from Ultradilute Gases. *J. Phys. Chem. Lett.* **2012**, 3 (9), 1136–1141. <https://doi.org/10.1021/jz300328j>.
- (41) Kreutzer, J.; Blaha, P.; Schubert, U. Assessment of Different Basis Sets and DFT Functionals for the Calculation of Structural Parameters, Vibrational Modes and Ligand Binding Energies of Zr₄O₂(Carboxylate)₁₂ Clusters. *Comput. Theor. Chem.* **2016**, 1084, 162–168. <https://doi.org/10.1016/j.comptc.2016.03.030>.
- (42) Pirngruber, G. D.; Carlier, V.; Leinekugel-Cocq, D. Post-Combustion CO₂ Capture by Vacuum Swing Adsorption Using Zeolites – a Feasibility Study. *Oil Gas Sci. Technol. – Rev. D'IFP Energ. Nouv.* **2014**, 69 (6), 989–1003. <https://doi.org/10.2516/ogst/2012067>.
- (43) Krishnamurthy, S.; Rao, V. R.; Guntuka, S.; Sharratt, P.; Haghpanah, R.; Rajendran, A.; Amanullah, M.; Karimi, I. A.; Farooq, S. CO₂ Capture from Dry Flue Gas by Vacuum Swing Adsorption: A Pilot Plant Study. *AIChE J.* **2014**, 60 (5), 1830–1842. <https://doi.org/10.1002/aic.14435>.
- (44) Jiang, J.; Gándara, F.; Zhang, Y.-B.; Na, K.; Yaghi, O. M.; Klemperer, W. G. Superacidity in Sulfated Metal-Organic Framework-808. *J. Am. Chem. Soc.* **2014**, 136 (37), 12844–12847. <https://doi.org/10.1021/ja507119n>.
- (45) Lide, D. R. *CRC Handbook of Chemistry and Physics: A Ready-Reference Book of Chemical and Physical Data*, 72nd ed. (1991-92 ed.); CRC Press: Boca Raton, FL, 1991.
- (46) Dawson, R. M. C. *Data for Biochemical Research*; Clarendon Press: Oxford, 1959.
- (47) Brownson, J. R. S.; Tejedor-Tejedor, M. I.; Anderson, M. A. FTIR Spectroscopy of Alcohol and Formate Interactions with Mesoporous TiO₂ Surfaces. *J. Phys. Chem. B* **2006**, 110 (25), 12494–12499. <https://doi.org/10.1021/jp0614547>.
- (48) Ji, P.; Solomon, J. B.; Lin, Z.; M. Wilders, A.; Jordan, R. F.; Lin, W. Transformation of Metal-Organic Framework Secondary Building Units into Hexanuclear Zr-Alkyl Catalysts for Ethylene Polymerization. *J. Am. Chem. Soc.* **2017**, 139 (33), 11325–11328. <https://doi.org/10.1021/jacs.7b05761>.
- (49) Zheng, H.-Q.; Liu, C.-Y.; Zeng, X.-Y.; Chen, J.; Lü, J.; Lin, R.-G.; Cao, R.; Lin, Z.-J.; Su, J.-W. MOF-808: A Metal-Organic Framework with Intrinsic Peroxidase-Like Catalytic Activity at Neutral pH for Colorimetric Biosensing. *Inorg. Chem.* **2018**, 57 (15), 9096–9104. <https://doi.org/10.1021/acs.inorgchem.8b01097>.
- (50) Formic acid, sodium salt <https://webbook.nist.gov/cgi/cbook.cgi?ID=B6010183&Units=SI&Mask=80#IR-Spec> (accessed 2021-07-31).
- (51) Hossain, M. I.; Cunningham, J. D.; Becker, T. M.; Grabicka, B. E.; Walton, K. S.; Rabideau, B. D.; Glover, T. G. Impact of MOF Defects on

- the Binary Adsorption of CO₂ and Water in UiO-66. *Chem. Eng. Sci.* **2019**, 203, 346–357. <https://doi.org/10.1016/j.ces.2019.03.053>.
- (52) Toth, J. State Equation of the Solid-Gas Interface Layers. *Acta Chim. Acad. Sci. Hung.* **1971**, 69 (3), 311–328.
- (53) Vaidya, P. D.; Kenig, E. Y. CO₂-Alkanolamine Reaction Kinetics: A Review of Recent Studies. *Chem. Eng. Technol.* **2007**, 30 (11), 1467–1474. <https://doi.org/10.1002/ceat.200700268>.

Table of Contents (TOC)

