

# High Entropy Electrolytes for Practical Lithium Metal Batteries

Sang Cheol Kim<sup>1‡</sup>, Jingyang Wang<sup>1‡</sup>, Rong Xu<sup>1</sup>, Pu Zhang<sup>1</sup>, Yuelang Chen<sup>2</sup>, Zhuojun Huang<sup>1</sup>, Yufei Yang<sup>1</sup>, Zhiao Yu<sup>2</sup>, Solomon T. Oyakhire<sup>3</sup>, Wenbo Zhang<sup>1</sup>, Mun Sek Kim<sup>3</sup>, David T. Boyle<sup>2</sup>, Philaphon Sayavong<sup>2</sup>, Jian Qin<sup>3</sup>, Zhenan Bao<sup>3</sup>, Yi Cui<sup>1,4,5\*</sup>

<sup>1</sup>Department of Materials Science and Engineering, Stanford University, Stanford, California 94305, USA.

<sup>2</sup>Department of Chemistry, Stanford University, Stanford, California 94305, USA.

<sup>3</sup>Department of Chemical Engineering, Stanford University, Stanford, California 94305, USA.

<sup>4</sup>Department of Energy Science and Engineering, Stanford University, Stanford, California 94305, USA.

<sup>5</sup>Stanford Institute for Materials and Energy Sciences, SLAC National Accelerator Laboratory, 2575 Sand Hill Road, Menlo Park, California 94025, USA.

‡ denotes equal contribution

\*Correspondence to: Y. C., yicui@stanford.edu

**Electrolyte engineering is a critical approach to improve battery performance, particularly for lithium metal batteries. In this work, we introduce the concept of high entropy electrolytes (HEEs) that achieve improved ionic conductivity while maintaining excellent electrochemical stability. We find that increasing the molecular diversity and concomitantly the mixing entropy of weakly solvating electrolytes can reduce ion clustering while retaining anion-rich solvation structure, confirmed through synchrotron-based X-ray scattering and molecular dynamics simulations. Less clustered electrolytes exhibit higher diffusivity and ionic conductivity, enabling high current density cycling up to 2C (> 6 mA cm<sup>-2</sup>) for up to ~80 cycles in anode-free NMC-Cu pouch cells. We substantiate the generality of the concept by verifying performance improvement in three disparate electrolyte systems. This work highlights a large unexplored design space of HEEs that can improve electrolyte properties for lithium metal batteries.**


Following the demonstration of the Li || TiS<sub>2</sub> battery chemistry by Whittingham in the 1970's,<sup>1</sup> the Li metal anode has been sought-after for its high theoretical capacity and low redox potential.<sup>2,3</sup> However, its problems in safety and cycle life led to the development of carbonaceous anodes that are now the commercially dominant anode technology.<sup>4</sup> Three decades after the first commercialization of lithium-ion batteries, lithium metal batteries have been revitalized as a viable technology<sup>2</sup> with the aid of nanoengineering,<sup>2,5</sup> solid electrolytes,<sup>6,7</sup> and particularly liquid electrolyte engineering.<sup>8-15</sup> Novel liquid electrolytes including localized high concentration electrolytes (LHCEs) and single-salt-single-solvent electrolytes (4SEs) have dramatically improved stability with Li metal anodes and high-voltage cathodes.<sup>3</sup>

Solvation has proven to be central to the stabilization of liquid electrolytes for Li metal batteries. Through molecular design and the use of highly fluorinated co-solvents, weakly solvating electrolytes

with anion-rich  $\text{Li}^+$  solvation structures have achieved superior interfacial stability and cycle life.<sup>9-11,16,17</sup> However, most weakly solvating electrolytes show compromised ionic conductivities compared to conventional carbonate and ether electrolytes<sup>8,10,25-27,17-24</sup> (Supplementary Fig. 1, Supplementary Table 1), limiting the battery's high-rate cycling capabilities (Supplementary Fig. 2, Supplementary Table 2).<sup>9,10,13,28-33</sup> An interesting finding is that weakly solvating electrolytes with comparable salt concentrations show similar viscosities to conventional electrolytes, implying that viscosity is unlikely to be the driver of the discrepancies in conductivity (Supplementary Fig. 1). As will be discussed extensively in this study, we hypothesize that conductivities are intricately related with mesoscopic solvation structures including  $\text{Li}^+$  clusters; increased clustering of ions due to poor ion dissociation in weakly solvating electrolytes<sup>34,35</sup> is expected to increase the hydrodynamic radius and hinder transport.<sup>27</sup> These weakly solvating electrolytes that form ion clusters possess improved electrochemical stability at the cost of ion conductivity, while strongly solvating electrolytes have high conductivity but poor stability, implying a trade-off in tuning solvation strength (Supplementary Fig. 3).

While many strategies have relied on tuning the enthalpic interactions between  $\text{Li}^+$  and its surrounding species,<sup>8,10,12,15,17,29</sup> entropy as a design knob has largely gone unnoticed for liquid electrolytes. In high entropy alloys and ceramics, entropic driving forces are exploited to modulate structure and phase behavior.<sup>36</sup> In these systems, the presence of a large number of components significantly increases the configurational entropic contribution to the free energy, thereby suppressing ordering in favor of mixing.<sup>37</sup> By utilizing this design principle, unexpected properties that surpass the averaged properties of the components can be attained.<sup>38</sup> The high entropy design concept has been applied to catalysts, thermoelectrics, corrosion-resistant materials and battery materials<sup>36,38</sup>, such as novel battery cathodes<sup>37,39</sup> and solid electrolytes<sup>40</sup> with superior electrochemical properties.

In this work, we introduce the high entropy concept to weakly solvating liquid electrolytes to improve ion transport capabilities without compromising stability with high voltage cathodes and Li metal anodes (Supplementary Fig. 4-5). We design high entropy electrolytes (HEEs) with increased mixing entropy by increasing molecular diversity (Fig. 1a). High entropy electrolytes are shown to have a two-fold increase in ionic conductivity and can stably cycle up to 2C ( $\sim 6.3 \text{ mA cm}^{-2}$ ) charging and discharging in high voltage anode-free Li metal batteries. Through a host of advanced characterizations including synchrotron-based X-ray scattering, we find that ion cluster sizes decrease with an increasing number of solvents. (Fig. 1b). This is attributed to higher mixing entropies driving the thermodynamic equilibrium to favor mixing and suppress clustering. HEEs with smaller ion clusters have improved diffusivity compared to low entropy electrolytes (LEEs), which mitigates concentration gradients during high-rate cycling and allows for denser and more uniform deposition morphologies (Fig. 1c). Lastly, we demonstrate the generality of the HEE concept by applying it to fluorinated ether electrolytes and carbonate-based LHCEs. We propose that molecular diversity to modulate the mixing entropy and tune the mesoscopic solvation structure can be a design strategy to improve ionic conductivity of advanced weakly solvating electrolytes.

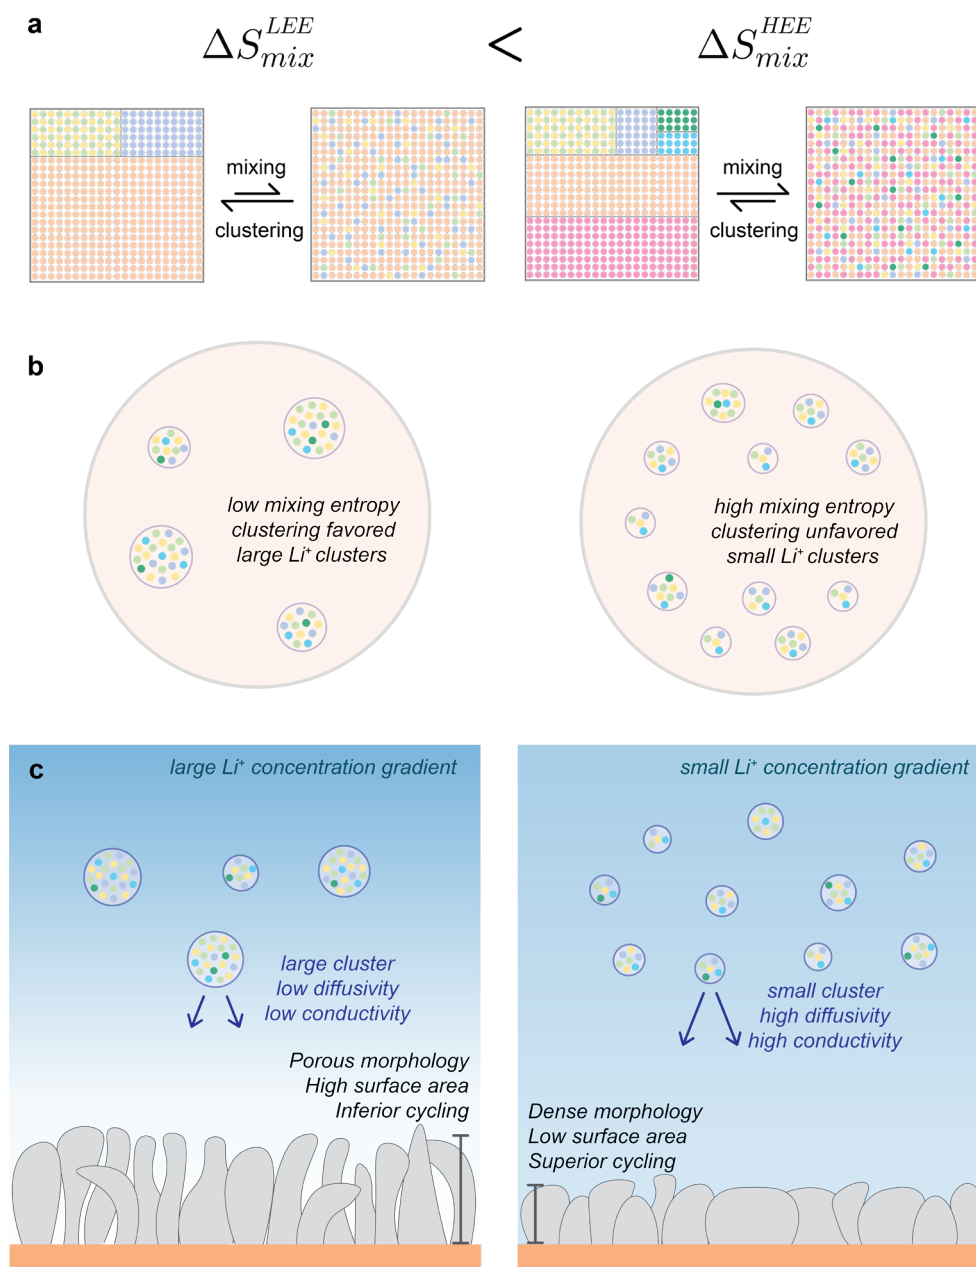

**Fig. 1. Design framework for HEEs.** **a**, Molecular diversity of HEE increases  $\Delta S_{mix}$ , which shifts the thermodynamic equilibrium to promote mixing and suppress clustering. **b**, HEE has smaller ion clusters than LEE. **c**, HEE with smaller ion clusters exhibits higher diffusivity and conductivity that leads to a smaller  $\text{Li}^+$  concentration gradient and a denser Li deposition morphology during high-rate cycling.

## Electrolyte Design and Electrochemical Performance

To investigate the effect of entropy on solvation structure, ionic conductivity and battery performance, we aim to systematically change entropy while maintaining similar enthalpic interactions. A route to increasing entropy is increasing the molecular diversity, analogous to increasing the number of elements in high-entropy materials.<sup>36–38</sup> To minimize differences in enthalpic interaction, however, we select structurally similar solvent compounds with comparable interactions with  $\text{Li}^+$  and design three


electrolytes with different number of solvents. EL2 (1 M LiFSI in DME-TTE), which consists of dimethoxyethane (DME) as the solvent and 1,1,2,2-tetrafluoroethyl-2,2,3,3-tetrafluoropropyl ether (TTE) as the co-solvent (Fig. 2a-b, Supplementary Table 3), is an LHCE inspired from the works of Zhang and coworkers.<sup>9,28</sup> This pair of solvent and co-solvent, together with lithium bis(fluorosulfonyl)imide (LiFSI) salt, was reported as one of the best solvent mixtures through systematic studies<sup>16,23</sup>, and showcases one of the best performances for lithium metal batteries<sup>9,28</sup>. EL4 (1 M LiFSI DME-DEE-DEGDME-TTE) uses 3 solvents and a co-solvent; diethoxyethane (DEE) and diethylene glycol dimethyl ether (DEGDME) and DME are used as solvents, with TTE as the co-solvent. DEE and DEGDME are both glymes structurally similar to DME, with DEE containing two ethyl groups in place of methyl groups, and DEGDME containing an additional glyme functional group (Fig. 2a, Supplementary Table 3). EL5 (1 M LiFSI DME-DEE-DEGDME-TTE-BTFE), compared to EL4, has an additional fluorinated ether co-solvent bis(2,2,2-trifluoroethyl) ether (BTFE), which mimics TTE in diluting the electrolyte (Fig. 2b). All electrolytes contain 10% v/v of solvent and 90% v/v of co-solvent (Supplementary Table 3). By deploying chemically similar compounds without changing the solvent to co-solvent ratio, we expect that the nature of intermolecular interactions between solvents, Li<sup>+</sup> and anions to be similar across all electrolytes—which we experimentally confirm later in the discussion—while modulating the entropy of the system.

Fig. 2c and Supplementary Fig. 6 show the ionic conductivities of the three electrolytes, where EL5 shows a remarkable 2-fold increase in conductivity compared to EL2. This result is particularly interesting as the viscosities of the electrolytes do not differ appreciably (Supplementary Fig. 7). Fig. 2d shows the impedance spectra of Li-Cu cells after Li deposition of 1 mAh cm<sup>-2</sup> onto the Cu electrodes. It shows that the bulk resistance plays a significant part in the overall impedance in all samples, and the bulk resistance decreases in the order of EL2-EL4-EL5, further validating the ionic conductivity results (Supplementary Fig. 8). Fig. 2e shows the Li-Cu Coulombic efficiency measurement results (Supplementary Fig. 9, Supplementary Table 4). At 0.5 mA cm<sup>-2</sup>, all three electrolytes show excellent CEs around 99.5%, and differences in CE across the three electrolytes are negligible. However, at higher current densities of 1 mA cm<sup>-2</sup>, the CE of EL2 with lower ionic conductivity shows a significant drop below 98%, whereas EL5 is able to retain 99.4%.

The differences in ionic conductivity and Li || Cu CE translate into cycling performances. Figure 2f-h show NMC532-Cu anode-free pouch cells cycled from 3.0 V to 4.4 V at various c-rates (Supplementary Table 5). At 0.2C charging and 0.5C discharging rates, which are in the range of regularly reported conditions, cyclability increases in the order of EL2-EL4-EL5, where EL5 shows anode-free cycling of 110 cycles at 70% capacity retention (Fig. 2f). This effect is magnified at increased rates of 1C charging and 1.5C discharging, where EL5 shows the highest initial capacity and cycling stability (Fig. 2g). At the fast rates of 2C charging and 2C discharging, EL2 and EL4 have limited initial capacity that quickly decay, while EL5 can cycle for almost 80 cycles at 70% capacity retention (Fig. 2h). Overpotential seems to be coupled with capacity retention, as EL5 shows the lowest cycling polarization (Fig. 2f-h) and overpotentials (Fig. 2i-k) at all three c-rates. This coupling between cycling stability and polarization will be explored in depth later in this work (Fig. 4).

To verify the effects of each solvent, we conducted cycling and ionic conductivity characterization for all possible LHCE from combining 3 solvents and 2 co-solvents. In Supplementary Fig. 10 we see that while different solvents have, to a certain degree, different effects, it is evident that EL5 exhibits performances that cannot be achieved by using any of the single-solvent-single-co-solvent mixtures. In addition, we also observe improved oxidative stability for electrolytes with increased number of solvents (Supplementary Fig. 11). Overall, we discover that EL5 with increased molecular diversity has an improved ionic conductivity which correlates with superior full cell cycling and Li-Cu CE, particularly at higher current densities, and this improvement is unattainable with low molecular diversity. We further validate that these findings hold true to other electrolyte systems in the final section

of this study (Fig. 5).

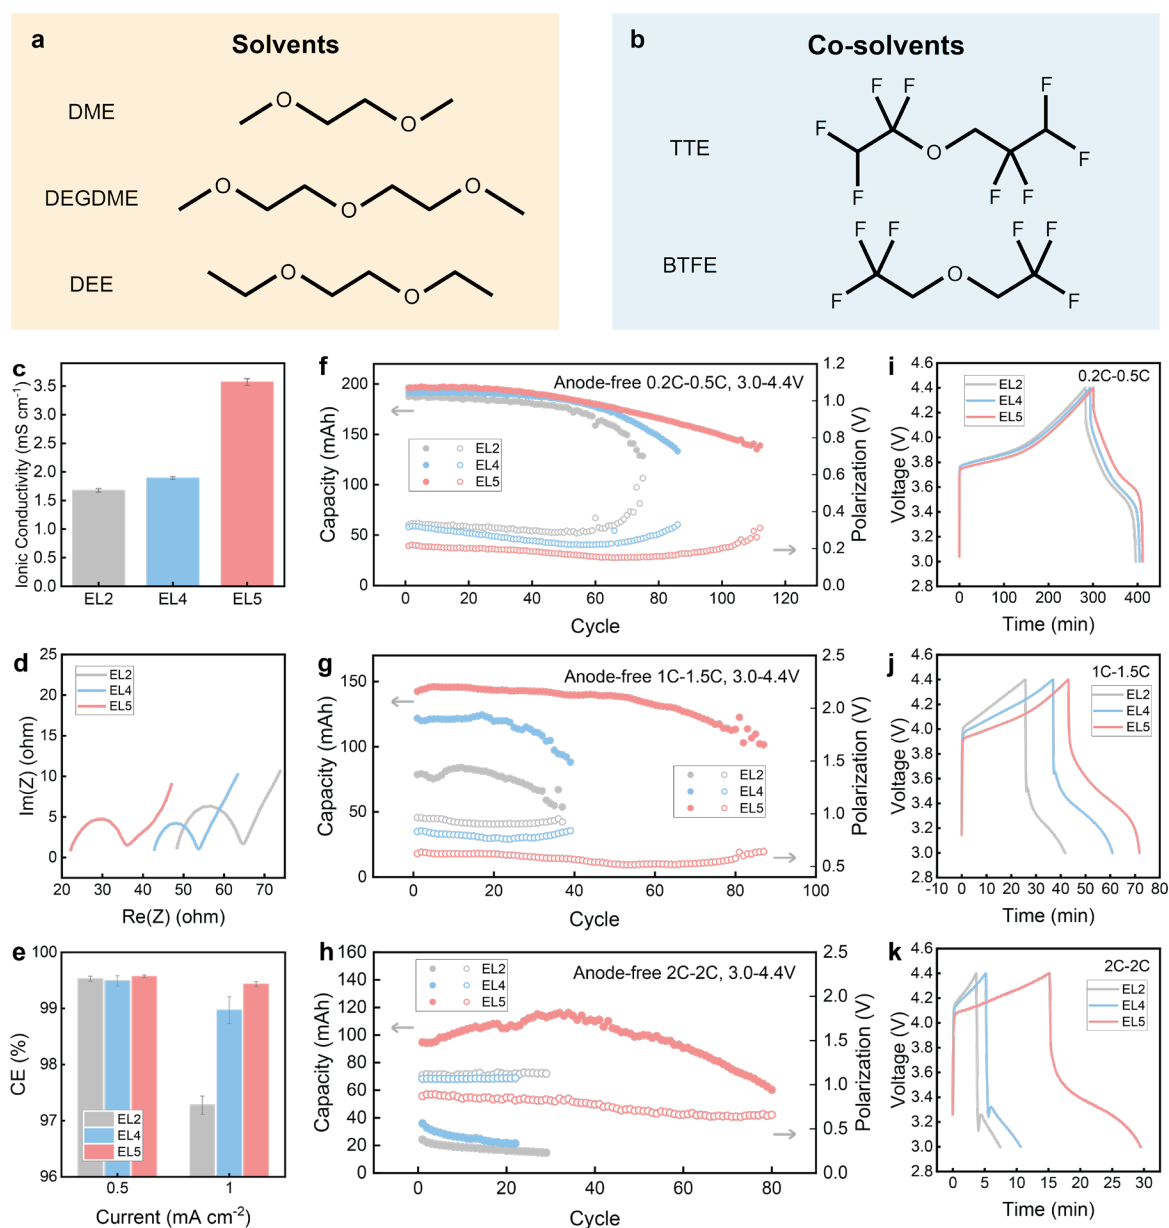

**Fig. 2. Electrochemical Performance of HEEs.** **a-b**, Chemical structures of the solvents and co-solvents. **c**, Ionic conductivities increase with increasing number of solvents. **d**, Impedance spectra shows decreased bulk impedance with increasing number of solvents. **e**, Li || Cu Coulombic efficiencies are similar for all electrolytes at 0.5  $\text{mA cm}^{-2}$  but show decreased efficiencies for EL2 at 1  $\text{mA cm}^{-2}$ . **f-h**, Anode-free NMC532-Cu pouch cell cycling at 3.0-4.4V for different current densities, showing lower polarization and more stable cycling with increased molecular diversity. **i-k**, Voltage profiles of the 1<sup>st</sup> cycle during pouch cell cycling showing lower overpotential with increased molecular diversity.

### Microscopic and Mesoscopic Solvation Structure

We observed greatly improved ionic conductivity for EL5 compared to EL2. To gain molecular-level

insights behind the differences in conductivity, we investigated the microscopic ( $\text{\AA}$  length scales) and mesoscopic solvation structures (nm length scales) through large-scale MD simulations (Supplementary Fig. 12). First, we analyze the microscopic Li coordination environment, where Fig. 3a-c show the cumulative distribution functions around the  $\text{Li}^+$  for the three electrolytes. It is evident that all three electrolytes have anion-rich solvation structures, containing approximately 3 anions and 1 solvent molecules in the first solvation shell. It can be noticed that the co-solvents (TTE and BTFE) do not populate the first solvation shell and lie beyond 4  $\text{\AA}$  from  $\text{Li}^+$ , which is in agreement with previous reports (Supplementary Fig. 13).<sup>9,16,34</sup> The simulated results are further corroborated by relative solvation enthalpies estimated using potentiometric measurements (Fig. 3d).<sup>41,42</sup> The solvation enthalpies, when compared to a reference electrolyte of 1 M LiFSI in DME, have relatively small differences across the three electrolytes. It can be summarized that the enthalpic interactions between the  $\text{Li}^+$  and the species in the first solvation shell are similar across all electrolytes, and their first solvation structures are all anion-rich. As the species in the solvation structure are preferentially decomposed at the anode interface,<sup>41</sup> this leads to the anion-derived SEIs found in all samples, which will be discussed in depth in the next section (Fig. 4d).

Although the microscopic solvation structures are not significantly different across the three electrolytes, clear differences in mesoscopic structures around the nanometer scale can be observed. Clustering of  $\text{Li}^+$  and anions has been previously reported<sup>16,34,35</sup> but quantitative analyses of the extent of clustering and the impact on ion transport has been lacking. We performed statistical analyses on the  $\text{Li}^+$  and anion clusters (Supplementary Fig. 14), where a large-scale MD simulation was critical to ensuring accurate and statistically significant results. Fig. 3e shows the average  $\text{Li}^+$  cluster sizes of the three electrolyte systems at 300K and 350K, where cluster size is the number of  $\text{Li}^+$  in a discrete cluster (see methods for the detailed definition). The average cluster size decreases with increased solvent diversity for both temperatures. The simulated results are further confirmed through synchrotron-based X-ray scattering characterization (Fig. 3g, Supplementary Fig. 15). Wide-angle X-ray scattering (WAXS) results show that for Q values of 0.4 to 1.0—corresponding to 1.56 nm and 0.62 nm, respectively—we see decreased scattering with increased molecular diversity. This result is consistent with the decrease in average cluster diameter observed in MD simulations (Supplementary Fig. 16), as well as with reports on scattering experiments for ion clusters in high-concentration aqueous electrolyte and diluted solvate ionic liquids, where similar Q ranges are attributed to the formation of clusters.<sup>43-45</sup>


Clustering can be a significant factor to the ionic conductivity. Stokes-Einstein relation (eq. 1) where  $k_B$  is the Boltzmann constant,  $\eta$  is viscosity and  $R$  is hydrodynamic radius, can serve as a model to aid our understanding of the impact of clustering. Diffusion coefficient is inversely proportional to hydrodynamic radius, which is directly related to cluster size; increase in cluster size leads to a larger hydrodynamic radius and decreased diffusivity of ions.<sup>46,47</sup>

$$D = \frac{k_B T}{6\pi\eta R} \quad (1)$$

This relationship is verified by diffusion-ordered spectroscopy nuclear magnetic resonance (DOSY-NMR), which can experimentally estimate the diffusion coefficient of  $\text{Li}^+$  (Supplementary Fig. 17-18, Supplementary Table 6). We see in Fig. 3f that  $\text{Li}^+$  diffusion coefficients increase in the order of EL2-EL4-EL5. Because the viscosities of the three electrolytes do not show significant differences (Supplementary Fig. 7), it is possible to reason that the hydrodynamic radii decrease in the order of EL2-EL4-EL5, which is consistent with the MD simulation and X-ray scattering results. The Nernst-Einstein relation (eq. 2), where  $\Lambda$  is molar conductivity,  $F$  is the Faraday constant,  $R$  is the gas constant,  $T$  is temperature,  $\nu$  is the number of cations or anions,  $z$  is charge, and  $D$  is diffusion coefficient can serve as a model to help understand the relationship between diffusivity and conductivity. Conductivity is proportional to the diffusion coefficient, which is in agreement with our results (Fig. 2c, Fig. 3f).

$$\Lambda = \sum \frac{F^2}{RT} (vz^2 D) \quad (2)$$

The differences in clustering behaviors that lead to disparate diffusivities and conductivities are attributed to entropic contributions. Solvation entropies, estimated through temperature coefficients of non-isothermal cells,<sup>42</sup> show that EL5 has the highest solvation entropy (Fig. 3h). In addition, Fig. 3i shows the makeup of the 1<sup>st</sup> solvation shell of the three electrolytes, where it is evident that EL5 with the highest number of solvents has the largest number of possible solvation configurations. We believe that the high entropy of EL5 drives the reduction in clustering and the improvement in ionic conductivity. Electrolyte solvation structure can be modeled as a product of the thermodynamic equilibrium between mixing and clustering, balanced by entropic and enthalpic driving forces (Fig. 1a).<sup>48</sup> In most liquid electrolytes, entropy favors mixing, as evidenced by salt solubility increasing with temperature<sup>49</sup>; because the effect of entropy is magnified at high temperature, it is evident that entropic forces drive the equilibrium towards mixing. Conversely, clustering is entropically unfavorable as evidenced by increased clustering at low temperatures.<sup>50,51</sup> This general trend applies to our electrolytes, where we observe reduced clustering at 350K relative to 300K (Fig. 3e). It can be reasoned that high entropy electrolytes with large mixing entropies will thermodynamically favor a less clustered solution with high ion mobilities (Fig. 1a-b).

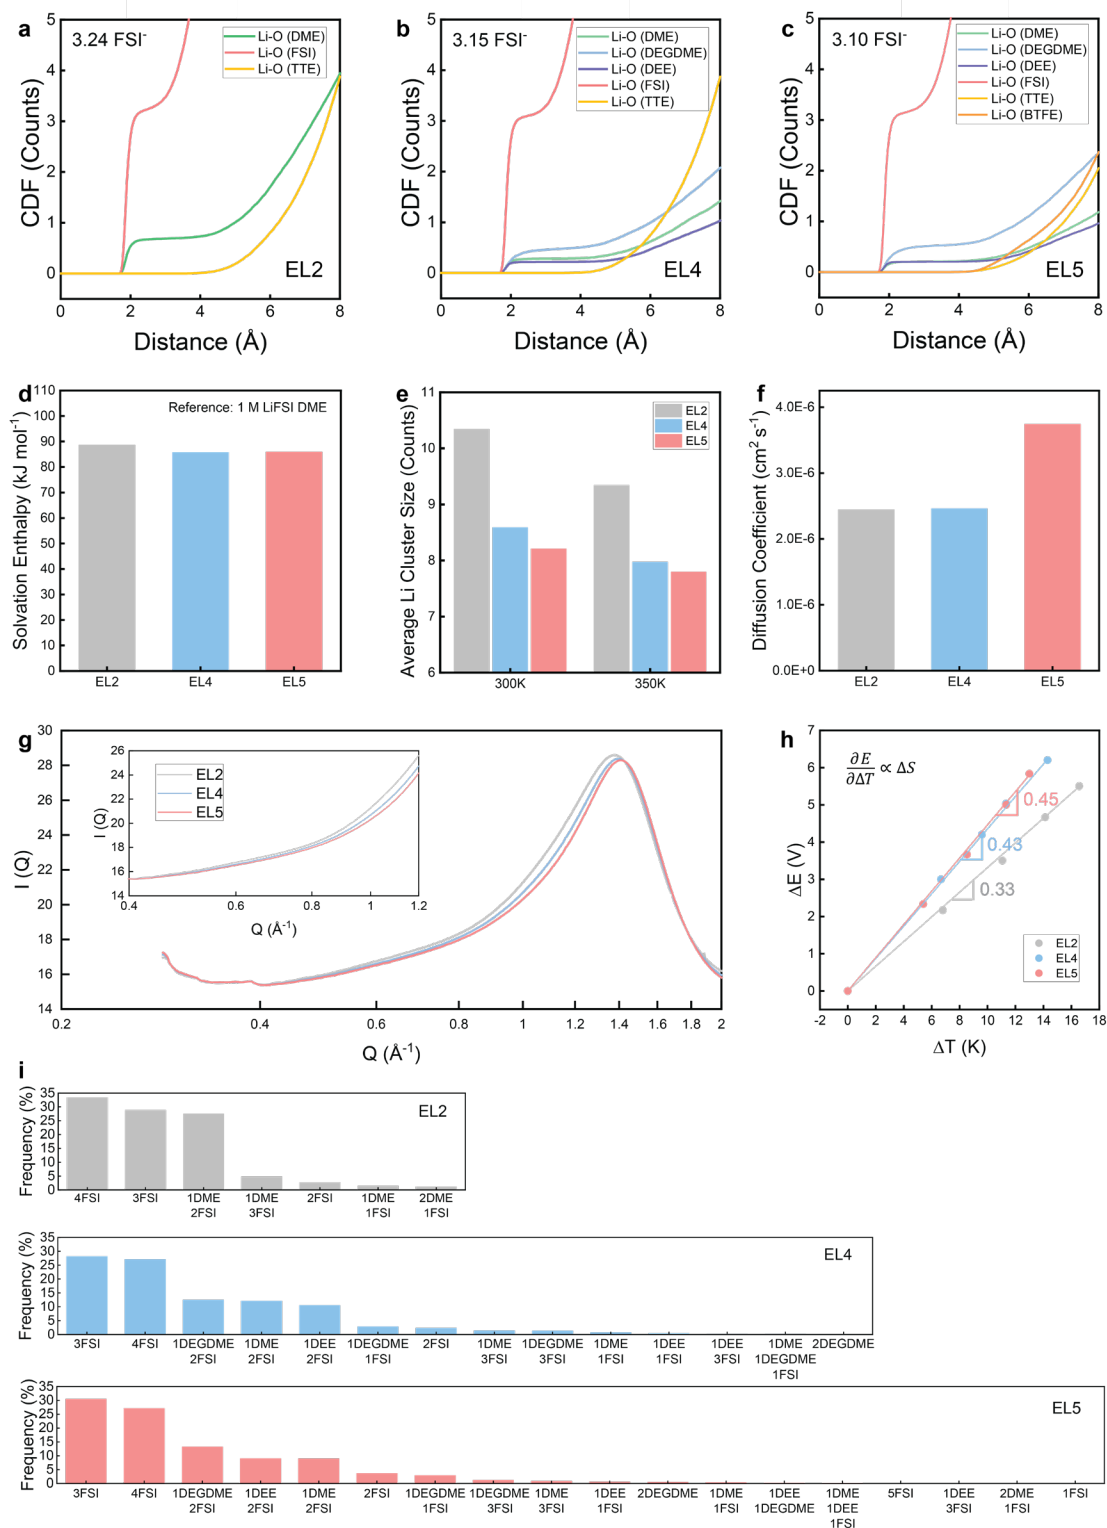

**Fig. 3. Microscopic and mesoscopic solvation structures.** **a-c**, Cumulative distribution functions of the three electrolytes, showing anion-rich primary solvation structures. **d**, Solvation enthalpy characterized through potentiometric methods shows similar values across the electrolytes. **e**, Average Li<sup>+</sup> cluster sizes obtained with MD simulations decrease with an increasing number of solvents at both 300 K and 350 K. **f**, Diffusion coefficients measured with DOSY-NMR shows the inverse trend of the cluster sizes. **g**, Wide-angle X-ray scattering (WAXS) shows decreased clustering with increased



molecular diversity. **h**, Temperature coefficients show that EL5 has the highest solvation entropy. **i**, Distribution of first solvation structures obtained by MD simulations shows that EL5 has access to the largest number of configurations.

## Electroplating Morphology and the Interphase

We observed that smaller Li cluster formation driven by entropy could improve diffusivity and ionic conductivity. To investigate the relationship between the improved ionic conductivity and high-rate cycling performance, we explore the Li deposition morphology; it is an important determinant of cycling stability as larger deposits reduce the surface area and the Li inventory loss due to solid-electrolyte interphase (SEI) formation.<sup>52</sup> Scanning electron microscopy (SEM) from the top-view shows that all of the electrolytes have large particles of smooth low surface area Li deposits (Supplementary Fig. 19-21). The cross-section view, however, reveals that the Li deposition thicknesses are different (Fig. 4a, Supplementary Fig. 22-24, Supplementary Table 7) and can be correlated with the cycling stability (Fig. 2). At low current densities of 0.5 mA cm<sup>-2</sup>, the differences in thicknesses are minimal. However, as the current density increases to 1 and 3 mA cm<sup>-2</sup>, EL2 with a lower ionic conductivity shows an increase in deposition thickness whereas EL5 retains a dense morphology with a low surface area, which can lead to reduced SEI formation and superior cyclability.


Multiphysics modeling was conducted to investigate the root cause of the discrepancies in Li deposition morphologies at high current densities. Given the electrolytes' physical parameters such as ionic conductivity and the cell parameters such as cathode loading, we simulated the voltage and concentration profiles at different current densities (Fig. 4b, Supplementary Fig. 25-26). Fig. 4b shows that EL2 forms sharp concentration gradients and Li<sup>+</sup> depletion at the interface at a plating current density of 3 mA cm<sup>-2</sup>, whereas EL5 has a much milder gradient, a phenomenon directly linked to the ionic conductivities and transport properties of the electrolytes. Concentration gradients promote highly heterogeneous current density distributions (Fig. 4c), where current hot-spots at the tip can lead to filamentary and porous deposition morphologies.<sup>53</sup> The relationship between concentration gradient and local current density is illustrated in the extended Butler-Volmer equation ( $j$  signifies the current density,  $j_0$  is the exchange current density,  $c_{Li}$  is the local Li concentration at the electrode-electrolyte interface,  $c_{Li}^*$  is the reference Li concentration in electrolytes,  $\alpha_c$  and  $\alpha_a$  are the cathodic and anodic charge-transfer coefficients,  $z$  is the number of electrons,  $F$  is the Faraday constant,  $\eta$  is the overpotential,  $R$  is the gas constant, and  $T$  is the temperature).

$$j = j_0 \left( \frac{c_{Li}}{c_{Li}^*} \right)^{\alpha_a} \left\{ \exp \left[ \frac{\alpha_a z F \eta}{RT} \right] - \exp \left[ - \frac{\alpha_c z F \eta}{RT} \right] \right\} \quad (3)$$

Although significant concentration gradients are formed, we believe that none of the electrolytes at 3 mA cm<sup>-2</sup> reach the Sand's time limit, where the Li<sup>+</sup> is completely depleted at the Li-electrolyte interface. We do not observe dendritic or mossy lithium (Supplementary Fig. 21), characteristic of such growth modes<sup>54</sup> and our Multiphysics simulations show that there remains a finite concentration for all electrolytes (Fig. 4c). Nonetheless, concentration gradients are significant factors in shaping the Li deposition morphologies and the cycling stability at high rates.

In addition to the electrolyte transport properties, another factor critical to the battery performance is the solid-electrolyte interphase (SEI); for example, anion-derived inorganic-rich SEIs have been correlated with superior cycling stability.<sup>8,41,55</sup> We performed X-ray photoelectron spectroscopy (XPS) on the SEIs of the three electrolytes, along with a well-studied reference electrolyte of 1 M LiFSI DME<sup>8,12,29,41</sup> to investigate the chemical composition of the interphases (Fig. 4d). Compared to 1 M LiFSI DME, all LHCEs show significant content of LiFSI salt decomposition products in the SEI, particularly evident in the F 1s, N 1s and S 2p spectra.<sup>56</sup> However, across the three electrolytes, the

differences are less pronounced and clear trends that correlate with the morphologies or electrochemical performance are not present. Particularly, differences in elemental compositions of the SEIs of the three electrolytes are statistically insignificant (Supplementary Fig. 27). In fact, similarity in the SEIs of the three electrolytes is not surprising, considering the similar primary solvation structures of the electrolytes (Fig. 3a-c).  $\text{Li}^+$  solvation structure is believed to dictate the decomposition products, as components within the solvation structure are more prone to reduction at the Li interface.<sup>41,57</sup>

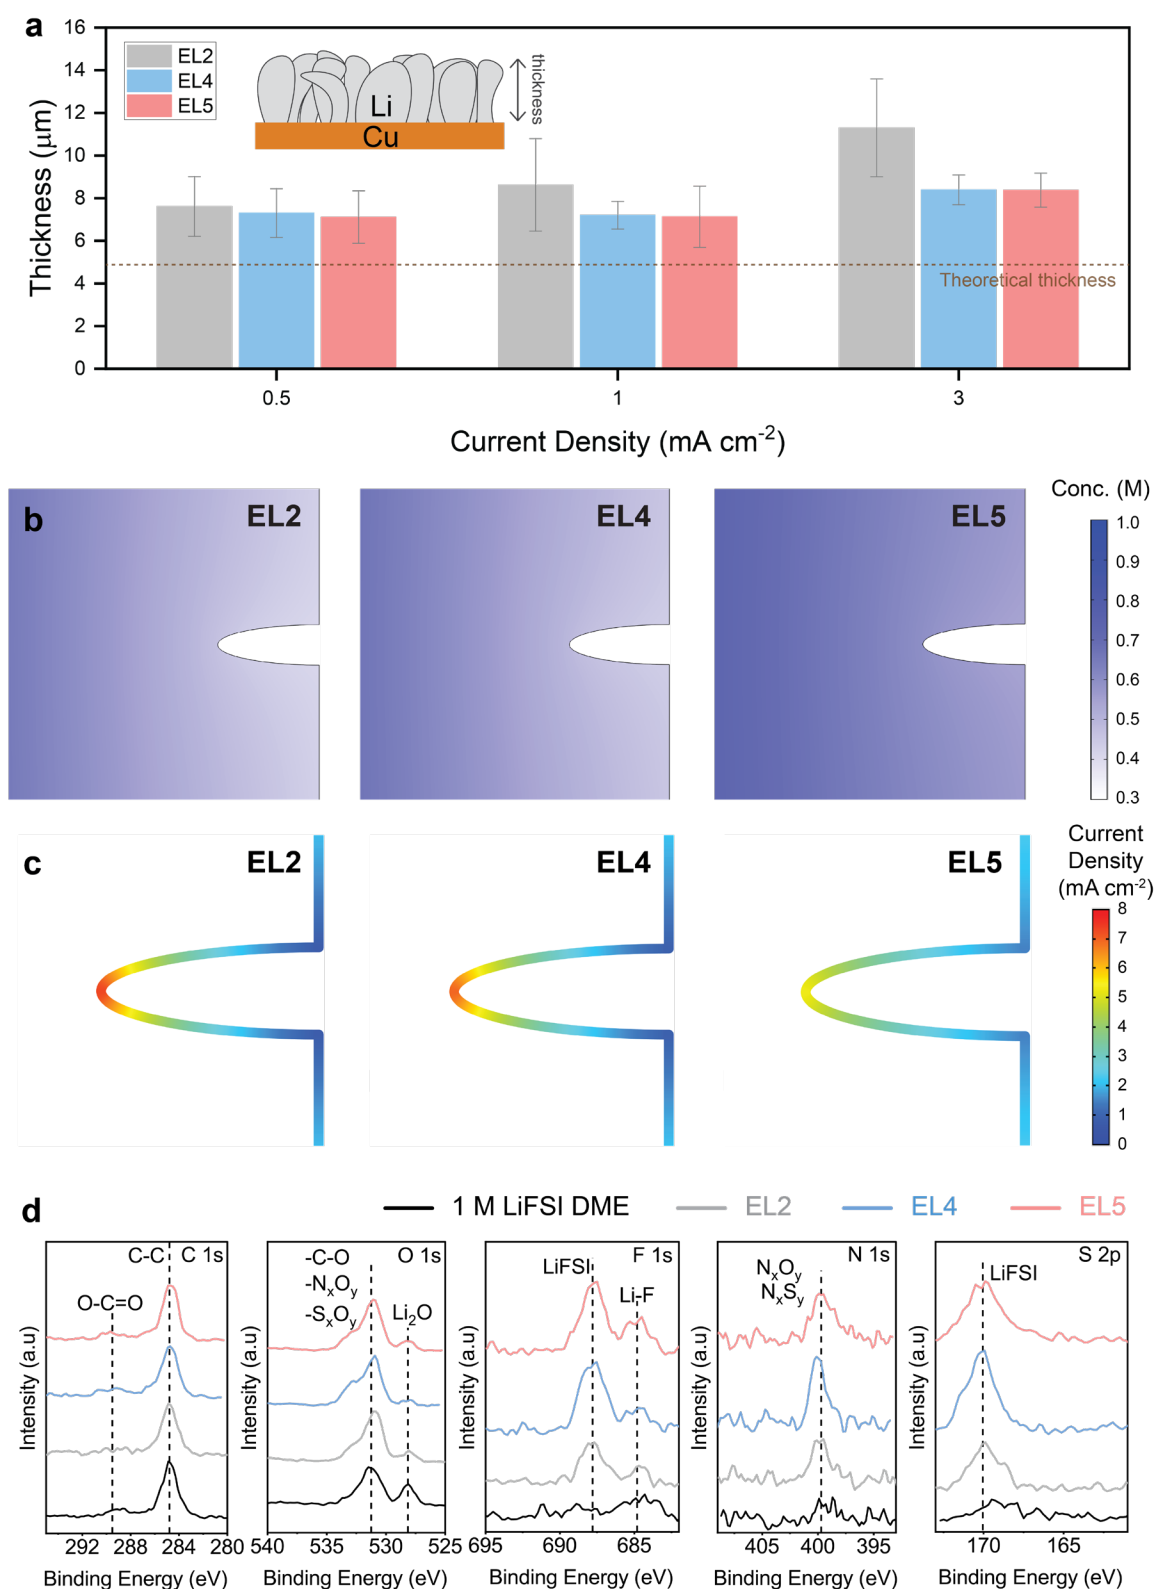

**Fig. 4. Electroplating Morphology and the Interphase.** **a**, Electrodeposition thicknesses measured through SEM characterization, showing that EL2 has increased thicknesses at high current densities. **b**,  $\text{Li}^+$  concentration gradients in the electrolyte at  $3 \text{ mA cm}^{-2}$ , showing that deposition thickness is correlated with concentration gradient buildup. **c**, Local current density profile along the interface of a Li particle shows that electrolytes with large  $\text{Li}^+$  concentration gradients develop large heterogeneities


in local current densities. **d**, XPS analysis shows that the three LHCEs have anion-derived SEIs.

### Extension to Broader Electrolyte Systems

Molecular diversity as a means to modulate the mesoscopic solvation structure and electrochemical properties can be a powerful design strategy for high-performance electrolytes. To support its generality, we extended the idea to fluorinated ether electrolytes and carbonate-based LHCEs (Fig. 5a-b). A series of fluorinated diethoxyethane (FDEE) solvents have been developed recently by some of us, which were deployed in electrolytes with state-of-the-art electrochemical performance for lithium metal batteries.<sup>10</sup> We applied the high entropy concept to FDEEs to further improve the electrochemical performance, especially their transport properties. Our high entropy FDEE electrolyte is an equivolume mixture of the four solvents F3-6DEE, mixed with 1 M of LiFSI salt. We compare the electrolyte with F5DEE solvent mixed with the same salt, as the solvent displayed the most stable cycling among the four solvents,<sup>10</sup> and consequently the averaged performance of the electrolytes containing F3-6DEE would be inferior to that using F5DEE. However, the high entropy FDEE electrolyte (F3-6DEE) displays superior ionic conductivity and high-rate cycling stability (Fig. 5c-g). The ionic conductivity improved by ~50% by diversifying the solvents (Fig. 5c, Supplementary Fig. 28), which is surprising as F3DEE, which has the highest conductivity among the FDEEs, only has a ~20% higher conductivity than F5DEE,<sup>10</sup> clearly showing the effects of molecular diversity. The CEs of Li || Cu cells are also slightly improved, with F3-6DEE with a CE of 99.6% (Fig. 5d, Supplementary Fig. 29). Anode-free pouch cell cycling of F3-6DEE shows significant improvement at higher rates of 1C-1.5C and 2C-2C compared to its single-solvent counterpart. As FDEEs are weakly solvating solvents owing to the electron withdrawing effects of fluorination, large fraction of Li ions exist as clusters.<sup>10</sup> We expect the increased mixing entropy in F3-6DEE electrolyte to mitigate clustering and improve the diffusivity and conductivity of Li<sup>+</sup>, improving the ionic conductivity and cyclability at high rates.

As another example of high entropy electrolytes, we developed high-entropy carbonate LHCEs. Dimethyl carbonate (DMC), ethyl methyl carbonate (EMC), and diethyl carbonate (DEC) were used as solvents (Fig. 5b), which were mixed with TTE and BTFE cosolvents. The solvents are linear carbonates that differ by the length of the hydrocarbon chain and exhibit close physicochemical properties.<sup>58</sup> EMC-TTE was selected as EL2 as EMC has properties that are intermediate to those of DEC and DMC.<sup>58</sup> Fig. 5h-i and Supplementary Fig. 30-31 illustrate that EL5c has the highest ionic conductivity and Li || Cu CE at higher current densities, consistent with the trend for ether-based LHCEs. In addition, NMC532 || Cu anode-free pouch cell cyclability increases in the order of EL2c-EL4c-EL5c, confirming the trend that increasing the solvent diversity can lead to improved cycle life (Fig. 5j, Supplementary Fig. 32).

As demonstrated in this discussion, molecular diversity as a design strategy can be applied widely to many electrolyte systems and provides a vast unexplored design space of high entropy electrolytes. In particular, for weakly solvating electrolytes that form extensive amounts of ion clustering, entropy can be utilized to modulate the mesoscopic solvation structures and improve transport properties and fast charging capabilities. We envision that this work can spur efforts to develop HEEs to improve transport properties, lithium deposition morphologies, fast-charging capabilities as well as other aspects of high-performance electrolytes that can push lithium metal batteries closer to practical applications.

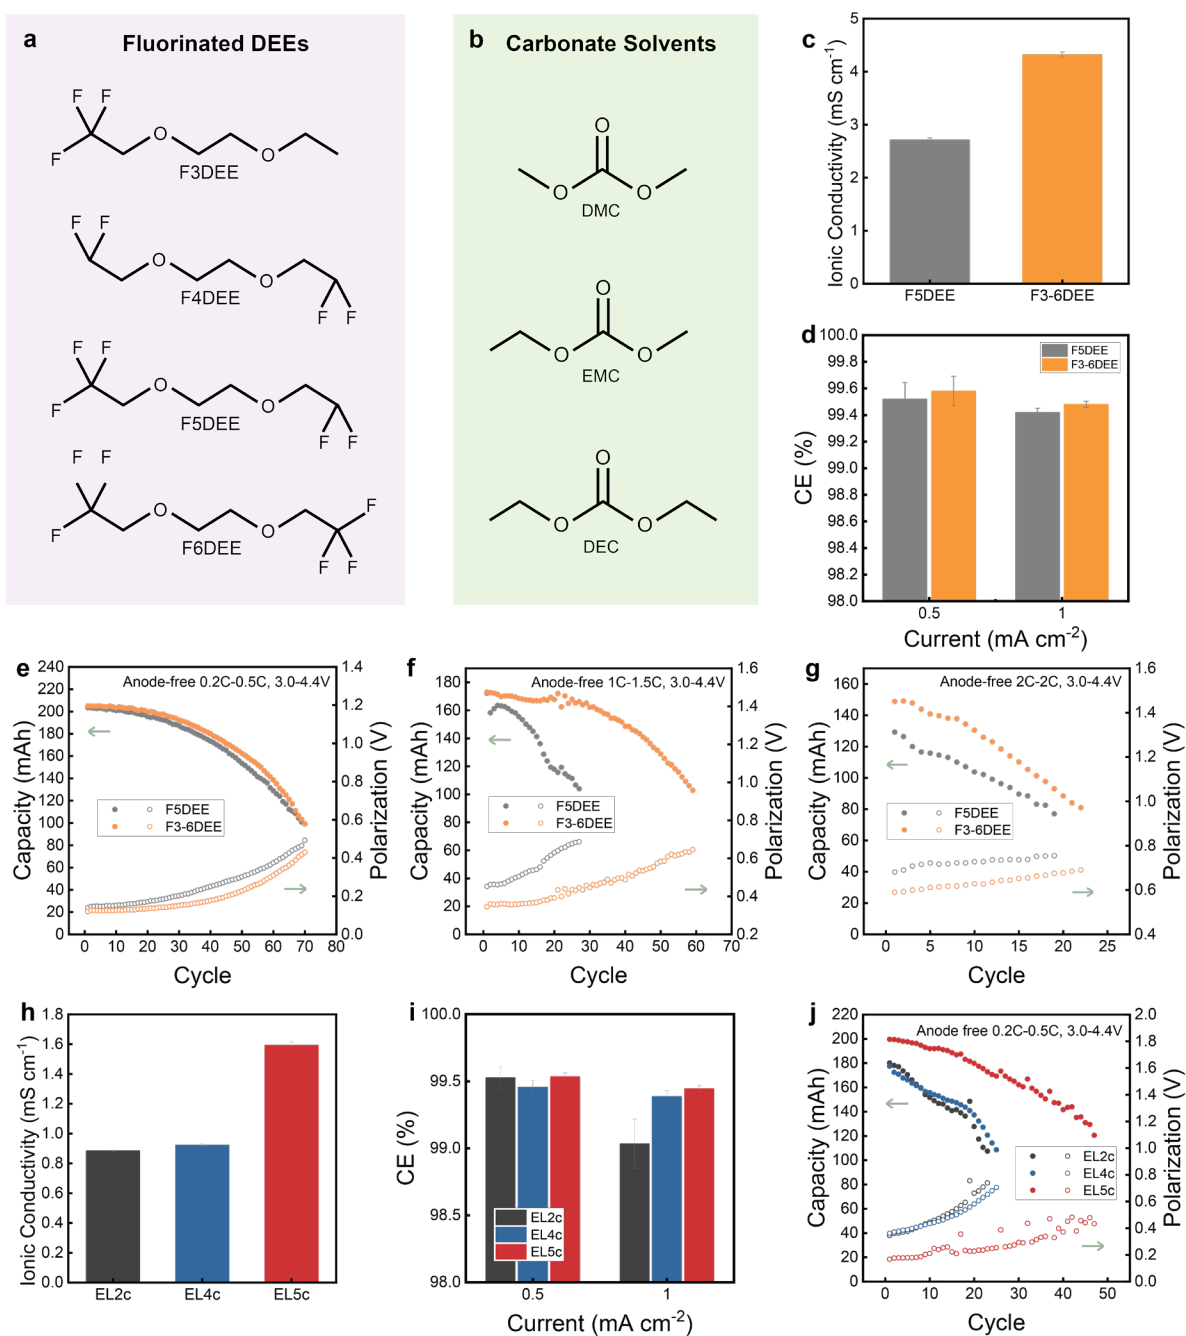

**Fig. 5. Electrochemical performances of broader HEE systems.** **a-b**, Chemical structures of solvents used in high entropy FDEEs and high entropy carbonate LHCEs. **c**, Ionic conductivity of F3-6DEE shows ~50% increase from F5DEE. **d**, Li || Cu Coulombic efficiencies are slightly improved for F3-6DEEs. **e-g**, Anode-free NMC532-Cu pouch cell cycling at 3.0-4.4V for different current densities, showing lower polarization and more stable cycling for F3-6DEE. **h**, Ionic conductivities increase with increasing number of solvents. **i**, Li || Cu Coulombic efficiencies are similar for EL2-5c at  $0.5 \text{ mA cm}^{-2}$  but show decreased efficiencies for EL2c at  $1 \text{ mA cm}^{-2}$ . **j**, Anode-free NMC532-Cu pouch cell cycling at 3.0-4.4V for different current densities, showing lower polarization and more stable cycling with increased number of solvents.

## Methods

### Electrolyte Preparation

All electrolytes were prepared and handled in an argon filled glovebox with O<sub>2</sub> concentration < 0.2 ppm and H<sub>2</sub>O concentration < 0.01 ppm. All electrolyte materials were used as received after molecular sieving to remove trace amounts of water. LiFSI (Fluolyte) was used as the salt DME (Sigma-Aldrich), DEGDME (Sigma-Aldrich), DEE (Acros), DMC (Sigma-Aldrich), EMC (Sigma-Aldrich), DEC (Sigma-Aldrich), TTE (SynQuest) and BTFE (SynQuest) were used as solvents. The fluorinated DEE (FDEE) solvents were synthesized in lab through methods described by Yu et al.<sup>10</sup> The electrolytes were filtered before use to eliminate any potentially remaining solid particles.

### Electrochemical Performance Testing

All pouch cells were commercial single-crystal NMC532 || Cu dry pouch cells purchased from Li-Fun Technology, with ~3.1 mAh cm<sup>-2</sup> of cathode loading and a cell capacity of ~200 mAh, then electrolytes were pipetted into the cells in an argon filled glovebox. Pouch cells were cycled using Biologic VMP3, first cycled with two formation cycles at C/10. Subsequent cycles were constant current cycles at different c-rates with voltage ranges of 3.0 V - 4.4 V. All pouch cells were pressurized using c-clamps and polyacrylic plates. 2032-type coin cells were assembled in the glovebox using Celgard 2325 separators and NMC532 electrodes purchased from MTI. Coin cells were used for impedance, cycling, linear sweep voltammetry (LSV), Coulombic efficiency, and electrode characterizations. Coin cell cycling was conducted using Land Instruments cyclers. The EIS measurements were taken over a frequency range of 1 MHz to 100 mHz. LSV tests were over a voltage range of 3 V to 6 V in Li || Al cells. For Li || Cu half-cell CE tests, initially 5 mA h cm<sup>-2</sup> of Li metal was deposited on Cu and stripped (formation cycle). Then 5 mA h cm<sup>-2</sup> of Li metal was deposited again, to act as a Li reservoir. Then Li was repeatedly stripped and plated 1 mA h cm<sup>-2</sup> for 9 cycles. The remaining Li on Cu was then stripped, and the average CE was calculated by dividing the total stripping capacity by the total plating capacity after the formation cycle. NMC || Cu full cells were first cycled with two formation cycles at C/10. Subsequent cycles were constant current cycles at different c-rates with voltage ranges of 3.0 V - 4.4 V. For ionic conductivity measurements a Swagelok cell was used with no separators and electrochemical impedance spectroscopy was used to measure the bulk resistance, which was then converted into conductivity using the length and area of the cell.

### Molecular Dynamics Simulations

MD simulations were carried out using the LAMMPS package. The OPLS-AA force field<sup>59</sup> with fitted parameters for LiFSI<sup>60</sup> and the solvent molecules DME, DEGDME, DEE, BTFE<sup>34</sup> was used in this work. The OPLS-AA parameters for TTE were fitted specifically for this work, and is included in the Supplementary Materials. Parameter fitting was performed using the density functional theory (DFT) package Orca,<sup>61</sup> with 6-31++G(d,p) basis set and LC-BLYP functional. The atomic charges for all species in this work are re-calculated using RESP analysis implemented in the Multiwfn package.<sup>62</sup> The EL2 system contains 384 DME molecules, 2376 TTE molecules, and 400 LiFSI molecules; the EL4 system contains 128 DME molecules, 96 DEE molecules, 92 DEGDME molecules, 2376 TTE molecules, and 400 LiFSI molecules; the EL5 system contains 128 DME molecules, 96 DEE molecules, 92 DEGDME molecules, 1388 TTE molecules, 1188 BTFE molecules, and 400 LiFSI molecules. The systems were initialized randomly using the Packmol package. The systems were then subjected to a simulated annealing equilibration protocol as follows: (1) energy minimization at temperature T=0 K; (2) equilibration at T=300K for 2 ns in NPT ensemble; (3) heating up the system to 450K over 1 ns in

NPT ensemble; (3) relaxation at T=450 K over 1 ns in NPT ensemble; (4) cooling down to T=300 K over 1 ns in NPT ensemble; (5) equilibration at T=300 K for 5 ns in NPT ensemble. The production run was subsequently performed at T=300 K over 20 ns in NVT ensemble. A second round of simulations with the equilibrium temperature T=350K were performed to study the entropic effects on cluster distribution. All the simulations in this work used a timestep of 1 fs, and a pressure of 1 atm. The temperature and pressure were regulated with a Nose-Hoover thermostat and barostat, with a damping parameter of 0.2 ps and 1 ps respectively.

The subsequent data analysis was carried out using the last 10 ns of the production-run trajectories. The cumulative distribution functions (CDF) and the first solvation shell coordination numbers were calculated with the python code MDAAnalysis.<sup>63</sup> The time averaging used snapshots taken every 250 ps to minimize temporal correlation effects. Structural analysis of salt ion clusters was carried out with custom code based on the breadth-first search algorithm. Specifically, the program starts with one random unvisited Li<sup>+</sup> atom as the starting atom (henceforth marked as visited) of a cluster, and search for its neighboring O atoms; the FSI<sup>-</sup> anions to which each O atom belongs are henceforth marked as visited and part of the cluster. This primary step is followed by a secondary step, where for every O atom of the marked FSI<sup>-</sup> ions in the primary step, its unvisited neighboring Li<sup>+</sup> ions are henceforth marked as visited as part of the cluster. These two steps are performed recursively to determine all the Li<sup>+</sup> and FSI<sup>-</sup> ions belonging to one common cluster. This search process is repeated for the whole system to determine the statistics of clusters present in the system. The criterion for neighboring atoms is such that their interatomic distance is less than 2.5 Å.

## COMSOL Multiphysics Simulations

All Multiphysics simulations on lithium electrodeposition are performed using COMSOL Multiphysics software. The physical parameters of electrodes (NMC and Li metal) and electrolytes (EL2, EL4 and EL5) in the numerical model are set to be consistent with the experiments. The electric current in the electrolyte is governed by the diffusion and migration of Li ions, and can be described using the Nernst–Planck equation:

$$\mathbf{i}_l = (-K_l \nabla \phi_l) + \frac{2K_l RT}{F} \left(1 + \frac{\partial \ln f}{\partial \ln c_{Li}}\right) (1 - t_+) \nabla \ln c_{Li},$$

where  $\mathbf{i}_l$  is the electric current in the electrolyte,  $K_l$  is the ionic conductivity of the electrolyte,  $\phi_l$  is the electrolyte potential,  $c_{Li}$  is the concentration of Li<sup>+</sup> in the electrolyte,  $R$  is the gas constant,  $T$  is the temperature,  $F$  is the Faraday's constant,  $t_+$  is the transference number of Li<sup>+</sup>, and  $f$  is the mean molar activity coefficient of the electrolyte. The Butler-Volmer equation was used to describe the relationship between the electrodeposition rate and the electrodeposition overpotential,

$$j = j_0 \left(\frac{c_{Li}}{c_{Li}^*}\right)^{\alpha_a} \left\{ \exp\left[\frac{\alpha_a z F \eta}{RT}\right] - \exp\left[-\frac{\alpha_c z F \eta}{RT}\right] \right\}$$

where  $j$  signifies the current density,  $j_0$  is the exchange current density, and  $c_{Li}^*$  is the reference Li concentration in electrolytes.  $\alpha_c$  and  $\alpha_a$  are the cathodic and anodic charge-transfer coefficients and  $z$  is the number of electrons. overpotential for lithium electrodeposition is defined as  $\eta = \phi_s - \phi_l$  where  $\phi_s$  is the electrode potential.

The mass transport of Li<sup>+</sup> in the electrolyte is defined as

$$\frac{\partial c_l}{\partial t} + \nabla \cdot \mathbf{J}_l = 0,$$

$$\mathbf{J}_l = -D_l \nabla C_l + \frac{\mathbf{i}_l t_+}{F},$$

where  $\mathbf{J}_l$  represents  $\text{Li}^+$  flux in the electrolyte, and  $D_l$  stands for the  $\text{Li}^+$  diffusivity in electrolytes.

### Electrode and Interphase Characterization

The SEM images were taken using an FEI Magellan 400 XHR. 2032-type Li || Cu coin cells were assembled using a Celgard 2325 separator with respective electrolytes. 1 mAh  $\text{cm}^{-2}$  of Li was plated onto a Cu current collector using various current densities. Then the coin cell was disassembled in a glovebox and the electrode was extracted then washed in DME to remove any excess Li salt. For cross-section imaging the electrodes were torn and mounted onto the SEM holder for imaging. X-ray photoelectron spectroscopy (XPS) signals were collected on a PHI VersaProbe 1 scanning XPS microprobe with an Al  $K\alpha$  source. 1 mAh  $\text{cm}^{-2}$  of Li was deposited onto Cu current collectors at 0.5 mA  $\text{cm}^{-2}$  current densities and SEI was characterized without sputtering.

### Electrolyte Characterization

Solvation entropy measurements were done using a potentiometric method developed previously in our group,<sup>41</sup> using a non-isothermal cell with Li metal as electrodes. A temperature gradient was progressively developed and the voltage response was recorded. The slope of voltage vs. temperature gradient was used to estimate the solvation entropy. Solvation energy measurements were done by using a similar method, using a H-cell with Li metal as electrodes and asymmetric electrolytes. An open circuit potential was measured to probe the relative solvation energy. The steady-state viscosity was measured at ambient condition with a TA Instrument ARES-G2 rheometer in parallel plate geometry.

### X-ray Scattering Characterization

Synchrotron small-angle x-ray scattering (SAXS) was conducted in capillary transmission mode at beamline 1-5 at the Stanford Synchrotron Radiation Lightsource (SSRL) of SLAC National Accelerator Laboratory, with 15 keV beam energy. The detector is Dectris Pilatus 1M, with a sample to detector distance of 835.685mm. All measurements were done in ambient air condition. Three spots along each sample capillary holder were collected, with an exposure time of 60 s for each spot, and ten repeats for each spot. 2D scattering data were exported into IgorPro, processed with the Irena and Nika packages and calibrated with the LaB6 standard. The 1D data is normalized with the beamstop value and background subtraction was done with data collected for the empty quartz capillaries (OD = 2 mm, Charles Sopper).

Synchrotron wide-angle X-ray scattering (WAXS) was conducted in capillary transmission mode at beamline 11-3 at the Stanford Synchrotron Radiation Lightsource (SSRL) of SLAC National Accelerator Laboratory, with 12.7 keV beam energy. The detector is Raxyonics 225, 73.242 micron<sup>2</sup>, with a sample to detector distance of 150 mm. All measurements were done in ambient air condition. Seven spots along each sample capillary holder were collected, with an exposure time of 25 s for each spot. 2D scattering data were exported and processed with the beamline customized software xdart and calibrated with the LaB6 standard. All 1D data were normalized with the intensity value of high Q (5  $\text{\AA}^{-1}$ ).



## DOSY-NMR Characterization

In an argon glovebox, electrolyte was injected into a thin-walled NMR tube. Ten percent toluene was added as an internal reference. A co-axial tube containing DMSO-d<sub>6</sub> was inserted into the NMR tube. The caps of the outer and inner tubes were sealed by parafilm to avoid moisture during DOSY-NMR experiment. All DOSY NMR experiments were performed on a Varian 400 MHz spectrometer at 25°C. <sup>7</sup>Li-pulsed field gradient (PFG) measurements were performed to determine the diffusion coefficients using the standard *dstebpgp3s* pulse sequence. Array of gradient strength was set to 2.908 to 12.504 G/cm with 12 linear steps. Recycling delay (*d1*) was 1 s. High power 90° pulse (*pw90*) was 9 μs. Acquisition time was 4 s. Diffusion delay ( $\Delta$ ) was 0.5 s for EL2 and 0.46 s for EL4 and EL5. Gradient pulse duration ( $\delta$ ) was 9 ms. Apparent diffusion coefficients were calculated by fitting peak integrals to the Stejskal–Tanner equation.

## References

1. Whittingham, M. S. Electrical Energy Storage and Intercalation Chemistry. *Science* (80-. ). **192**, 1126–1127 (1976).
2. Lin, D., Liu, Y. & Cui, Y. Reviving the lithium metal anode for high-energy batteries. *Nat. Nanotechnol.* **12**, 194–206 (2017).
3. Zhang, J. G., Xu, W., Xiao, J., Cao, X. & Liu, J. Lithium Metal Anodes with Nonaqueous Electrolytes. *Chem. Rev.* **120**, 13312–13348 (2020).
4. Winter, M., Barnett, B. & Xu, K. Before Li Ion Batteries. *Chem. Rev.* **118**, 11433–11456 (2018).
5. Lin, D. *et al.* Layered reduced graphene oxide with nanoscale interlayer gaps as a stable host for lithium metal anodes. *Nat. Nanotechnol.* **11**, 626–632 (2016).
6. Zhou, L. *et al.* High areal capacity, long cycle life 4 V ceramic all-solid-state Li-ion batteries enabled by chloride solid electrolytes. *Nat. Energy* **7**, 83–93 (2022).
7. Fu, C. *et al.* Universal chemomechanical design rules for solid-ion conductors to prevent dendrite formation in lithium metal batteries. *Nat. Mater.* **19**, 758–766 (2020).
8. Cao, X. *et al.* Monolithic solid–electrolyte interphases formed in fluorinated orthoformate-based electrolytes minimize Li depletion and pulverization. *Nat. Energy* **4**, 796–805 (2019).
9. Ren, X. *et al.* Enabling High-Voltage Lithium-Metal Batteries under Practical Conditions. *Joule* **3**, 1662–1676 (2019).
10. Yu, Z. *et al.* Rational solvent molecule tuning for high-performance lithium metal battery electrolytes. *Nat. Energy* (2022) doi:10.1038/s41560-021-00962-y.
11. Fan, X. *et al.* All-temperature batteries enabled by fluorinated electrolytes with non-polar solvents. *Nat. Energy* **4**, 882–890 (2019).
12. Chen, Y. *et al.* Steric Effect Tuned Ion Solvation Enabling Stable Cycling of High-Voltage Lithium Metal Battery. *J. Am. Chem. Soc.* (2021) doi:10.1021/jacs.1c09006.
13. Louli, A. J. *et al.* Diagnosing and correcting anode-free cell failure via electrolyte and morphological analysis. *Nat. Energy* **5**, 693–702 (2020).
14. Kim, M. S. *et al.* Suspension electrolyte with modified Li<sup>+</sup> solvation environment for lithium metal batteries. *Nat. Mater.* (2022) doi:10.1038/s41563-021-01172-3.
15. Wang, H. *et al.* Liquid electrolyte: The nexus of practical lithium metal batteries. *Joule* (2022)

doi:<https://doi.org/10.1016/j.joule.2021.12.018>.

16. Cao, X. *et al.* Effects of fluorinated solvents on electrolyte solvation structures and electrode/electrolyte interphases for lithium metal batteries. *Proc. Natl. Acad. Sci.* **118**, e2020357118 (2021).
17. Chen, S. *et al.* High-Voltage Lithium-Metal Batteries Enabled by Localized High-Concentration Electrolytes. *Adv. Mater.* **30**, 1706102 (2018).
18. Yu, Z. *et al.* Molecular design for electrolyte solvents enabling energy-dense and long-cycling lithium metal batteries. *Nat. Energy* **2020 57 5**, 526–533 (2020).
19. Chen, S. *et al.* High-Efficiency Lithium Metal Batteries with Fire-Retardant Electrolytes. *Joule* **2**, 1548–1558 (2018).
20. Berhaut, C. L. *et al.* Ionic association analysis of LiTDI, LiFSI and LiPF<sub>6</sub> in EC/DMC for better Li-ion battery performances. *RSC Adv.* **9**, 4599–4608 (2019).
21. Lundgren, H., Behm, M. & Lindbergh, G. Electrochemical Characterization and Temperature Dependency of Mass-Transport Properties of LiPF<sub>6</sub> in EC:DEC. *J. Electrochem. Soc.* **162**, A413–A420 (2014).
22. Yamada, Y. *et al.* Unusual stability of acetonitrile-based superconcentrated electrolytes for fast-charging lithium-ion batteries. *J. Am. Chem. Soc.* **136**, 5039–5046 (2014).
23. Ren, X. *et al.* Role of inner solvation sheath within salt–solvent complexes in tailoring electrode/electrolyte interphases for lithium metal batteries. *Proc. Natl. Acad. Sci.* **117**, 28603–28613 (2020).
24. Ren, X. *et al.* Localized High-Concentration Sulfone Electrolytes for High-Efficiency Lithium-Metal Batteries. *Chem* **4**, 1877–1892 (2018).
25. Zheng, J. *et al.* High-Fluorinated Electrolytes for Li–S Batteries. *Adv. Energy Mater.* **9**, 1803774 (2019).
26. Xue, W. *et al.* Ultra-high-voltage Ni-rich layered cathodes in practical Li metal batteries enabled by a sulfonamide-based electrolyte. *Nat. Energy* (2021) doi:10.1038/s41560-021-00792-y.
27. Holoubek, J. *et al.* Electrolyte design implications of ion-pairing in low-temperature Li metal batteries. *Energy Environ. Sci.* **15**, 1647–1658 (2022).
28. Niu, C. *et al.* Balancing interfacial reactions to achieve long cycle life in high-energy lithium metal batteries. *Nat. Energy* **6**, 723–732 (2021).
29. Yu, Z. *et al.* Molecular design for electrolyte solvents enabling energy-dense and long-cycling lithium metal batteries. *Nat. Energy* 1–8 (2020) doi:10.1038/s41560-020-0634-5.
30. Weber, R. *et al.* Long cycle life and dendrite-free lithium morphology in anode-free lithium pouch cells enabled by a dual-salt liquid electrolyte. *Nat. Energy* **2019 48 4**, 683–689 (2019).
31. Genovese, M. *et al.* Hot Formation for Improved Low Temperature Cycling of Anode-Free Lithium Metal Batteries. *J. Electrochem. Soc.* **166**, A3342–A3347 (2019).
32. Louli, A. J. *et al.* Exploring the Impact of Mechanical Pressure on the Performance of Anode-Free Lithium Metal Cells. *J. Electrochem. Soc.* **166**, A1291–A1299 (2019).
33. Wang, H. *et al.* Dual-Solvent Li-Ion Solvation Enables High-Performance Li-Metal Batteries. *Adv. Mater.* **33**, 2008619 (2021).
34. Perez Beltran, S., Cao, X., Zhang, J. G. & Balbuena, P. B. Localized High Concentration Electrolytes for High Voltage Lithium-Metal Batteries: Correlation between the Electrolyte

- Composition and Its Reductive/Oxidative Stability. *Chem. Mater.* **32**, 5973–5984 (2020).
35. Liu, H. *et al.* Ultrahigh coulombic efficiency electrolyte enables Li||SPAN batteries with superior cycling performance. *Mater. Today* **42**, 17–28 (2021).
  36. Ye, Y. F., Wang, Q., Lu, J., Liu, C. T. & Yang, Y. High-entropy alloy : challenges and prospects. **19**, (2016).
  37. Lun, Z. *et al.* Cation-disordered rocksalt-type high-entropy cathodes for Li-ion batteries. *Nat. Mater.* **20**, 214–221 (2021).
  38. Oses, C., Toher, C. & Curtarolo, S. High-entropy ceramics. *Nat. Rev. Mater.* **5**, 295–309 (2020).
  39. Wang, Q. *et al.* Multi-anionic and -cationic compounds: new high entropy materials for advanced Li-ion batteries. *Energy Environ. Sci.* **12**, 2433–2442 (2019).
  40. Bérardan, D., Franger, S., Meena, A. K. & Dragoë, N. Room temperature lithium superionic conductivity in high entropy oxides. *J. Mater. Chem. A* **4**, 9536–9541 (2016).
  41. Kim, S. C. *et al.* Potentiometric Measurement to Probe Solvation Energy and Its Correlation to Lithium Battery Cyclability. *J. Am. Chem. Soc.* **143**, 10301–10308 (2021).
  42. Wang, H. *et al.* Correlating Li-Ion Solvation Structures and Electrode Potential Temperature Coefficients. *J. Am. Chem. Soc.* (2021) doi:10.1021/jacs.0c10587.
  43. Saito, S. *et al.* Li<sup>+</sup> Local Structure in Hydrofluoroether Diluted Li-Glyme Solvate Ionic Liquid. *J. Phys. Chem. B* **120**, 3378–3387 (2016).
  44. Zheng, J. *et al.* Understanding Thermodynamic and Kinetic Contributions in Expanding the Stability Window of Aqueous Electrolytes. *Chem* **4**, 2872–2882 (2018).
  45. Qian, K., Winans, R. E. & Li, T. Insights into the Nanostructure, Solvation, and Dynamics of Liquid Electrolytes through Small-Angle X-Ray Scattering. *Adv. Energy Mater.* **11**, (2021).
  46. Hassan, S. A. Morphology of ion clusters in aqueous electrolytes. *Phys. Rev. E - Stat. Nonlinear; Soft Matter Phys.* **77**, 1–5 (2008).
  47. Tan, P. *et al.* Solid-Like Nano-Anion Cluster Constructs a Free Lithium-Ion-Conducting Superfluid Framework in a Water-in-Salt Electrolyte. *J. Phys. Chem. C* **125**, 11838–11847 (2021).
  48. McEldrew, M., Goodwin, Z. A. H., Bi, S., Bazant, M. Z. & Kornyshev, A. A. Theory of ion aggregation and gelation in super-concentrated electrolytes. *J. Chem. Phys.* **152**, 234506 (2020).
  49. Xin, N., Sun, Y., He, M., Radke, C. J. & Prausnitz, J. M. Solubilities of six lithium salts in five non-aqueous solvents and in a few of their binary mixtures. *Fluid Phase Equilib.* **461**, 1–7 (2018).
  50. McEldrew, M., Goodwin, Z. A. H., Zhao, H., Bazant, M. Z. & Kornyshev, A. A. Correlated Ion Transport and the Gel Phase in Room Temperature Ionic Liquids. (2021) doi:10.1021/acs.jpcc.0c09050.
  51. Gupta, A. & Manthiram, A. Unifying the clustering kinetics of lithium polysulfides with the nucleation behavior of Li<sub>2</sub>S in. 13242–13251 (2021) doi:10.1039/d1ta02779d.
  52. Fang, C. *et al.* Pressure-tailored lithium deposition and dissolution in lithium metal batteries. *Nat. Energy* **6**, 987–994 (2021).
  53. Xiao, B. J. How lithium dendrites form in liquid batteries. **366**, 426–428 (2019).
  54. Bai, P., Li, J., Brushett, F. R. & Bazant, M. Z. Transition of lithium growth mechanisms in liquid electrolytes. *Energy Environ. Sci.* 13–17 (2016) doi:10.1039/C6EE01674J.

55. Fan, X. *et al.* Highly Fluorinated Interphases Enable High-Voltage Li-Metal Batteries. *Chem* **4**, 174–185 (2018).
56. Oyakhire, S. T., Gong, H., Cui, Y., Bao, Z. & Bent, S. F. An X-ray Photoelectron Spectroscopy Primer for Solid Electrolyte Interphase Characterization in Lithium Metal Anodes. *ACS Energy Lett.* **7**, 2540–2546 (2022).
57. Yao, Y. X. *et al.* Regulating Interfacial Chemistry in Lithium-Ion Batteries by a Weakly Solvating Electrolyte\*\*. *Angew. Chemie - Int. Ed.* **60**, 4090–4097 (2021).
58. Xu, K. Nonaqueous liquid electrolytes for lithium-based rechargeable batteries. *Chem. Rev.* **104**, 4303–4417 (2004).
59. Kaminski, G. A., Friesner, R. A., Tirado-Rives, J. & Jorgensen, W. L. Evaluation and Reparametrization of the OPLS-AA Force Field for Proteins via Comparison with Accurate Quantum Chemical Calculations on Peptides. *J. Phys. Chem. B* **105**, 6474–6487 (2001).
60. Canongia Lopes, J. N. *et al.* Potential Energy Landscape of Bis(fluorosulfonyl)amide. *J. Phys. Chem. B* **112**, 9449–9455 (2008).
61. Neese, F., Wennmohs, F., Becker, U. & Riplinger, C. The ORCA quantum chemistry program package. *J. Chem. Phys.* **152**, 224108 (2020).
62. Lu, T. & Chen, F. Multiwfn: A multifunctional wavefunction analyzer. *J. Comput. Chem.* **33**, 580–592 (2012).
63. Michaud-Agrawal, N., Denning, E. J., Woolf, T. B. & Beckstein, O. MDAAnalysis: A toolkit for the analysis of molecular dynamics simulations. *J. Comput. Chem.* **32**, 2319–2327 (2011).

#### Acknowledgements

S.T.O. acknowledges support from the TomKat Center Fellowship for Translational Research at Stanford University. D. T. B. acknowledges the National Science Foundation Graduate Research Fellowship Program (NSF GRFP) for funding. Z.H. acknowledges support from American Association of University Women (AAUW) International Fellowship. The battery and electrolyte measurement part were supported by the Assistant Secretary for Energy Efficiency and Renewable Energy, Office of Vehicle Technologies, of the U.S. Department of Energy under the Battery Materials Research (BMR) Program and the Battery500 Consortium program. Part of this work was performed at the Stanford Nano Shared Facilities (SNSF). The authors acknowledge Dr. Johanna Nelson Weker for fruitful discussions on X-ray scattering experiments.

#### Author contributions

S. C. K. and J. W. contributed equally. S. C. K. and Yi. C. conceived and designed the investigation. S. C. K. conducted materials synthesis and electrochemical performance testing. J. W. conducted molecular dynamics simulations. R. X. conducted Multiphysics simulations. P. Z. and Z. H. conducted X-ray scattering experiments. Yu. C. conducted DOSY-NMR experiments. Y. Y. conducted SEM characterizations. Z. Y. conducted electrolyte solvent synthesis. Z. H. conducted viscosity characterization. S. T. O. conducted XPS characterization. S. C. K. conducted solvation measurements. W. Z., P. S., M. S. K., D. T. B., assisted with interpretation of results. J. Q, Z. B, and Yi. C supervised the project. S. C. K., J. W., and Yi. C. co-wrote the paper. All authors discussed the results and commented on the manuscript.

#### Competing interests

Authors declare no competing interests.

#### Data and materials availability

All data is available in the main text or the supplementary materials.

Correspondence and Requests for Materials should be addressed to [yicui@stanford.edu](mailto:yicui@stanford.edu).