

Frenkel Excitons in Vacancy-Ordered Titanium Halide Perovskites (Cs_2TiX_6)

Seán R. Kavanagh,^{*,†,‡} Christopher N. Savory,[†] Shanti M. Liga,[¶] Gerasimos Konstantatos,^{¶,§} Aron Walsh,^{*,‡} and David O. Scanlon^{*,†}

[†]*Thomas Young Centre and Department of Chemistry, University College London, 20 Gordon Street, London WC1H 0AJ, UK*

[‡]*Thomas Young Centre and Department of Materials, Imperial College London, Exhibition Road, London SW7 2AZ, UK*

[¶]*ICFO, Institut de Ciències Fotoniques, The Barcelona Institute of Science and Technology, 08860 Castelldefels, Barcelona, Spain*


[§]*ICREA, Institució Catalana de Recerca i Estudis Avançats, 08010 Barcelona, Spain*

E-mail: sean.kavanagh.19@ucl.ac.uk; a.walsh@imperial.ac.uk; d.scanlon@ucl.ac.uk

Abstract

Low-cost, non-toxic and earth-abundant photovoltaic materials are a long-sought target in the solar cell research community. Perovskite-inspired materials have emerged as promising candidates for this goal, with researchers employing materials design strategies including structural, dimensional and compositional transformations to avoid the use of rare and toxic elemental constituents, while attempting to maintain high optoelectronic performance. These strategies have recently been invoked to propose Ti-based vacancy-ordered halide perovskites (A_2TiX_6 ; $\text{A} = \text{CH}_3\text{NH}_3$, Cs, Rb, K; $\text{X} = \text{I}, \text{Br}, \text{Cl}$) for photovoltaic operation, following the initial promise of Cs_2SnX_6 compounds. Theoretical investigations of these materials, however, consistently overestimate their band gaps — a fundamental property for photovoltaic applications. Here,

we reveal strong excitonic effects as the origin of this discrepancy between theory and experiment; a consequence of both low structural dimensionality and band localization. These findings have vital implications for the optoelectronic application of these compounds, while also highlighting the importance of frontier-orbital character for chemical substitution in materials design strategies.

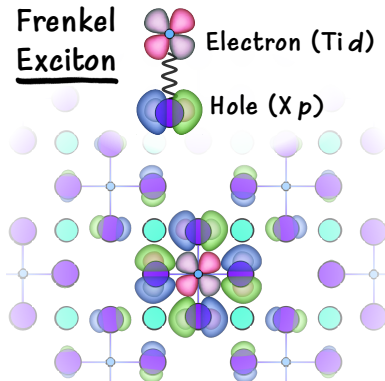

Perovskite-inspired materials aim to replicate the exceptional optoelectronic performance of lead-halide perovskites (LHPs), while avoiding issues of toxicity and operational stability.¹ For decades, the standard materials design approach for identifying novel inorganic semiconductors has been chemical substitution, where the undesirable elemental constituents (e.g. toxic Pb^{2+} in LHPs) are replaced by more favorable counterparts, while retaining the same structural motifs. For example, in the diamond-cubic crystal family, research moved from Group IV elements Si and Ge to II-VI compounds like CdTe – to yield direct rather than indirect electronic band gaps – and then further splitting into the I-III-VI₂ (e.g. CuInSe_2) and I₂-II-IV-VI₄ families (e.g. $\text{Cu}_2\text{ZnSnS}_4$) – to give earth-abundant compositions. While strategies such as dimensional modification² and disorder engineering^{3,4} have recently risen in popularity, elemental substitution remains the prevailing design approach.

Strategies to replace the divalent B-site cation in halide perovskites, while retaining the BX_6 octahedral motif, have led to the exploration of $\text{A}_2\text{BB}'\text{X}_6$ double perovskites with a pair of monovalent and trivalent cations at the B and B' sites,^{1,5,6} as well as the $\text{A}_3\text{B}_2\text{X}_9$ ‘vacancy-

ordered perovskites', where a trivalent B cation is combined with a 1/3 vacancy of the B-site to satisfy electroneutrality.⁷⁻⁹ Issues of indirect and/or large band gaps in these materials has led to the emergence of A_2BX_6 vacancy-ordered double perovskites (VODPs), where now the combination of a tetravalent cation and a 50 % vacancy of the B site is employed, giving a checkerboard arrangement (Fig. 1).¹⁰⁻¹² Also known as defective or tetravalent perovskites, these compounds are actually one of the decomposition products of conventional ABX_3 perovskites, for example $CsSnI_3$ which breaks down to form Cs_2SnI_6 .¹³

A_2BX_6 vacancy-ordered perovskites have shown promise for optoelectronic applications, with good stability under air, moisture, light and thermal stresses, as well as being solution-processable and non-toxic.^{11,14,15} As with the single and double perovskites, the frontier orbitals of the B-cation and X-anion govern the conduction and valence band-edge properties, respectively. This combination allows tunability in the energy gap, absorption profile and carrier effective masses for example. The A-site species, on the other hand, is a large monovalent cation such as Cs^+ which behaves as a spectator, dictating the spacing between BX_6 octahedra but with no direct contribution to the band edges. A crucial difference to the ABX_3 perovskite template, is the lack of corner-sharing BX_6 octahedra caused by vacancy introduction. Consequently, the crystal structure is comprised of isolated octahedra and thus an effective zero-dimensional (0D) framework, with this dramatic reduction in connectivity being a key factor in the properties of this material family.^{10,11,14} Research efforts in this area initially focused on the Sn-based compounds (A_2SnX_6),¹⁶ but have since expanded so that a range of tetravalent species have successfully been implemented in A_2BX_6 materials, including Te, Pd, Zr and Pt.¹⁷⁻²⁰ While some of these compounds have shown promise as potential white-light and tunable emitters, it is the Sn and Ti-based materials which have shown the most promising results in the context of solar photovoltaic applications, and thus received the majority of research attention. Cs_2SnI_6 was originally used as a hole-transporting layer in dye-sensitized solar cells, for instance, achieving efficiencies of 8%,¹⁶ while a Cs_2TiBr_6 photovoltaic device demonstrated a modest efficiency of 3%.¹⁴ The poor performance of

these materials has been attributed to relatively weak visible light absorption and indirect band gaps.²¹

As issues of defect intolerance and operational instability becoming apparent for Cs_2SnI_6 ,²² there is growing interest in the Ti-based compounds. The effects on structure, stability and electronic properties in going from the Group 14 $d^{10}s^0$ Sn^{4+} to Group 4 d^0s^0 Ti^{4+} cations have been probed,^{10,11,23} however the performance limits of these materials remains an open question. Notably, while theoretical methods are found to successfully reproduce the experimental electronic structure of the Te- and Sn-based compounds,¹¹ a major discrepancy exists for the d^0 Ti-based compounds,^{10,14,21,23–29} with severe overestimation of the experimental band gap by both hybrid Density Functional Theory (DFT) and Green’s function (GW) methods. So extreme is the error, that these theoretical methods actually yield qualitatively incorrect relative band gap energies for the Sn vs Ti compounds, as we show in this study.

Through in-depth computations including explicit electron-hole interactions via the Bethe-Salpeter equation (BSE), we resolve the Ti perovskite discrepancy and reveal strong excitonic effects as the origin. Electron-hole interactions result in significant renormalization of the lowest-energy electronic excitation, as well as qualitative reshaping of the optical absorption spectrum, finally reconciling computational predictions with experimental measurements. We elucidate the origins of this behavior, and highlight the implications of strong exciton binding for applications of these materials in optoelectronic devices.

The crystal structure of the Cs_2BX_6 ($\text{B} = \text{Sn}, \text{Ti}$; $\text{X} = \text{Cl}, \text{Br}, \text{I}$) family of vacancy-ordered perovskites is shown in Fig. 1. The low structural dimensionality of this family is expected to produce similar behavior to the corresponding $[\text{BX}_6]^{2-}$ molecular salts.^{16,24} One consequence of this ‘molecular’ crystal structure is the possibility for intermolecular interactions, such as London dispersion, between the localized octahedra. Table 1 corroborates this hypothesis, showing contraction of the calculated lattice parameters upon inclusion of dispersion corrections in the model, demonstrating the presence of important van der Waals

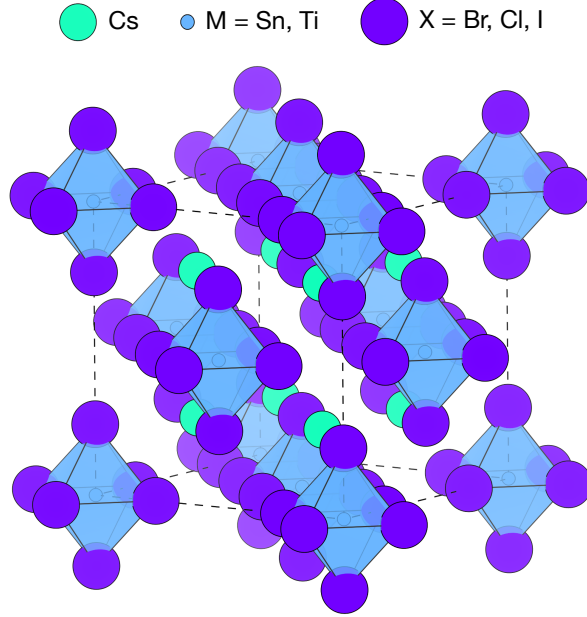


Figure 1: **a.** Crystal structure of Cs_2BX_6 vacancy-ordered perovskites, in the conventional cubic unit cell (space group: $Fm\bar{3}m$). Cs atoms in green, M-cations in blue, and halide anions (X) in purple.

(vdW) bonding contributions. Indeed, geometry optimization with hybrid DFT excluding dispersion corrections consistently overestimates the experimental lattice parameters by $\sim 3\%$, whereas inclusion of vdW effects gives lattice constants with errors $< 1\%$ in all cases. Semi-local DFT including dispersion corrections (PBE+D3) was also found to accurately reproduce the experimental lattice constants (Table S1). The change in lattice parameter (Δa_{D3}) is consistent within each halide subclass, irrespective of the B-site identity (Sn or Ti), reflecting the expected *inter-* ($\text{BX}_6\text{-BX}_6$) rather than *intra*-octahedral (B-X) origin of these vdW interactions. Moreover, we demonstrate the importance of dispersion interactions between the BX_6 molecular blocks on the electronic properties, showing the calculated energy band gap to shift by 0.04 – 0.31 eV in the optimized crystal structure. There is an increasing sensitivity of the band gap to the lattice parameter as we move down the halogen group (Cl \rightarrow Br \rightarrow I), as the through-space B-X and X-X interactions in the conduction and valence bands strengthen with larger X p orbitals, also explaining the reduced band gap shifts for B = Ti due to the more localized d orbitals. We further note a sensitivity of the

electronic band gap on the DFT functional choice for *geometry optimization*, with a band gap 0.4 eV lower (-40%) obtained for Cs_2SnI_6 using semi-local DFT (PBEsol) for structure relaxation.³⁰ Hybrid DFT including dispersion corrections was employed for all further DFT calculations in this study.

Table 1: Calculated cubic lattice parameters and electronic band gap shifts ($\Delta E_{g, \text{D3}}$) for Cs_2BX_6 (B = Sn, Ti; X = Cl, Br, I) using hybrid DFT including spin-orbit coupling (HSE06+SOC), with and without explicit inclusion of vdW dispersion interactions (D3 correction). Lattice parameter errors (Δa) given with respect to experimental values.^a

	Cs_2SnCl_6	Cs_2SnBr_6	Cs_2SnI_6	Cs_2TiCl_6	Cs_2TiBr_6	Cs_2TiI_6
a_{HSE06}	10.65 Å	11.15 Å	11.95 Å	10.51 Å	10.99 Å	11.76 Å
Δa_{HSE06}	2.8 %	3.5 %	2.7 %	2.6 %	2.9 %	2.3 %
$a_{\text{HSE06+D3}}$	10.32 Å	10.78 Å	11.54 Å	10.18 Å	10.62 Å	11.32 Å
$\Delta a_{\text{HSE06+D3}}$	-0.4 %	0.1 %	-0.9 %	-0.6 %	-0.6 %	-1.5 %
a_{Exp}	10.36 Å	10.77 Å	11.64 Å	10.24 Å	10.68 Å	11.5 Å
Δa_{D3}	-0.33 Å	-0.37 Å	-0.41 Å	-0.33 Å	-0.37 Å	-0.44 Å
$\Delta E_{g, \text{D3}}$	-0.14 eV	-0.23 eV	-0.31 eV	-0.04 eV	-0.08 eV	-0.15 eV

^a Experimental values taken from Refs: Cs_2SnCl_6 ,^{31,32} Cs_2SnBr_6 ,^{32,33} Cs_2SnI_6 ,^{30,32,34-36} Cs_2TiCl_6 ,^{23,37} Cs_2TiBr_6 ,^{21,23,37} Cs_2TiI_6 ,³⁸ matching with our measured values (Section S1.6)

The electronic band structures, density of states and charge densities at the valence band maximum (VBM) and conduction band minimum (CBM) for Cs_2TiI_6 and Cs_2SnI_6 are shown in Figs. 2 and 3. While Cs_2SnX_6 exhibit direct electronic band gaps at Γ , Cs_2TiX_6 have indirect gaps with the CBM at the \mathbf{X} high-symmetry k -point and the VBM remaining at Γ – in agreement with experimental studies.^{15,21} The direct/indirect gap energy difference (Δ) is relatively small however, with $\Delta = 0.06$ eV, 0.07 eV and 0.04 eV for the I, Br and Cl isomorphs respectively calculated using HSE06+SOC. As previously noted,^{10,11} the VBM and CBM electronic levels follow that predicted by BX_6^{2-} crystal-field splitting molecular orbital diagrams, with a $t_{2g}^*(\pi)$ Ti $d - \text{X } p$ CBM for Cs_2TiX_6 (d_{xy} , d_{xz} , d_{yz} ; threefold degenerate at Γ) and an $e_g^*(\sigma)$ band just above (d_{z^2} & $d_{x^2-y^2}$), a single $a_{1g}^*(\sigma)$ Sn $s - \text{X } p$ CBM for

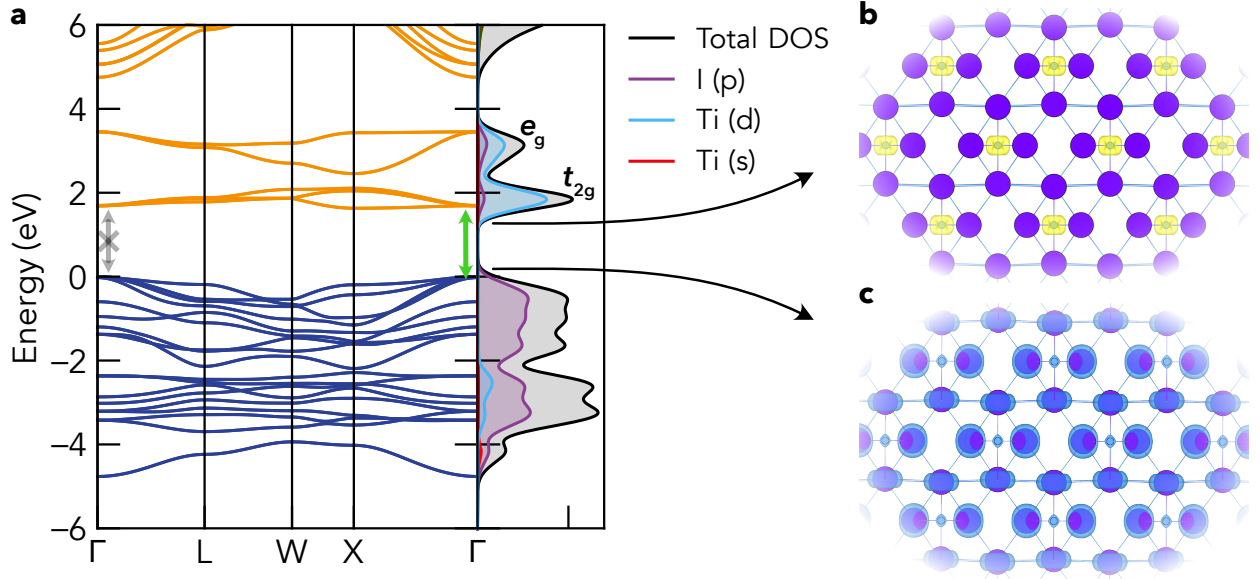


Figure 2: **a.** Electronic band structure of Cs_2TiI_6 calculated with hybrid DFT including spin-orbit coupling (HSE06+SOC), alongside a vertical plot of the orbital-projected electronic density of states. Faded gray and green arrows indicate the lowest-energy symmetry-forbidden and allowed electronic transition ($\Delta E_{t_{1g}/t_{1u}} = 0.02 \text{ eV}$), respectively. Valence band in blue, conduction band in orange, and valence band maximum (VBM) set to 0 eV. Ti d conduction bands are labeled with their crystal field orbital symmetries. Charge densities at the **(b.)** conduction band minimum (CBM) and **(c.)** VBM. Unoccupied states in yellow, occupied states in blue.

Cs_2SnX_6 , and non-bonding X p $t_{2g}(\pi)$ states at the VBM in all cases (Figs. 2 and 3 c). The centrosymmetric crystal structure and equal (gerade) parity with respect to inversion for the VBM and CBM states (Figs. 2 and 3 b,c) results in a dipole-forbidden transition at the direct band gap. Consequently, the symmetry-allowed direct band gap ($E_{g, \text{Allowed}}$) corresponds to the vertical transition from the second-highest valence band at Γ (t_{1u} (Γ_{15}) symmetry; $\psi_{\text{VBM}-1}$) to the CBM.

The halide p valence band is similar for both compounds, though with a slightly wider bandwidth ($\sim 0.5 \text{ eV}$) for the Ti analogues (Figs. 2 and 3 & Figs. S3 to S8) due to a significantly reduced anion-anion distance ($d_{\text{I-I}} = 4.03 \text{ \AA}$ vs 3.87 \AA for Cs_2SnI_6 vs Cs_2TiI_6) and wider interaction range between the cation valence orbitals (Ti s and d) with anion p states in the lower valence band, compared to Sn p . This is a consequence of reduced M-X bond lengths (2.73 \AA vs 2.85 \AA) and lattice parameters for B = Ti vs Sn (Table 1) — aided by

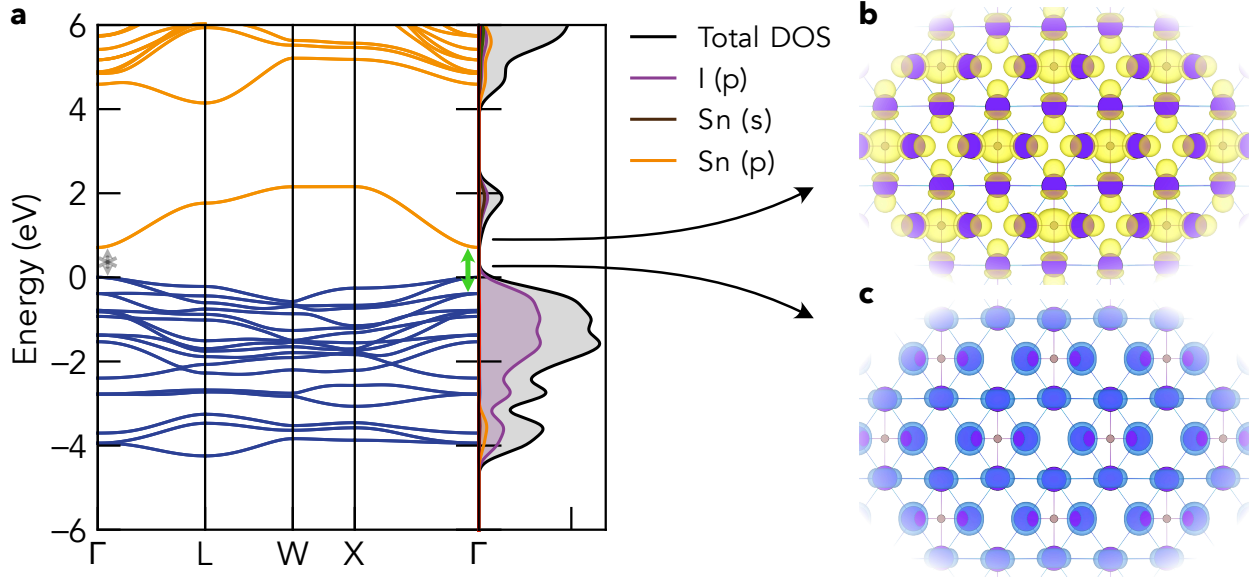


Figure 3: **a.** Electronic band structure of Cs_2SnI_6 calculated with hybrid DFT including spin-orbit coupling (HSE06+SOC), alongside a vertical plot of the orbital-projected electronic density of states. Faded gray and green arrows indicate the lowest-energy symmetry-forbidden and allowed electronic transition ($\Delta E_{t_{1g}/t_{1u}} = 0.38$ eV), respectively. Valence band in blue, conduction band in orange, and VBM set to 0 eV. Charge densities at the (**b.**) conduction band minimum (CBM) and (**c.**) valence band maximum (VBM), using the same isosurface levels as for Cs_2TiI_6 . Unoccupied states in yellow, occupied states in blue.

the reduced ionic radius of Ti^{4+} vs Sn^{4+} — resulting in a much lower energy difference between the t_{1g} ψ_{VBM} and t_{1u} $\psi_{\text{VBM}-1}$ for $B = \text{Ti}$ vs Sn , with $\Delta E_{t_{1g}/t_{1u}} = 0.02$ eV/0.38 eV, 0.07 eV/0.30 eV and 0.07 eV/0.07 eV for $B = \text{Ti/Sn}$; $X = \text{I, Br, Cl}$ (using HSE06+SOC). Another consequence is that, in contrast to the electron masses, the hole effective masses are actually larger for Cs_2SnX_6 than for Cs_2TiX_6 (Table 2). Unlike conventional perovskites and many other ‘perovskite-inspired’ materials which retain the partially-oxidized, filled valence subshell of the B cation (yielding antibonding character at the VBM^{1,39,40}), the fully-oxidized B^{4+} in $A_2\text{BX}_6$ means we have a less dispersive, non-bonding VBM;⁴ yielding heavier hole masses (particularly for $X = \text{Br, Cl}$) and aiding carrier localization. In contrast, the conduction band of the Sn analogues is relatively dispersive with low electron effective masses (Table 2) due to strong mixing and delocalization of the Sn s and X p states, while extremely flat bands are found for $B = \text{Ti}$ due to weak Ti d - X p mixing and localized, isolated Ti d states. The band structures of the bromide and chloride isomorphs are in-

cluded in Figs. S3 to S8, showing similar results, though with larger band gaps and reduced dispersion as X changes from I to Br to Cl. Further analysis of the electronic structure is provided in Section S2.

The electronic properties of the Cs_2BX_6 family are tabulated in Table 2. In order to illustrate the expected trends in exciton binding based on band structure and dielectric screening, the Wannier-Mott model binding energies are also included, calculated using the average carrier effective masses ($\overline{m}_{e/h}$) and high-frequency dielectric constants (ε_∞) from hybrid DFT (HSE06+SOC) according to:⁴¹

$$E_{\text{ex}} = -\frac{\mu}{m_0\varepsilon_\infty^2}\text{Ry} \quad (1)$$

where $\mu = (\overline{m}_e \times \overline{m}_h)/(\overline{m}_e + \overline{m}_h)$ is the reduced mass of the electron-hole pair, Ry is the Rydberg energy (13.6 eV) and m_0 is the electron rest mass.

Table 2: Calculated direct ($E_{g, \text{Direct}}$) and direct-allowed band gaps ($E_{g, \text{Allowed}}$), effective masses (\overline{m}_x)^a, high-frequency dielectric constants (ε_∞) and Wannier-Mott model exciton binding energies ($E_{\text{ex, Wannier}}$) for Cs_2BX_6 (B = Sn, Ti; X = Cl, Br, I) using hybrid DFT including spin-orbit coupling (HSE06+SOC). Comparison given to experimentally-reported band gap ranges.^b

	Cs_2SnCl_6	Cs_2SnBr_6	Cs_2SnI_6	Cs_2TiCl_6	Cs_2TiBr_6	Cs_2TiI_6
$E_{g, \text{Direct}}$	4.10 eV	2.39 eV	0.71 eV	3.68 eV	2.75 eV	1.69 eV
$E_{g, \text{Allowed}}$	4.38 eV	2.70 eV	1.09 eV	3.79 eV	2.84 eV	1.71 eV
$E_{g, \text{Exp}}$	4.4-4.9 eV	2.7-3.3 eV	1.25-1.3 eV	2.8-3.4 eV	1.8-2.3 eV	1.0-1.2 eV
\overline{m}_e	0.55 m_0	0.38 m_0	0.26 m_0	3.5 m_0	2.7 m_0	1.8 m_0
\overline{m}_h	2.2 m_0	1.3 m_0	0.78 m_0	2.2 m_0	0.90 m_0	0.55 m_0
ε_∞	2.86	3.37	4.54	3.26	3.84	5.08
$E_{\text{ex, Wannier}}$	0.73 eV	0.35 eV	0.13 eV	1.73 eV	0.62 eV	0.22 eV

^a \overline{m}_x are computed from the harmonic mean over directions and light/heavy bands for the effective masses. Values greater than 1 are given to 1 decimal place.

^b Experimental band gap values taken from Refs: Cs_2SnCl_6 ,^{31,32,42,43} Cs_2SnBr_6 ,^{32,35,36,42-44} Cs_2SnI_6 ,^{16,17,31,32,35,42,45} Cs_2TiCl_6 ,^{23,37} Cs_2TiBr_6 ,^{14,15,21,23,24,37,38,46} Cs_2TiI_6 .^{24,37}

From Table 2, we witness the typical trend of larger band gap with smaller and more electronegative halogen anions ($E_g(\text{Cl}) > E_g(\text{Br}) > E_g(\text{I})$), as observed across the perovskite(-

inspired) family.^{1,10} Typically, the smaller the B-site atom, the smaller the band gap in the A_2BX_6 family.^{10,47} This is the case experimentally here, with all Ti isomorphs having smaller experimentally-measured band gaps than their Sn counterparts. The opposite trend is found in the computed band gaps, for which hybrid DFT incorrectly predicts larger gaps for the Ti compounds (except for $X = Cl$). While the direct-allowed gaps computed by hybrid DFT mostly coincide with the lower end of experimental ranges for Cs_2SnX_6 , neglecting Wannier-Mott predicted exciton binding, the entirely opposite trend is found for each Cs_2TiX_6 isomorph, with a consistent severe *overestimation* of the experimental band gap. Notably, screened hybrid DFT (HSE06) tends to slightly *underestimate* rather than overestimate semiconductor band gaps, with this underestimation typically worsening with larger band gaps.^{48,49} The error in predicted band gaps for Cs_2TiX_6 results in *qualitatively* incorrect relative band gap energies for Cs_2SnX_6 vs Cs_2TiX_6 ($X = I, Br$).

A dielectric-dependent hybrid functional approach was also tested, which can improve the description of dielectric screening from hybrid DFT with fixed exchange (e.g. HSE06) and give reduced band gap prediction errors,^{49–51} though this only slightly reduced the hybrid DFT gap for Cs_2TiI_6 by 0.04 eV ($\alpha_{SCF} = 24\%$), still giving a significantly over-estimated band gap with a relative error $\Delta E_g = \sim 70\%$. Even using the computationally-intensive *GW* approximation, typically a gold standard for predicting band gaps,^{52,53} the calculated quasiparticle gaps in fact show far worse overestimation (both for Cs_2TiX_6 — as previously noted by Cucco et al.,¹⁰ and Cs_2SnX_6 ; Section S3). These observations suggest the presence of physical interactions in Cs_2TiX_6 which are not captured in these single-particle electronic models.

This major experiment-theory discrepancy is witnessed in reported values across the literature,^{10,14,21,23–29} but has not been addressed until now. In many cases, semi-local DFT (known to severely underestimate semiconductor band gaps)⁴⁸ has been employed in order to yield fortuitous error cancellation and thus theoretical values closer to experiment. As we show in this work, however, semi-local DFT predicts qualitatively incorrect relative

band gaps (even finding Cs_2SnI_6 to be metallic for example; Table S3), alongside incorrect absorption spectra, thus being unsuitable for modeling the electronic structure of A_2BX_6 compounds.

Using the Wannier-Mott effective mass model (Table 2),⁵⁴ we find large exciton binding energies, particularly for the Ti compounds (due to flat bands and heavy carrier masses), suggesting strong electron-hole interactions in these materials. Moreover, the large Wannier-Mott binding energies, isolated octahedra, low dielectric screening and highly-localized d orbitals suggests that strongly-bound excitons may be formed for Cs_2TiX_6 .⁴¹ To explore this hypothesis, we extend our model using GW to calculate quasiparticle eigenvalues and include electron-hole interactions via the Bethe-Salpeter equation (BSE). The optical absorption spectrum calculated with this approach, alongside that obtained from hybrid DFT and the experimental data, is shown in Fig. 4.

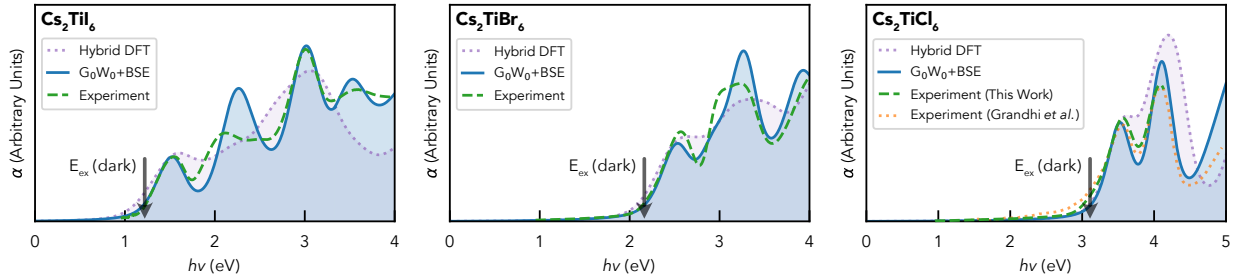


Figure 4: Optical absorption spectra of (left to right) Cs_2TiI_6 , Cs_2TiBr_6 and Cs_2TiCl_6 , calculated with both hybrid DFT (dotted violet) and the $G_0W_0 + BSE$ method (solid blue), alongside the experimental data from UV-Vis spectroscopy (dashed green). To directly compare the spectral shapes, calculated curves have been rigidly shifted to match the experimental absorption onset (unshifted results shown in Section S3).

Electron-hole interactions are found to dramatically redshift (Tables S2 and S3 and Fig. S10) and qualitatively alter the absorption spectra for Cs_2TiX_6 , now yielding excellent agreement with the peaked experimental spectra. Analysis of the electronic states reveals the lowest energy *bright* exciton peak to originate from the $t_{1u}(\pi + \sigma) \rightarrow t_{2g}(d)$ electronic transition as expected, i.e. from the second-highest valence band ($\psi_{\text{VBM}-1}$) at Γ (Fig. 2) to the CBM. The lowest energy *dark* excitonic state, indicated by the arrows in Fig. 4 and located

0.3-0.4 eV below the first bright peak, corresponds to the symmetry-forbidden $t_{1g}(\pi) \psi_{\text{VBM}} \rightarrow t_{2g}(d) \psi_{\text{CBM}}$ transition mentioned previously. While improved agreement with the experimental spectra is found for all Cs_2TiX_6 isomorphs, smaller changes in the spectral shapes are noticed for $\text{X} = \text{Br}, \text{Cl}$. This results from the low band dispersion in these compounds (demonstrated by the large effective masses in Table 2), resulting in similar strong excitonic downshifting of the low-energy excitations; $t_{1u}(\pi + \sigma) \rightarrow t_{2g}(d)$ and $t_{2u}(\pi) \rightarrow t_{2g}(d)$ corresponding to $\langle \psi_{\text{VBM}-1} | H' | \psi_{\text{CBM}} \rangle$ and $\langle \psi_{\text{VBM}-2} | H' | \psi_{\text{CBM}} \rangle$ transitions. Indeed in their recent paper, Grandhi et al.³⁷ refer to the absorption onset of Cs_2TiBr_6 as an exciton peak, with our calculations revealing in fact both low-energy peaks to be excitonic in nature. This strong renormalization of the low-energy excitations and lack of a band-like absorption onset rules out standard spectrum fitting techniques (such as the Tauc and Elliott models) for extracting band gap and exciton binding energies.^{55,56} Notably, the experimental spectra for TiBr_6^{2-} and TiCl_6^{2-} salts reported in Brisdon et al.⁵⁷ closely resemble the results for Cs_2TiBr_6 and Cs_2TiCl_6 reported here and in the literature,^{37,38} evidencing the conclusion of molecular crystal behavior, the orbital assignments of the absorption peaks and the presence of strong electron-hole interactions. Improved agreement between the calculated and experimental spectra is also found for the Sn compounds upon inclusion of electron-hole interactions, as weaker exciton interactions modify transition intensities and shift spectral weights to give more peak-like absorption onsets. The small residual mismatch in some cases between the GW +BSE and experimental spectra could be a result of temperature effects (vibrations can lower the symmetry-restriction of dark excitonic transitions in this range), quasiparticle lifetime broadening or the neglect of higher order terms in GW .^{56,58,59}

We highlight that the low-energy absorption peaks for Cs_2TiX_6 correspond to charge-transfer Frenkel excitons, with the electron wavefunction localized on the Ti t_{2g} d orbitals (d_{xy}, d_{xz}, d_{yz}) and the hole localized on the surrounding X p orbitals of the BX_6 octahedron. This form of exciton is commonly witnessed in organic and molecular crystals,⁶⁰ and has been well-established in other $3d^0$ ($\text{Ti}^{4+}, \text{Sc}^{3+}, \text{Ca}^{2+}$) halides,⁶¹ arising here as a consequence

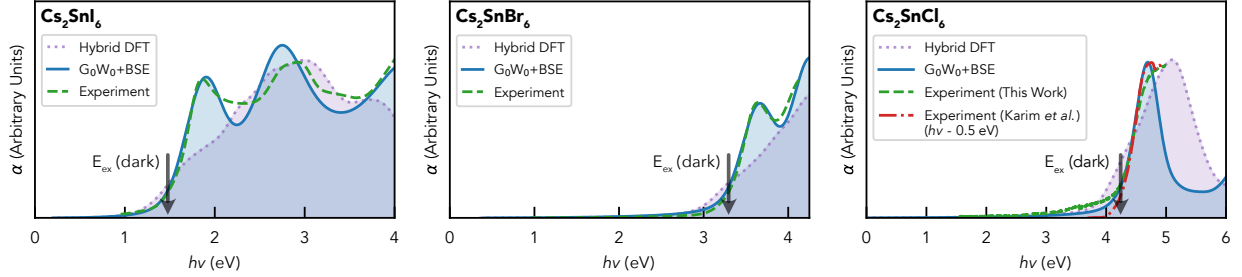


Figure 5: Optical absorption spectra of (left to right) Cs_2SnI_6 , Cs_2SnBr_6 and Cs_2SnCl_6 , calculated with both hybrid DFT (dotted violet) and the $G_0W_0 + BSE$ method (solid blue), alongside the experimental data from UV-Vis spectroscopy (dashed green). To directly compare the spectral shapes, calculated curves have been rigidly shifted to match the experimental absorption onset (unshifted results shown in Section S3). For Cs_2SnCl_6 , the absorption spectrum recorded by Karim et al.³² is also shown for comparison (downshifted by 0.5 eV as discussed in Section S3.4).

of the 0D polyhedral connectivity. The strongly-bound nature of these excitons is further demonstrated by the band contributions (“fatband plot”) shown in Fig. 6, where the delocalization of the exciton wavefunctions in reciprocal space for the Ti compounds corresponds to real space localization of the exciton wavepacket.⁴¹ The large Stokes shifts (~ 0.5 eV) and broad PL emission observed for this family of materials in both this and other studies^{15,21,23} is another characteristic result of localized bound excitons, as well as strong exciton-phonon coupling and low-energy dark excitons, with the photogenerated electron-hole pair readily localizing within the lattice to yield emissive self-trapped exciton (STE) states.

In contrast, the reduced effective masses of Cs_2SnX_6 yield a weakly-bound exciton as expected, demonstrated by dominant band contributions at the Γ point to the first bright exciton state. Fig. 6 also illustrates the differing trends in band structure for $B = \text{Sn}/\text{Ti}$, as X changes from I to Br to Cl, with a greater band gap increase and reduction in conduction band dispersion for Cs_2SnX_6 than Cs_2TiX_6 (such that the relative band gap energies of $B = \text{Sn}/\text{Ti}$ changes from $X = \text{I}$ ($E_{g, \text{Sn}} < E_{g, \text{Ti}}$) to $X = \text{Cl}$ ($E_{g, \text{Ti}} < E_{g, \text{Sn}}$)), due to the greater localization of the Ti d states. As discussed in Section S3, quasiparticle band gaps and thus exciton binding energies from $GW(+BSE)$ remain overestimated for these vacancy-ordered compounds, consistent with recent studies which attribute this behavior to under-screening

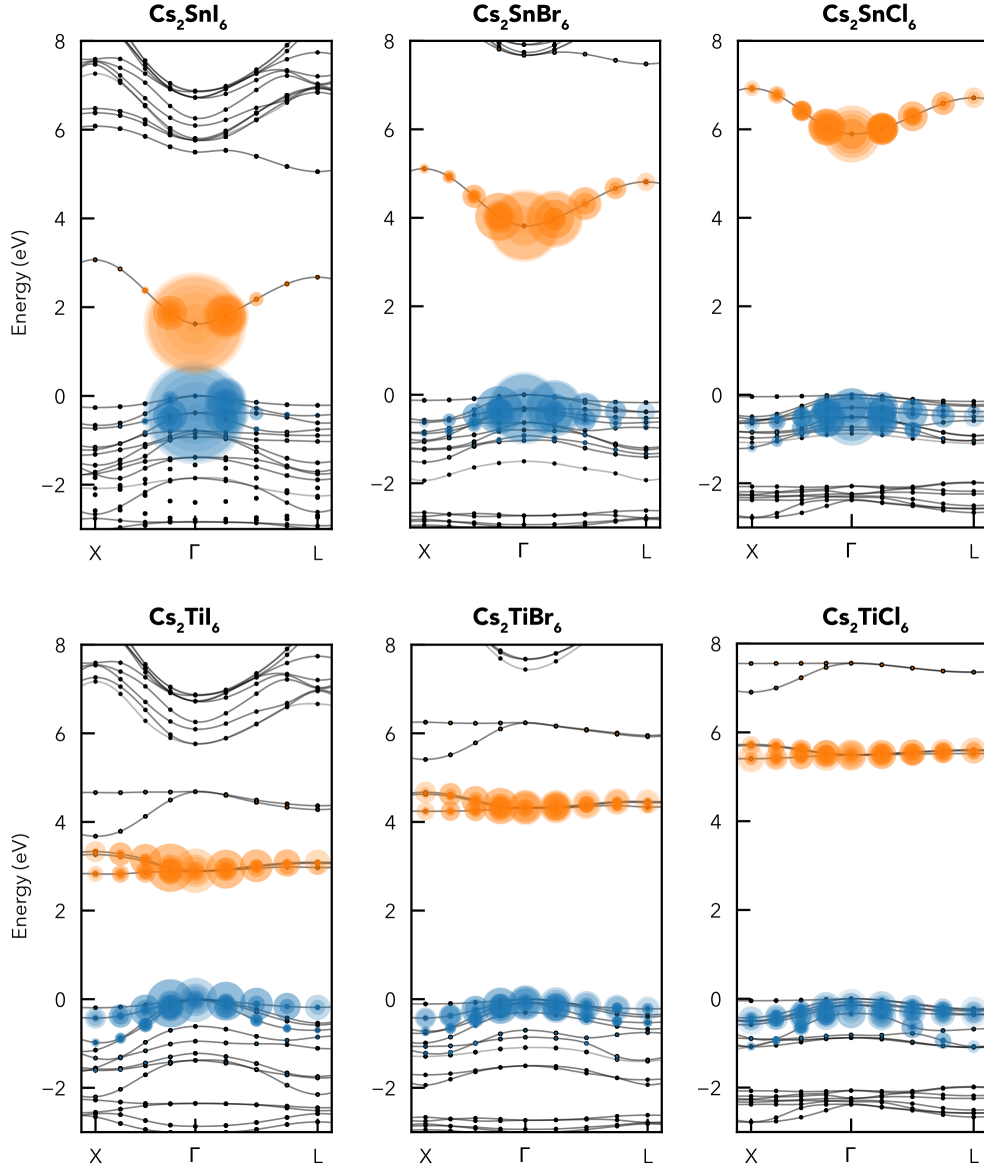


Figure 6: Band contributions to the brightest exciton state at the absorption onset in Cs_2SnX_6 (**top**) and Cs_2TiX_6 (**bottom**), calculated using the *BSE* approach. Band eigenvalues are indicated by the black dots, with filled circles weighted by their contributions to the exciton state and gray interpolating bands. The average of the three degenerate brightest states at the absorption onset is used, with the sum area of the filled circles normalized across all compositions. Hole and electron states are shown in blue and orange, respectively, and the VBM is set to 0 eV.

errors within the Random Phase Approximation (RPA) employed within GW .^{10,62–64} As such, to avoid this issue and obtain a reasonable estimate of the exciton binding energies in these systems, we also employed a constrained-supercell approach in which an exciton state is generated by controlling spin initialisation and band occupation. Here we calculate the exciton binding energy using hybrid DFT for multiple supercell sizes up to 972 atoms, then extrapolate to the dilute limit using the relevant scaling relationship to avoid supercell-size effects.^{65,66} With this approach, we obtain localised Frenkel exciton states as expected for each Cs_2TiX_6 (Fig. S13, TOC), with extrapolated binding energies of 0.44 eV, 0.52 eV and 0.72 eV for $X = \text{I}, \text{Br}, \text{Cl}$ (Fig. S14), which when subtracted from the HSE06+SOC direct-allowed transition energies in Table 2 brings the hybrid DFT optical transition energy into agreement with the experimental values in each case. For Cs_2SnX_6 , the electron and hole remain delocalised across the supercell with this approach (under a maximum cell length of 23.1 Å; Fig. S13), yielding extrapolated binding energies close to zero (Fig. S15). Further details provided in Section S3.3.

Crucially, these results demonstrate the presence of *qualitatively* different electronic behavior in the Cs_2SnX_6 and Cs_2TiX_6 families, where despite retaining the same cation valence, the change in frontier orbital character upon substitution of Sn^{4+} with Ti^{4+} dramatically alters the electronic structure and optical absorption. From the band structures in Fig. 6 and values in Table 2, it is clear that the electron effective masses (\overline{m}_e) dictate the exciton behavior in this family, with the weak dispersion and strong real-space localization of the flat d orbital conduction bands in Cs_2TiX_6 , aided by the zero-dimensional crystal structure, yielding strong electron-hole interactions. This strong excitonic renormalization of the optical absorption in Cs_2TiX_6 explains the origin of longstanding discrepancies between experiment and theoretical models of their electronic structure. Moreover, these findings serve as a warning of the changes that can occur when employing ionic substitution as a materials design approach, when such strategies involve changes in valence orbital character.

The presence of strong excitonic interactions in this material family is unsurprising, given

the low structural and electronic dimensionality (Figs. 1 and 2), weak band dispersion and large carrier effective masses (Table 2) discussed above. We find the exciton binding strength to be governed by the conduction band character in these compounds, giving the expectation for similar strongly-bound Frenkel excitons in A_2BX_6 compounds with isoelectronic (d^0) B^{4+} cations, such as Zr and Hf. Indeed, strong excitonic interactions have been recently been reported in Cs_2ZrX_6 — promising white-light emitters,²⁰ and a distinct excitonic feature is seen at the absorption onset in Cs_2HfCl_6 ^{67,68} — which has emission and radiation detection applications. Moreover, the bound excitonic behavior in this material class is very similar to that witnessed in the double perovskites,^{55,69,70} which despite a greater structural connectivity, exhibit a low *effective* electronic dimensionality due to orbital mismatch between the B-site cations.^{5,71} Likewise, extension of theoretical models to include explicit electron-hole interactions was required in order to reproduce the experimental spectrum,^{55,70,72} explaining the excitonic origin of the direct absorption onset.

In conclusion, by revealing strongly-bound excitonic behavior in the caesium titanium halide vacancy-ordered perovskites (Cs_2TiX_6), we reconcile longstanding discrepancies between theoretical predictions and experimental measurements for this material class. While previous theoretical studies have found semi-local DFT to yield band gaps matching experiment, we show this to be the result of fortuitous error cancellation with qualitatively incorrect absorption spectra and relative band gaps for Cs_2SnX_6 vs Cs_2TiX_6 ($X = I, Br$). Our results show that electron-hole interactions are crucial to obtaining the correct polarizability and dielectric screening between octahedra within many-body perturbation theory (MBPT) in these low-electronic-dimensionality systems. A range of optical, photoelectron and polarization spectroscopies could be employed to further study the behavior of excitons in this material class, including Stark spectroscopy, temperature-dependent optical measurements, excitation-dependent THz and electromodulation spectroscopies.^{58,61,69,73} Moreover, the majority of previous theoretical studies have not included vdW dispersion interactions when modeling these systems, yet here we demonstrate their importance in obtaining ac-

curate crystal and electronic structure predictions, calling for their inclusion in future computational studies of these and related low-dimensional and ‘molecular’ crystals such as the A_4BX_6 family.

These findings have important implications for optoelectronic applications. Strong exciton binding can significantly reduce charge separation and open-circuit voltages (V_{oc}) in solar cells, likely one of the key origins of the poor photovoltaic performance achieved thus far in this material class. Our results show the key role of structural dimensionality and octahedral connectivity, alongside orbital chemistry, in determining the effective electronic dimensionality and optoelectronic properties of inorganic perovskite-inspired materials. More generally, these findings illustrate the importance of considering frontier orbital character when employing atomic substitution in materials engineering and design strategies – here resulting in qualitatively different electronic behavior despite equal cation valence and similar band gaps.

Calculations were performed using both Density Functional Theory (DFT) and quasiparticle Green’s function (GW) approaches within periodic boundary conditions, through the Vienna Ab Initio Simulation Package (VASP).⁷⁴ Scalar-relativistic pseudo-potentials were employed to describe the interaction between core and valence electrons, via the projector-augmented wave (PAW) method.⁷⁵ Specifically, the Cs_sv, Sn_d, Ti_pv, I, Br and Cl VASP PAW potentials were used. The effect of pseudopotential choice and DFT starting point (semi-local vs hybrid) on the GW results was tested and found to give qualitatively similar results, with the same large overestimation of bandgaps relative to experiment (details in Section S3).

Initial guesses for the crystal structures were obtained from the Materials Project, before relaxing the geometry using the HSE06 screened hybrid DFT functional.⁷⁶ The plane-wave energy cutoff and Γ -centered k -point mesh were sequentially increased using `vaspup2.0`⁷⁷ until total energies from static calculations were converged to 0.1 meV/atom – giving values of 300 eV and $3 \times 3 \times 3$ (for the 9-atom primitive unit cell, equivalent to a k -point density

of 0.33 \AA^{-1} in reciprocal space) respectively. During structural optimization, a convergence criterion of 0.01 eV/\AA was imposed on the forces on each atom, and the plane-wave energy cutoff was increased to 500 eV , as well as re-relaxing the final geometries, to avoid Pulay stress effects. As discussed at the beginning of the results section, the effect of dispersion corrections (Grimme’s D3)⁷⁸ on the structural relaxation was tested and shown to be important; and so the HSE06+D3 (using the recommended PBE0+BJ parameterizations)⁷⁹ relaxed unit cells were used for all further calculations in this work.

Electronic band structures and independent-particle optical absorption spectra were initially calculated with the HSE06 hybrid DFT functional, including spin-orbit coupling effects (HSE06+SOC) due to the presence of heavy-atom elements (see Results and Section S4). For density of states (DOS) and optical calculations, the k -point mesh for the primitive unit cell was increased to $8 \times 8 \times 8$ (reciprocal space density of 0.12 \AA^{-1}), and the tetrahedron smearing method was used. The number of virtual states in the optical calculations was increased using `vaspup2.0`⁷⁷ until the high-frequency dielectric constant ϵ_∞ was converged to a precision of 0.01. Electronic band structure diagrams were generated using `sumo`.⁸⁰ Carrier effective masses were determined using non-parabolic fitting of the band edges through the `effmass`⁸¹ package.

Wavefunctions calculated using HSE06+SOC were used as input orbitals for the $G_0W_0(+\text{BSE})$ calculations. While only having a modest effect on the band gap energies, SOC was found to have a relatively significant effect on the spectral shape above the absorption onset, as shown in Section S4. Convergence with respect to the number of virtual states / empty bands, imaginary frequency and time grid points, and electron-hole excitation pairs was confirmed in each case. Given the lack of symmetry reduction, requirement for large numbers of virtual states / empty bands (particularly when including spin-orbit coupling effects) and rapid scaling of computational cost (memory) with k -point density in the $G_0W_0+\text{BSE}$ calculations, a $3 \times 3 \times 3$ mesh (for the 9-atom primitive unit cell, equivalent to a k -point density of 0.33 \AA^{-1} in reciprocal space) was the maximum tractable k -point mesh for Cs_2BX_6

with our computational resources. While converged for the Br and Cl compounds, the greater band dispersion of the iodides (Cs_2BI_6) means the spectra are not well converged for this k -point density, thus the ‘model BSE’ approach^{82,83} was employed to reach converged k -point meshes of $4 \times 4 \times 4$ and $8 \times 8 \times 8$ for Cs_2TiI_6 and Cs_2SnI_6 respectively. Further details on the G_0W_0 +BSE calculations are given in Section S3.

Details of the experimental synthesis and absorption measurements are provided in Section S1.

Author contributions. Conceptualization: Seán R. Kavanagh, Gerasimos Konstantatos, Aron Walsh, David O. Scanlon. Investigation and methodology: Seán R. Kavanagh, Shanti M. Liga, Christopher N. Savory. Writing - original draft: Seán R. Kavanagh. Writing - review & editing: Seán R. Kavanagh, Christopher N. Savory, Shanti M. Liga, Gerasimos Konstantatos, Aron Walsh, David O. Scanlon. Supervision, resources and funding acquisition: Gerasimos Konstantatos, Aron Walsh, David O. Scanlon. These author contributions are defined according to the CRediT contributor roles taxonomy.

Acknowledgement

The authors thank Alex M. Ganose for useful discussions regarding the electronic structure of A_2BX_6 vacancy-ordered perovskites. Seán R. Kavanagh acknowledges the EPSRC Centre for Doctoral Training in the Advanced Characterisation of Materials (CDT-ACM)(EP/S023259/1) for funding a PhD studentship. AW acknowledges support from a National Research Foundation of Korea (NRF) grant funded by the Korean Government (MSIT) (2018R1C1B6008728). DOS acknowledges support from the EPSRC (EP/N01572X/1) and from the European Research Council, ERC (Grant No. 758345). We acknowledge the use of the UCL Kathleen High Performance Computing Facility (Kathleen@UCL), the Imperial College Research Computing Service, and associated support services, in the completion of this work. Via membership of the UK’s HEC Materials Chemistry Consortium, which

is funded by the EPSRC (EP/L000202, EP/R029431, EP/T022213), this work used the ARCHER2 UK National Supercomputing Service (www.archer2.ac.uk) and the UK Materials and Molecular Modelling (MMM) Hub (Thomas – EP/P020194 & Young – EP/T022213). The authors acknowledge financial support from the European Research Council (ERC) under the European Union’s Horizon 2020 research and innovation programme (grant agreement no. 725165) as well as from the European Union’s Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie grant agreement no. 713729. This project has received funding also from the Spanish State Research Agency, through the Severo Ochoa Center of Excellence CEX2019-000910-S, the CERCA Programme/Generalitat de Catalunya and Fundacio´ Mir-Puig. We also acknowledge funding by the Fundacio´ Joan Ribas Araquistain (FJRA). This project was funded also by EQC2019-005797-P (AEI/FEDER UE).

Supporting Information Available

Experimental Methods; DFT Functional Dependence of Lattice Parameters; Additional Electronic Structure Analysis; Further *GW* Calculation Details & Analysis; Spin-Orbit Coupling (SOC) Analysis. Data produced during this work is freely available at: [10.5281/zenodo.6906620](https://doi.org/10.5281/zenodo.6906620).

References

- (1) Huang, Y.-T.; Kavanagh, S. R.; Scanlon, D. O.; Walsh, A.; Hoye, R. L. Z. Perovskite-Inspired Materials for Photovoltaics and beyond—from Design to Devices. *Nanotechnology* **2021**, *32*, 132004.
- (2) Aubrey, M. L.; Saldivar Valdes, A.; Filip, M. R.; Connor, B. A.; Lindquist, K. P.; Neaton, J. B.; Karunadasa, H. I. Directed Assembly of Layered Perovskite Heterostructures as Single Crystals. *Nature* **2021**, *597*, 355–359.

- (3) Wang, Y.; Kavanagh, S. R.; Burgués-Ceballos, I.; Walsh, A.; Scanlon, D.; Konstantatos, G. Cation Disorder Engineering Yields AgBiS₂ Nanocrystals with Enhanced Optical Absorption for Efficient Ultrathin Solar Cells. *Nat. Photon.* **2022**, *16*, 235–241.
- (4) Huang, Y.-T. et al. Strong Absorption and Ultrafast Localisation in NaBiS₂ Nanocrystals with Slow Charge-Carrier Recombination. *Nat Commun* **2022**, *13*, 4960.
- (5) Savory, C. N.; Walsh, A.; Scanlon, D. O. Can Pb-Free Halide Double Perovskites Support High-Efficiency Solar Cells? *ACS Energy Lett.* **2016**, *1*, 949–955.
- (6) Nie, R.; Sumukam, R. R.; Reddy, S. H.; Banavoth, M.; Seok, S. I. Lead-Free Perovskite Solar Cells Enabled by Hetero-Valent Substitutes. *Energy Environ. Sci.* **2020**, *13*, 2363–2385.
- (7) Krajewska, C. J.; Kavanagh, S. R.; Zhang, L.; Kubicki, D. J.; Dey, K.; Galkowski, K.; Grey, C. P.; Stranks, S. D.; Walsh, A.; Scanlon, D. O.; Palgrave, R. G. Enhanced Visible Light Absorption in Layered Cs₃Bi₂Br₉ through Mixed-Valence Sn(II)/Sn(IV) Doping. *Chem. Sci.* **2021**, *12*, 14686–14699.
- (8) Peng, Y.; Li, F.; Wang, Y.; Li, Y.; Hoye, R. L. Z.; Feng, L.; Xia, K.; Pecunia, V. Enhanced Photoconversion Efficiency in Cesium-Antimony-Halide Perovskite Derivatives by Tuning Crystallographic Dimensionality. *Appl. Mater. Today* **2020**, *19*, 100637.
- (9) Roy, M.; Ghorui, S.; Bhawna.; Kangsabanik, J.; Yadav, R.; Alam, A.; Aslam, M. Enhanced Visible Light Absorption in Layered Cs₃Bi₂Br₉ Halide Perovskites: Heterovalent Pb²⁺ Substitution-Induced Defect Band Formation. *J. Phys. Chem. C* **2020**, *124*, 19484–19491.
- (10) Cucco, B.; Boudier, G.; Pedesseau, L.; Katan, C.; Even, J.; Kepenekian, M.; Volonakis, G. Electronic Structure and Stability of Cs₂TiX₆ and Cs₂ZrX₆ (X = Br, I) Vacancy Ordered Double Perovskites. *Appl. Phys. Lett.* **2021**, *119*, 181903.

- (11) Maughan, A. E.; Ganose, A. M.; Scanlon, D. O.; Neilson, J. R. Perspectives and Design Principles of Vacancy-Ordered Double Perovskite Halide Semiconductors. *Chem. Mater.* **2019**, *31*, 1184–1195.
- (12) Sa, R.; Zhang, Q.; Luo, B.; Liu, D. Exploring the Electronic and Optical Properties of Vacancy-Ordered Double Perovskites Cs_2PtX_6 ($X = \text{Cl}, \text{Br}, \text{I}$). *J. Solid State Chem.* **2021**, *304*, 122602.
- (13) Wu, J.; Fang, F.; Zhao, Z.; Li, T.; Ullah, R.; Lv, Z.; Zhou, Y.; Sawtell, D. Fluorine Ion Induced Phase Evolution of Tin-Based Perovskite Thin Films: Structure and Properties. *RSC Adv.* **2019**, *9*, 37119–37126.
- (14) Chen, M.; Ju, M.-G.; Carl, A. D.; Zong, Y.; Grimm, R. L.; Gu, J.; Zeng, X. C.; Zhou, Y.; Padture, N. P. Cesium Titanium(IV) Bromide Thin Films Based Stable Lead-free Perovskite Solar Cells. *Joule* **2018**, *2*, 558–570.
- (15) He, Y.; Guo, X.; Zheng, H.; Xu, L.; Li, S. Stability Investigation of the Titanium-Based Eco-Friendly Perovskite-like Antifluorite Cs_2TiBr_6 . *J. Mater. Chem. C* **2022**, *10*, 9301–9309.
- (16) Lee, B.; Stoumpos, C. C.; Zhou, N.; Hao, F.; Malliakas, C.; Yeh, C.-Y.; Marks, T. J.; Kanatzidis, M. G.; Chang, R. P. H. Air-Stable Molecular Semiconducting Iodosalts for Solar Cell Applications: Cs_2SnI_6 as a Hole Conductor. *J. Am. Chem. Soc.* **2014**, *136*, 15379–15385.
- (17) Maughan, A. E.; Ganose, A. M.; Bordelon, M. M.; Miller, E. M.; Scanlon, D. O.; Neilson, J. R. Defect Tolerance to Intolerance in the Vacancy-Ordered Double Perovskite Semiconductors Cs_2SnI_6 and Cs_2TeI_6 . *J. Am. Chem. Soc.* **2016**, *138*, 8453–8464.
- (18) Evans, H. A.; Fabini, D. H.; Andrews, J. L.; Koerner, M.; Preefer, M. B.; Wu, G.; Wudl, F.; Cheetham, A. K.; Seshadri, R. Hydrogen Bonding Controls the Structural

- Evolution in Perovskite-Related Hybrid Platinum(IV) Iodides. *Inorg. Chem.* **2018**, *57*, 10375–10382.
- (19) Sakai, N.; Haghghirad, A. A.; Filip, M. R.; Nayak, P. K.; Nayak, S.; Ramadan, A.; Wang, Z.; Giustino, F.; Snaith, H. J. Solution-Processed Cesium Hexabromopalladate(IV), Cs₂PdBr₆, for Optoelectronic Applications. *J. Am. Chem. Soc.* **2017**, *139*, 6030–6033.
- (20) Abfalterer, A.; Shamsi, J.; Kubicki, D. J.; Savory, C. N.; Xiao, J.; Divitini, G.; Li, W.; Macpherson, S.; Galkowski, K.; MacManus-Driscoll, J. L.; Scanlon, D. O.; Stranks, S. D. Colloidal Synthesis and Optical Properties of Perovskite-Inspired Cesium Zirconium Halide Nanocrystals. *ACS Mater. Lett.* **2020**, *2*, 1644–1652.
- (21) Euvrard, J.; Wang, X.; Li, T.; Yan, Y.; Mitzi, D. B. Is Cs₂TiBr₆ a Promising Pb-free Perovskite for Solar Energy Applications? *J. Mater. Chem. A* **2020**, *8*, 4049–4054.
- (22) Saparov, B.; Sun, J.-P.; Meng, W.; Xiao, Z.; Duan, H.-S.; Gunawan, O.; Shin, D.; Hill, I. G.; Yan, Y.; Mitzi, D. B. Thin-Film Deposition and Characterization of a Sn-Deficient Perovskite Derivative Cs₂SnI₆. *Chem. Mater.* **2016**, *28*, 2315–2322.
- (23) Kong, D.; Cheng, D.; Wang, X.; Zhang, K.; Wang, H.; Liu, K.; Li, H.; Sheng, X.; Yin, L. Solution Processed Lead-Free Cesium Titanium Halide Perovskites and Their Structural, Thermal and Optical Characteristics. *J. Mater. Chem. C* **2020**, *8*, 1591–1597.
- (24) Ju, M.-G.; Chen, M.; Zhou, Y.; Garces, H. F.; Dai, J.; Ma, L.; Padture, N. P.; Zeng, X. C. Earth-Abundant Nontoxic Titanium(IV)-Based Vacancy-Ordered Double Perovskite Halides with Tunable 1.0 to 1.8 eV Bandgaps for Photovoltaic Applications. *ACS Energy Lett.* **2018**, *3*, 297–304.
- (25) Li, W.; Zhu, S.; Zhao, Y.; Qiu, Y. Structure, Electronic and Optical Properties of

- $\text{Cs}_2\text{Ti}(\text{Br}_{1-x}\text{Y}_x)_6$ ($\text{Y} = \text{Cl, I}$; $x = 0, 0.25, 0.5, 0.75, 1$) Perovskites: The First Principles Investigations. *J. Solid State Chem.* **2020**, *284*, 121213.
- (26) Mahmood, Q.; Hassan, M.; Yousaf, N.; AlObaid, A. A.; Al-Muhimeed, T. I.; Morsi, M.; Albalawi, H.; Alamri, O. A. Study of Lead-Free Double Perovskites Halides Cs_2TiCl_6 , and Cs_2TiBr_6 for Optoelectronics, and Thermoelectric Applications. *Mater. Sci. Semicond. Process* **2022**, *137*, 106180.
- (27) Zhao, P.; Su, J.; Guo, Y.; Wang, L.; Lin, Z.; Hao, Y.; Ouyang, X.; Chang, J. Cs_2TiI_6 : A Potential Lead-Free All-Inorganic Perovskite Material for Ultrahigh-Performance Photovoltaic Cells and Alpha-Particle Detection. *Nano Res.* **2021**,
- (28) Natick, A.; Abid, Y.; Moubah, R.; Abid, M.; Lassri, H. Ab-Initio Investigation of the Structural, Electronic and Optical Properties of Lead-Free Halide Cs_2TiI_6 Double Perovskites. *Solid State Commun.* **2020**, *319*, 114006.
- (29) Liu, D.; Zha, W.; Yuan, R.; Chen, J.; Sa, R. A First-Principles Study on the Optoelectronic Properties of Mixed-Halide Double Perovskites $\text{Cs}_2\text{TiI}_{6-x}\text{Br}_x$. *New J. Chem.* **2020**, *44*, 13613–13618.
- (30) Maughan, A. E.; Ganose, A. M.; Candia, A. M.; Granger, J. T.; Scanlon, D. O.; Neilson, J. R. Anharmonicity and Octahedral Tilting in Hybrid Vacancy-Ordered Double Perovskites. *Chem. Mater.* **2018**, *30*, 472–483.
- (31) Zhu, W.; Xin, G.; Wang, Y.; Min, X.; Yao, T.; Xu, W.; Fang, M.; Shi, S.; Shi, J.; Lian, J. Tunable Optical Properties and Stability of Lead Free All Inorganic Perovskites ($\text{Cs}_2\text{SnI}_x\text{Cl}_{6-x}$). *J. Mater. Chem. A* **2018**, *6*, 2577–2584.
- (32) Karim, M. M. S.; Ganose, A. M.; Pieters, L.; Winnie Leung, W. W.; Wade, J.; Zhang, L.; Scanlon, D. O.; Palgrave, R. G. Anion Distribution, Structural Distortion, and Symmetry-Driven Optical Band Gap Bowing in Mixed Halide Cs_2SnX_6 Vacancy Ordered Double Perovskites. *Chem. Mater.* **2019**, *31*, 9430–9444.

- (33) Ketelaar, J. A. A.; Rietdijk, A. A.; van Staveren, C. H. Die Kristallstruktur von Ammonium-, Kalium-, Rubidium- und Cäsiumstannibromid. *Recl. Trav. Chim. Pays-Bas* **1937**, *56*, 907–908.
- (34) Stoumpos, C. C.; Malliakas, C. D.; Kanatzidis, M. G. Semiconducting Tin and Lead Iodide Perovskites with Organic Cations: Phase Transitions, High Mobilities, and Near-Infrared Photoluminescent Properties. *Inorg. Chem.* **2013**, *52*, 9019–9038.
- (35) Lee, B.; Krenselewski, A.; Baik, S. I.; Seidman, D. N.; Chang, R. P. H. Solution Processing of Air-Stable Molecular Semiconducting Iodosalts, $\text{Cs}_2\text{SnI}_{6-x}\text{Br}_x$, for Potential Solar Cell Applications. *Sustain. Energy Fuels* **2017**, *1*, 710–724.
- (36) Kaltzoglou, A.; Antoniadou, M.; Kontos, A. G.; Stoumpos, C. C.; Perganti, D.; Siranidi, E.; Raptis, V.; Trohidou, K.; Psycharis, V.; Kanatzidis, M. G.; Falaras, P. Optical-Vibrational Properties of the Cs_2SnX_6 ($X = \text{Cl}, \text{Br}, \text{I}$) Defect Perovskites and Hole-Transport Efficiency in Dye-Sensitized Solar Cells. *J. Phys. Chem. C* **2016**, *120*, 11777–11785.
- (37) Grandhi, G.; Matuhina, A.; Liu, M.; Annurakshita, S.; Ali-Löytty, H.; Bautista, G.; Vivo, P. Lead-Free Cesium Titanium Bromide Double Perovskite Nanocrystals. *Nanomaterials* **2021**, *11*, 1458.
- (38) Liga, S. M.; Konstantatos, G. Colloidal Synthesis of Lead-Free $\text{Cs}_2\text{TiBr}_{6-x}\text{I}_x$ Perovskite Nanocrystals. *J. Mater. Chem. C* **2021**, *9*, 11098–11103.
- (39) Kavanagh, S. R.; Savory, C. N.; Scanlon, D. O.; Walsh, A. Hidden Spontaneous Polarisation in the Chalcogenide Photovoltaic Absorber $\text{Sn}_2\text{SbS}_2\text{I}_3$. *Mater. Horiz.* **2021**, *8*, 2709–2716.
- (40) Tang, G.; Ghosez, P.; Hong, J. Band-Edge Orbital Engineering of Perovskite Semiconductors for Optoelectronic Applications. *J. Phys. Chem. Lett.* **2021**, *12*, 4227–4239.

- (41) Fox, M. *Optical Properties of Solids*, second edition ed.; Oxford Master Series in Physics; Oxford University Press: Oxford, New York, 2010.
- (42) Dalpian, G. M.; Liu, Q.; Stoumpos, C. C.; Douvalis, A. P.; Balasubramanian, M.; Kanatzidis, M. G.; Zunger, A. Changes in Charge Density vs Changes in Formal Oxidation States: The Case of Sn Halide Perovskites and Their Ordered Vacancy Analogues. *Phys. Rev. Mater.* **2017**, *1*, 025401.
- (43) Zhou, J.; Luo, J.; Rong, X.; Wei, P.; Molokeev, M. S.; Huang, Y.; Zhao, J.; Liu, Q.; Zhang, X.; Tang, J.; Xia, Z. Lead-Free Perovskite Derivative $\text{Cs}_2\text{SnCl}_{6-x}\text{Br}_x$ Single Crystals for Narrowband Photodetectors. *Adv. Opt. Mater.* **2019**, *7*, 1900139.
- (44) Bonomi, S.; Patrini, M.; Bongiovanni, G.; Malavasi, L. Versatile Vapor Phase Deposition Approach to Cesium Tin Bromide Materials CsSnBr_3 , CsSn_2Br_5 and Cs_2SnBr_6 . *RSC Adv.* **2020**, *10*, 28478–28482.
- (45) Zhang, J.; Yu, C.; Wang, L.; Li, Y.; Ren, Y.; Shum, K. Energy Barrier at the N719-dye/ CsSnI_3 Interface for Photogenerated Holes in Dye-Sensitized Solar Cells. *Sci. Rep.* **2015**, *4*, 6954.
- (46) Mendes, J. L.; Gao, W.; Martin, J. L.; Carl, A. D.; Deskins, N. A.; Granados-Focil, S.; Grimm, R. L. Interfacial States, Energetics, and Atmospheric Stability of Large-Grain Antifluorite Cs_2TiBr_6 . *J. Phys. Chem. C* **2020**, *124*, 24289–24297.
- (47) Cai, Y.; Xie, W.; Ding, H.; Chen, Y.; Thirumal, K.; Wong, L. H.; Mathews, N.; Mhaisalkar, S. G.; Sherburne, M.; Asta, M. Computational Study of Halide Perovskite-Derived A_2BX_6 Inorganic Compounds: Chemical Trends in Electronic Structure and Structural Stability. *Chem. Mater.* **2017**, *29*, 7740–7749.
- (48) Chen, W.; Pasquarello, A. Band-Edge Levels in Semiconductors and Insulators: Hybrid Density Functional Theory versus Many-Body Perturbation Theory. *Phys. Rev. B* **2012**, *86*, 035134.

- (49) Chen, W.; Miceli, G.; Rignanese, G.-M.; Pasquarello, A. Nonempirical Dielectric-Dependent Hybrid Functional with Range Separation for Semiconductors and Insulators. *Phys. Rev. Mater.* **2018**, *2*, 073803.
- (50) Zheng, H.; Govoni, M.; Galli, G. Dielectric-Dependent Hybrid Functionals for Heterogeneous Materials. *Phys. Rev. Mater.* **2019**, *3*, 073803.
- (51) Skone, J. H.; Govoni, M.; Galli, G. Self-Consistent Hybrid Functional for Condensed Systems. *Phys. Rev. B* **2014**, *89*, 195112.
- (52) Shishkin, M.; Marsman, M.; Kresse, G. Accurate Quasiparticle Spectra from Self-Consistent *GW* Calculations with Vertex Corrections. *Phys. Rev. Lett.* **2007**, *99*, 246403.
- (53) Leppert, L.; Rangel, T.; Neaton, J. B. Towards Predictive Band Gaps for Halide Perovskites: Lessons from One-Shot and Eigenvalue Self-Consistent *G W*. *Phys. Rev. Mater.* **2019**, *3*, 103803.
- (54) Wannier, G. H. The Structure of Electronic Excitation Levels in Insulating Crystals. *Phys. Rev.* **1937**, *52*, 191–197.
- (55) Biega, R.-I.; Filip, M. R.; Leppert, L.; Neaton, J. B. Chemically Localized Resonant Excitons in Silver–Pnictogen Halide Double Perovskites. *J. Phys. Chem. Lett.* **2021**, *12*, 2057–2063.
- (56) Radha, S. K.; Lambrecht, W. R. L.; Cunningham, B.; Grüning, M.; Pashov, D.; van Schilfgaarde, M. Optical Response and Band Structure of LiCoO_2 Including Electron-Hole Interaction Effects. *Phys. Rev. B* **2021**, *104*, 115120.
- (57) Brisdon, B. J.; Lester, T. E.; Walton, R. A. Complex Halides of Transition Metals—III Electronic Absorption Spectra of Hexahalotitanates(IV), Vanadates(IV), and

- Zirconates(IV). *Spectrochimica Acta Part A: Molecular Spectroscopy* **1967**, *23*, 1969–1976.
- (58) Qiu, D. Y.; da Jornada, F. H.; Louie, S. G. Optical Spectrum of MoS₂: Many-Body Effects and Diversity of Exciton States. *Phys. Rev. Lett.* **2013**, *111*, 216805.
- (59) Marini, A.; Del Sole, R. Dynamical Excitonic Effects in Metals and Semiconductors. *Phys. Rev. Lett.* **2003**, *91*, 176402.
- (60) Lanzani, G. *The Photophysics behind Photovoltaics and Photonics*; John Wiley & Sons, 2012.
- (61) de Boer, D. K. G.; Haas, C.; Sawatzky, G. A. Exciton Satellites in Photoelectron Spectra. *Phys. Rev. B* **1984**, *29*, 4401–4419.
- (62) Acharya, S.; Pashov, D.; Rudenko, A. N.; Rösner, M.; van Schilfhaarde, M.; Katsnelson, M. I. Importance of Charge Self-Consistency in First-Principles Description of Strongly Correlated Systems. *npj Comput. Mater.* **2021**, *7*, 208.
- (63) Cunningham, B.; Gruening, M.; Pashov, D.; van Schilfhaarde, M. QSGW: Quasiparticle Self Consistent GW with Ladder Diagrams in W. *arXiv:2106.05759 [cond-mat]* **2021**,
- (64) Cunningham, B.; Grüning, M.; Azarhoosh, P.; Pashov, D.; van Schilfhaarde, M. Effect of Ladder Diagrams on Optical Absorption Spectra in a Quasiparticle Self-Consistent GW Framework. *Phys. Rev. Mater.* **2018**, *2*, 034603.
- (65) Freysoldt, C.; Neugebauer, J.; Van de Walle, C. G. Fully *Ab Initio* Finite-Size Corrections for Charged-Defect Supercell Calculations. *Phys. Rev. Lett.* **2009**, *102*, 016402.
- (66) Swift, M. W.; Peelaers, H.; Mu, S.; Morton, J. J. L.; Van de Walle, C. G. First-Principles Calculations of Hyperfine Interaction, Binding Energy, and Quadrupole Coupling for Shallow Donors in Silicon. *npj Comput Mater* **2020**, *6*, 1–9.

- (67) Buryi, M.; Babin, V.; Lighthart, R. A. M.; Nagorny, S. S.; Mikhailik, V. B.; Vaněček, V.; Prouzová Prochazková, L.; Kandel, R.; Nahorna, V. V.; Wang, P. Correlation of Emission, Scintillation and Charge Trapping Properties in Cs_2HfCl_6 and Cs_2ZrCl_6 Single Crystals. *J. Mater. Chem. C* **2021**, *9*, 2955–2968.
- (68) Liu, S.; Yang, B.; Chen, J.; Zheng, D.; Tang, Z.; Deng, W.; Han, K. Colloidal Synthesis and Tunable Multicolor Emission of Vacancy-Ordered Cs_2HfCl_6 Perovskite Nanocrystals. *Laser Photonics Rev.* **2022**, *16*, 2100439.
- (69) Wright, A. D.; Buizza, L. R. V.; Savill, K. J.; Longo, G.; Snaith, H. J.; Johnston, M. B.; Herz, L. M. Ultrafast Excited-State Localization in $\text{Cs}_2\text{AgBiBr}_6$ Double Perovskite. *J. Phys. Chem. Lett.* **2021**, *12*, 3352–3360.
- (70) Palummo, M.; Berrios, E.; Varsano, D.; Giorgi, G. Optical Properties of Lead-Free Double Perovskites by Ab Initio Excited-State Methods. *ACS Energy Lett.* **2020**, *5*, 457–463.
- (71) Xiao, Z.; Meng, W.; Wang, J.; Mitzi, D. B.; Yan, Y. Searching for Promising New Perovskite-Based Photovoltaic Absorbers: The Importance of Electronic Dimensionality. *Mater. Horiz.* **2017**, *4*, 206–216.
- (72) Li, Z.; Kavanagh, S. R.; Napari, M.; Palgrave, R. G.; Abdi-Jalebi, M.; Andajifar, Z.; Davies, D. W.; Laitinen, M.; Julin, J.; Isaacs, M. A.; Friend, R. H.; Scanlon, D. O.; Walsh, A.; Hoye, R. L. Z. Bandgap Lowering in Mixed Alloys of $\text{Cs}_2\text{Ag}(\text{Sb}_x\text{Bi}_{1-x})\text{Br}_6$ Double Perovskite Thin Films. *J. Mater. Chem. A* **2020**, *8*, 21780–21788.
- (73) Feldmann, S.; Gangishetty, M. K.; Bravić, I.; Neumann, T.; Peng, B.; Winkler, T.; Friend, R. H.; Monserrat, B.; Congreve, D. N.; Deschler, F. Charge Carrier Localization in Doped Perovskite Nanocrystals Enhances Radiative Recombination. *J. Am. Chem. Soc.* **2021**, *143*, 8647–8653.

- (74) Kresse, G.; Furthmüller, J. Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set. *Phys. Rev. B* **1996**, *54*, 11169–11186.
- (75) Blöchl, P. E. Projector Augmented-Wave Method. *Phys. Rev. B* **1994**, *50*, 17953–17979.
- (76) Heyd, J.; Scuseria, G. E.; Ernzerhof, M. Hybrid Functionals Based on a Screened Coulomb Potential. *J. Chem. Phys.* **2003**, *118*, 8207–8215.
- (77) Kavanagh, S. R. Vaspup2.0; Github.Com/Kavanase/Vaspup2.0. 2022.
- (78) Grimme, S.; Antony, J.; Ehrlich, S.; Krieg, H. A Consistent and Accurate Ab Initio Parametrization of Density Functional Dispersion Correction (DFT-D) for the 94 Elements H-Pu. *J. Chem. Phys.* **2010**, *132*, 154104.
- (79) Grimme, S.; Ehrlich, S.; Goerigk, L. Effect of the Damping Function in Dispersion Corrected Density Functional Theory. *J. Comp. Chem.* **2011**, *32*, 1456–1465.
- (80) Ganose, A. M.; Jackson, A. J.; Scanlon, D. O. Sumo: Command-line Tools for Plotting and Analysis of Periodic *Ab Initio* Calculations. *J. Open Source Softw.* **2018**, *3*, 717.
- (81) Whalley, L. D. Effmass: An Effective Mass Package. *J. Open Source Softw.* **2018**, *3*, 797.
- (82) Varrassi, L.; Liu, P.; Yavas, Z. E.; Bokdam, M.; Kresse, G.; Franchini, C. Optical and Excitonic Properties of Transition Metal Oxide Perovskites by the Bethe-Salpeter Equation. *Phys. Rev. Mater.* **2021**, *5*, 074601.
- (83) Tal, A.; Liu, P.; Kresse, G.; Pasquarello, A. Accurate Optical Spectra through Time-Dependent Density Functional Theory Based on Screening-Dependent Hybrid Functionals. *Phys. Rev. Res.* **2020**, *2*, 032019.