

Engineering Robust Battery Interphases with Dilute Fluorinated Cations

Chulgi Nathan Hong¹, Mengwen Yan², Oleg Borodin³, Travis P. Pollard³, Langyuan Wu⁴, Manuel Reiter¹, Dario Gomez Vazquez¹, Katharina Trapp¹, Jimun Yoo¹, Netanel Shpigel⁴, Jeremy I. Feldblyum², and Maria R. Lukatskaya^{1,*}

¹ Electrochemical Energy Systems Laboratory, Department of Mechanical and Process Engineering, ETH Zurich, Zürich 8092, Switzerland

² Department of Chemistry, The University at Albany, State University of New York, Albany, NY, 12222, USA

³ Battery Science Branch, DEVCOM Army Research Laboratory, Adelphi, MD 20783, USA

⁴ Department of Chemical Sciences, Ariel University, Ariel 40700, Israel

* Correspondence address: mlukatskaya@ethz.ch

Controlling solid electrolyte interphase (SEI) in batteries is crucial for their efficient cycling. Herein, we demonstrate an approach to enable robust battery performance that does not rely on high fractions of fluorinated species in electrolytes, thus substantially decreasing the environmental footprint and cost of high-energy batteries. In this approach, we use very low fractions of readily reducible fluorinated cations in electrolyte (~0.1 wt.%) and employ electrostatic attraction to generate a substantial population of these cations at the anode surface. As a result, we can form a robust fluorine-rich SEI that allows for dendrite-free deposition of dense Li and stable cycling of Li-metal full cells with high-voltage cathodes. Our approach represents a general strategy for delivering desired chemical species to battery anodes through electrostatic attraction while using minute amounts of additive.

KEYWORDS: Lithium metal batteries, electrolytes, electrolyte additives, electrostatic interaction, solid electrolyte interphase, cathode electrolyte interphase

Replacement of traditional intercalation anodes such as graphite (372 mAh g⁻¹) or lithium titanium oxide (175 mAh g⁻¹) with Li metal (3860 mAh g⁻¹) can enable high-energy battery cells,¹ providing a solution to the current energy density bottlenecks for batteries.^{2,3,4} However, Li metal anodes are prone to developing dendritic and porous (mossy) deposits during repetitive charge/discharge cycling. This leads to an unacceptably low cycle life and introduces serious safety concerns, prohibiting practical implementation of lithium metal batteries (LiMBs).^{2, 3, 4, 5} The Li plating/stripping process and cycle life of LiMBs are strongly affected by the properties of the so-called solid electrolyte interphase (SEI). An SEI is a layer formed on the electrode surface as a result of the decomposition of electrolyte components such as solvent, salt, and molecular additives.^{3,6} Electrolyte composition is known to dramatically affect the properties of the resulting SEI (e.g. structure, chemistry, and homogeneity) and lithium plating/stripping (coulombic) efficiency, morphology and cycle life.⁴ Commercial Li-ion electrolyte chemistries are based on carbonate solvents and Li-ion salts that were originally developed and optimized for graphite anodes. However, when these conventional carbonate-based electrolytes are used in combination with Li-metal anodes, they yield highly unsatisfactory cycle life due to unfavorable SEI chemistry at the Li-metal surface.^{2, 3, 4, 5} Specifically, insufficient electronic insulation, structural instability and heterogeneity of the SEI result in uncontrolled SEI growth and the formation of electronically disconnected “dead lithium” and/or dendrites.^{5, 7} This results in low coulombic efficiencies (well below 99 % that is required⁷ for every cycle

in long-life LiMBs). Therefore, the development of new electrolytes that can yield favorable SEI on Li-metal anodes constitutes a critical research direction.⁷

Recent research suggests that fluorine-rich SEI yields superior performance compared to fluorine-free SEI.^{3, 8, 9} To achieve fluorine-rich SEI, state-of-the-art approaches rely on large volume fractions of fluorinated species in the electrolyte that have a statistically higher probability of being reduced at the electrode surface and, therefore, generate fluorine-rich SEI.¹⁰ For example, solvent-in-salt electrolytes with a high concentration of fluorine-containing anions yield fluorine-rich SEIs and much improved coulombic efficiencies compared to their dilute counterparts.¹¹ Recently, another way to generate a fluorine enriched SEI from fluorine-containing salts at intermediate concentrations was reported by employing a modified solvent with siloxane groups¹² or through usage of surface-modified separators.¹³ Also, fluorinated solvents themselves can be used to form high-quality SEIs.^{8, 14} Yet, despite enabling promising performance, these approaches have notable drawbacks when it comes to their practical implementation. The high cost of Li salts and increased solution viscosity at high salt concentration makes highly concentrated electrolytes challenging to implement in commercial batteries. Similarly, the replacement of conventional solvents with heavily fluorinated ones can lead to substantial increases in battery costs and environmental footprint.

Herein, we establish an alternative approach that relies on the electrostatic attraction of fluorinated cations to a negatively charged anode. Through this approach, a significant population of fluorinated species can reach the electrode surface even when the overall additive concentration in the bulk electrolyte is in the millimolar range. Importantly, to ensure the predominant contribution of fluorinated cations to SEI formation, their reduction potential should be significantly higher than that of solvent molecules or anions in electrolyte (as schematically depicted in Fig. 1a). To this end, we selected fluorinated methylpyridinium cations (Fig. 1a) that can offer early decomposition potentials of ~ 2 V vs. Li/Li⁺ (at least ~ 1.5 V before solvent decomposition starts). First, we show that the addition of fluorinated methylpyridinium cations even in millimolar amounts (0.08 - 0.14 wt. %) to a conventional electrolyte based on 1,2-dimethoxyethane (DME) enables F-enriched SEI and dense Li plating with an increased coulombic efficiency of 99.6 % (compared to 96.4 % obtained in additive-free electrolytes). Second, we demonstrate prolonged cycling of a full cell with Li metal anode and Ni-rich high-voltage cathode in ether-based electrolytes with 99.6 % average coulombic efficiency, which is achieved by suppressing oxidative decomposition of DME upon addition of small amounts of fluorinated cations. Third, the fluorinated cations also suppress corrosion of the Al current collector caused by chlorine impurities in the electrolyte, thus assisting with prolonged cycling of the full cell.

Effect of fluorinated cations on cycling of lithium metal anodes

The choice of fluorinated methylpyridinium cations was dictated by the following considerations: (1) previous experiments showed pyridinium-based cations undergo reductive decomposition at ~ 1.75 V vs. Li/Li⁺,^{15, 16} which is well above the decomposition potentials of non-aqueous solvents and anions; (2) quantum-chemical calculations suggest that fluorination of methylpyridinium cations would further shift the reduction potential to even higher values¹⁷ (Supplementary Fig. 1), potentially providing a simple pathway for the formation of fluorine-rich SEI. In our experiments, we used N-methyl-2,4,6-trifluoropyridinium (TFP) as a fluorinated cationic additive in a form of perchlorate salt. As the baseline electrolyte we used 1 M lithium bis(fluorosulfonyl)imide (LiFSI) in DME because it shows one of the highest coulombic efficiencies (96.4 %) for Li plating/stripping among additive-free electrolyte formulations.⁸

Cyclic voltammetry (CV) profiles collected in additive-containing electrolytes show a pronounced reduction peak at ~ 1.98 V vs. Li/Li⁺ (Figure 1b) during the 1st cycle, which is absent in the additive-free electrolyte. The current associated with the reduction peak scales with the concentration of TFP (Supplementary Fig. 2). Furthermore, identical position of TFP-related reduction peak is observed regardless of whether TFP additive is used in the form of perchlorate or triflate salt (Supplementary Fig. 3). The reduction peak disappears in the 2nd cycle, consistent with passivation of the anode surface, preventing further reduction of fluorinated cations. These experiments confirm that the reduction of fluorinated cations occurs at potentials nearly ~ 1.5 V higher than the onset of decomposition of the additive-free electrolyte.¹⁸ In contrast, no distinct reduction CV peaks or subsequent passivation was observed upon addition of the same concentrations of the neutral analogue, 2,4,6-trifluoropyridine (TFN), indicating importance of the additive charge in enabling its efficiency. These results are also in agreement with density functional theory (DFT) calculations that predict TFN's low reduction potential of 0.23 V vs Li/Li⁺ (Supplementary Fig. 1a).

To quantify how the addition of fluorinated cations affects the coulombic efficiency of Li plating/stripping, we used a modified Aurbach protocol¹⁹ (Supplementary Fig. 4a). The test revealed a substantial improvement of average coulombic efficiency from 96.4 % for the TFP-free electrolyte to 99.6 % for the cells containing TFP (~ 0.1 wt. %, Supplementary Fig. 4b). This efficiency is comparable to those reported for the best-performing electrolytes containing fluorinated solvent^{8, 20} or salts in high concentrations,^{11, 21} demonstrating that large fractions of fluorinated species in electrolytes can be avoided when aiming for high coulombic efficiencies.

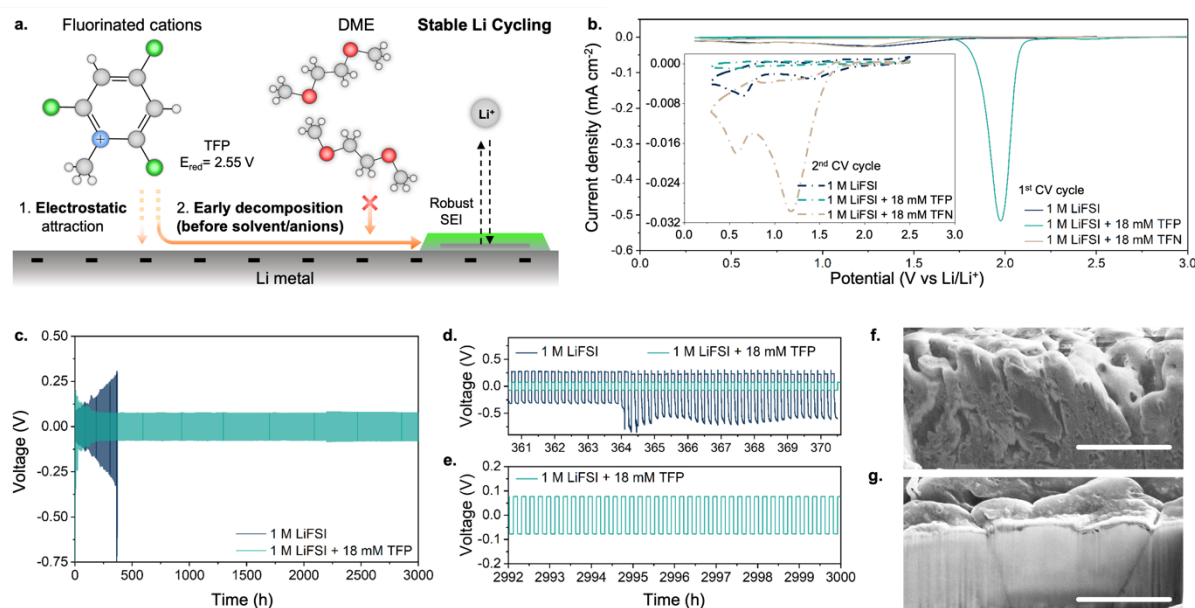


Figure 1. a. Schematic diagram of SEI formation from a fluorinated cationic additive on a Li-metal anode. b. First and second (inset) cycle CV profiles collected in DME + 1 M LiFSI electrolytes with and without fluorinated cations (TFP) and fluorinated neutral analogue (TFN) using a 1 mm Cu disk working electrode at a 0.5 mV s^{-1} scan rate and a voltage window of 0.3 – 2.5 V vs. Li/Li⁺. c. Galvanostatic cycling of a Li⁰-Li⁰ symmetric cell at 10 mA cm^{-2} using DME + 1 M LiFSI as an electrolyte with and without fluorinated cations (TFP). d-e. Zoomed-in voltage profile of c. f-g. Cross-sectional SEM images of the cycled Li metal (f – after 1852 cycles in DME + 1 M LiFSI, g – after 2000 cycles in DME + 1 M LiFSI + 12 mM TFP) showing Li metal deposit morphologies. Scale bar: 5 μm . Before SEM, a lamella (5 μm deep) was cut out using cryo-FIB.

Next, we performed long-term galvanostatic cycling at 10 mA cm^{-2} using a Li⁰-Li⁰ symmetric cell configuration (Fig. 1c). A dramatic difference was observed between the cells with and without TFP. For cells with additive-free electrolyte, a continuous increase in overpotential due to the

formation of dead lithium was observed with cycling (similar to previous reports^{22,23}), resulting in cell failure after 400 h (Fig. 1d). In contrast, addition of millimolar amounts of fluorinated cations enabled outstanding cycling stability and, after initial stabilization, the overpotential remained almost unchanged for at least 3000 h of cycling (Fig. 1e). Moreover, the cycling stability increases with the concentration of fluorinated cations (Supplementary Fig. 5), showing the greatest stability for the 18 mM concentration (Figure 1c).

Importantly, the morphology of Li metal correlated with the evolution of overpotential with cycling. Initially, comparable overpotentials and similar Li morphology were observed for both electrolytes (Supplementary Fig. 6). After 371 hours of cell cycling, for the additive-free electrolyte a rough Li surface with multiple cracks can be seen by scanning electron microscopy (SEM; Fig. 1f, Supplementary Fig. 7a), with highly porous Li deposits and in agreement with prior studies.²⁴ In contrast, a smooth surface with large and dense Li grains was observed for Li metal that was cycled in the electrolyte containing TFP (Fig. 1g, Supplementary Fig. 7b).

Solid Electrolyte Interphase

To understand the origin of the superior cycling performance of the Li-metal anode in TFP-containing electrolytes, we performed studies of the SEI layers formed in the presence of TFP using X-ray photoelectron spectroscopy (XPS), electrochemical quartz crystal microbalance with dissipation monitoring (EQCM-D), and quantum chemistry calculations (Fig. 2). The XPS data collected from cycled Cu electrodes revealed a high fluorine:carbon (F:C) atomic ratio for the SEI formed in the presence of cationic additives (F:C = 3.1 – 4.5), whereas no fluorine was detected for the SEI generated in reference electrolyte (Fig 2a). This indicates a dramatically decreased relative contribution of the solvent decomposition products. Furthermore, analysis of F 1s and Li 1s spectra revealed LiF as a dominant species for SEI samples obtained in the presence of fluorinated cations (Fig. 2b, Supplementary Fig. 8 and Supplementary Table 1). Similarly, a more than three-fold enrichment of SEI with fluorine was observed for a Li metal electrode cycled in the presence of TFP (Li⁰ || Li⁰ symmetric cell, one week of galvanostatic cycling at 10 mA cm⁻², Supplementary Fig. 9). This indicates that even millimolar addition of the fluorinated cations can yield favorable F-rich SEI.

Next, EQCM-D measurements show that the SEI formed in electrolytes with cationic additive is highly rigid since the change of the overtone-normalized resonant frequency ($\Delta f_n/n$) and energy dissipation (ΔD_n) are independent²⁵ of overtone order (n) (Fig. 2c). Therefore, we can apply the Sauerbrey equation to obtain gravimetric information for the formed SEI. By comparing the theoretical and experimental frequencies²⁶, we attribute the main frequency decrease at ~ 2 V to the formation of LiF, which is in good agreement with the XPS results (Supplementary Fig. 10 and Fig. 2b). Moreover, no further mass gain was observed after the first CV cycle, indicating the highly desirable robust and passivating nature of the formed SEI. In contrast, the SEI formed in the additive-free electrolyte displays viscoelastic behavior: ΔD_n depends on overtone order and larger values of dissipation modulus are observed.^{25,26,27} Upon cycling, a continuous increase in charge, $\Delta f_n/n$ and ΔD_n can be seen, indicative of uncontrolled SEI growth due to the non-compact and porous nature of the formed interfacial layers.²⁵

Since both XPS and EQCM-D suggest that SEI formed in the presence of TFP is mainly LiF, we further investigated the detailed SEI formation pathway using DFT calculations and MD simulations. The DFT calculations suggest that TFP reduction is the dominant process due to the electrostatic attraction of TFP to the negative electrode and its higher reduction potential (2.1 - 2.5 V vs. Li/Li⁺) compared to FSI⁻ (Fig. 2d and Supplementary Fig. 11). Meanwhile, FSI⁻ reduction is unlikely here due

to the low affinity of FSI^- to the negative electrode²⁸ and low fraction of contact ion pairs (CIPs) or aggregates of LiFSI in DME at this salt concentration (<30%) observed in MD simulations (see Supplementary Discussion) and previous work.^{29, 30} Reduced TFP^* radicals at the anode surface undergo a second reduction and release of F^- that results in the formation of LiF when TFP^* is in close proximity to Li^+ (Fig. 2d and Supplementary Fig. 11). A subsequent reduction and defluorination is also likely when the $\text{Li}^+/\text{TFP}^*_{(-\text{F})}$ complex is exposed to potentials below 1.9 V vs. Li/Li^+ . This allows the additive to deliver multiple F^- to form LiF-rich SEI. Alternatively, the reduced TFP^* radicals can dimerize after their 1st reduction to form a fluorinated viologen species which undergoes spontaneous defluorination in proximity of Li^+ across the newly formed C-C bond (left panel of Supplementary Fig. 12). The viologen species can form an anion (2nd reduction) at ~ 0.6 V with subsequent release of another LiF (3rd reduction; in the box in Supplementary Fig. 12).

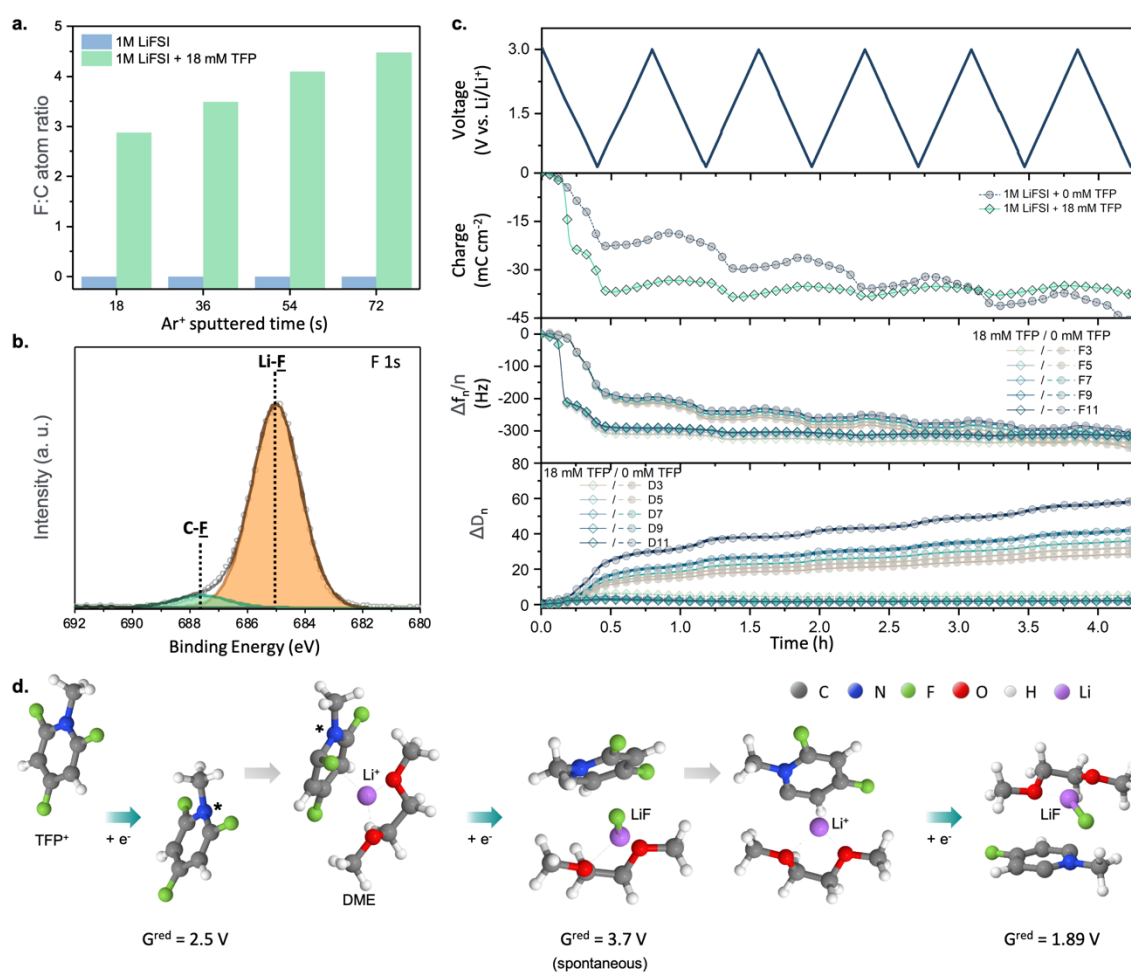


Figure 2. a. F:C atomic ratio in the SEI layer formed on a Cu electrode as a function of depth. b. XPS F 1s spectrum of a SEI layer formed on a Cu electrode after cycling in DME + 1 M LiFSI + 18 mM TFP with Ar⁺ sputtered time of 72 s (estimated depth: 2.0 nm). c. Voltage, charge, frequency, and dissipation change versus time using EQCM-D analysis for DME + 1 M LiFSI and DME + 1 M LiFSI + 18 mM TFP. d. Products of reduction at the negative electrode obtained from DFT calculations, see Supplementary Fig. 11 for further details.

Oxidative decomposition of electrolytes and full cell performance

Improvement of battery energy density requires coupling of Li-metal anodes with high-voltage cathodes.^{11, 31} Previous studies suggest that high-voltage cathode materials cannot be used in non-concentrated DME-based electrolytes due to the oxidative decomposition of DME solvent above 4 V vs. Li/Li^+ .^{8, 20, 32} When we studied the oxidative stability of DME-based electrolytes with fluorinated

cations, we found that the potential for the oxidative decomposition is shifted by approximately +200 mV (4.76 V to 4.95 V at 0.5 mA cm⁻²) when TFP⁺ is added to the electrolyte (Supplementary Fig. 13). Because we use perchlorate as a counter anion, we also explored its effect on the stability of the electrolyte. By performing cyclic voltammetry tests in solutions containing 10 mM LiClO₄ and 10 mM TFP-ClO₄ (in DME + 1M LiFSI), we observed that the addition of 10 mM LiClO₄ results in lower decomposition currents at 5 V compared to a pure DME + 1M LiFSI solution. This observation suggests that perchlorate anions contribute to enhancing the oxidation stability of DME-based electrolytes (as shown in Supplementary Fig. 13 c). Notably, the electrolyte containing both TFP⁺ and ClO₄⁻ demonstrates even greater stability, with oxidative currents reduced by half, emphasizing the advantageous role of TFP⁺.

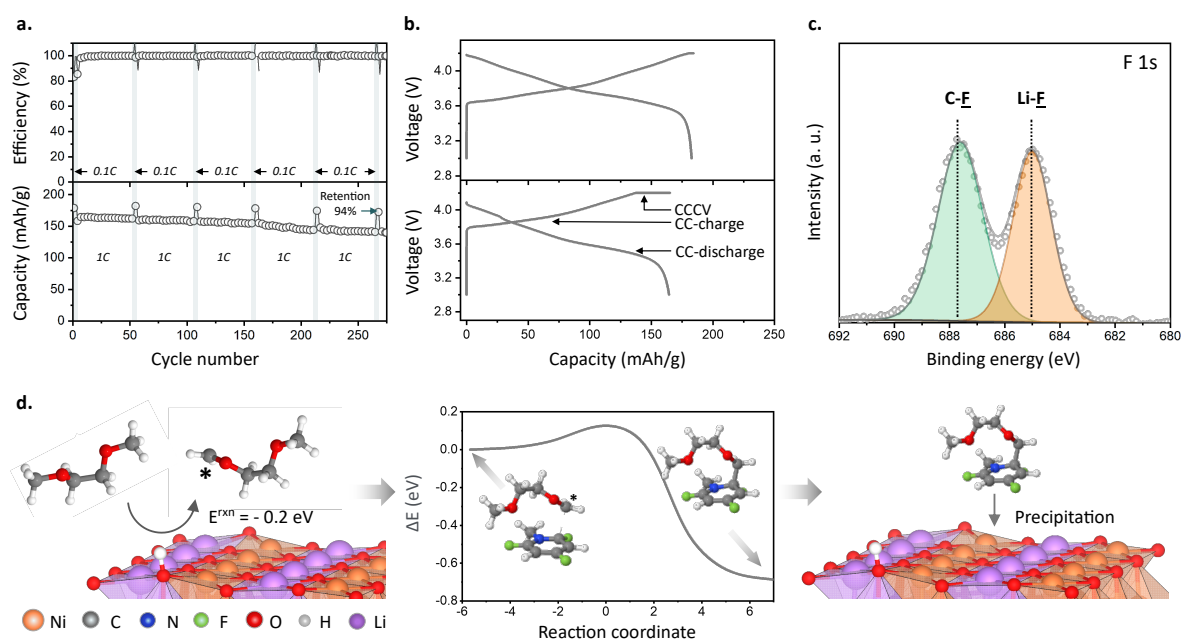


Figure 3. NCM811 || Li full-cell performance. **a.** Long-term cycling of NCM811 || 50 μm Li full cells in DME + 0.96 M LiFSI + 12 mM TFP ClO₄ (0.1 C-rate for three cycles and 1 C-rate for 50 cycles in a loop). **b.** Voltage profile of NCM811 || Li full-cells at 0.1 C-rate and 1 C-rate. **c.** XPS F 1s spectra of CEI layer formed on NCM811 electrodes cycled in DME + 0.96 M LiFSI + 12 mM TFP ClO₄. **d.** DFT results predicting H-transfer from DME to LiNiO₂ positive electrode followed by DME*_(-H) reaction with TFP⁺ that leads to the F-enriched CEI formation in the presence of additive.

Such an increase in the oxidation stability of the DME-based electrolyte with TFP cations implies that these electrolytes can be used with high voltage cathodes. To study this, we first performed galvanostatic cycling using a LiNi_{0.8}Co_{0.1}Mn_{0.1}O₂ (NCM811) cathode and the Li metal anode (NCM811 || Li metal) in a coin cell configuration with different concentrations of TFP additive to find the optimal one (Supplementary Fig 14a). Without TFP, the cells show severe capacity fading and a decrease in coulombic efficiency around the 30th cycle, in agreement with previous reports (Supplementary Fig. 14 and 15).⁸ In contrast, cells with TFP demonstrate a dramatic improvement in cycling stability even for the TFP concentrations as low as 4 mM (~ 0.03 wt %; 250 μm Li full cells; Supplementary Fig. 14a), with the optimal concentration being 12 mM (0.1 wt %). The NCM811 || 50 μm Li metal full cells with the electrolyte containing 12 mM TFP maintained 94 % of its discharge capacity even after 275 cycles (as measured at 0.1 C) and an average coulombic efficiency of 99.6 % (1C, Fig. 3a). In comparison, for the full cells containing 12 mM LiClO₄ (Supplementary Fig. 15), we observed a much faster capacity loss than for 12 mM TFP-ClO₄.

The charge/discharge voltage profiles (Fig. 3b) show that the cells containing fluorinated cations can be successfully and repetitively charged up to 4.2 V. The differential capacity profiles (dQ/dV , Supplementary Fig. 16) for the cells with TFP showed both phase transitions expected for the NCM811 cathode during charging/discharging [from hexagonal (H1) to monoclinic (M) occurring between 3.6 V and 3.8 V and from monoclinic to hexagonal (H2) at ~ 4.0 V].^{33,34} This is in contrast to the cells without additive that showed severe discharge capacity fading when charging up to 4.2 V due to electrolyte decomposition (Supplementary Fig. 14).⁸ The electrochemical impedance spectroscopy data also show a minimal increase in impedance with cycling for the full cells with TFP (Supplementary Fig. 17), in good agreement with the cells' dQ/dV profiles.

We hypothesize that the improved oxidation stability of the electrolyte and stable cycling of NCM811 || Li cells with fluorinated cations are due to the formation of a favorable cathode electrolyte interphase (CEI). We verify this hypothesis using XPS (Fig. 3c) and quantum chemistry calculations (Fig. 3d). XPS of cycled NCM811 shows that the CEI has a substantial amount of fluorine only in the TFP-containing electrolyte and not the reference one, indicating an active role of fluorinated cations in CEI formation (Fig. 3c, Supplementary Fig. 18 and Supplementary Table 1). According to DFT calculations, direct oxidation of isolated TFP cation is unlikely due to its high oxidation potential and electrostatic repulsion (Supplementary Fig. 1a). Next, we considered participation of $\text{TFP}^+ - \text{FSI}^-$ and $\text{TFP}^+ - (\text{FSI}^-)_2$ aggregates in CEI formation. Although these aggregates would not be electrostatically repelled from the cathode surface, direct oxidation of these complexes is also unlikely within our operating potential window of 3.0 – 4.2 V vs. Li/Li⁺ (Supplementary Fig. 1c). Therefore, we considered a different mechanism that involves reaction of TFP cations with DME radicals $[\text{C}_4\text{H}_9\text{O}_2]^*$ that are formed at the cathode surface (Fig. 3d).^{35, 36, 37} DFT calculations show that this process has a low energy barrier indicative of fast kinetics (Fig. 3d, central panel). Further H-transfer³⁵ from the ether tail of the $[\text{C}_4\text{H}_9\text{O}_2]^* - \text{TFP}^+$ to the cathode surface leads to the formation of radicals that are scavenged by TFP cations (Fig. 3d, left panel). After that, the formed molecular aggregates precipitate at the cathode surface (Fig. 3d, right panel), resulting in the protective CEI that is rich in C-F containing species which agrees well with the XPS results for the surface layer formed in the presence of TFP (Fig 3c and Supplementary Fig. 18). Apart from the CEI mechanism associated with TFP⁺ forming aggregates with DME, we cannot rule out the possibility that TFP-based products that form at the anode can diffuse to the cathode and contribute to the CEI formation (i.e. cross-talk). Although DFT calculations shed light on the interplay between TFP⁺ and DME, additional *in situ* experiments are required to unveil how TFP⁺ participates in the CEI formation. Also, our results show that the counter-ions for TFP⁺ play an important role in stabilizing the cathode-electrolyte interphase.

In addition, we found that the presence of TFP in the electrolyte helps to suppress current collector corrosion. SEM of the aluminum current collectors that supported the NCM811 cathode showed that after 160 cycles in the electrolyte with TFP⁺, the current collector had no signs of corrosion, while in the additive-free electrolyte a significant roughening of the Al current collector was observed already after 20 cycles (Supplementary Fig. 19). Based on the DFT calculations, we suggest that TFP⁺ may act as a scavenger of chloride ions and chlorine radicals that are often present in commercial LiFSI, resulting in decreased corrosion of aluminum and cathode surfaces (Supplementary Fig. 20).

In summary, we demonstrate that high fractions of fluorinated species in electrolytes are not necessary to generate robust battery interphases. Instead, a very low fraction of readily reducible fluorinated cations can be used to form a favorable fluorine-rich SEI and allow for the deposition of dense Li. Moreover, we show that fluorinated cations, when coupled with perchlorate anions, can

dramatically suppress the oxidative decomposition of ether-based electrolytes and corrosion of the aluminum current collectors, enabling stable cycling of full cells with nickel-rich high-voltage cathodes with 99.6 % coulombic efficiency. In general, we present a strategy for delivering desired chemical species to the battery anodes through electrostatic attraction while using minute amounts of additive and therefore can notably reduce costs and environmental footprint of implementing high energy batteries.

Methods

Materials. 2,4,6-trifluoropyridine (98%, Matrix Scientific), methyl trifluoromethanesulfonate (97%, Matrix Scientific), ion exchange resin Amberlyst® A26 (hydroxide form, Acros Organics), perchloric acid (70%, VWR BDH Chemicals), acetonitrile (ACS reagent, \geq 99.5%, EMD Millipore), dichloroethane (\geq 99.8%, Spectrum Chemical), methanol (\geq 99.8%, VWR BDH Chemicals) and anhydrous DME (99.5 %, Sigma Aldrich) were used as received without further purification. LiFSI salt (98.0 %, TCI Europe) was dried under vacuum at 110 °C for 24 hours before use. Unless otherwise stated, this LiFSI salt (98.0 %, TCI Europe) was used to prepare electrolytes for all measurements. High-purity LiFSI (99.9%, solvionic) was used only for measurements presented in Supplementary Figure 14.

Preparation of ion exchange column in ClO_4^- form. The desired amount of Amberlyst® A26 ion exchange resin in OH^- form (approximately 20 g of Amberlyst per 2 mmol of ionic starting material) was washed with deionized water twice before loading into a glass column (1.5 cm in diameter). The column was then flushed with methanol. Perchloric acid solution (2% in methanol) was passed through the column until the eluted solution possessed the same pH value as the original acid solution; the color of the column also changed from pink to light yellow during this process. Pure methanol was used to thoroughly remove acid residue from the column, which was then washed with acetonitrile to replace the methanol for further ion exchange. We note that all compounds passed through the ion exchange column in this work are sensitive to base and alcohol. Hence, the complete removal of methanol is imperative for successfully obtaining the desired compounds.

Synthesis of N-methyl-2,4,6-trifluoropyridinium (TFP) Perchlorate. N-methyl-2,4,6-trifluoropyridinium triflate (0.5 g, 1.68 mmol) was synthesized first as reported previously with slight modification.³⁸ Briefly, 2,4,6-trifluoropyridine (0.45 mL, 5 mmol) and methyl triflate (0.7 mL, 6.4 mmol) were mixed in a 25 mL degassed Schlenk tube and stirred at 50 °C for 4 h, leading to precipitation of a white solid. This solid was collected by filtration and washed with ether (3 \times 15 mL). The solid was then recrystallized in an acetonitrile:dichloroethane 1:3 (v:v) mixture at 60 °C to obtain the final product (1.4 g, 4.7 mmol, 94%). Approximately 0.5 g of pure N-methyl-2,4,6-trifluoropyridinium triflate was then dissolved in acetonitrile (2 mL) and passed through the ClO_4^- ion exchange column with a constant flow of acetonitrile. The eluted solution (ca. 75 mL) was subject to rotary evaporation to afford the crude N-methyl-2,4,6-trifluoropyridinium perchlorate solid salt. The compound was then recrystallized by allowing an acetonitrile:dichloroethane 1:3 (v:v) solution to cool from 40 °C to 0 °C to obtain the final product (0.24 g, 0.97 mmol, 48%).

IR: ν_{max} 3070 cm^{-1} , 2161 cm^{-1} , 2034 cm^{-1} , 1675 cm^{-1} , 1597 cm^{-1} , 1496 cm^{-1} , 1167 cm^{-1} , 1077 cm^{-1} , 877 cm^{-1} , 622 cm^{-1} .

¹H NMR (500 MHz, Acetonitrile- d_3) δ 1.94 (p, J = 2.5 Hz, 1H), 4.02 (s, 1H), 7.64 (dd, J = 7.0, 2.4 Hz, 1H).
(Supplementary Fig. 21a)

13C NMR (126 MHz, Acetonitrile-d₃) δ 1.31, 35.56, 100.99, 118.26, 159.01, 161.09, 176.58, 178.69. (**Supplementary Fig. 21b**)

19F NMR (471 MHz, Acetonitrile-d₃) δ -75.32 (t, J = 28.6 Hz), -69.33 (s) (**Supplementary Fig. 21c**)

HRMS (m/z) N-methyl-2,4,6-trifluoropyridinium cation [M+H]⁺: Calcd.: 148.0368, found: 148.0370; perchlorate anion [M-H]⁻: Calcd.: 98.9410, found: 98.8446

Density functional theory (DFT) calculations. DFT calculations of the additive reduction, oxidation and reactivity were performed using Gaussian 16 package, revision C.01.³⁹ All complexes were immersed in implicit solvent represented using polarized continuum model (PCM) with ether parameters with the exception of the molecules shown in Supplementary Fig. 1. Computationally expedient wb97XD DFT calculations with a compact 6-31+G(d,p) basis set yielded oxidation and reduction potentials for additives in good agreement with the more computationally expensive and reliable hybrid DFT/wavefunction G4MP2 methodology (Supplementary Fig. 1) and were used throughout the paper. All optimized geometries were confirmed to be minima without imaginary frequencies. Intrinsic reaction coordinate calculations (IRC) are shown in Figure 3d.

Reduction potential for the complexes containing an additive, solvent, Li⁺ denoted as a complex A was calculated as the negative of the free energy of formation of the reduced species A⁻ in solution [$\Delta G_{298}^S(A \rightarrow A^-) = G_{298}^S(A^-) - G_{298}^S(A)$] divided by Faraday's constant as given by:

$$E^{red} = -\frac{\Delta G_{298K}^S(A \rightarrow A^-)}{F} - 1.4 V$$

The difference between the Li/Li⁺ and absolute reduction potential of 1.4 V was subtracted to convert results to Li/Li⁺ scale as discussed extensively elsewhere.⁴⁰ Oxidation potential for a complex A was calculated as the free energy of formation of the oxidized specie A⁺ in solution [$\Delta G_{298}^S(A \rightarrow A^+) = G_{298}^S(A^+) - G_{298}^S(A)$] divided by Faraday's constant as given by:

$$E^{ox} = \frac{\Delta G_{298K}^S(A \rightarrow A^+)}{F} - 1.4 V$$

The H-transfer reaction from DME to LiNiO₂ cathode surface was adapted from previous work³⁵ and is shown in Figure 3d. Details and discussion of the molecular dynamics simulations is expanded upon in the Supplementary Information.

Electrochemical characterization. CV profiles were collected using 3-electrode electrochemical cell with a Cu disc working electrode (ϕ = 1 mm, embedded in PEEK, eDAQ), a Li chip (ϕ = 4 mm, 250 μ m, Xiamen Tmax Battery Equipments Limited) physically attached to stainless steel rod (McMaster Carr) was used as a counter electrode, leakless Ag/AgCl was used as a reference electrode (ϕ = 5 mm, eDAQ). The 3-electrode CV data were collected using a VSP-300 Biologic potentiostat.

Li|Li symmetric cell tests were performed using CR2032 coin cell parts (Hohsen Corp), 250 μ m Li chips (ϕ = 11 mm, Xiamen Tmax Battery Equipments Limited), and 8 μ m Cu current collectors (ϕ = 13 mm, Xiamen Tmax Battery Equipment Limited). Two layers of Celgard 2500 were used as a separator (ϕ = 19 mm). The amount of electrolyte used for every coin cell was 75 μ l. The cells were aged at room temperature for at least 5 hours before operation. Galvanostatic cycling was performed for the symmetric cell tests with a current density of 10 mA cm⁻² (6 min cycle, specific areal capacity of 1 mAh cm⁻²).⁴¹ Biologic MPG-200 potentiostat and Arbin battery cycler (LBT21084UC) were used for the data collection.

The coulombic efficiency was obtained by averaging results of at least 5 independent measurements that were generated using a modified Aurbach protocol (described below). The modified Aurbach protocol was performed using asymmetric Cu|Li coin cells, assembled with 75 μ l

of electrolyte. The detailed experimental sequence was the following: (1) 10 CV cycles were performed to pre-form SEI on a Cu electrode with a scan rate of 5 mV s^{-1} within the voltage range of 0 V to 2.5 V; (2) a deposition, stripping and re-deposition of excess amount of Li was performed (25 mAh cm^{-2} with a current density of 2.5 mA cm^{-2}); (3) 100 galvanostatic Li plating and stripping cycles were performed at current density of 10 mA cm^{-2} and a specific areal capacity of 1 mAh cm^{-2} ; (4) final Li stripping was carried out with current density of 2.5 mA cm^{-2} with a cut off voltage of 1 V.

For full cell tests, a single-sided NCM811 electrodes (2 mAh cm^{-2} areal loading on $16 \text{ }\mu\text{m}$ thick Al current collector, 99.6 %, NEI Corp) were used as a cathode and Li metal chips ($50 \text{ }\mu\text{m}$ and $250 \text{ }\mu\text{m}$, Xiamen Tmax Battery Equipments Limited) were used as anodes. $50 \text{ }\mu\text{m}$ thick Li metal anodes were prepared by thinning $250 \text{ }\mu\text{m}$ thick Li foil using a roll press. For full cell cycling tests a constant current (CC) step was initially used for all charging steps with a cut-off voltage of 4.2 V followed by a constant current constant voltage (CCCV) step with the terminating conditions of either 5% of the 1C-rate current or 30 minutes of the constant voltage step. A CC step was applied for all discharging steps with a cut-off voltage of 3 V. A sequence of three cycles at 0.1C-rate and 50 cycles at 1C-rate was repeated during full cell testing. EIS data were acquired using a VSP-300 (Biologic) in a frequency range from 200 kHz to 100 mHz, with a sinus amplitude of 10.0 mV.

EQCM-D measurements. The frequency and dissipation change for 3-11 overtones were collected by QCM-D instrument (Biolin Scientific AB). The measurements were conducted in a sealed homemade cell connected to a potentiostat (Biologic VSP-300). A 5 MHz Cu-coated quartz sensor (QC) served as a working electrode and Li foil as both counter and reference electrodes. The gravimetric information was obtained by comparing the theoretical frequency F_{theo} calculated from the Faradaic mass using Sauerbrey equation to the experimental frequency as given by ²⁵:

$$F_{theo} = \frac{C_m M_w Q}{nF}$$

Where C_m is the mass sensitivity constant of 5 MHz quartz sensor, Q is the obtained charge, M_w is the atomic mass of the inserted cation in its desolvated form, n is the number of electrons, and F is Faraday's constant.

Preparation of the cycled Li anode cross-section using cryogenic focused-ion beam. Sample transfer to the cryo-sample holder was performed within 3 seconds of air exposure. After sample transfer, the sample was cooled to below $-140 \text{ }^\circ\text{C}$ and subject to reduced pressure (ca. 10^{-6} mbar). Continuous sample cooling was performed using nitrogen gas during the FIB operation. First, a preliminary Ga^+ beam cross-sectional cut was performed with a current of 5 nA followed by a cleaning cut with a 0.5 nA beam current.

X-ray photoelectron spectroscopy (XPS). The cycled electrodes were rinsed 3 times with DME prior to analysis. XPS analysis was performed on a PHI Quantum 2000 using a monochromated Al K_α X-ray source (1486.6 eV) with a pass energy of 30 eV. Sample charging was minimized by charge compensation with a low energy electron and an Ar ion gun. XPS data were processed with the CasaXPS software. The corrected relative sensitivity factors (RSFs) were derived from in-house Matlab code. The corrected RSF values for Li 1s, C 1s, N 1s, O 1s, F 1s and S 2p are 0.625, 7.388, 12.075, 18.301, 25.924 and 18.715, respectively. Shirley background subtraction was applied before peak fitting. Gaussian/Lorentzian product line functions with 30 % Lorentzian and 70 % Gaussian contribution were used for fitting each XPS spectrum. The spectra were calibrated by assigning the Li-F component of the F 1s spectra to a 685.0 eV binding energy. Samples for XPS were prepared in three-electrode cell with fixed working electrode area: Cu ($\geq 99.8 \%$, NEI Corporation) or Al metal foils (99.6 %, NEI

Corporation) were used as a working electrode (geometrical area of 0.126 cm^2) and $250 \mu\text{m}$ Li metal ($\phi = 11 \text{ mm}$, Xiamen Tmax Battery Equipments Limited) as a counter and Ag/AgCl leakless electrode (eDAQ) as a reference electrode. The cycled NCM811 and Li metal samples were retrieved from 2032-type coin cell samples. The cells were disassembled, and the retrieved electrodes were washed three times with fresh DME prior to analysis. A custom-made transfer vessel was used for air-free transfer of the samples to the XPS machine.

FTIR measurements. *Ex situ* ATR-FTIR spectra were obtained by averaging 128 scans using a Vertex-70v spectrometer equipped with a high-resolution MCT detector and a Specac Golden Gate Diamond ATR accessory

Raman measurements. The *ex situ* Raman spectra were obtained with 0.5% Laser power (785 nm Laser) and 20x magnification using a Renishaw InVia Raman microscope.

NMR spectroscopy. ^1H -, ^{13}C - and ^{19}F -solution nuclear magnetic resonance (NMR) spectra were recorded at room temperature on a Bruker ASCEND 400 spectrometer. Acetonitrile- d_3 was used as solvent for all measurements. Spectra were analyzed using MestReNova. For indirect referencing, the magnet was locked and shimmed using a sample containing 0.4 mL DME and 0.1 mL acetonitrile- d_3 (referenced to residual solvent signals of acetonitrile- d_3), and subsequent samples were measured without locking/shimming.

Acknowledgements

M.R.L. and N.H. acknowledge support from Swiss National Science Foundation (Starting Grant TMSGI_218234). J.I.F. acknowledges the support of startup funds from the University at Albany, State University of New York. L.W. acknowledges financial support from the program of China Scholarships Council (202106830054). O.B. and T.P.P. acknowledge support from the US Army and DEVCOM Army Research Laboratory as well as support under the Department of Energy interagency agreement 89243322SEE000018. We thank Jan Bosse, Dr. Zbynek Novotny and Dr. Andrei Akbashev (Paul Scherrer Institute) and Dr. Andrea Arcifa (Swiss Federal Laboratories for Materials Science and Technology (EMPA)) for helpful discussions on XPS experiments and analysis. We also thank Dr. Rabeb Grissa, Dr. Corsin Battaglia (EMPA) for providing XPS transfer vessel for air-free sample transfer.

Author Contributions

M.R.L. planned the study and supervised the research. C.N.H. performed all electrochemical studies and conducted detailed XPS analysis. J.Y. contributed to interpretation of the data and research supervision. D.G.V. performed SEM and NMR measurements. M.Y. synthesized and characterized the fluorinated cationic additive under supervision of J.I.F. M.R. performed synthesis of additives following procedure from M.Y. and contributed to electrochemical testing to ensure reproducibility and NMR studies. T.P.P. and O.B performed DFT calculations and MD simulations. N.S. and L.W. performed EQCM-D measurements and relevant data analysis. KT performed Raman and FTIR measurements and assisted in CEI characterization. All authors discussed the results and contributed to the writing of the manuscript.

Author Information

Reprints and permissions information is available at www.nature.com/reprints. The authors declare financial interests: details are available in the online version of the paper. Readers are encouraged to

comment on the online version of the paper. Correspondence and requests for materials should be addressed to M.R.L. (mlukatskaya@ethz.ch).

Competing interests: The authors have a patent (US patent provisional application number 63398320) related to the electrolytes described in this article.

References

1. Liu J, Bao Z, Cui Y, Dufek EJ, Goodenough JB, Khalifah P, *et al.* Pathways for practical high-energy long-cycling lithium metal batteries. *Nature Energy* 2019, **4**(3): 180-186.
2. Lin D, Zhao J, Sun J, Yao H, Liu Y, Yan K, *et al.* Three-dimensional stable lithium metal anode with nanoscale lithium islands embedded in ionically conductive solid matrix. *Proceedings of the National Academy of Sciences of the United States of America* 2017, **114**(18): 4613-4618.
3. Louli AJ, Eldesoky A, Weber R, Genovese M, Coon M, deGooyer J, *et al.* Diagnosing and correcting anode-free cell failure via electrolyte and morphological analysis. *Nature Energy* 2020, **5**(9): 693-702.
4. Lin D, Liu Y, Cui Y. Reviving the lithium metal anode for high-energy batteries. *Nature Nanotechnology* 2017, **12**(3): 194-206.
5. Chen K-H, Wood KN, Kazyak E, LePage WS, Davis AL, Sanchez AJ, *et al.* Dead lithium: mass transport effects on voltage, capacity, and failure of lithium metal anodes. *Journal of Materials Chemistry A* 2017, **5**(23): 11671-11681.
6. Xu K. Electrolytes and Interphases in Li-Ion Batteries and Beyond. *Chemical Reviews* 2014, **114**(23): 11503-11618.
7. Hobold GM, Lopez J, Guo R, Minafra N, Banerjee A, Shirley Meng Y, *et al.* Moving beyond 99.9% Coulombic efficiency for lithium anodes in liquid electrolytes. *Nature Energy* 2021, **6**(10): 951-960.
8. Yu Z, Wang H, Kong X, Huang W, Tsao Y, Mackanic DG, *et al.* Molecular design for electrolyte solvents enabling energy-dense and long-cycling lithium metal batteries. *Nature Energy* 2020, **5**(7): 526-533.
9. Fan T, Kai W, Harika VK, Liu C, Nimkar A, Leifer N, *et al.* Operating Highly Stable LiCoO₂ Cathodes up to 4.6 V by Using an Effective Integration of Surface Engineering and Electrolyte Solutions Selection. *Advanced Functional Materials* 2022, **32**(33).
10. Yamada Y, Wang J, Ko S, Watanabe E, Yamada A. Advances and issues in developing salt-concentrated battery electrolytes. *Nature Energy* 2019, **4**(4): 269-280.
11. Fan X, Chen L, Ji X, Deng T, Hou S, Chen J, *et al.* Highly Fluorinated Interphases Enable High-Voltage Li-Metal Batteries. *Chem* 2018, **4**(1): 174-185.
12. Huang Y, Li R, Weng S, Zhang H, Zhu C, Lu D, *et al.* Eco-friendly electrolytes via a robust bond design for high-energy Li metal batteries. *Energy Environ Sci* 2022, **15**(10): 4349-4361.
13. Liu Y, Tao X, Wang Y, Jiang C, Ma C, Sheng O, *et al.* Self-assembled monolayers direct a LiF-rich interphase toward long-life lithium metal batteries. *Science* 2022, **375**(6582): 739-745.
14. Yu Z, Rudnicki PE, Zhang Z, Huang Z, Celik H, Oyakhire ST, *et al.* Rational solvent molecule tuning for high-performance lithium metal battery electrolytes. *Nature Energy* 2022.
15. Lebegue E, Agullo J, Belanger D. Electrochemical Behavior of Pyridinium and N-Methyl Pyridinium Cations in Aqueous Electrolytes for CO₂ Reduction. *ChemSusChem* 2018, **11**(1): 219-228.
16. Lucio AJ, Shaw SK. Pyridine and Pyridinium Electrochemistry on Polycrystalline Gold Electrodes and Implications for CO₂ Reduction. *The Journal of Physical Chemistry C* 2015, **119**(22): 12523-12530.
17. Jankowski P, Wiczorek W, Johansson P. Functional ionic liquids: Cationic SEI-formers for lithium batteries. *Energy Storage Materials* 2019, **20**: 108-117.
18. Aurbach; D, Daroux; M, Faguy; P, Yeager E. The electrochemistry of noble metal electrodes in aprotic organic solvents containing lithium salts. *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry* 1991, **297**: 225-244.
19. Adams BD, Zheng J, Ren X, Xu W, Zhang JG. Accurate Determination of Coulombic Efficiency for Lithium Metal Anodes and Lithium Metal Batteries. *Advanced Energy Materials* 2017, **8**(7).

20. Yu Z, Rudnicki PE, Zhang Z, Huang Z, Celik H, Oyakhire ST, *et al.* Rational solvent molecule tuning for high-performance lithium metal battery electrolytes. *Nature Energy* 2022, **7**(1): 94-106.
21. Wang J, Yamada Y, Sodeyama K, Chiang CH, Tateyama Y, Yamada A. Superconcentrated electrolytes for a high-voltage lithium-ion battery. *Nat Commun* 2016, **7**: 12032.
22. Zheng J, Fan X, Ji G, Wang H, Hou S, DeMella KC, *et al.* Manipulating electrolyte and solid electrolyte interphase to enable safe and efficient Li-S batteries. *Nano Energy* 2018, **50**: 431-440.
23. Angarita-Gomez S, Balbuena PB. Insights into lithium ion deposition on lithium metal surfaces. *Phys Chem Chem Phys* 2020, **22**(37): 21369-21382.
24. Lee JZ, Wynn TA, Schroeder MA, Alvarado J, Wang X, Xu K, *et al.* Cryogenic Focused Ion Beam Characterization of Lithium Metal Anodes. *ACS Energy Letters* 2019, **4**(2): 489-493.
25. Shpigel N, Levi MD, Aurbach D. EQCM-D technique for complex mechanical characterization of energy storage electrodes: Background and practical guide. *Energy Storage Materials* 2019, **21**: 399-413.
26. Dargel V, Shpigel N, Sigalov S, Nayak P, Levi MD, Daikhin L, *et al.* In situ real-time gravimetric and viscoelastic probing of surface films formation on lithium batteries electrodes. *Nat Commun* 2017, **8**(1): 1389.
27. Kitz PG, Lacey MJ, Novak P, Berg EJ. Operando EQCM-D with Simultaneous in Situ EIS: New Insights into Interphase Formation in Li Ion Batteries. *Anal Chem* 2019, **91**(3): 2296-2303.
28. Zhou Y, Su M, Yu X, Zhang Y, Wang JG, Ren X, *et al.* Real-time mass spectrometric characterization of the solid-electrolyte interphase of a lithium-ion battery. *Nat Nanotechnol* 2020, **15**(3): 224-230.
29. Wan C, Hu MY, Borodin O, Qian J, Qin Z, Zhang J-G, *et al.* Natural abundance ¹⁷O, ⁶Li NMR and molecular modeling studies of the solvation structures of lithium bis(fluorosulfonyl)imide/1,2-dimethoxyethane liquid electrolytes. *Journal of Power Sources* 2016, **307**: 231-243.
30. Kim H, Wu F, Lee JT, Nitta N, Lin H-T, Oschatz M, *et al.* In Situ Formation of Protective Coatings on Sulfur Cathodes in Lithium Batteries with LiFSI-Based Organic Electrolytes. *Advanced Energy Materials* 2015, **5**(6).
31. Fan X, Chen L, Borodin O, Ji X, Chen J, Hou S, *et al.* Non-flammable electrolyte enables Li-metal batteries with aggressive cathode chemistries. *Nat Nanotechnol* 2018, **13**(8): 715-722.
32. Amanchukwu CV, Yu Z, Kong X, Qin J, Cui Y, Bao Z. A New Class of Ionically Conducting Fluorinated Ether Electrolytes with High Electrochemical Stability. *J Am Chem Soc* 2020, **142**(16): 7393-7403.
33. Zhang Z, Yang J, Huang W, Wang H, Zhou W, Li Y, *et al.* Cathode-Electrolyte Interphase in Lithium Batteries Revealed by Cryogenic Electron Microscopy. *Matter* 2021, **4**(1): 302-312.
34. Busà C, Belekoukia M, Loveridge MJ. The effects of ambient storage conditions on the structural and electrochemical properties of NMC-811 cathodes for Li-ion batteries. *Electrochimica Acta* 2021, **366**.
35. Ren X, Zou L, Jiao S, Mei D, Engelhard MH, Li Q, *et al.* High-Concentration Ether Electrolytes for Stable High-Voltage Lithium Metal Batteries. *ACS Energy Letters* 2019, **4**(4): 896-902.
36. Carboni M, Marrani AG, Spezia R, Brutti S. 1,2-Dimethoxyethane Degradation Thermodynamics in Li-O₂ Redox Environments. *Chemistry* 2016, **22**(48): 17188-17203.
37. Alvarado J, Schroeder MA, Pollard TP, Wang X, Lee JZ, Zhang M, *et al.* Bisalt ether electrolytes: a pathway towards lithium metal batteries with Ni-rich cathodes. *Energy & Environmental Science* 2019, **12**(2): 780-794.
38. Leitch AA, Yu X, Robertson CM, Secco RA, Tse JS, Oakley RT. Isostructural bis-1,2,3-thiaselenazolyli dimers. *Inorg Chem* 2009, **48**(20): 9874-9882.
39. Frisch MJ, Trucks GW, Schlegel HB, Scuseria GE, Robb MA, Cheeseman JR, *et al.* Gaussian 16 Rev. C.01. Wallingford, CT; 2016.
40. Borodin O. Molecular Modeling of Electrolytes. In: Jow TR, Xu K, Borodin O, Ue M (eds). *Electrolytes for Lithium and Lithium-Ion Batteries*, vol. 58. Springer New York, 2014, pp 371-401.
41. Xiao J, Li Q, Bi Y, Cai M, Dunn B, Glossmann T, *et al.* Understanding and applying coulombic efficiency in lithium metal batteries. *Nature Energy* 2020, **5**(8): 561-568.