

Chemically Recyclable, High Molar Mass Polyoxazolidinones via Ring Opening Metathesis Polymerization

Arpan Pal, Allison R. Wong, Jessica R. Lamb*

Department of Chemistry, University of Minnesota–Twin Cities, Minneapolis, Minnesota 55455, United States

KEYWORDS: chain growth polymerization, chemical recycling to monomer, polyurethanes, ring opening metathesis polymerization


ABSTRACT: The development of robust methods for the synthesis of chemically recyclable polymers with tunable properties is necessary for the design of next-generation materials. Polyoxazolidinones (POxa) – polymers with five-membered urethanes in their backbones – are an attractive target because they are strongly polar and have high thermal stability, but existing step-growth syntheses limit molar masses and chemical recyclability to monomer is rare. Herein, we report the synthesis of high molar mass POxa via ring opening metathesis polymerization of oxazolidinone-fused cyclooctenes. These novel polymers show <5% mass loss up to 382–411 °C and have tunable glass transition temperatures (14–56 °C) controlled by side chain structure. We demonstrate facile chemical recycling to monomer and re-polymerization despite moderately high monomer ring strain energies, which we hypothesize is facilitated by the conformational restriction introduced by the fused oxazolidinone ring. This method represents the first chain growth synthesis of POxa and provides a versatile platform for the study and application of this emerging subclass of polyurethanes.

Synthetic polymers have revolutionized every aspect of modern life, but current mass polymer production is unsustainable as common materials generate tremendous amounts of waste^{1–3} and pollution^{4–6} after their intended use. Therefore, next-generation materials require both competitive properties and designed end-of-life strategies to mitigate their environmental impact. Polyoxazolidinones (POxa) are an emerging class of polyurethanes with competitive properties for high temperature applications^{7,8} due to the five-membered oxazolidinone rings imparting high thermal stability^{7,9–13} and glass transition temperatures (T_g),^{7,8,11–15} Despite their promise, POxa have been limited to low molar masses ($M_n \leq 32$ kDa^{8,13,15,16}) for decades due to the step-growth nature of previous syntheses (Figure 1A) and very little work has been reported on sustainable approaches for their end-of-life.¹⁷ We sought to break this paradigm by using chain growth polymerization to access high molar mass POxa while enabling chemical recycling to monomer via depolymerization.^{18–21}


We chose ring opening metathesis polymerization (ROMP) because (1) it is a powerful chain growth method for strained cycloalkenes^{22–24} and (2) ROMP-based polymers obtained from low ring strain monomers (~5.2 kcal/mol) are known to depolymerize at elevated temperatures via ring closing metathesis (RCM)^{25–29} (Figure 1B). This RCM strategy has recently resurfaced in the design of new polymers due to its promising contribution to chemical recycling.^{27,28,30–32} Chemical recycling to monomer is ideal for a circular polymer economy because this approach can minimize the net mass loss during recycling²¹ compared to other strategies, such as mechanical recycling,^{2,33–35} biodegradation,^{36,37} and upcycling of commodity plastics to value added products.^{38–47} Recently, Wang and co-workers showed that the addition of *trans*-fused cyclobutene or ace-

tonide rings to cyclooctene lowered the monomer ring strain energy (RSE), which they hypothesized was the critical factor that enabled the depolymerization of the resulting polymers.^{28,30}

A. Traditional synthetic strategy and properties of POxa



B. Variable reversibility of ROMP

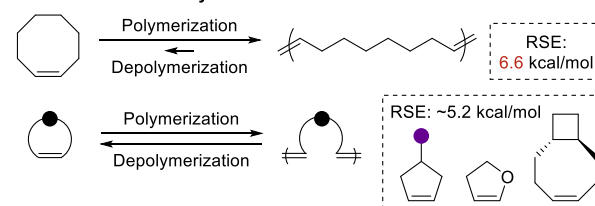

C. This work: chemically recyclable POxa from ROMP

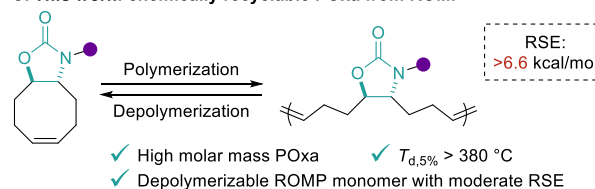



Figure 1. (A) Traditional POxa from step growth polymerization (SGP) (A, B = reactive functionality). (B) Reversibility of ring-opening metathesis for monomers with different ring-strain energies (RSEs). (C) Design of chemically recyclable POxa.

Herein, we utilize ROMP for the first chain growth synthesis of POxa with the oxazolidinones (Oxa) in the backbone of the polymer using *trans*-Oxa-fused cyclooctene monomers (Figure 1C). We demonstrate access to POxa with high molar mass, moderate dispersity, and control over molar mass by using a

chain transfer agent (CTA). These novel POxa show <5% mass loss up to 382 °C and have tunable T_g via side chain alteration and post-polymerization hydrogenation. Furthermore, we show clean depolymerization back to monomer, despite higher RSE than *cis*-cyclooctene (COE) calculated by density functional theory (DFT). This method provides access to POxa with higher molar masses than previous methods, which will enable future structure-property relationship studies and the addition of a broad-spectrum of new Oxa monomers for ROMP and chemical recycling to monomer.

We began our investigation by synthesizing the Oxa-fused COE monomers **M1–M4** in 4–5 steps from 1,5-cyclooctadiene (Scheme 1, see Supporting Information Section S3A for full synthetic details). Gratifyingly, **M1** readily polymerized using G2 (see Figure S1 for all catalyst structures) in dichloromethane (DCM) to yield POxa **P1** with a number-average molar mass (M_n) of 23.9 kDa; however, **P1** precipitated out during the polymerization due to poor solubility in DCM and was only soluble in *N,N*-dimethylformamide (DMF) and dimethyl sulfoxide (DMSO), which are incompatible with metathesis catalysts.^{48–50} Therefore, we focused on the *N*-alkylated monomers **M2–M4** which yielded polymers (**P2–P4**) that were soluble in common metathesis solvents (e.g., DCM, CHCl₃, THF).

Scheme 1. Oxa-fused COE monomers from cyclooctadiene.

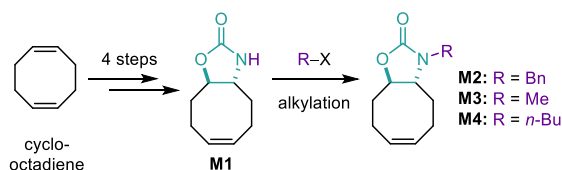

Using **M2** as a model substrate, we optimized the polymerization conditions (Table 1). Except for G1 (entry 1), common metathesis catalysts (i.e., G2, G3, HG2, see Figure S1) all resulted in high conversions and molar masses ($M_n = 118$ –487 kDa, entries 2–4). We selected G2 as the standard catalyst because it resulted in the lowest \bar{D} and is relatively inexpensive. Increasing the initial monomer concentration from 1.0 to 2.0 M decreased conversion in 20 min and resulted in a bimodal distribution with high \bar{D} (entry 5), whereas lowering the concentration to 0.5 and 0.25 M progressively decreased both conversion and molar mass (entries 6 and 7). Therefore, our standard polymerization conditions consisted of 1.0 M monomer in DCM using G2 as the ROMP catalyst at 24 °C. **M3** and **M4** were similarly polymerized to access high molar mass POxa ($M_n = 112.3$ and 88.1 kDa for **P3** and **P4**, respectively) in 1 h with variable side chains (see Section S3B for synthetic details). Because these Oxa-fused COE monomers are unsymmetrical, we characterized the regioregularity of enchainment for **M2–M4** using IR and NMR spectroscopies. While the side chain does affect regioregularity to some extent, all polymers had over 88% head-to-tail enchainment (see Section S2E for more details).

As expected for ROMP of COE derivatives,^{51–56} we observed evidence of slow initiation: M_n is initially very high and decreases (i.e., approaches $M_{n,theo}$) by extending the reaction time (entry 2 vs. 8–9 and Figure S5) and there was a non-linear trend between M_n and $[M]:[Ru]$ ratio (Figure 2A). To improve control over M_n , we added *cis*-1,4-diacetoxy-2-butene as a chain transfer agent (CTA) (Figure 2B). CTAs are known to decrease the difference between $M_{n,theo}$ and M_n ,^{57,58} enable the use of catalytic Ru,^{55,59–64} and – for this CTA – result in homotelechelic

polymers that can be deprotected to the corresponding diol for further functionalization.^{57,58} Despite requiring longer reaction times due to the slower rate of polymerization (78% conv. in 3 h vs. 90% without CTA), M_n had a linear relationship with $[M]:([CTA]+[G2])$ and was within 1–37 kDa of $M_{n,theo}$ for a wide range of molar masses, demonstrating improved control over POxa molar mass. Secondary cross-metathesis helps dispersity remain relatively constant ($\bar{D} \approx 1.5$ –1.6) with and without the CTA (when $t = 3$ h).

Table 1 Optimization of ROMP conditions.

| entry | [Ru] | conc. (M) | conv. (%) ^a | M_n (kDa) ^b | \bar{D} ^b |
|----------------|------|-----------|------------------------|--------------------------|------------------------|
| 1 | G1 | 1.0 | 9 | – | – |
| 2 | G2 | 1.0 | 82 | 487 | 1.20 |
| 3 | G3 | 1.0 | 85 | 118 | 1.41 |
| 4 | HG2 | 1.0 | 81 | 384 | 1.27 |
| 5 ^c | G2 | 2.0 | 62 | 203 | 2.35 |
| 6 | G2 | 0.5 | 69 | 168 | 1.40 |
| 7 | G2 | 0.25 | 48 | – ^d | – ^d |
| 8 ^e | G2 | 1.0 | 86 | 42.7 | 1.20 |
| 9 ^f | G2 | 1.0 | 86 | 34.4 | 1.55 |

^aDetermined by ¹H NMR analysis of the crude reaction mixture.

^bCrude M_n and \bar{D} were determined by size exclusion chromatography with multi-angle light scattering (SEC-MALS) in DMF.

^c $[M2]:[Ru] = 50:1$. ^dSEC peak is overlapping with small molecule peaks, but M_n of oligomers is < 1 kDa. ^ePolymerization was run for 1 h. ^fPolymerization was run for 3 h. See Figure S1 for catalyst structures.

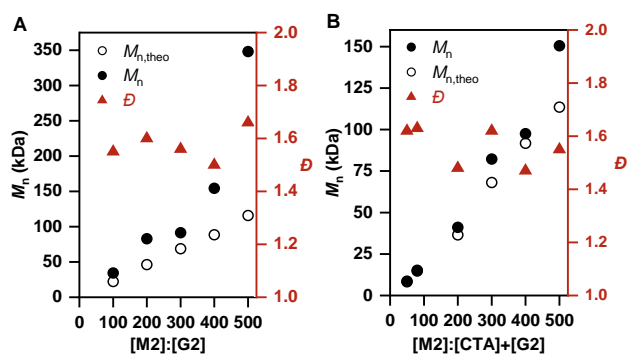


Figure 2. Plots of M_n (black circles), $M_{n,theo}$ (open circles), and \bar{D} (red triangles) as a function of (A) $[M2]:[G2]$ and (B) $[M2]:[CTA]+[G2]$. Polymerization time = 3 h.

Having established the synthesis of POxa via ROMP, we next investigated the thermal properties of **P2–P4**. Thermogravimetric analysis (TGA) showed **P2–P4** had high decomposition temperatures at 5% mass loss ($T_{d,5\%}$) of 382–411 °C (Figure 3A), as expected for POxa.^{7,9–13} Differential scanning calorimetry (DSC) indicated the POxa were amorphous with glass transition temperatures (T_g) tuned by the *N*-substituent (Figure 3B). Increasing the substituent length from methyl (**P3**) to *n*-butyl (**P4**) lowered the T_g from 29 to 14 °C whereas the benzyl substituent in **P2** increased the T_g to 56 °C. These results indicate that our

modular platform for monomer synthesis enables the synthesis of POxa with tunable T_g 's while maintaining high $T_{d,5\%}$.

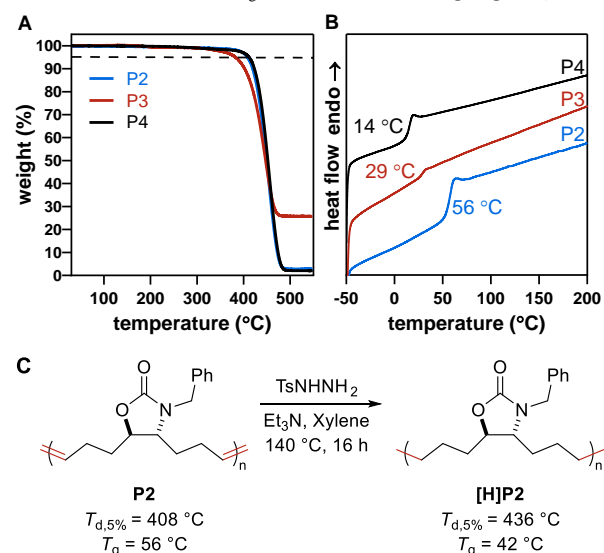


Figure 3. Thermal data – (A) TGA and (B) DSC thermograms – of **P2–P4** and (C) hydrogenated [**H**]P2.

To explore the range of properties accessible via this method, we hydrogenated the backbone olefins of **P2** to form polyethylene-like polymer [**H**]P2 that still contains embedded polar Oxa rings (Figure 3C). Such polar-functionalized polyethylene⁶⁵ often exhibit excellent ionic conductivity,^{66–68} surface hydrophilicity,^{69,70} and antimicrobial properties^{71,72} while maintaining the mechanical strength of polyethylene. We speculated common olefin hydrogenation catalysts (e.g. Pd/C) would deprotect the benzyl group from the Oxa nitrogen⁷³ and thus used in situ-generated diimide from *N*-tosyl hydrazide for hydrogenation,^{56,74} resulting in 92% conversion of the olefins via ¹H NMR spectroscopy after 16 h. The $T_{d,5\%}$ increased slightly after hydrogenation (436 °C for [**H**]P2 vs. 408 °C for **P2**) whereas the T_g decreased from 56 to 42 °C due to increased backbone flexibility,^{75–78} indicating that post-polymerization modification provides an additional handle to tune thermal properties.

Because we are interested in the end-of-life for these materials, we explored the depolymerization of the non-hydrogenated **P2** via RCM. After a brief optimization of the depolymerization conditions (Table S4) we observed quantitative depolymerization of the polymer to **M2** using G2 in chloroform-*d* (20 mM) at 70 °C for 4 h (Figure 4). No oligomers or side reactions were observed. The recovered monomer (90% by mass) behaved identically to fresh monomer when re-polymerized using our standard conditions (see Figure S32), demonstrating the facile circular recyclability of these materials. Detrembleur and co-workers recently reported mechanical and chemical recycling of POxa-containing covalent adaptable networks,¹⁷ but this RCM approach is the first example of chemical recycling for linear POxa.

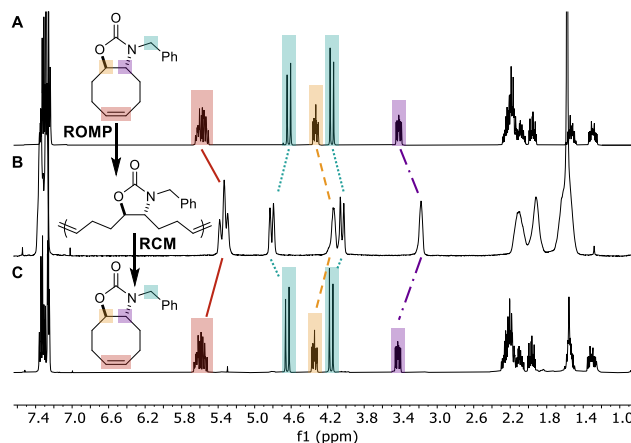


Figure 4. ¹H NMR spectra (CDCl₃) of (A) **M2**, (B) **P2**, and (C) the crude reaction mixture of **P2** depolymerization. Depolymerization conditions: G2 (1 mol %), CDCl₃ (20 mM), 70 °C, 4 h.

Because low monomer RSE (≤ 5.3 kcal/mol) has been reported as the key factor in the depolymerization of ROMP-based polymers,^{28,30} we expected **M1–M4** to have lower RSE than COE, which does not readily depolymerize.^{24,79} However, the calculated RSE values were actually higher for **M1–M4** (7.2–8.2 kcal/mol) than COE (6.6 kcal/mol) (Table S5), indicating that RSE is not the most important factor governing the depolymerization of these polymers. (Note that due to inconsistencies in the reported RSE of COE in the literature,^{28,51,80,81} we calculated this value using the same method as **M1–M4** at the B3LYP/6-31G (d,p) level of theory.) On the basis of the rich small-molecule literature using RCM to construct medium-sized (5–9 membered) fused rings (RSE > 7 kcal/mol),^{82–88} we hypothesize the favorable depolymerization of **P2** is facilitated by the conformational restriction introduced by the fused Oxa ring helping to bring the adjacent alkenes together (conceptually similar to the Thorpe-Ingold effect⁸⁹ that has previously been invoked for polymer depolymerization^{30,90}).

In summary, we successfully developed the first chain growth synthesis of POxa. We designed and synthesized novel Oxa-fused COE monomers with easily diversified side chains. **P1** – which contains free N-H groups – was insoluble in common ROMP solvents, but **P2–P4** were accessed with high molar mass and moderate dispersity (M_n up to 487 kDa, $D \approx 1.5$) via ROMP. We demonstrated that the molar mass could be efficiently controlled using a commercially available CTA. This method delivers new POxa with $T_{d,5\%} > 382$ °C and tunable T_g by changing the nitrogen substituent. We showed hydrogenation of the olefin backbone of the polymer to give access to polyethylene-like POxa. We furthermore established the quantitative chemical recyclability to monomer of **P2** by employing RCM to deliver pure monomer that could be readily re-polymerized. Further studies on controlled copolymerization, mechanistic insight, and mechanical properties are underway.

ASSOCIATED CONTENT

Additional polymer characterization, including SEC chromatograms, TGA and DSC thermograms, tabulated data, experimental details, calculation details, methods, reagent sources, synthetic procedures. This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

Jessica R. Lamb – Department of Chemistry, University of Minnesota–Twin Cities, Minneapolis, Minnesota 55455, United States; orcid.org/0000-0001-9391-9515; Email: jrlamb@umn.edu

Authors

Arpan Pal – Department of Chemistry, University of Minnesota–Twin Cities, Minneapolis, Minnesota 55455, United States; orcid.org/0000-0002-7985-0598

Allison R. Wong – Department of Chemistry, University of Minnesota–Twin Cities, Minneapolis, Minnesota 55455, United States; orcid.org/0000-0002-2511-2098

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Funding Sources

This work was supported by National Science Foundation Center for Sustainable Polymers, which is a National Science Foundation (NSF)-supported Center for Chemical Innovation (CHE-1901635) and the University of Minnesota (UMN). A.R.W. was partially supported by the Wayland E. Noland Fellowship in Organic Chemistry.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENT

The authors would like to thank Dr. Thomas Smith for his help with the microstructure analysis of the polymers. NMR analyses were done in the Nuclear Magnetic Resonance Laboratory and the Minnesota NMR Center, which are supported by the Research and Innovation Office (RIO), the Medical School, the College of Biological Science, the College of Science and Engineering (CSE), and the Department of Chemistry at UMN, and the Office of the Director, National Institutes of Health (NIH, S10OD011952), the NSF, and the Minnesota Medical Foundation. Part of this work was carried out in the CSE Polymer Characterization Facility at UMN, which has received capital equipment funding from the NSF through the UMN Materials Research Science and Engineering Center (MRSEC) (DMR-2011401). Mass spectrometry analysis was performed at the UMN Department of Chemistry Mass Spectrometry Laboratory (MSL), supported by RIO, CSE, and the Department of Chemistry at UMN, as well as the NSF (CHE-1336940). The content of this paper is the sole responsibility of the authors and does not represent the official views of or endorsement by the NIH or NSF.


REFERENCES

- (1) Stubbins, A.; Law, K. L.; Muñoz, S. E.; Bianchi, T. S.; Zhu, L. Plastics in the Earth System. *Science* **2021**, *373*, 51–55. <https://doi.org/10.1126/science.abb0354>.
- (2) Geyer, R.; Jambeck, J. R.; Law, K. L. Production, Use, and Fate of All Plastics Ever Made. *Sci. Adv.* **2017**, *3*, e1700782. <https://doi.org/10.1126/sciadv.1700782>.
- (3) MacLeod, M.; Arp, H. P. H.; Tekman, M. B.; Jahnke, A. The Global Threat from Plastic Pollution. *Science* **2021**, *373*, 61–65. <https://doi.org/10.1126/science.abg5433>.
- (4) Nguyen, B.; Claveau-Mallet, D.; Hernandez, L. M.; Xu, E. G.; Farnier, J. M.; Tufenkji, N. Separation and Analysis of Microplastics and Nanoplastics in Complex Environmental Samples. *Acc. Chem. Res.* **2019**, *52*, 858–866. <https://doi.org/10.1021/acs.accounts.8b00602>.
- (5) Pan, Z.; Guo, H.; Chen, H.; Wang, S.; Sun, X.; Zou, Q.; Zhang, Y.; Lin, H.; Cai, S.; Huang, J. Microplastics in the Northwestern Pacific: Abundance, Distribution, and Characteristics. *Sci. Total Environ.* **2019**, *650*, 1913–1922. <https://doi.org/10.1016/j.scitotenv.2018.09.244>.
- (6) Machovsky-Capuska, G. E.; Amiot, C.; Denuncio, P.; Grainger, R.; Raubenheimer, D. A Nutritional Perspective on Plastic Ingestion in Wildlife. *Sci. Total Environ.* **2019**, *656*, 789–796. <https://doi.org/10.1016/j.scitotenv.2018.11.418>.
- (7) Prokofyeva, A.; Laurenzen, H.; Dijkstra, D. J.; Frick, E.; Schmidt, A. M.; Guertler, C.; Koopmans, C.; Wolf, A. Poly-2-Oxazolidones with Tailored Physical Properties Synthesized by Catalyzed Polyaddition of 2,4-Toluene Diisocyanate and Different Bisphenol-Based Diepoxides. *Polym. Int.* **2017**, *66*, 399–404. <https://doi.org/10.1002/pi.5279>.
- (8) Altmann, H. J.; Clauss, M.; König, S.; Frick-Delaittre, E.; Koopmans, C.; Wolf, A.; Guertler, C.; Naumann, S.; Buchmeiser, M. R. Synthesis of Linear Poly(Oxazolidin-2-One)s by Cooperative Catalysis Based on N-Heterocyclic Carbenes and Simple Lewis Acids. *Macromolecules* **2019**, *52*, 487–494. <https://doi.org/10.1021/acs.macromol.8b02403>.
- (9) Kordomenos, P. I.; Kresta, J. E. Thermal Stability of Isocyanate-Based Polymers. 1. Kinetics of the Thermal Dissociation of Urethane, Oxazolidinone, and Isocyanurate Groups. *Macromolecules* **1981**, *14*, 1434–1437. <https://doi.org/10.2533/00094290477677759>.
- (10) Kordomenos, P. I.; Kresta, J. E.; Frisch, K. C. Thermal Stability of Isocyanate-Based Polymers. 2. Kinetics of the Thermal Dissociation of Model Urethane, Oxazolidone, and Isocyanurate Block Copolymers. *Macromolecules* **1987**, *20*, 2077–2083. <https://doi.org/10.1021/ma00175a006>.
- (11) Sendjarevic, V.; Sendjarevic, A.; Lekovic, H.; Lekovic, H.; Frisch, K. C. Polyoxazolidones for High Temperature Applications. *J. Elastomers Plast.* **1996**, *28*, 63–83. <https://doi.org/10.1177/009524439602800104>.
- (12) Kim, N. K.; Sogawa, H.; Yamamoto, K.; Hayashi, Y.; Kawachi, S.; Takata, T. DBU-Mediated Highly Efficient CO₂-Fixation to Propargylamines and Polypropargylamine. *Chem. Lett.* **2018**, *47*, 1063–1066. <https://doi.org/10.1246/cl.180477>.
- (13) Habets, T.; Siragusa, F.; Grignard, B.; Detrembleur, C. Advancing the Synthesis of Isocyanate-Free Poly(Oxazolidones): Scope and Limitations. *Macromolecules* **2020**, *53*, 6396–6408. <https://doi.org/10.1021/acs.macromol.0c01231>.
- (14) Herweh, J. E.; Whitmore, W. Y. Poly-2-Oxazolidones: Preparation and Characterization. *J. Polym. Sci. [A1]* **1970**, *8*, 2759–2773. <https://doi.org/10.1002/pol.1970.150081004>.
- (15) Harris, F. W.; Gupta, R. K. Synthesis and Intramolecular Cyclization of Ethynyl-Substituted Polyurethanes. *Polym. Prepr.* **1981**, *22*, 25–26.
- (16) Wong, A. R.; Barrera, M.; Pal, A.; Lamb, J. R. Improved Characterization of Polyoxazolidinones by Incorporating Solubilizing Side Chains. *Macromolecules* **2022**, *55*, 11006–11012. <https://doi.org/10.1021/acs.macromol.2c02104>.
- (17) Habets, T.; Seychal, G.; Calieri, M.; Raquez, J.-M.; Sardon, H.; Grignard, B.; Detrembleur, C. Covalent Adaptable Networks through Dynamic N,S-Acetal Chemistry: Toward Recyclable CO₂-Based Thermosets. *J. Am. Chem. Soc.* **2023**, *145*, 25450–25462. <https://doi.org/10.1021/jacs.3c10080>.
- (18) Hong, M.; Chen, E. Y.-X. Chemically Recyclable Polymers: A Circular Economy Approach to Sustainability. *Green Chem.* **2017**, *19*, 3692–3706. <https://doi.org/10.1039/C7GC01496A>.
- (19) Schneiderman, D. K.; Hillmyer, M. A. 50th Anniversary Perspective: There Is a Great Future in Sustainable Polymers. *Macromolecules* **2017**, *50*, 3733–3749. <https://doi.org/10.1021/acs.macromol.7b00293>.
- (20) Lu, X.-B.; Liu, Y.; Zhou, H. Learning Nature: Recyclable Monomers and Polymers. *Chem. – Eur. J.* **2018**, *24*, 11255–11266. <https://doi.org/10.1002/chem.201704461>.
- (21) Coates, G. W.; Getzler, Y. D. Y. L. Chemical Recycling to Monomer for an Ideal, Circular Polymer Economy. *Nat. Rev. Mater.* **2020**, *5*, 501–516. <https://doi.org/10.1038/s41578-020-0190-4>.

- (22) Bielawski, C. W.; Grubbs, R. H. Living Ring-Opening Metathesis Polymerization. *Prog. Polym. Sci.* **2007**, *32*, 1–29. <https://doi.org/10.1016/j.progpolymsci.2006.08.006>.
- (23) Ogba, O. M.; Warner, N. C.; O'Leary, D. J.; Grubbs, R. H. Recent Advances in Ruthenium-Based Olefin Metathesis. *Chem. Soc. Rev.* **2018**, *47*, 4510–4544. <https://doi.org/10.1039/C8CS00027A>.
- (24) Martínez, H.; Ren, N.; Matta, M. E.; Hillmyer, M. A. Ring-Opening Metathesis Polymerization of 8-Membered Cyclic Olefins. *Polym. Chem.* **2014**, *5*, 3507. <https://doi.org/10.1039/c3py01787g>.
- (25) Tuba, R.; Balogh, J.; Hlil, A.; Barlóg, M.; Al-Hashimi, M.; Bazzi, H. S. Synthesis of Recyclable Tire Additives via Equilibrium Ring-Opening Metathesis Polymerization. *ACS Sustain. Chem. Eng.* **2016**, *4*, 6090–6094. <https://doi.org/10.1021/acssuschemeng.6b01496>.
- (26) Neary, W. J.; Isais, T. A.; Kennemur, J. G. Depolymerization of Bottlebrush Polypentenamers and Their Macromolecular Metamorphosis. *J. Am. Chem. Soc.* **2019**, *141*, 14220–14229. <https://doi.org/10.1021/jacs.9b05560>.
- (27) Feist, J. D.; Xia, Y. Enol Ethers Are Effective Monomers for Ring-Opening Metathesis Polymerization: Synthesis of Degradable and Depolymerizable Poly(2,3-Dihydrofuran). *J. Am. Chem. Soc.* **2020**, *142*, 1186–1189. <https://doi.org/10.1021/jacs.9b11834>.
- (28) Sathe, D.; Zhou, J.; Chen, H.; Su, H.-W.; Xie, W.; Hsu, T.-G.; Schrage, B. R.; Smith, T.; Ziegler, C. J.; Wang, J. Olefin Metathesis-Based Chemically Recyclable Polymers Enabled by Fused-Ring Monomers. *Nat. Chem.* **2021**, *13*, 743–750. <https://doi.org/10.1038/s41557-021-00748-5>.
- (29) Ofstead, E. A.; Calderon, N. Equilibrium Ring-Opening Polymerization of Mono- and Multicyclic Unsaturated Monomers. *Makromol. Chem.* **1972**, *154*, 21–34. <https://doi.org/10.1002/macp.1972.021540102>.
- (30) Zhou, J.; Sathe, D.; Wang, J. Understanding the Structure–Polymerization Thermodynamics Relationships of Fused-Ring Cyclooctenes for Developing Chemically Recyclable Polymers. *J. Am. Chem. Soc.* **2022**, *144*, 928–934. <https://doi.org/10.1021/jacs.1c11197>.
- (31) Sathe, D.; Zhou, J.; Chen, H.; Schrage, B. R.; Yoon, S.; Wang, Z.; Ziegler, C. J.; Wang, J. Depolymerizable Semi-Fluorinated Polymers for Sustainable Functional Materials. *Polym. Chem.* **2022**, *13*, 2608–2614. <https://doi.org/10.1039/D2PY00240J>.
- (32) Chen, H.; Shi, Z.; Hsu, T.-G.; Wang, J. Overcoming the Low Driving Force in Forming Depolymerizable Polymers through Monomer Isomerization. *Angew. Chem. Int. Ed.* **2021**, *60*, 25493–25498. <https://doi.org/10.1002/anie.202111181>.
- (33) Schyns, Z. O. G.; Shaver, M. P. Mechanical Recycling of Packaging Plastics: A Review. *Macromol. Rapid Commun.* **2021**, *42*, 2000415. <https://doi.org/10.1002/marc.202000415>.
- (34) Vollmer, I.; Jenks, M. J. F.; Roelands, M. C. P.; White, R. J.; van Harmelen, T.; de Wild, P.; van der Laan, G. P.; Meirer, F.; Keurentjes, J. T. F.; Weckhuysen, B. M. Beyond Mechanical Recycling: Giving New Life to Plastic Waste. *Angew. Chem. Int. Ed.* **2020**, *59*, 15402–15423. <https://doi.org/10.1002/anie.201915651>.
- (35) Billiet, S.; Trenor, S. R. 100th Anniversary of Macromolecular Science Viewpoint: Needs for Plastics Packaging Circularity. *ACS Macro Lett.* **2020**, *9*, 1376–1390. <https://doi.org/10.1021/acsmacrolett.0c00437>.
- (36) Tournier, V.; Duquesne, S.; Guillamot, F.; Cramail, H.; Taton, D.; Marty, A.; André, I. Enzymes' Power for Plastics Degradation. *Chem. Rev.* **2023**, *123*, 5612–5701. <https://doi.org/10.1021/acs.chemrev.2c00644>.
- (37) Westlie, A. H.; Quinn, E. C.; Parker, C. R.; Chen, E. Y.-X. Synthetic Biodegradable Polyhydroxyalkanoates (PHAs): Recent Advances and Future Challenges. *Prog. Polym. Sci.* **2022**, *134*, 101608. <https://doi.org/10.1016/j.progpolymsci.2022.101608>.
- (38) Jehanno, C.; Pérez-Madriral, M. M.; Demarteau, J.; Sardon, H.; Dove, A. P. Organocatalysis for Depolymerisation. *Polym. Chem.* **2018**, *10*, 172–186. <https://doi.org/10.1039/C8PY01284A>.
- (39) Rahimi, A.; García, J. M. Chemical Recycling of Waste Plastics for New Materials Production. *Nat. Rev. Chem.* **2017**, *1*, 1–11. <https://doi.org/10.1038/s41570-017-0046>.
- (40) Polyethylene upcycling to long-chain alkylaromatics by tandem hydrogenolysis/arylation | Science <https://www.science.org/doi/10.1126/science.abc5441> (accessed 2023 -08 -21).
- (41) Korley, L. T. J.; Epps, T. H.; Helms, B. A.; Ryan, A. J. Toward Polymer Upcycling—Adding Value and Tackling Circularity. *Science* **2021**, *373*, 66–69. <https://doi.org/10.1126/science.abcg4503>.
- (42) Siddiqi, Z.; Sarlah, D. Electrochemical Dearomatization of Commodity Polymers. *J. Am. Chem. Soc.* **2021**, *143*, 21264–21269. <https://doi.org/10.1021/jacs.1c11546>.
- (43) Kumar, A.; Von Wolff, N.; Rauch, M.; Zou, Y.-Q.; Shmul, G.; Ben-David, Y.; Leitun, G.; Avram, L.; Milstein, D. Hydrogenative Depolymerization of Nylons. *J. Am. Chem. Soc.* **2020**, *142*, 14267–14275. <https://doi.org/10.1021/jacs.0c05675>.
- (44) Eisenreich, F. Photocatalysis as an Effective Tool for Upcycling Polymers into Value-Added Molecules. *Angew. Chem. Int. Ed.* **2023**, *62*, e202301303. <https://doi.org/10.1002/anie.202301303>.
- (45) Huang, Z.; Shanmugam, M.; Liu, Z.; Brookfield, A.; Bennett, E. L.; Guan, R.; Vega Herrera, D. E.; Lopez-Sanchez, J. A.; Slater, A. G.; McInnes, E. J. L.; Qi, X.; Xiao, J. Chemical Recycling of Polystyrene to Valuable Chemicals via Selective Acid-Catalyzed Aerobic Oxidation under Visible Light. *J. Am. Chem. Soc.* **2022**, *144*, 6532–6542. <https://doi.org/10.1021/jacs.2c01410>.
- (46) Barber, V. J.; Borden, M. A.; Alty, J. W.; Tran, L. D.; Koerner, H.; Baldwin, L. A.; Alexanian, E. J.; Leibfarth, F. A. Modifying Poly(Caprolactone) Degradation through C–H Functionalization. *Macromolecules* **2023**, *56*, 3679–3686. <https://doi.org/10.1021/acs.macromol.3c00125>.
- (47) Korpusik, A. B.; Adili, A.; Bhatt, K.; Anatot, J. E.; Seidel, D.; Sumerlin, B. S. Degradation of Polyacrylates by One-Pot Sequential Dehydrodecarboxylation and Ozonolysis. *J. Am. Chem. Soc.* **2023**, *145*, 10480–10485. <https://doi.org/10.1021/jacs.3c02497>.
- (48) Skowerski, K.; Białecki, J.; Tracz, A.; Olszewski, T. K. An Attempt to Provide an Environmentally Friendly Solvent Selection Guide for Olefin Metathesis. *Green Chem.* **2014**, *16*, 1125–1130. <https://doi.org/10.1039/C3GC41943F>.
- (49) Nienalowski, T.; Krzeński, P.; Baumert, M. E.; Skoczeń, A.; Suska-Kauf, E.; Pawłowska, J.; Kajetanowicz, A.; Grela, K. 4-Methyltetrahydropyran as a Convenient Alternative Solvent for Olefin Metathesis Reaction: Model Studies and Medicinal Chemistry Applications. *ACS Sustain. Chem. Eng.* **2020**, *8*, 18215–18223. <https://doi.org/10.1021/acssuschemeng.0c06668>.
- (50) Bailey, G. A.; Lummiss, J. A. M.; Foscatto, M.; Occhipinti, G.; McDonald, R.; Jensen, V. R.; Fogg, D. E. Decomposition of Olefin Metathesis Catalysts by Brønsted Base: Metallacyclobutane Deprotonation as a Primary Deactivating Event. *J. Am. Chem. Soc.* **2017**, *139*, 16446–16449. <https://doi.org/10.1021/jacs.7b08578>.
- (51) Walker, R.; Conrad, R. M.; Grubbs, R. H. The Living ROMP of *Trans*-Cyclooctene. *Macromolecules* **2009**, *42*, 599–605. <https://doi.org/10.1021/ma801693q>.
- (52) Mulhearn, W. D.; Register, R. A. Synthesis of Narrow-Distribution, High-Molecular-Weight ROMP Polycyclopentene via Suppression of Acyclic Metathesis Side Reactions. *ACS Macro Lett.* **2017**, *6*, 112–116. <https://doi.org/10.1021/acsmacrolett.6b00969>.
- (53) Neary, W. J.; Kennemur, J. G. Polypentenamer Renaissance: Challenges and Opportunities. *ACS Macro Lett.* **2019**, *8*, 46–56. <https://doi.org/10.1021/acsmacrolett.8b00885>.
- (54) Thompson, C. B.; Orski, S. V. Synthesis and Dilute Solution Properties of Precision Short-Chain Branched Poly(Ethylene) Block Copolymers Derived from Ring-Opening Metathesis Polymerization. *Macromolecules* **2023**, *56*, 5575–5587. <https://doi.org/10.1021/acs.macromol.3c00191>.
- (55) Sample, C. S.; Kellstedt, E. A.; Hillmyer, M. A. Tandem ROMP/Hydrogenation Approach to Hydroxy-Telechelic Linear Polyethylene. *ACS Macro Lett.* **2022**, *11*, 608–614. <https://doi.org/10.1021/acsmacrolett.2c00144>.
- (56) Dingwell, C. E.; Hillmyer, M. A. Regiospecific Poly(Ethylene-Co-Vinyl Alcohol) by ROMP of 3-Acetoxy-cyclooctene and Postpolymerization Modification for Barrier Material Applications. *ACS Appl. Polym. Mater.* **2023**, *5*, 1828–1836. <https://doi.org/10.1021/acsapm.2c01918>.
- (57) Hillmyer, M. A.; Nguyen, S. T.; Grubbs, R. H. Utility of a Ruthenium Metathesis Catalyst for the Preparation of End-Functionalized Polybutadiene. *Macromolecules* **1997**, *30*, 718–721. <https://doi.org/10.1021/ma961316n>.

- (58) Bielawski, C. W.; Scherman, O. A.; Grubbs, R. H. Highly Efficient Syntheses of Acetoxy- and Hydroxy-Terminated Telechelic Poly(Butadiene)s Using Ruthenium Catalysts Containing N-Heterocyclic Ligands. *Polymer* **2001**, *42*, 4939–4945. [https://doi.org/10.1016/S0032-3861\(00\)00504-8](https://doi.org/10.1016/S0032-3861(00)00504-8).
- (59) Mandal, I.; Kilbinger, A. F. M. Practical Route for Catalytic Ring-Opening Metathesis Polymerization. *JACS Au* **2022**, *2*, 2800–2808. <https://doi.org/10.1021/jacsau.2c00566>.
- (60) Mandal, I.; Mandal, A.; Rahman, M. A.; Kilbinger, A. F. M. Chain Transfer Agents for the Catalytic Ring Opening Metathesis Polymerization of Norbornenes. *Chem. Sci.* **2022**, *13*, 12469–12478. <https://doi.org/10.1039/D2SC04078F>.
- (61) Mandal, A.; Mandal, I.; Kilbinger, A. F. M. Catalytic Syntheses of Degradable Polymers via Ring-Opening Metathesis Copolymerization Using Vinyl Ethers as Chain Transfer Agents. *Macromolecules* **2022**, *55*, 7827–7833. <https://doi.org/10.1021/acs.macromol.2c01373>.
- (62) Onbulak, S.; Hillmyer, M. A. Precision Ethylene-Styrene Copolymers through the Ring Opening Metathesis Polymerization of 3-Phenyl Cyclododecenes. *Polym. Chem.* **2021**, *12*, 1681–1691. <https://doi.org/10.1039/D0PY01721C>.
- (63) Zhang, J.; Matta, M. E.; Martinez, H.; Hillmyer, M. A. Precision Vinyl Acetate/Ethylene (VAE) Copolymers by ROMP of Acetoxy-Substituted Cyclic Alkenes. *Macromolecules* **2013**, *46*, 2535–2543. <https://doi.org/10.1021/ma400092z>.
- (64) Scherman, O. A.; Walker, R.; Grubbs, R. H. Synthesis and Characterization of Stereoregular Ethylene-Vinyl Alcohol Copolymers Made by Ring-Opening Metathesis Polymerization. *Macromolecules* **2005**, *38*, 9009–9014. <https://doi.org/10.1021/ma050686l>.
- (65) Zhang, Y.; Wang, T.; Bai, J.; You, W. Repurposing Mitsunobu Reactions as a Generic Approach toward Polyethylene Derivatives. *ACS Macro Lett.* **2022**, *11*, 33–38. <https://doi.org/10.1021/acsmacrolett.1c00689>.
- (66) Noonan, K. J. T.; Hugar, K. M.; Kostalik, H. A. I.; Lobkovsky, E. B.; Abruña, H. D.; Coates, G. W. Phosphonium-Functionalized Polyethylene: A New Class of Base-Stable Alkaline Anion Exchange Membranes. *J. Am. Chem. Soc.* **2012**, *134*, 18161–18164. <https://doi.org/10.1021/ja307466s>.
- (67) Robertson, N. J.; Kostalik, H. A. I.; Clark, T. J.; Mutolo, P. F.; Abruña, H. D.; Coates, G. W. Tunable High Performance Cross-Linked Alkaline Anion Exchange Membranes for Fuel Cell Applications. *J. Am. Chem. Soc.* **2010**, *132*, 3400–3404. <https://doi.org/10.1021/ja908638d>.
- (68) Zhang, M.; Kim, H. K.; Chalkova, E.; Mark, F.; Lvov, S. N.; Chung, T. C. M. New Polyethylene Based Anion Exchange Membranes (PE-AEMs) with High Ionic Conductivity. *Macromolecules* **2011**, *44*, 5937–5946. <https://doi.org/10.1021/ma200836d>.
- (69) Jian, Z.; Leicht, H.; Mecking, S. Direct Synthesis of Imidazolium-Functional Polyethylene by Insertion Copolymerization. *Macromol. Rapid Commun.* **2016**, *37*, 934–938. <https://doi.org/10.1002/marc.201600073>.
- (70) Na, Y.; Chen, C. Catechol-Functionalized Polyolefins. *Angew. Chem. Int. Ed.* **2020**, *59*, 7953–7959. <https://doi.org/10.1002/anie.202000848>.
- (71) Paxton, N. C.; Allenby, M. C.; Lewis, P. M.; Woodruff, M. A. Biomedical Applications of Polyethylene. *Eur. Polym. J.* **2019**, *118*, 412–428. <https://doi.org/10.1016/j.eurpolymj.2019.05.037>.
- (72) Zou, C.; Zhang, H.; Tan, C.; Cai, Z. Polyolefins with Intrinsic Antimicrobial Properties. *Macromolecules* **2021**, *54*, 64–70. <https://doi.org/10.1021/acs.macromol.0c02018>.
- (73) Wuts, P. G. M.; Greene, T. W. *Greene's Protective Groups in Organic Synthesis*; John Wiley & Sons, 2006.
- (74) Hahn, S. F. An Improved Method for the Diimide Hydrogenation of Butadiene and Isoprene Containing Polymers. *J. Polym. Sci. Part Polym. Chem.* **1992**, *30*, 397–408. <https://doi.org/10.1002/pola.1992.080300307>.
- (75) Imrie, C. T.; Karasz, F. E.; Attard, G. S. Effect of Backbone Flexibility on the Transitional Properties of Side-Chain Liquid-Crystalline Polymers. *Macromolecules* **1993**, *26*, 3803–3810. <https://doi.org/10.1021/ma00067a013>.
- (76) Craig, A. A.; Imrie, C. T. Effect of Backbone Flexibility on the Thermal Properties of Side-Group Liquid-Crystal Polymers. *Macromolecules* **1999**, *32*, 6215–6220. <https://doi.org/10.1021/ma990525f>.
- (77) Xie, R.; Weisen, A. R.; Lee, Y.; Aplan, M. A.; Fenton, A. M.; Masucci, A. E.; Kempe, F.; Sommer, M.; Pester, C. W.; Colby, R. H.; Gomez, E. D. Glass Transition Temperature from the Chemical Structure of Conjugated Polymers. *Nat. Commun.* **2020**, *11*, 893. <https://doi.org/10.1038/s41467-020-14656-8>.
- (78) Shrivastava, A. I - Introduction to Plastics Engineering. In *Introduction to Plastics Engineering*; Shrivastava, A., Ed.; Plastics Design Library; William Andrew Publishing, 2018; pp 1–16. <https://doi.org/10.1016/B978-0-323-39500-7.00001-0>.
- (79) Yarolimek, M. R.; Bookbinder, H. R.; Coia, B. M.; Kenner, J. G. Ring-Opening Metathesis Polymerization of δ -Pinene: Well-Defined Polyolefins from Pine Sap. *ACS Macro Lett.* **2021**, *10*, 760–766. <https://doi.org/10.1021/acsmacrolett.1c00284>.
- (80) Hejl, A.; Scherman, O. A.; Grubbs, R. H. Ring-Opening Metathesis Polymerization of Functionalized Low-Strain Monomers with Ruthenium-Based Catalysts. *Macromolecules* **2005**, *38*, 7214–7218. <https://doi.org/10.1021/ma0501287>.
- (81) Huang, B.; Wei, M.; Vargo, E.; Qian, Y.; Xu, T.; Toste, F. D. Backbone-Photodegradable Polymers by Incorporating Acylsilane Monomers via Ring-Opening Metathesis Polymerization. *J. Am. Chem. Soc.* **2021**, *143*, 17920–17925. <https://doi.org/10.1021/jacs.1c06836>.
- (82) Fürstner, A.; Langemann, K. A Concise Total Synthesis of Dactylol via Ring Closing Metathesis. *J. Org. Chem.* **1996**, *61*, 8746–8749. <https://doi.org/10.1021/jo961600c>.
- (83) Wittmann, S.; Tiniakos, A. F.; Prunet, J. Diastereoselective Synthesis of Trisubstituted Olefins Using a Silicon-Tether Ring-Closing Metathesis Strategy. *Org. Biomol. Chem.* **2020**, *18*, 2297–2306. <https://doi.org/10.1039/C9OB02563D>.
- (84) Wang, Y.; Jimenez, M.; Hansen, A. S.; Raiber, E.-A.; Schreiber, S. L.; Young, D. W. Control of Olefin Geometry in Macrocyclic Ring-Closing Metathesis Using a Removable Silyl Group. *J. Am. Chem. Soc.* **2011**, *133*, 9196–9199. <https://doi.org/10.1021/ja202012s>.
- (85) Bing, J. A.; Johnston, J. N. Enantioselective Synthesis of Cis- and Trans-Cycloheptyl β -Fluoro Amines by Sequential Aza-Henry Addition/Ring-Closing Metathesis. *Org. Lett.* **2023**, *25*, 950–955. <https://doi.org/10.1021/acs.orglett.2c04285>.
- (86) Wang, H.; Goodman, S. N.; Dai, Q.; Stockdale, G. W.; Clark, W. M. Jr. Development of a Robust Ring-Closing Metathesis Reaction in the Synthesis of SB-462795, a Cathepsin K Inhibitor. *Org. Process Res. Dev.* **2008**, *12*, 226–234. <https://doi.org/10.1021/op700288p>.
- (87) Subramanian, T.; Lin, C.-C.; Lin, C.-C. Synthesis of Oxazolidinyl Azacycles via Ring-Closing Olefin Metathesis: A Practical Entry to the Synthesis of Deoxy-Azasugars and Hydroxypyrrolizidines. *Tetrahedron Lett.* **2001**, *42*, 4079–4082. [https://doi.org/10.1016/S0040-4039\(01\)00635-9](https://doi.org/10.1016/S0040-4039(01)00635-9).
- (88) White, J. D.; Hrcnciar, P. Synthesis of Polyhydroxylated Pyrrolizidine Alkaloids of the Alexine Family by Tandem Ring-Closing Metathesis–Transannular Cyclization. (+)-Australine. *J. Org. Chem.* **2000**, *65*, 9129–9142. <https://doi.org/10.1021/jo0012748>.
- (89) Jung, M. E.; Piizzi, G. Gem-Disubstituent Effect: Theoretical Basis and Synthetic Applications. *Chem. Rev.* **2005**, *105*, 1735–1766. <https://doi.org/10.1021/cr940337h>.
- (90) Xiong, W.; Chang, W.; Shi, D.; Yang, L.; Tian, Z.; Wang, H.; Zhang, Z.; Zhou, X.; Chen, E.-Q.; Lu, H. Geminal Dimethyl Substitution Enables Controlled Polymerization of Penicillamine-Derived β -Thiolactones and Reversed Depolymerization. *Chem* **2020**, *6*, 1831–1843. <https://doi.org/10.1016/j.chempr.2020.06.003>.

Insert Table of Contents artwork here

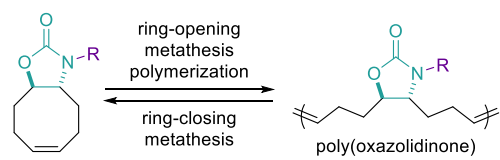

- ✓ Chain growth method
 - ✓ High molar mass
 - ✓ $T_{d,5\%} > 380$ °C
 - ✓ Depolymerizable monomer with moderate ring-strain energy
-