

# Liquid-Assisted Grinding Enables a Direct Mechanochemical Functionalization of Polystyrene Waste

Morgan E. Skala,<sup>[a]</sup> Sarah M. Zeitler,<sup>[a]</sup> and Matthew R. Golder<sup>\*[a]</sup>


[a] Department of Chemistry and Molecular Engineering & Science Institute  
University of Washington  
36 Bagley Hall, Seattle, WA 98195  
E-mail: goldermr@uw.edu

**Abstract:** The plastic waste crisis has grave consequences for our environment, as most single-use commodity polymers remain in landfills and oceans long after their commercial lifetimes. Utilizing modern synthetic techniques to chemically modify the structure of these post-consumer plastics (e.g., upcycling) can impart new properties and added value for commercial applications. To expand beyond the abilities of current solution-state chemical processes, we demonstrate post-polymerization modification of polystyrene via solid-state mechanochemistry enabled by liquid-assisted grinding (LAG). Importantly, this emblematic trifluoromethylation study modifies discarded plastic, including dyed materials, using minimal exogenous solvent and plasticizers for improved sustainability. Ultimately, this work serves as a proof-of-concept for the direct mechanochemical post-polymerization modification of commodity polymers, and we expect future remediation of plastic waste via similar mechanochemical reactions.

## Introduction

Aromatic polymers such as polystyrene (PS) and polycarbonates make up roughly 9.2 million metric tons of the plastic products consumed each year in the United States.<sup>1–8</sup> PS is particularly difficult to recycle due to high glass transition temperatures ( $T_g$ ) and food contamination; therefore, recycling requires energy intensive and cost-prohibitive methods culminating in a recycling rate of less than 1%.<sup>2,5,8</sup> To help mitigate the increasing amounts of plastic waste and avoid conventional mechanical recycling that may not recover bulk properties, chemical upcycling can be used to transform plastic waste into value added products.<sup>1,3,9</sup> One attractive pathway for upcycling is post-polymerization modification (PPM) which can directly edit a polymer backbone to alter physical and thermal properties. Desirable bulk properties such as surface wettability,<sup>10,11</sup> adhesion,<sup>12,13</sup> and enhanced thermal properties<sup>14</sup> can be accessed even at low levels of chemical functionalization. For example, Hartwig recently demonstrated that the addition of <1 mol% polar functional groups to polyolefin waste increases elongation and toughness.<sup>10,12</sup> PPM of plastic wastes is also theorized to only require the same low functionalization densities, <1 wt% of an acidic or basic pendant, to maintain proper rheology for ionic compatibilization.<sup>15</sup> For aromatic polymer modification, promising methods have emerged via C-H activation<sup>9,16–18</sup> and (photo)redox catalysis<sup>19,20</sup> that allow for the direct functionalization of commodity plastics (Figure 1A). While successful in modulating bulk properties, these PPM methods often require complete polymer dissolution and are thereby limited by the solubility of high molar mass plastics and/or requisite solvent volumes.<sup>9,21</sup> In addition, dyed plastics are particularly challenging to upcycle due to photon scattering.<sup>22–24</sup> To overcome these limitations

and improve sustainability of PPM processes, mechanochemistry via solid-state ball mill grinding (BMG) presents itself as an attractive method for PPM of plastic waste.

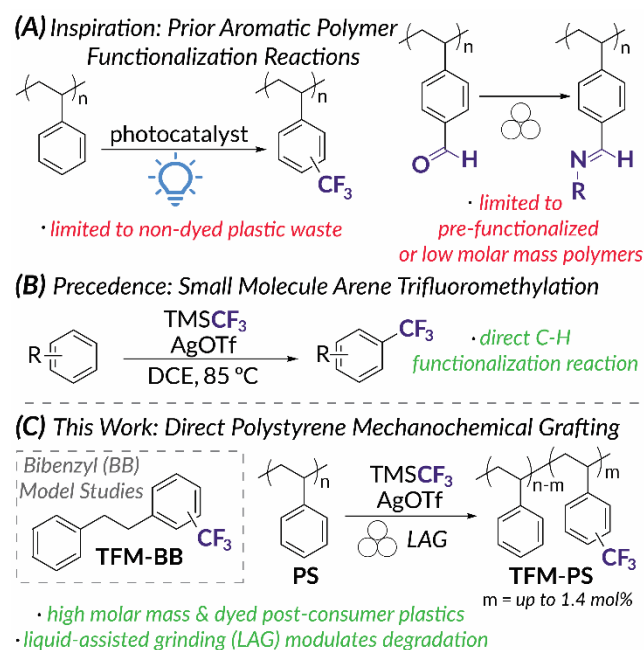

**Figure 1.** (A) Evolution of (photo)redox-catalyzed (left) and force-induced (right) aromatic polymer functionalization and (B) silver-mediated small molecule arene trifluoromethylation that inspired (C) this work's mechanochemical trifluoromethylation of bibenzyl and polystyrene (PS).

In the context of polymer science, mechanochemistry is intuitively perceived to promote destructive processes.<sup>24–28</sup> Following the early work of Staudinger,<sup>29–31</sup> mechanochemical chain scission has been redirected to mechanoresponsive functions (e.g., color change, catalyst activation, cargo release) via activation of engineered mechanophores using ultrasonic irradiation.<sup>27,32–38</sup> On the other hand, BMG in polymer mechanochemistry has largely focused on constructive chemistry for polymer synthesis.<sup>36,37,39,40</sup> Less studied in polymer mechanochemistry is PPM. Reactive extrusion is an example of an industrially relevant, mechanochemical method for PPM that relies on shear forces for mixing, but typically requires elevated temperatures for melt phase thermally mediated processes.<sup>13,41–43</sup> Force-induced polymer modifications via BMG, however, have rarely been applied to industrially relevant polymers. Instead, accounts are limited to low molar mass or low  $T_g$  materials that will not degrade under BMG conditions (i.e., oligomeric polystyrene<sup>44</sup> and poly(ethylene glycol)<sup>45</sup>) and polymers with pre-installed functional handles that


facilitate efficient modification in the solid-state (i.e., polystyrene-based copolymers containing aldehyde<sup>46</sup> or benzyl chloride<sup>47</sup> moieties, functionalized polyethers,<sup>48</sup> and poly(vinyl alcohol) and poly(vinyl chloride)<sup>49</sup>) (Figure 1A). Most commercial polymers, however, are high molar mass species and do not have such pre-installed moieties and therefore require longer reaction times for direct functionalization. The kinetics of prolonged functionalization reactions under BMG conditions are likely to be competitive with those of chain scission, resulting in excessive backbone degradation and loss of desired bulk properties.<sup>50</sup> This degradation via BMG can be leveraged for polymer depolymerization,<sup>26,51,52</sup> chain-end functionalization,<sup>53,54</sup> or radical functionalization.<sup>55</sup> For **PS**, while chain scission under BMG is well documented above a limiting molar mass,  $M_{lim}$  (ca. 7.0–13.0 kDa),<sup>50</sup> a recent report demonstrates a more specific relationship between  $T_g$  and the rate of degradation under BMG conditions.<sup>50</sup> In this work, Peterson, Hwang, and Choi also demonstrate that the addition of exogenous plasticizer could decrease the rate of degradation. Inspired by this finding, we hypothesized that liquid-assisted grinding (LAG) could plasticize post-consumer plastic under BMG conditions such that the rate of PPM significantly outcompeted the rate of mechanochemical chain scission. LAG, commonly used in synthetic organic mechanochemistry, is customarily defined as the ratio of a liquid additive to the mass of the reaction components within the range of 0.1–1  $\mu\text{L}/\text{mg}$ .<sup>56,57</sup> With plasticization of the polymer substrate, the  $T_g$  and the magnitude of shear forces experienced by polymer chains would decrease and result in slower degradation rates.<sup>50,58</sup>

To demonstrate the power of PPM using LAG, we identified trifluoromethylation as an emblematic arene functionalization reaction. Electrophilic  $\text{CF}_3$  sources should be reactive enough to add directly to aromatic monomer units in **PS**; importantly, for this study subsequent fluorinated products could be quantified easily via  $^{19}\text{F}$  NMR spectroscopy.<sup>19,20</sup> Previous reports have shown **TFM-PS** possesses increased hydrophobicity and improved interfacial and bulk polarization compared to unfunctionalized **PS**, making **TFM-PS** useful for applications in coatings and as a potential replacement for **PS** as a gate dielectric in organic electronics.<sup>19,59</sup> Recent work by Kubota and Ito on the mechanoredox fluoroalkylation of activated arenes<sup>60</sup> inspired us to extend trifluoromethylation to PPM via BMG. Although these conditions proved to be ineffective (Table S1), we later identified a direct arene trifluoromethylation reported by Sanford<sup>61</sup> (Figure 1B) as a method adaptable to mechanochemical functionalization of unactivated aromatics, such as **PS** model substrate bibenzyl (**BB**) (Figure 1C). Inspired by these previous reports, we now demonstrate the first example of direct mechanochemical **PS** functionalization using BMG and investigate the impact of varying LAG conditions on competitive polymer functionalization versus degradation (Figure 1C). Overall, we obtain **PS** trifluoromethyl incorporation up to 1.4 mol%, including 0.60 mol% for post-consumer dyed **PS**. This work serves as a proof-of-concept for sustainable aromatic polymer upcycling via LAG enabled mechanochemistry.


## Results & Discussion

With up to 5.5 mol% functionalization obtained using the **BB** model (see Tables S2–S4 for mechanochemical reaction

optimization and corresponding control reactions), we translated the methodology from small molecules to well-defined polymer substrates. We synthesized low molar mass **PS** ( $M_n, \text{MALS} = \text{ca. } 9.0 \text{ kDa}$ ) via atom transfer radical polymerization (ATRP)<sup>62</sup> utilizing a trifluoroethyl bromoisobutyrate initiator for facile chain-end analysis and PPM quantification via  $^{19}\text{F}$  NMR spectroscopy.<sup>19</sup> The  $^{19}\text{F}$  NMR spectra for **TFM-PS** revealed a single broad peak (ca.  $-62.1 \text{ ppm}$ ) which is consistent with analytical data from prior reports of radical **PS** trifluoromethylations (Figures S58–S65).<sup>19–21,63</sup> To determine the optimal mechanochemical parameters needed for lower molar mass **PS** functionalization, we varied the size of the milling jar, size and number of milling balls, and reaction scale for an optimized charge ratio (Table 1). The highest density of trifluoromethylation resulted from the mechanochemical parameters optimized on **BB** (Table 1, Entries 1 and 2). Neither increasing the number of milling balls nor increasing jar size resulted in improved trifluoromethyl radical addition (Table 1, Entries 3 and 5, respectively). Increasing the diameter of the milling balls from 8 mm to 10 mm did result in a slight increase in trifluoromethylation density, but also caused more chain scission (i.e., lower  $M_n$ ), presumably due to increased shear forces (Table 1, Entry 4). Additionally, the reaction was successfully scaled up, albeit with a higher experimental  $M_n$  (Table 1, Entry 6). Notably, the functionalization density does not entirely account for the general increase in **TFM-PS**  $M_n$ . The second compounding factor is a high molar mass shoulder observed at all functionalization densities that is not seen when **PS** is milled without additives (Figure 2). Isolation and characterization of both the parent and shoulder peaks by preparative gel permeation chromatography revealed the shoulder peak maintained a molar mass roughly twice that of the parent **PS** (Figure S4, parent  $M_n = 8.9 \text{ kDa}$  and shoulder  $M_n = 18.6 \text{ kDa}$ ), suggestive of dimerization through chain coupling events (Figure S5). Recently, interchain coupling was reported during the solution-state degradation of **PS** in the presence of small amounts of triflic acid,<sup>64</sup> a byproduct of the silver-mediated trifluoromethylation methodology utilized in this work, that may be a cause of dimerization.<sup>61</sup> To ensure these deleterious chain coupling/branching reactions do not impact our chain-end analysis, we first calculated functionalization densities using  $^{19}\text{F}$  NMR spectroscopy based on chain-end analysis (Equation S3). When compared to those obtained using 4,4'-difluorobenzophenone as an internal standard (Equation S4), both methods were generally in agreement with one another (Table S5).

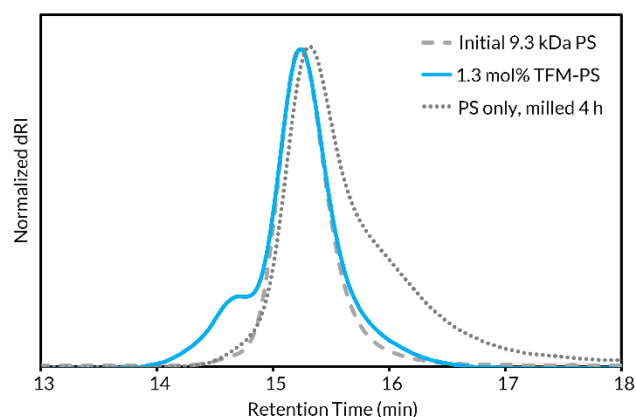

**Figure 2.** GPC-RI traces comparing unground parent **PS**, 1.3 mol% **TFM-PS** containing a high molar mass shoulder, and **PS** milled without additives for 4 h.

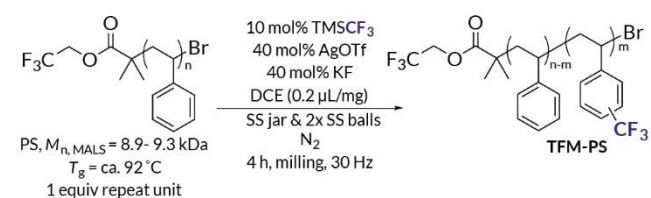**Table 1.** Optimization of mechanochemical parameters.<sup>[a]</sup>

Entry	Jar size (mL)	Ball size (mm)	Initial $M_n$ <sup>[f]</sup> (kDa)	$m$ <sup>[e]</sup> (mol%)	TFM-PS $M_n$ <sup>[f]</sup> (kDa)	Final $\mathcal{D}$ <sup>[f]</sup>
1	5	8	8.9	1.1	9.0	1.05
2	5	8	9.3	1.2	9.6	1.17
3	5	5 <sup>[b]</sup>	9.3	0.76	9.5	1.07
4	5	10	9.3	1.6	9.1	1.07
5	25	8 <sup>[c]</sup>	9.3	0.97	10.2	1.09
6 <sup>[d]</sup>	25	8 <sup>[c]</sup>	8.9	0.86	10.2	1.10


[a] Reaction conditions: **PS** repeat unit = 0.81 mmol,  $\text{AgOTf}$  = 0.32 mmol,  $\text{KF}$  = 0.32 mmol,  $\text{TMSCF}_3$  = 0.08 mmol, DCE (for LAG) = 37.4  $\mu\text{L}$  (0.2  $\mu\text{L}/\text{mg}$ ), jar temperature =  $20^\circ\text{C}$  –  $36^\circ\text{C}$ . [b] 3x SS balls were used. [c] 4 SS balls were used. [d] Reaction conditions: **PS** repeat unit = 1.62 mmol,  $\text{AgOTf}$  = 0.65 mmol,  $\text{KF}$  = 0.65 mmol,  $\text{TMSCF}_3$  = 0.16 mmol, DCE (for LAG) = 79.3  $\mu\text{L}$  (0.2  $\mu\text{L}/\text{mg}$ ). [e] Functionalization density ( $m$ ) was determined by  $^{19}\text{F}$  NMR spectroscopy using 4,4'-difluorobenzophenone as an internal standard. Based on  $\text{TMSCF}_3$  as the limiting reagent, a maximum  $m$  is 10 mol%. [f]  $M_n$  and  $\mathcal{D}$  were determined by GPC-MALS-RI.

With mechanochemical parameters optimized, we next focused on LAG conditions for well-defined higher molar mass **PS**. **PS** ( $M_{n, \text{MALS}} = 26.0$  kDa), also synthesized via ATRP, is well above the  $M_{\text{lim}}$  of **PS** and therefore allows better visualization of how  $M_n$  and  $\mathcal{D}$  are impacted by DCE LAG and chain scission kinetics (see Tables S6 and S7 for evaluation of different LAG solvents). LAG volumes were then varied from 0.2  $\mu\text{L}/\text{mg}$  to 1.2  $\mu\text{L}/\text{mg}$  (Figure 3A). At 0.2  $\mu\text{L}/\text{mg}$  LAG, while  $M_n$  decreases and dispersity increases as evidenced by low molar mass tailing in the GPC trace, the highest  $\text{CF}_3$  density (1.3 mol%) is also observed. As LAG volume increases above 0.2  $\mu\text{L}/\text{mg}$ , only a slight shift to lower molar masses and minimal changes in dispersity compared to the initial polymer are observed. We hypothesize this lack of chain scission is due to increased plasticization above 0.2  $\mu\text{L}/\text{mg}$  of LAG solvent. Additionally, increasing LAG volume results in decreased interchain coupling as evidenced by the decreasing  $M_n$  and shoulder peak area; these results are likely due to increasingly more dilute concentrations of triflic acid. The highest functionalization density with minimal degradation of **TFM-PS** was achieved at 0.4  $\mu\text{L}/\text{mg}$  LAG volume. At this LAG loading, plasticization appears to hinder the degradation kinetics while maintaining productive impact forces needed for efficient functionalization. At LAG loadings above 0.4  $\mu\text{L}/\text{mg}$ , we attribute decreases in trifluoromethylation to dissipation

of force in the reaction mixture. To assess the impact of plasticization and stress dissipation to the solid reagents on mechanochemical chain scission, we milled 26.0 kDa **PS** with either just the solid reagents ( $\text{AgOTf}$  and  $\text{KF}$ ) or just 0.4  $\mu\text{L}/\text{mg}$  LAG solvent (DCE) and liquid reagent ( $\text{TMSCF}_3$ ) for 4 h, the length of the standard reaction time (Figure 3B). When milled with only solid reactants, **PS** saw slightly less chain scission occur ( $M_{n, \text{final}} = 8.3$  kDa) than the initial **PS** milled alone ( $M_n = 7.0$  kDa), likely due to powder cushioning effects.<sup>65</sup> When **PS** was milled with only the LAG solvent and liquid additive, virtually no degradation or deleterious side reactions occur as assessed by GPC. To further confirm this result was due to plasticization, we used differential scanning calorimetry (DSC) to determine the  $T_g$  of the 26.0 kDa **PS** after milling with only 0.4  $\mu\text{L}/\text{mg}$  of the LAG solvent and the liquid additive (Figure 3C). The DSC curves of this liquid-milled **PS** compared to the initial 26.0 kDa **PS** reveal a decrease in  $T_g$  by ca.  $30^\circ\text{C}$ , indicative of plasticization. Based on these results, we determined that plasticization suppresses  $T_g$  and diminishes the force experienced by polymer chains, thus decreasing the rate of chain scission.

With BMG functionalization now demonstrated on well-defined **PS**, we turned our attention to modifying commercial and post-consumer plastic waste, particularly expanded polystyrene (EPS) foam waste (**EPS Foam**) and dyed **PS** coffee cup lids (**PS Lid**). To optimize grafting density while minimizing degradation, LAG amounts were first evaluated on **Precipitated EPS Foam** waste, which was precipitated as an attempt to control for the impact of inherent plasticizers and additives present in the “native” post-consumer plastics (Table 2). LAG amounts between 0.2 and 0.6  $\mu\text{L}/\text{mg}$  resulted in 0.68–0.89 mol%  $\text{CF}_3$  incorporation, retaining a similar efficiency to the PPM of well-defined **PS**, although significant degradation was now observed, likely due to higher molar mass starting material (Table 2, Entries 1-3). Milling with 0.8  $\mu\text{L}/\text{mg}$  of DCE resulted in the highest amount of functionalization, 1.1 mol%, with significantly less chain scission than with lower LAG volumes (Table 2, Entry 4). At 1.0 and 1.2  $\mu\text{L}/\text{mg}$  LAG, trifluoromethylation incorporation begins to decrease alongside minimal changes in  $M_n$ , likely due to less effective applied force (Table 2, Entries 5 and 6).

With optimized LAG conditions in hand (0.8 – 1.0  $\mu\text{L}/\text{mg}$  DCE), we subjected high molar mass ( $M_n = 132$  kDa) **Commercial PS** and post-consumer **PS** waste to mechanochemical trifluoromethylation conditions (Table 3). We refer to the crude post-consumer waste (i.e., containing all additives and plasticizers) as **Native EPS Foam** and **Native PS Lid** and the purified **PS** as **Precipitated EPS Foam** and **Precipitated PS Lid**. Utilizing LAG, we achieved trifluoromethylation loadings of 0.65 mol%, 0.29 mol%, and 0.60 mol% of **Commercial PS**, **Native EPS Foam**, and **Native PS Lid**, respectively (Table 3, Entries 1–3). As assessed by GPC-MALS, less degradation was seen during mechanochemical trifluoromethylation for the **Commercial PS** and both post-consumer “native” **PS** substrates relative to “precipitated” **PS** substrates (Table 3). These results are supported by differential scanning calorimetry (DSC) experiments that reveal glass transitions of  $93^\circ\text{C}$ – $94^\circ\text{C}$  for the **Native EPS Foam** and **Native PS Lid** (Figures S72 and S74); these values are lower than the  $T_g$ 's of their respective precipitated forms<sup>66</sup> (Figures S73 and S75) and indicate the presence of plasticizers and/or additives in the crude polymers. When combined with LAG conditions, the result is limited

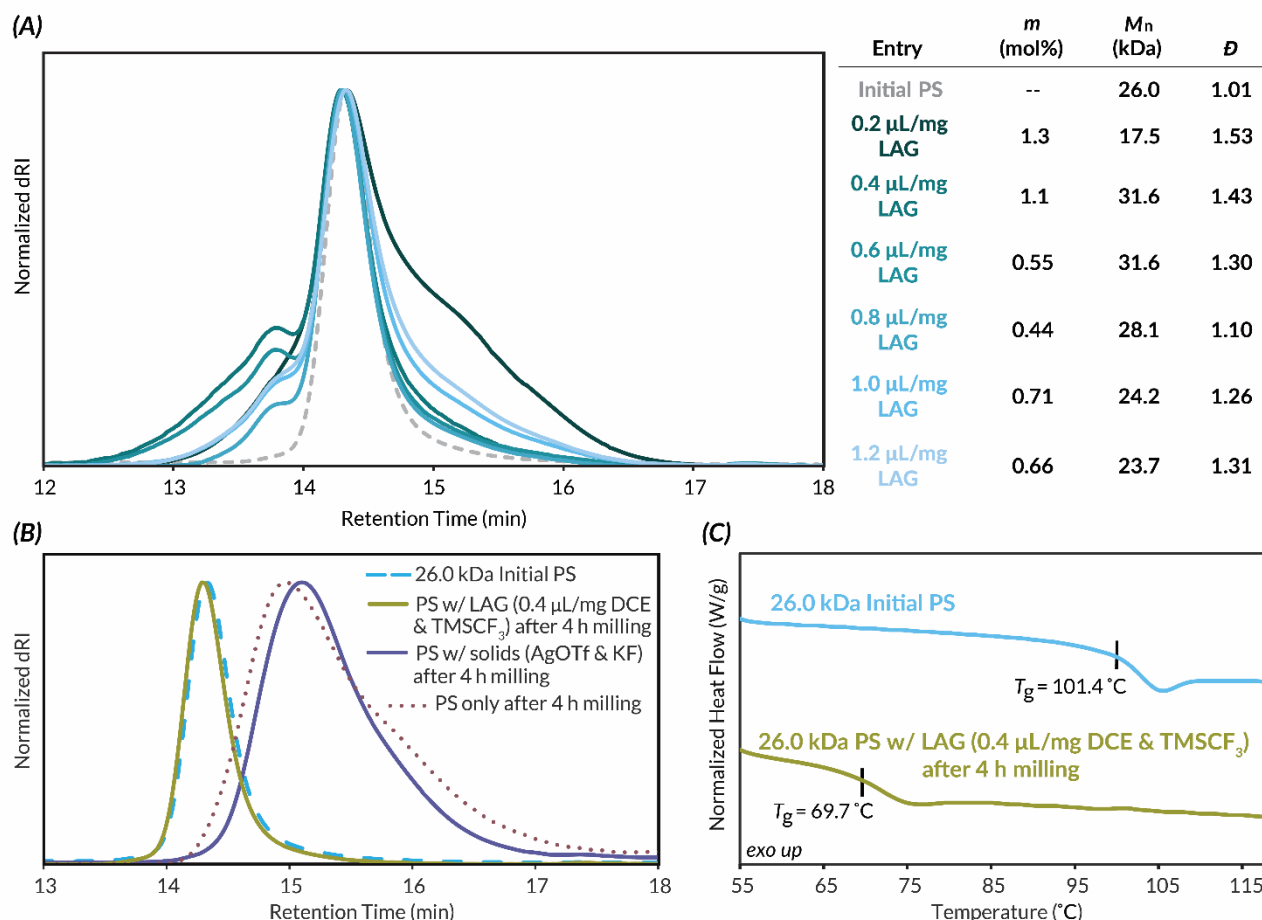

**Figure 3.** (A) GPC-RI traces and corresponding analytical data highlighting the effect of increasing LAG volume on functionalization density ( $m$ ),  $M_n$ , and dispersity of 26.0 kDa **PS** trifluoromethylation. Based on  $\text{TMSCF}_3$  as the limiting reagent, a maximum  $m$  is 10 mol%. (B) GPC-RI traces of a control study demonstrating the impact of LAG on **PS** chain scission kinetics. (C) DSC curves showing a decrease in  $T_g$  for 26.0 kDa **PS** after pre-milling with DCE (0.4  $\mu\text{L}/\text{mg}$ ) and  $\text{TMSCF}_3$  (12.4  $\mu\text{L}$ ) for 4 h


backbone degradation compared to precipitated high molar mass **PS**. To further explore the advantages of mechanochemistry, we subjected **Commercial PS**, **Native EPS Foam**, and **Native PS Lid** waste to force-free trifluoromethylation conditions in solution (Table S8, Entries 5–9). In all cases, we noted, at best, trace functionalization while also obtaining insoluble cross-linked materials (Figure S8) from **Native EPS Foam** and **Commercial PS**. Overall, these efforts highlight the efficacy of our mechanochemical methodology over solution-state methods (see Table S8 for solution-state reactions of additional substrates).

Despite the benefits of LAG for reducing mechanochemical chain scission during **PS** trifluoromethylation, for commercially relevant high molar mass samples, we generally still observe a decrease in  $M_n$  during trifluoromethylation (Table 3); such changes can drastically impact downstream bulk properties. At the outset, we hypothesized that the intrinsic plasticizers<sup>67</sup> in “native” **PS** waste *could* reduce the rate of mechanochemical chain scission through  $T_g$  depression, but such phenomena may vary across different post-consumer substrates. Indeed, in the case of the **Native PS Lid** (Table 3, Entry 2) no change in  $M_n$  was observed, while **Native EPS Foam** (Table 3, Entry 1) showed a decrease in  $M_n$  by ca. 35 kDa. However, any potential benefits of these plasticizers still require synergistic LAG solvent; mechanochemical

trifluoromethylation experiments with **Native EPS Foam** and **Native PS Lid** run in the absence of LAG solvent (Figures S9 and S10) leads to low molar mass **PS** approaching  $M_{\text{lim}}$  (ca. 9.0 kDa) for both substrates. We also performed identical experiments on **Precipitated EPS Foam** without LAG, but with the addition of 2 or 4 wt% of exogenous plasticizers dioctyl terephthalate (DOTP) and tributyl citrate (TBC) (Figures S11 and S12). Interestingly, we still achieved ca. 0.5–1 mol% functionalization across these representative examples, suggesting that “plasticizers” support our mechanochemical trifluoromethylation chemistry.

Given that LAG is clearly necessary for maintaining high molar mass polymers during mechanochemical PPM, we then subjected **Precipitated EPS Foam** to trifluoromethylation conditions with exogenous plasticizer (2 or 4 wt% of DOTP or TBC) and 0.8  $\mu\text{L}/\text{mg}$  DCE LAG (Figure 4). We investigated two different plasticizers because LAG additive polarity can alter reaction kinetics and/or reactivity.<sup>68,69</sup> At just 2 wt% DOTP we maintain functionalization density (1.4 mol%) but now observe less chain scission, with a loss of ca. 15 kDa in  $M_n$  (Figure 4A). Use of 2 wt% TBC increases  $M_n$  ca. 50 kDa with similar functionalization (1.2

**Table 2.** LAG effects on degradation and functionalization study of **Precipitated EPS Foam** waste.<sup>[a]</sup>

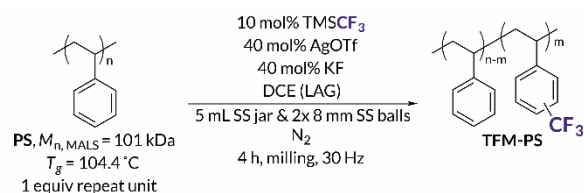


Entry	LAG (μL/mg)	<i>m</i> <sup>[b]</sup> (mol%)	<i>M<sub>n</sub></i> <sup>[c]</sup> (kDa)	<i>Đ</i> <sup>[c]</sup>
SM	-	-	101	1.87
1	0.2	0.89	16.0	2.25
2	0.4	0.86	55.6	2.64
3	0.6	0.68	32.3	4.96
4	0.8	1.1	71.0	1.45
5	1.0	0.89	79.9	1.66
6	1.2	0.61	66.6	1.69

[a] Reaction conditions: **PS** repeat unit = 0.81 mmol, AgOTf = 0.32 mmol, KF = 0.32 mmol, TMSCF<sub>3</sub> = 0.08 mmol, DCE (for LAG) = 0.2 – 1.2 μL/mg, internal jar temperature = 20 °C – 36 °C. [b] Functionalization density (*m*) was determined by <sup>19</sup>F NMR spectroscopy using 4,4'-difluorobenzophenone as an internal standard. Based on TMSCF<sub>3</sub> as the limiting reagent, a maximum *m* is 10 mol%. [c] *M<sub>n</sub>* and *Đ* were determined by GPC-MALS-RI

mol%). At 4 wt% DOTP and TBC, functionalization density decreases slightly with similar plasticizer dependent outcomes in the final product molar mass (Figure 4B). At 8 wt% TBC loading we recovered mostly insoluble cross-linked material, while at 8 wt% DOTP we maintain similar degradation kinetics as at 2 and 4 wt% DOTP (Table S9). Because added TBC often led to insoluble material, we opted to study the impact of 2 wt% DOTP + LAG on the mechanochemical functionalization of native post-consumer waste and commercial **PS**.


With the ability to effectively maintain high *M<sub>n</sub>* polymers through addition of LAG solvent *and* plasticizer, we set out to optimize the mechanochemical trifluoromethylation of commercial and post-consumer “native” substrates (Figure 5). Although **Native EPS Foam** contains plasticizer, we still observed a decrease in *M<sub>n</sub>* by ca. 35 kDa (Table 3, Entry 1). However, the addition of just 2 wt% DOTP with LAG (1.0 μL/mg DCE) provided efficient functionalization (1.0 mol%) with a slight increase in *M<sub>n</sub>* and dispersity relative to the initial substrate. Without exogenous plasticizer but with 1.0 μL/mg LAG, **Native PS Lid** still maintains similar trifluoromethylation densities (0.60 mol%) with a slight increase in dispersity. **Commercial PS** results in small amounts of chain scission (loss of ca. 30 kDa) with 2 wt% DOTP and 0.8 μL/mg LAG. We attribute this increased chain scission to the higher dispersity of the **Commercial PS** (*Đ* = 2.19).<sup>50</sup> To increase *M<sub>n</sub>* via chain coupling/branching (132 kDa to 373 kDa), 2 wt% TBC can be used instead (Figure S13). These results are promising for future mechanochemical functionalizations of post-consumer plastic waste that already contains additives and/or high degrees of plasticizers. Additives that might otherwise hinder solution-state PPM reactions can potentially tune reactivity under mechanochemical conditions.

**Table 3.** Mechanochemical trifluoromethylation of commercial, precipitated post-consumer and native post-consumer **PS**.<sup>[a]</sup>

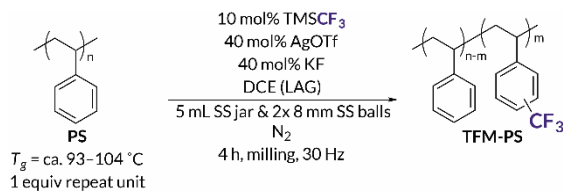


Entry	Substrate	LAG (μL/mg)	Initial <i>M<sub>n</sub></i> <sup>[b]</sup> (kDa)	Initial <i>Đ</i> <sup>[b]</sup>	<i>m</i> <sup>[c]</sup> (mol%)	TFM-PS <i>M<sub>n</sub></i> <sup>[b]</sup> (kDa)	Final <i>Đ</i> <sup>[b]</sup>
1	Native EPS Foam	0.8	119	1.82	0.29	83.6	2.57
2	Native PS Lid	1.0	113	1.78	0.60	114	2.62
3	Commercial PS	1.0	132	2.19	0.65	93.2	1.65
4	Precipitated EPS Foam	0.8	101	1.87	1.1	71.0	1.45
5	Precipitated PS Lid	1.0	131	1.72	0.46	13.3	3.78

[a] Reaction conditions: **PS** repeat unit = 0.81 mmol, AgOTf = 0.32 mmol, KF = 0.32 mmol, TMSCF<sub>3</sub> = 0.08 mmol, DCE (for LAG) = 0.8 – 1.0 μL/mg, jar temperature = 20 °C – 36 °C. [b] Functionalization density (*m*) was determined by <sup>19</sup>F NMR spectroscopy using 4,4'-difluorobenzophenone as an internal standard. Based on TMSCF<sub>3</sub> as the limiting reagent, a maximum *m* is 10 mol%. [c] *M<sub>n</sub>* and *Đ* were determined by GPC-MALS-RI.

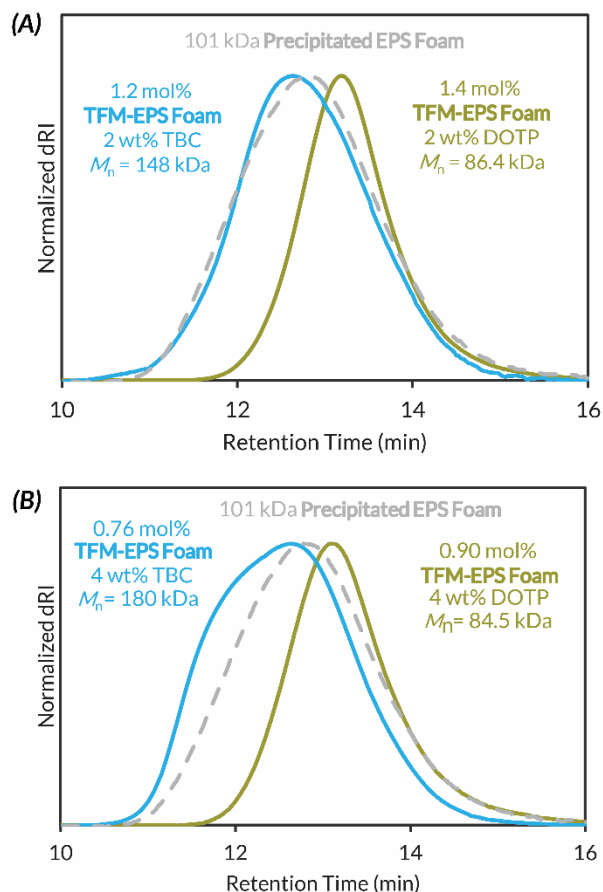

**Figure 4.** GPC-RI traces and corresponding analytical data highlighting the addition of plasticizers with 0.8  $\mu\text{L}/\text{mg}$  LAG and their effect on functionalization density,  $M_n$ , and dispersity of **Precipitated EPS Foam** trifluoromethylation: (A) 2 wt% DOTP or 2 wt% TBC; (B) 4 wt% DOTP or 4 wt% TBC.

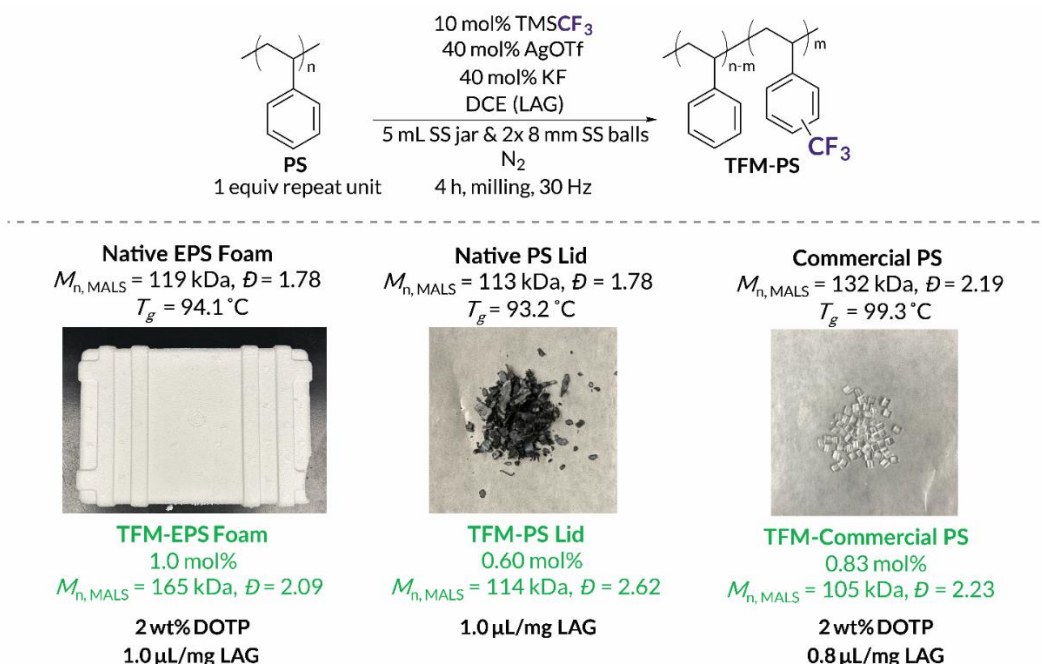

**Figure 5.** Optimized mechanochemical trifluoromethylations and corresponding analytical data of **Native EPS Foam**, **Native PS Lid**, and **Commercial PS**. Based on  $\text{TMSCF}_3$  as the limiting reagent, a maximum  $m$  is 10 mol%.

## Conclusions

In summary, we developed methodology for the direct mechanochemical trifluoromethylation of **PS** under BMG conditions utilizing LAG to limit mechanochemical chain scission. Initially, we evaluated and identified a silver-mediated trifluoromethylation that maintained similar efficiency of 5.5 mol% grafting density compared to the solution-state method under milder conditions (e.g., shorter reaction times, ambient temperature). After translation to **PS** substrates, we obtained trifluoromethylation incorporation up to 1.4 mol% without significant changes in  $M_n$  or  $\mathcal{D}$  and studied the effects of LAG on these processes. Additionally, we confirmed that LAG conditions decreased the  $T_g$  of **PS**, demonstrating that LAG and exogenous liquid additives act as a plasticizer under BMG conditions. Through this plasticization effect, we can simultaneously decrease the rate of mechanochemical chain scission without dramatically compromising the rate of functionalization. To prevent mechanochemical chain scission on high molar mass **PS**, we incorporated 2 wt% of DOTP to optimized trifluoromethylation conditions to maintain high  $M_n$  and ca. 1 mol% grafting of post-consumer and commercial substrates. Notably, these examples include the functionalization of **Native EPS Foam** and a dyed, **Native PS Lid**. Together, these findings serve as a proof-of-concept for the outlook of direct mechanochemical PPM; our work reveals the importance of future mechanochemical upcycling methods utilizing synergistic LAG and exogenous plasticizers with a focus on dyed materials and other challenging post-consumer plastic waste without employing copious volumes of exogenous organic solvent.

## Author Contributions

M.E.S. and M.R.G. conceived of the idea. M.E.S. and S.M.Z. conducted synthetic experiments and analyzed physical properties. M.E.S. and M.R.G. wrote the manuscript; all authors discussed and edited the manuscript.

## Conflicts of Interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by generous start-up funds from the University of Washington. M.E.S. acknowledges the University of Washington Clean Energy Institute for a graduate research fellowship. Differential scanning calorimetry instrumentation is funded by the Student Technology Fund (STF) at the University of Washington. The authors thank Prof. Dianne Xiao for use of thermogravimetric analysis instrumentation. This material is based in part upon work supported by the state of Washington through the University of Washington Clean Energy Institute. NMR spectroscopy resources are supported under NIH S10 OD030224-01A1.

## Notes and References

- 1 S. C. Kosloski-Oh, Z. A. Wood, Y. Manjarrez, J. P. De Los Rios and M. E. Fieser, *Mater. Horiz.*, 2021, **8**, 1084–1129.
- 2 A. Rahimi and J. M. García, *Nat. Rev. Chem.*, 2017, **1**, 0046.
- 3 C. Jehanno, J. W. Alty, M. Roosen, S. De Meester, A. P. Dove, E. Y.-X. Chen, F. A. Leibfarth and H. Sardon, *Nature*, 2022, **603**, 803–814.
- 4 Z. R. Hinton, M. R. Talley, P. A. Kots, A. V. Le, T. Zhang, M. E. Mackay, A. M. Kunjapur, P. Bai, D. G. Vlachos, M. P. Watson, M. C. Berg, T. H. Epps, and L. T. J. Korley, *Annu. Rev. Mater. Res.*, 2022, **52**, 249–280.
- 5 S. R. Nicholson, N. A. Rorrer, A. C. Carpenter and G. T. Beckham, *Joule*, 2021, **5**, 673–686.
- 6 R. Geyer, J. R. Jambeck and K. L. Law, *Sci. Adv.*, 2017, **3**, e1700782.
- 7 T. H. Epps, L. T. J. Korley, T. Yan, K. L. Beers and T. M. Burt, *JACS Au*, 2022, **2**, 3–11.
- 8 X. Zhao, B. Boruah, K. F. Chin, M. Đokić, J. M. Modak and H. S. Soo, *Adv. Mater.*, 2022, **34**, 2100843.
- 9 J. B. Williamson, S. E. Lewis, R. R. Johnson, I. M. Manning and F. A. Leibfarth, *Angew. Chem. Int. Ed.*, 2019, **58**, 8654–8668.
- 10 J. X. Shi, N. R. Ciccía, S. Pal, D. D. Kim, J. N. Brunn, C. Lizandara-Pueyo, M. Ernst, A. M. Haydl, P. B. Messersmith, B. A. Helms and J. F. Hartwig, *J. Am. Chem. Soc.*, 2023, **145**, 21527–21537.
- 11 M. N. Hodges, M. J. Elardo, J. Seo, A. F. Dohoda, F. E. Michael and M. R. Golder, *Angew. Chem. Int. Ed.*, 2023, **62**, e202303115.
- 12 N. R. Ciccía, J. X. Shi, S. Pal, M. Hua, K. G. Malollari, C. Lizandara-Pueyo, E. Risto, M. Ernst, B. A. Helms, P. B. Messersmith and J. F. Hartwig, *Science*, 2023, **381**, 1433–1440.
- 13 J. B. Williamson, C. G. Na, R. R. Johnson, W. F. M. Daniel, E. J. Alexanian and F. A. Leibfarth, *J. Am. Chem. Soc.*, 2019, **141**, 12815–12823.
- 14 J. Li and H.-M. Li, *Eur. Polym. J.*, 2005, **41**, 823–829.
- 15 G. H. Fredrickson, S. Xie, J. Edmund, M. L. Le, D. Sun, D. J. Grzetic, D. L. Vigil, K. T. Delaney, M. L. Chabynec and R. A. Segalman, *ACS Polym. Au*, 2022, **2**, 299–312.
- 16 E. Blasco, M. B. Sims, A. S. Goldmann, B. S. Sumerlin and C. Barner-Kowollik, *Macromolecules*, 2017, **50**, 5215–5252.
- 17 B. Xue, P.-P. Huang, M.-Z. Zhu, S.-Q. Fu, J.-H. Ge, X. Li and P.-N. Liu, *ACS Macro Lett.*, 2022, **11**, 1252–1257.
- 18 J. Wencel-Delord and F. Glorius, *Nat. Chem.*, 2013, **5**, 369–375.
- 19 S. E. Lewis, B. E. Wilhelmy and F. A. Leibfarth, *Chem. Sci.*, 2019, **10**, 6270–6277.
- 20 S. E. Lewis, B. E. Wilhelmy and F. A. Leibfarth, *Polym. Chem.*, 2020, **11**, 4914–4919.
- 21 Y. Hayakawa, N. Terasawa and H. Sawada, *Polymer*, 2001, **42**, 4081–4086.
- 22 S. Oh and E. E. Stache, *J. Am. Chem. Soc.*, 2022, **144**, 5745–5749.
- 23 J. L. Howard, Q. Cao and D. L. Browne, *Chem. Sci.*, 2018, **9**, 3080–3094.
- 24 T. Friščić, C. Mottillo and H. M. Titi, *Angew. Chem. Int. Ed.*, 2020, **59**, 1018–1029.
- 25 A. Stolle, T. Szuppa, S. E. S. Leonhardt and B. Ondruschka, *Chem. Soc. Rev.*, 2011, **40**, 2317.
- 26 E. Jung, D. Yim, H. Kim, G. I. Peterson and T. Choi, *J. Polym. Sci.*, 2023, **61**, 553–560.
- 27 B. A. Versaw, T. Zeng, X. Hu and M. J. Robb, *J. Am. Chem. Soc.*, 2021, **143**, 21461–21473.
- 28 J. Li, C. Nagamani and J. S. Moore, *Acc. Chem. Res.*, 2015, **48**, 2181–2190.
- 29 H. Staudinger and H. F. Bondy, *Ber. dtsh. Chem. Ges. A/B*, 1930, **63**, 734–736.
- 30 H. Staudinger and W. Heuer, *Ber. dtsh. Chem. Ges. A/B*, 1934, **67**, 1159–1164.
- 31 H. Staudinger and E. O. Leupold, *Ber. dtsh. Chem. Ges. A/B*, 1930, **63**, 730–733.
- 32 M. E. McFadden and M. J. Robb, *J. Am. Chem. Soc.*, 2019, **141**, 11388–11392.
- 33 D. A. Davis, A. Hamilton, J. Yang, L. D. Cremer, D. Van Gough, S. L. Potisek, M. T. Ong, P. V. Braun, T. J. Martínez, S. R. White, J. S. Moore and N. R. Sottos, *Nature*, 2009, **459**, 68–72.
- 34 Y. Lin, T. B. Kouznetsova and S. L. Craig, *J. Am. Chem. Soc.*, 2020, **142**, 2105–2109.
- 35 J. A. Leitch and D. L. Browne, *Chem. Eur. J.*, 2021, **27**, 9721–9726.
- 36 P. Chakma, S. M. Zeitler, F. Baum, J. Yu, W. Shindy, L. D. Pozzo and M. R. Golder, *Angew. Chem. Int. Ed.*, 2023, **62**, e202215733.
- 37 S. M. Zeitler, P. Chakma and M. R. Golder, *Chem. Sci.*, 2022, **13**, 4131–4138.
- 38 C. L. Brown and S. L. Craig, *Chem. Sci.*, 2015, **6**, 2158–2165.
- 39 G. S. Lee, B. R. Moon, H. Jeong, J. Shin and J. G. Kim, *Polym. Chem.*, 2019, **10**, 539–545.
- 40 A. Krusenbaum, S. Grätz, G. T. Tigineh, L. Borchardt and J. G. Kim, *Chem. Soc. Rev.*, 2022, **51**, 2873–2905.
- 41 A. Breuillac, F. Caffy, T. Vialon and R. Nicolaÿ, *Polym. Chem.*, 2020, **11**, 6479–6491.
- 42 G. Moad, *Prog. Polym. Sci.*, 1999, **24**, 81–142.
- 43 Y.-J. Sun, R. J. G. Willemsse, T. M. Liu and W. E. Baker, *Polymer*, 1998, **39**, 2201–2208.
- 44 D. Chatterjee, A. Sajeevan, S. Jana, R. S. Birajdar, S. H. Chikkali, S. Sivaram and S. S. Gupta, *ACS Catal.*, 2024, **14**, 7173–7181.
- 45 M. Y. Malca, P.-O. Ferko, T. Friščić and A. Moores, *Beilstein J. Org. Chem.*, 2017, **13**, 1963–1968.
- 46 N. Ohn and J. G. Kim, *ACS Macro Lett.*, 2018, **7**, 561–565.
- 47 M. Ashlin and C. E. Hobbs, *Macro Chemistry & Physics*, 2019, **220**, 1900350.
- 48 J. W. Lee, J. Park, J. Lee, S. Park, J. G. Kim and B.-S. Kim, *ChemSusChem*, 2021, **14**, 3801–3805.
- 49 B. G. Fiss, L. Hatherly, R. S. Stein, T. Friščić and A. Moores, *ACS Sustain. Chem. Eng.*, 2019, **7**, 7951–7959.
- 50 G. I. Peterson, W. Ko, Y.-J. Hwang and T.-L. Choi, *Macromolecules*, 2020, **53**, 7795–7802.
- 51 S. Aydonat, A. H. Hergesell, C. L. Seitzinger, R. Lennarz, G. Chang, C. Sievers, J. Meisner, I. Vollmer and R. Göstl, *Polym. J.*, 2024, DOI:10.1038/s41428-023-00863-9.

- 52 J. Zhou, T. Hsu and J. Wang, *Angew. Chem. Int. Ed.*, 2023, **62**, e202300768.
- 53 R. Schwarz and C. E. Diesendruck, *Adv. Sci.*, 2023, **10**, 2304571.
- 54 K. Kubota, N. Toyoshima, D. Miura, J. Jiang, S. Maeda, M. Jin and H. Ito, *Angew. Chem. Int. Ed.*, 2021, **60**, 16003–16008.
- 55 K. Kubota, J. Jiang, Y. Kamakura, R. Hisazumi, T. Endo, D. Miura, S. Kubo, S. Maeda and H. Ito, *J. Am. Chem. Soc.*, 2024, **146**, 1062–1070.
- 56 G. A. Bowmaker, *Chem. Commun.*, 2013, **49**, 334–348.
- 57 J.-L. Do and T. Friščić, *ACS Cent. Sci.*, 2017, **3**, 13–19.
- 58 J. Csernica and A. Brown, *J. Chem. Educ.*, 1999, **76**, 1526.
- 59 E. Plunkett, T. S. Kale, Q. Zhang, H. E. Katz and D. H. Reich, *Appl. Phys. Lett.*, 2019, **114**, 023301.
- 60 Y. Pang, J. W. Lee, K. Kubota and H. Ito, *Angew. Chem. Int. Ed.*, 2020, **59**, 22570–22576.
- 61 Y. Ye, S. H. Lee and M. S. Sanford, *Org. Lett.*, 2011, **13**, 5464–5467.
- 62 K. Matyjaszewski and J. Xia, *Chem. Rev.*, 2001, **101**, 2921–2990.
- 63 B. Briou, O. Gimello, C. Totee, T. Ono and B. Ameduri, *Chem. Eur. J.*, 2020, **26**, 16001–16010.
- 64 A. Thigale, C. Trant, J. Ahn, M. Nelson, C. Y. Ryu, C. Bae and S. Lee, *Macromolecules*, 2023, **56**, 5117–5126.
- 65 S. Cayirli, *Physicochem. Probl. Miner. Process.*, 2018, **54**, 751–762.
- 66 J. Rieger, *J. Therm. Anal.*, 1996, **46**, 965–972.
- 67 A. A. Cuthbertson, C. Lincoln, J. Miscall, L. M. Stanley, A. K. Maurya, A. S. Asundi, C. J. Tassone, N. A. Rorrer and G. T. Beckham, *Green Chem.*, 2024, 10.1039.D4GC00659C.
- 68 J. L. Howard, Y. Sagatov, L. Repousseau, C. Schotten and D. L. Browne, *Green Chem.*, 2017, **19**, 2798–2802.
- 69 J. L. Howard, M. C. Brand and D. L. Browne, *Angew. Chem. Int. Ed.*, 2018, **57**, 16104–16108.